

# Magnetic and Magnetoelectric Properties of Self-Assembled $\text{Fe}_{2.5}\text{Mn}_{0.5}\text{O}_4$ Nanocrystals

Shigemi Kohiki,<sup>\*,†</sup> Koichi Okada,<sup>†,‡</sup> Masanori Mitome,<sup>§</sup> Atsushi Kohno,<sup>#</sup> Tomoki Kinoshita,<sup>†</sup> Koichiro Iyama,<sup>†</sup> Fumiya Tsunawaki,<sup>†</sup> and Hiroyuki Deguchi<sup>†</sup>

<sup>†</sup>Department of Materials Science and <sup>‡</sup>Department of Basic Science, Kyushu Institute of Technology, Kitakyushu 804-8550, Japan


<sup>§</sup>Institute of Scientific and Industrial Research, Osaka University, Osaka 567-0047, Japan

<sup>§</sup>National Institute for Materials Science, Tsukuba 305-0044, Japan

<sup>#</sup>Faculty of Science, Fukuoka University, Fukuoka 814-0180, Japan

**ABSTRACT:** We report magnetoresistance of  $-40\%$ , corresponding to  $80\%$  spin polarization, at magnetic field of  $0.5\text{ T}$  and  $200\text{ K}$  for oleic acid-coated  $\text{Fe}_{2.5}\text{Mn}_{0.5}\text{O}_4$  nanocrystals (FMO NCs) self-assembled on a  $\text{SiO}_2/\text{Si}$  substrate by drop casting fabrication. The FMO NCs exhibited spin glass transition around  $150\text{ K}$  and nonlinear current–voltage ( $I$ – $V$ ) characteristics. Fowler–Nordheim plot of the  $I$ – $V$  characteristics indicated that electrons tunnel directly barriers between the FMO NCs. Transmission electron microscopy revealed that the FMO NCs are elongated hexagon in shape with size of  $\sim 15 \times 20\text{ nm}$ . The FMO NCs self-assembled in two-dimension hexagonal networks of collinear ferromagnetic moments. The  $[111]$  easy magnetization axis of each FMO NC was parallel to each other in the hexagonal arrays. Geometrically frustrated lattice of collinear ferromagnetic moments supports both a low and a high intergranular tunneling conductance for the self-assembled FMO NCs without and with magnetic fields, respectively.

**KEYWORDS:** low field magnetoresistance, spin polarization, magnetite-type  $\text{Fe}_{2.5}\text{Mn}_{0.5}\text{O}_4$ , self-assembled nanocrystals, oleic acid coating

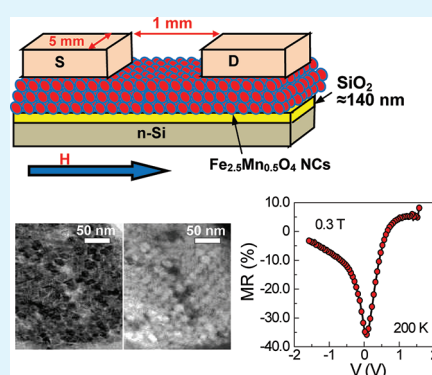

## INTRODUCTION

After findings of a large magnetoresistance (MR) for  $\text{LaMnO}_3$  analogues,<sup>1,2</sup> materials called half-metal including analogues of  $\text{LaMnO}_3$  and  $\text{Fe}_3\text{O}_4$  have attracted great interest because of their possible  $100\%$  spin-polarized carriers promising for spintronics device applications. Half-metal oxides are conductor for one spin channel and insulator for the other spin channel. In the structure consisted of two ferromagnetic metal electrodes sandwiching a thin insulating barrier, the tunneling magnetoresistance (TMR) ratio is defined as  $\text{TMR} = (R_{\text{AP}} - R_{\text{P}})/R_{\text{P}}$ , where  $R_{\text{AP}}$  and  $R_{\text{P}}$  are the resistances of the junction in the antiparallel and parallel configurations, respectively. A large TMR ratio of  $1850\%$  was reported for  $(\text{La,Sr})\text{MnO}_3/\text{SrTiO}_3/(\text{La,Sr})\text{MnO}_3$  junctions at  $4.2\text{ K}$ , however the TMR ratio declined rapidly with rising temperature.<sup>3</sup>  $(\text{La,Sr})\text{MnO}_3$  is a half-metal with rather high Curie temperature  $T_c \approx 360\text{ K}$ , whereas half-metal material with  $T_c \geq 500\text{ K}$  is requested for spintronics devices workable above room temperature (RT). Thus half-metal  $\text{Fe}_3\text{O}_4$  ( $T_c \approx 840\text{ K}$ ) and its analogues are suitable for such applications.

In the multiple junctions systems consisted of conducting ferromagnet NCs weakly contacted electrically one another via thin insulating barriers, the MR ratio is defined as  $\text{MR} = (R_{\text{H}} - R_0)/R_0$ , where  $R_{\text{H}}$  and  $R_0$  are the resistances in applied field  $H \neq 0$  and  $H = 0$ , respectively. Furthermore the MR ratio is connected to the spin polarization  $P$  of the material by  $\text{MR} \equiv P^2/(1+P^2)$ .<sup>4</sup> The MR ratio of  $50\%$  corresponds to  $P$  of  $100\%$ .

Zeng et al.<sup>5</sup> reported MR ratio of  $-35\%$  in  $H = 3.5\text{ T}$  at  $60\text{ K}$  for an assembly of  $\text{Fe}_3\text{O}_4$  NCs with diameter  $\phi \approx 6\text{ nm}$ . They reported that the NCs are superparamagnet with the blocking temperature of  $40\text{ K}$ . Kant et al.<sup>6</sup> reported MR ratios of  $-11.5\%$  and  $-5.8\%$  with  $H = 1\text{ T}$  at  $100\text{ K}$  for assemblies of  $\text{Fe}_3\text{O}_4$  NCs ( $\phi \approx 7.6\text{ nm}$ ) coated by  $\text{SiO}_2$  and  $\text{ZnO}$  with thickness of  $\sim 2\text{ nm}$ , respectively. They also reported that the NCs coated by  $\text{SiO}_2$  and  $\text{ZnO}$  are superparamagnet with the blocking temperature of  $200\text{ K}$ . Wang et al.<sup>7</sup> reported MR ratio of  $-40.9\%$  in  $H = 14\text{ T}$  at  $110\text{ K}$  for an assembly of polystyrene coated  $\text{Fe}_3\text{O}_4$  NCs with  $\phi = 10$ – $30\text{ nm}$ . Superparamagnetic systems of  $\text{Fe}_3\text{O}_4$  NCs with randomly oriented magnetic easy axes displayed rather low MR ratio than that expected from almost complete spin polarization of the material. Therefore, control of intergranular relationship among the NCs is important to examine MR ratio intrinsic for the material.

Conductance of the magnetic tunnel junctions depends on the relative orientation of the half-metal NCs' magnetization, therefore controlling of the NCs' arrangement into hexagonal symmetry in two and three dimensions is crucial to the MR ratio for the half-metal NC arrays. The common way to build ordered architectures at the nanometer scale is the spontaneous self-assembly phenomenon.<sup>8</sup> Self-assembled half-metal NC arrays are

Received: June 23, 2011

Accepted: August 26, 2011

Published: August 26, 2011

known to represent an idealized granular magnetic material, in that the NC size, spacing, and density can be controlled with high precision. When we deposit drops of a monodisperse NC dispersion liquid with controlled concentration and allow the liquid to dry slowly on a substrate, NCs order in two-dimensional hexagonal networks as a result of competition between the NC diffusion speed in the colloidal solution and the solvent evaporation speed.


We intended to fabricate hexagonal arrangement of single domain  $\text{Fe}_{2.5}\text{Mn}_{0.5}\text{O}_4$  (FMO) NCs by drop casting method. The material FMO, an analogue of  $\text{Fe}_3\text{O}_4$ , is known as high  $T_C$  ferromagnetic oxide with  $n$ -type carriers. The MR ratio defined as  $(G_0 - G_B)/G_B$ , where  $G_0$  and  $G_B$  are differential conductance ( $G = dI/dV$ ) without and with a magnetic field, respectively, of 150% at RT was reported for the 50 nm width nanoconstrained structure of FMO.<sup>9</sup>

In the first step, we synthesized monodisperse oleic acid-coated FMO NCs.<sup>10</sup> We added oleic acid as stabilizing agent into organic solvent to prevent aggregation during FMO NC formation. Oleic acid,  $\text{CH}_3(\text{CH}_2)_7\text{CH}=\text{CH}(\text{CH}_2)_7\text{COOH}$ , is an unsaturated carboxylic acid with a *cis*-double-bond kink in the middle of its  $\text{C}_{18}$  tale. The polar headgroup chemisorbs to the hydrophilic NCs' surface and steric repulsion of the long chain prevents the NCs from agglomerating.<sup>11</sup> Because the FMO NCs coated with oleic acid are hydrophobic, we can readily prepare colloidal suspensions in nonpolar organic solvent useful for the drop-casting fabrication, and more the hydrophobization by oleic acid is highly advantageous for preventing the surface oxidation occurring even at RT, which is known to diminish observed spin polarization for  $\text{Fe}_3\text{O}_4$ .<sup>12</sup> In the second step, we deposited drops of the FMO NCs suspension in hexane on a substrate and dried slowly for self-assembling of the NCs in hexagonal arrangement. Transmission electron microscopy (TEM) revealed that the  $[111]$  easy magnetization axis of each NC in hexagonal arrays aligned almost parallel one another. Therefore, we succeeded to fabricate the hexagonal lattice of collinear ferromagnetic moments of the FMO NCs.

Geometrical frustration among the collinear ferromagnetic moments of the self-assembled FMO NCs resulted in both a high and a low tunneling conductance under finite and zero magnetic fields, respectively. The FMO NCs showed spin glass transition with the freezing temperature  $T_F$  of 150 K based on the intergranular relationship among the NCs. The intermediate frustration lowers more or less the MR of the NCs hexagonal arrays. The low magnetic field ( $H = 0.5$  T) MR of  $-40\%$  was observed at 200 K for the FMO NCs, the value corresponds to 80% spin polarization.

## EXPERIMENTAL SECTION

**Synthesis of FMO NCs and Fabrication of Ordered Arrays by Self-Assembly.** FMO NCs were synthesized by slightly modified method of Kim et al.<sup>10</sup> from  $\text{Fe}(\text{acac})_3$  and  $\text{Mn}(\text{acac})_3$  in a solution of dibenzylether mixed with oleic acid. At first  $\text{Fe}(\text{acac})_3$ ,  $\text{Mn}(\text{acac})_3$ , dibenzylether, and oleic acid, weighed with the molar ratio of 5:1:157:12, were mixed with vigorous stirring for an hour at RT, and then the mixture was kept at 300 °C for half an hour. After cooling to RT, NCs were precipitated from the crude solution by adding a mixed solvent of toluene/hexane (1:1) followed by centrifugation. Precipitated NCs were washed with anhydrous chloroform. The NCs were dispersed in a weak alkaline (pH 10.4) aqueous solution. After stirring for 10 min, oleic acid with the molar ratio of  $[\text{Fe}]:[\text{C}_{18}\text{H}_{34}\text{O}_2] = 1:42$  was added to

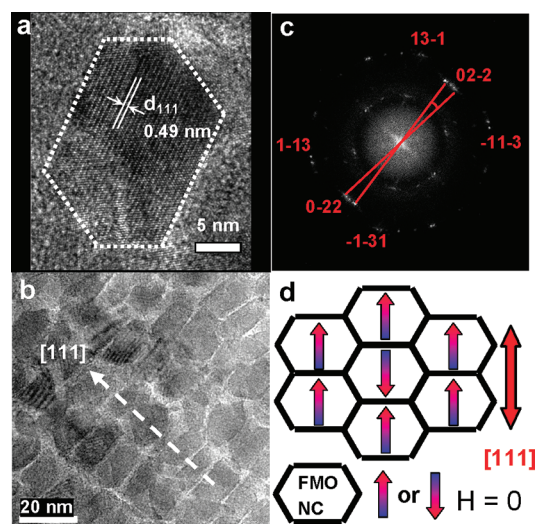


**Figure 1.** (a) TEM image of an FMO NC coated with oleic acid. Dotted line surrounding the NC is a guide for eye. (b) Cross-sectional TEM image of the FMO NCs/SiO<sub>2</sub>/Si sample. (c) FFT pattern for all the area of the image b. Indices of distinctive FFT spots with the incident beam direction along the  $[-2\ 1\ 1]$  axis are overlapped, and crystallographic orientation distribution ( $\sim 10^\circ$ ) is represented by crossed bars. (d) Schematic representation of hexagonally ordered collinear ferromagnetic moments. The ferromagnetic moment of single domain FMO NCs align parallel to the  $\langle 111 \rangle$  direction.

the solution with vigorous stirring. After stirring for 20 min, 1N-HCl aqueous solution was added for neutralization of the solution. After removal of transparent solution, precipitated NCs surface coated with oleic acid were dispersed in hexane.

The as-synthesized NCs were used without postpreparative size-selection for fabrication of self-assembled nanostructure by drop casting on a SiO<sub>2</sub>/Si substrate. The colloidal suspensions in hexane was dropped on a Si wafer covered with  $\sim 140$  nm thick SiO<sub>2</sub> layer, and then dried at 300 °C for half an hour at 100 Pa. Pt electrodes with thickness of a few 100 nm were sputter deposited on surface of the casted FMO NCs layer.

**Structural, Magnetic, and Electric Characterization.** The size and shape of as-synthesized FMO NCs were examined by using a JEOL JEM-3100FEF TEM operated at the electron acceleration voltage of 300 kV, and the crystal structure of the NCs was confirmed by X-ray diffraction (XRD) using a Rigaku CN2013 diffractometer with Cu  $K\alpha$  radiation. For the FMO NCs/SiO<sub>2</sub>/Si sample, the size, shape and arrangement of the NCs were examined by TEM, and the crystal structure of the NCs was reconfirmed by XRD.

For magnetic and electric characterization, we used a Quantum Design superconducting quantum interference device magnetometer MPM-5S. Diamagnetism from a SiO<sub>2</sub> layer was not compensated in any magnetization measurements. For temperature dependence of dc magnetization ( $M-T$ ) measurement, the sample was cooled from RT to 5 K without field, then  $H = 100$  Oe was applied. Zero-field-cooled (ZFC) magnetization was recorded with rising temperature up to 300 K. After the ZFC measurement, the sample was cooled again to 5 K in the same field, and then field-cooled (FC) magnetization was recorded with rising temperature to 300 K. For electrical measurement, Pt electrodes were bonded by gold wires to the MPM-5S system. At 200 K, current–voltage ( $I-V$ ) characteristic without field was first measured, and then  $H = 0.01, 0.1, 0.15, 0.3,$  and  $0.5$  T were applied parallel to the current flow at each  $I-V$  measurement.

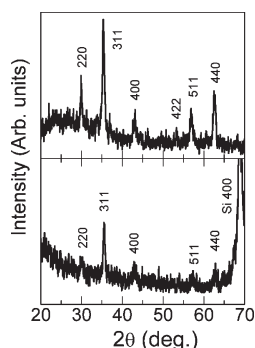


**Figure 2.** XRD patterns of the as-synthesized FMO NCs (upper panel) and the FMO NCs/SiO<sub>2</sub>/Si sample (lower panel).

## RESULTS AND DISCUSSION


**TEM and XRD.** TEM revealed that as-synthesized FMO NCs are elongated hexagon in shape with size of  $\sim 15 \times 20$  nm, and the [111] axis of each NC are parallel to one another in the FMO NCs/SiO<sub>2</sub>/Si sample. As seen in a TEM image of Figure 1a, as-synthesized FMO NC is single crystal with a lattice spacing of 0.49 nm. Such a lattice spacing is characteristic for the Fe<sub>3</sub>O<sub>4</sub> (111) planes (JCPDS 19–0629). Thus the NCs enclosed by (111) planes are octahedron.<sup>13</sup> As well-known for self-assembly fabrication, the FMO NCs ordered in two-dimension hexagonal networks in the FMO NCs/SiO<sub>2</sub>/Si sample. As depicted in Figure 1b, a cross-sectional TEM image revealed that the NCs aligned hexagonally, and direction of the [111] easy magnetization axis of each NC is parallel one another. The Fast Fourier Transform (FFT) pattern for all the area of Figure 1b is shown in Figure 1c, and distinctive FFT spots can be simulated well for magnetite type crystal structure. Splitting seen for each FFT spot indicates that orientation distribution of the [111] axis amounted to approximately ten degrees. However, the NCs ordered rather regularly than randomly in the FMO NCs/SiO<sub>2</sub>/Si sample because the FFT pattern lacks the Debye–Scherrer ring. The FMO NCs aligned parallel to the <111> direction in the region of approximately several hundred nanometers. For hexagonally arranged single domain FMO NCs shown in Figure 1d, geometrical frustration of collinear ferromagnetic moments is expected to bring about spin glass transition and a low intergranular electrical conductance with  $H = 0$ . In  $H \neq 0$ , ferromagnetic moment of the NCs align more parallel one another, and then the intergranular electrical conductance increases with an increase of  $H$ . Therefore, we expect to observe both spin glass transition and a high MR ratio for the FMO NCs/SiO<sub>2</sub>/Si sample.

Figure 2 compares XRD patterns of the as-synthesized FMO NCs and the FMO NCs/SiO<sub>2</sub>/Si sample. The as-synthesized NCs exhibited diffraction peaks in the upper panel, only attributable to cubic Fe<sub>3</sub>O<sub>4</sub> crystal lattice with space group of Fd-3 m (JCPDS 19–0629  $a = 0.8396$  nm for cubic cell). The FMO NCs/SiO<sub>2</sub>/Si sample showed diffraction peaks in the lower panel, due to cubic Fe<sub>3</sub>O<sub>4</sub> crystal lattice mentioned above and that from a Si wafer beneath the SiO<sub>2</sub> layer. The crystallite size of the FMO NCs/SiO<sub>2</sub>/Si sample, estimated from half-width of the (311) reflection peak by using Scherrer's equation, amounted to  $\sim 15$  nm, which agrees with the NC size by TEM shown in Figure 1a.

**Magnetic and Magnetoelectric Properties.** Self-assembly of the FMO NCs gave rise to two-dimensional hexagonal ordering

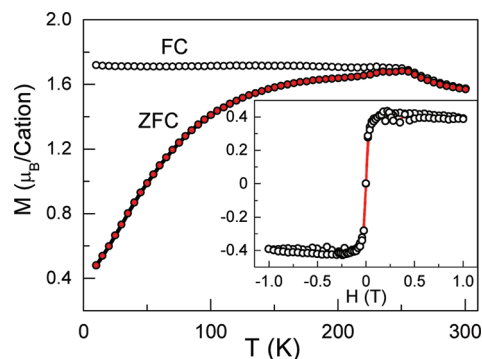

**Figure 3.** Field dependence at 300 K (the inset) and temperature dependence in  $H = 100$  Oe of magnetization of the FMO NCs/SiO<sub>2</sub>/Si sample.

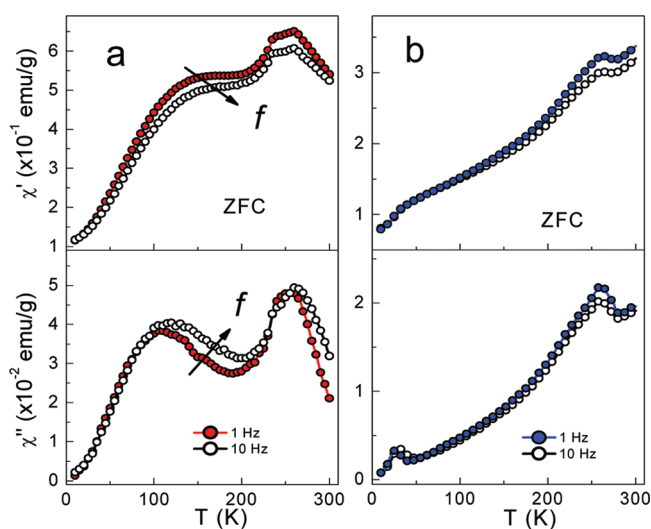


**Figure 4.** Temperature dependence of  $\chi'$  and  $\chi''$  for the FMO NCs/SiO<sub>2</sub>/Si sample (a) and for oleic acid-coated FMO NCs for the drop casting (b) in the ac field  $h = 3.8$  Oe and at both the frequency  $f = 1$  and 10 Hz.

of collinear ferromagnetic moments, which is expected to bring about magnetic frustration resulting in a large MR based on intergranular relationship. As shown by the inset of Figure 3, the FMO NCs/SiO<sub>2</sub>/Si sample demonstrated ferromagnetic behavior at 300 K in field dependence of magnetization ( $M$ - $H$ ). Sigmoidal  $M$ - $H$  curve almost saturated above  $H \approx 0.25$  T. Present sample consisting of single domain FMO NCs is ferromagnetic with the values of saturated magnetization  $M_s = 0.4 \mu_B/\text{cation}$ , remnant magnetization  $M_r = 0.01 \mu_B/\text{cation}$ , and coercive field  $H_c = 6$  Oe.

Figure 3 demonstrates bifurcation of FC and ZFC magnetizations below 250 K. FC magnetization remained at almost constant below 250 K, whereas ZFC one fell off gradually with lowering the temperature. Such cooling history dependence of magnetization supports the structure of agglomerated ferromagnetic NCs, and suggests spin glass or superparamagnetic behavior in frequency dependence of magnetization.

Figure 4a shows in-phase ( $\chi'$ ) and out-of-phase ( $\chi''$ ) components of temperature-dependent ac susceptibility of the ZFC sample measured from 5 to 300 K on warming. In the  $\chi' - T$  curve

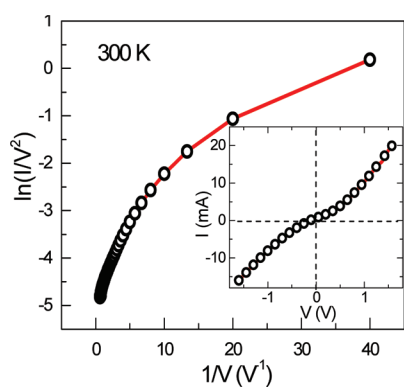


**Figure 5.**  $I$ – $V$  characteristics measured at 300 K in  $H = 0$  (the inset) and Fowler–Nordheim plot of the  $I$ – $V$  curve.


magnetic anomalies appeared around 250 K as a double cusp and around 150 K as a broad shoulder. Rather narrow peak around 250 K and broad peak around 100 K corresponding to the  $\chi'$  anomalies are seen in the  $\chi''$ – $T$  curve. Although the temperature and height of the narrow  $\chi''$  peak around 250 K stayed at constant despite the change in  $f$  from 1 to 10 Hz, those of the broad  $\chi''$  peak around 100 K obviously increased and decreased with the increase of  $f$ , respectively. Such changes in  $\chi''$  around 100 K are indicative of slow relaxation processes in spin glass or superparamagnetic materials.<sup>14</sup> The value of the relative variation of the peak temperature ( $T_F$ ) per decade of  $f$  for the  $\chi''$  peak,  $(\Delta T_F/T_F)/\Delta(\log_{10}f) = 0.06$ , places the sample in the range of canonical spin glasses.<sup>15</sup>

Thermal energy assists the reversal of magnetic moment in a single domain particle over the anisotropy energy barrier  $E_a$ .  $E_a$  is given by  $KV$ , where  $K$  is the effective magnetic anisotropy constant and  $V$  is the particle volume. In estimation of  $V$  we used diameter of 20 nm for present FMO NC. The relaxation time  $\tau$  ( $=1/2\pi f$ ) exhibits an exponential dependence on temperature represented by a Néel-Arrhenius law. Thus one obtain the eq  $1/T_F = (-k_B/E_a)\{\ln(2\pi f) + \ln(\tau_0)\}$ , where  $k_B$  is the Boltzmann constant and  $\tau_0$  is the pre-exponential factor. Since an inverse of  $T_F$  linearly shifted with a logarithm of  $f$ , the values of  $E_a = 5.4 \times 10^{-20}$  J and  $K = 1.4 \times 10^4$  J/m<sup>3</sup> were obtained from the gradient,  $\tau_0 = 5.5 \times 10^{-17}$  s from the intercept of the straight line in a  $T^{-1}$  vs  $\ln f$  plot. The  $\tau_0$  value is largely smaller than that typical for superparamagnet with the order of  $1 \times 10^{-9}$  to  $1 \times 10^{-11}$  s,<sup>16</sup> which indicates a finite interaction between the NCs in the sample. Since magnetic moments become progressively frozen with lowering temperature to  $T_F$ , the sample is in the intermediately frustrated magnetic state below 200 K and in the fully frustrated magnetic state below 100 K.

$\chi'$ – and  $\chi''$ – $T$  curves of the ZFC sample of oleic acid coated FMO NCs for the drop casting fabrication are shown in Figure 4b. Contrary to the  $\chi'$  and  $\chi''$  anomalies respectively around 150 and 100 K for the FMO NCs/SiO<sub>2</sub>/Si sample, oleic acid coated FMO NCs showed no anomalies due to magnetic frustration. The anomaly around 250 K observed commonly for both the FMO NCs/SiO<sub>2</sub>/Si sample and oleic acid coated FMO NCs is based on freezing effect of oleic acid. The  $\chi''$  anomaly around 30 K for oleic acid coated FMO NCs indicated  $(\Delta T_F/T_F)/\Delta(\log_{10}f) = 0.14$ , which places the sample in the range of superparamagnet.<sup>15</sup> Therefore, the FMO NCs/SiO<sub>2</sub>/Si sample demonstrated the spin glass transition based on intergranular magnetic interaction.

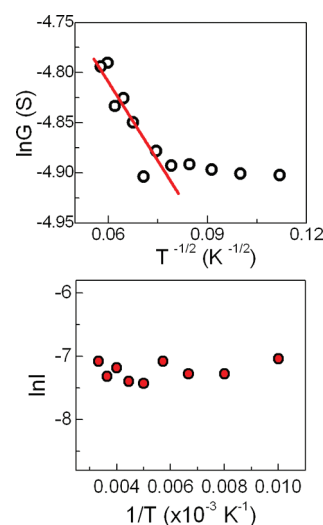

**Figure 6.** Temperature dependence of  $G$  at 0.4 V (upper panel) and  $\ln I$  versus  $1/T$  plot (lower panel).

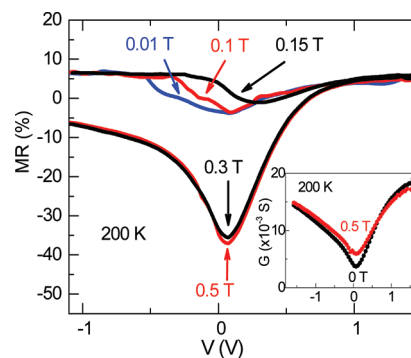

**Figure 7.**  $G$  versus  $V$  plot in  $H = 0$  and 0.5 T (the inset) and MR in  $H = 0.01, 0.1, 0.15, 0.3,$  and 0.5 T at 200 K.

As shown in the inset of Figure 5, the FMO NCs/SiO<sub>2</sub>/Si sample demonstrated nonlinear  $I$ – $V$  characteristics at 300 K, which is typical for intergranular tunneling conduction mechanism.<sup>17</sup> Fowler–Nordheim plot shown in Figure 5 revealed that electrons tunnel across the interface between two adjacent NCs. The barrier height  $\Phi$  for electron tunneling of 0.47 eV was derived from the equation for zero-bias limit,  $\ln(I/V^2) \propto \ln(1/V) - [2s(2m_e)^{1/2}/\hbar]\Phi^{1/2}$ , where  $s$  is the barrier thickness, and  $m_e$  is the electron effective mass.<sup>18</sup>

The sample exhibited linear relationship for  $\ln G$  versus  $T^{-1/2}$  above 200 K, as depicted by the straight line from linear fit in the upper panel of Figure 6. The resistance below 200 K was rather high and stayed at almost constant. We have tested the  $T^{-1/4}$  form expected for variable range hopping, however we found that  $\ln G$  could not be simulated well by such a law. Temperature dependent  $I$ – $V$  measurements were performed below 300 K because the electrical conduction obeying the Pool–Frenkel mechanism is known to be highly temperature dependent.<sup>19</sup> The current  $\ln I$  stayed at constant notwithstanding changes in temperature  $1/T$ , as shown by the lower panel of Figure 6. Carrier transport in the sample is dominated by direct electron tunneling between the NCs.

Negative MR was observed for the sample. As shown by the inst of Figure 7,  $G$  at 200 K became high and low in  $H = 0.5$  and

0 T, respectively. The MR ratio defined as  $(G_0 - G_H)/G_H$ , where  $G_0$  and  $G_H$  are differential conductance without and with  $H$ , respectively. The MR ratio at  $H \leq 0.15$  T was rather small than that at  $H \geq 0.3$  T, as shown in Figure 7. The MR ratio at 200 K reached  $-40\%$  at  $H = 0.3$  T, and stayed at almost constant up to  $H = 0.5$  T. The MR saturated at  $H \geq 0.3$  T, which is consistent to the saturation in the  $M-H$  curve above  $H \approx 0.25$  T as shown in the inset of Figure 3. The hexagonal arrangement of the FMO NCs involves antiparallel configuration of the ferromagnetic moments between adjoining NCs in the array. Consequently the electron tunneling probability remains at small in such a magnetically frustrated system. The tunneling conductance of electrons moving across insulating barrier is small for the sample in  $H = 0$ . Alternatively, applied  $H$  aligns the collinear ferromagnetic moments in the hexagonal lattice into parallel. Parallel configuration of the ferromagnetic moments between the NCs enhances the electron tunneling probability in the arrays, and results in enlarged electron tunneling conductance for the sample. Thus the magnetically frustrated sample leads to a large negative MR based on intergranular magnetic interaction.

From the  $MR \equiv P^2/(1+P^2)$  equation connecting MR to  $P$ ,<sup>4</sup> the observed low-field (0.5 T) MR of  $-40\%$  at 200 K corresponds to 80% spin polarization of the material. The MR of 50% corresponds to  $P$  of 100%, which is possible for half-metal material at a low temperature. In Figure 1c, we see some fluctuation in preferred orientation of the [111] axis of each NC in hexagonal arrays, therefore spin-dependent conductance in  $H = 0$  between adjacent FMO NCs still remains rather high because of imperfections in antiparallel configuration of ferromagnetic moments than that expected for perfect antiparallel configuration. Intermediate frustration of collinear ferromagnetic moments in the hexagonal lattice reduces the observed tunneling MR even if the FMO was half-metal material with  $P = 100\%$ .

## CONCLUSIONS

Two-dimension hexagonal ordering of collinear ferromagnetic moments fabricated by self-assembly of the FMO NCs was used for exploring intrinsic  $P$ . The assembly provided nonlinear  $I-V$  characteristics typical for intergranular tunneling of electrons. The electrons tunnel across the insulating barrier of oleic acid that coated the surface of the NCs. Geometrically frustrated arrays of the NCs exhibited spin glass transition around 150 K because of intergranular magnetic interactions. TEM supported the hexagonal ordering of collinear ferromagnetic moment of the NCs. Because of spin-dependent tunneling, magnetic frustration enlarged MR to  $-40\%$ . At 200 K, a large spin polarization ( $P = 80\%$ ) was achieved even in the low field  $H = 0.5$  T. FMO has the potential to play an important role in spintronic devices such a spin injector.

## AUTHOR INFORMATION

### Corresponding Author

\*E-mail: kohiki@che.kyutech.ac.jp.

## ACKNOWLEDGMENT

S.K. thanks Professor M. Mito and Professor H. Tanaka for discussion, and Dr. H. Shimooka for support in this work.

## REFERENCES

- (1) Jin, S.; Tiefel, T. H.; McCormack, M.; Fastnacht, R. A.; Ramesh, R.; Chen, L. H. *Science* **1994**, *264*, 413.
- (2) Tokura, Y.; Urushibara, A.; Moritomo, Y.; Arima, T.; Asamitsu, A.; Kido, G.; Furukawa, N. *J. Phys. Soc. Jpn.* **1994**, *63*, 3931.
- (3) Bowen, M.; Bibes, M.; Barthélémy, A.; Contour, J.-P.; Anane, A.; Lemaitre, Y.; Fert, A. *Appl. Phys. Lett.* **2003**, *82*, 233.
- (4) Inoue, J.; Maekawa, S. *Phys. Rev. B* **1996**, *53*, R11927.
- (5) Zeng, H.; Black, C. T.; Sandstrom, R. L.; Rice, P. M.; Murray, C. B.; Sun, S. *Phys. Rev. B* **2006**, *73*, 020402(R).
- (6) Kant, K. M.; Sethupathi, K.; Rao, M. S. R. *J. Appl. Phys.* **2008**, *103*, 07F318.
- (7) Wang, W.; Yu, M.; Batzill, M.; He, J.; Diebold, U.; Tang, J. *Phys. Rev. B* **2006**, *73*, 134412.
- (8) Prasad, B. L. V.; Sorensen, C. M.; Klabunde, K. J. *Chem. Soc. Rev.* **2008**, *37*, 1871.
- (9) Goto, K.; Kanki, T.; Kawai, T.; Tanaka, H. *Nano Lett.* **2010**, *10*, 2772.
- (10) Kim, D.; Lee, N.; Park, M.; Kim, B. H.; An, K.; Hyeon, T. *J. Am. Chem. Soc.* **2009**, *131*, 454.
- (11) Tadmor, R.; Rosensweig, R. E.; Frey, J.; Klein, J. *Langmuir* **2000**, *16*, 9117.
- (12) Rybchenko, S. I.; Fujishiro, Y.; Takagi, Y.; Awano, M. *Phys. Rev. B* **2005**, *72*, 054424.
- (13) Zhang, L.; Wu, J.; Liao, H.; Hou, Y.; Gao, S. *Chem. Commun.* **2009**, 4378.
- (14) Doman, J. L.; Fiorani, D.; Trone, E. *Adv. Chem. Phys.* **1997**, *98*, 283.
- (15) Mydosh, J. A. *Spin Glasses: An Experimental Introduction*; Taylor & Francis: London, 1993.
- (16) Goya, G. F.; Berquó, T. S.; Fonseca, F. C.; Morales, M. P. *J. Appl. Phys.* **2003**, *94*, 3520.
- (17) Simmons, J. G. *J. Appl. Phys.* **1963**, *34*, 1793.
- (18) Beebe, J. M.; Kim, B.; Gadzuk, J. W.; Frisbie, C. D.; Kushmerick, J. G. *Phys. Rev. Lett.* **2006**, *97*, 026801.
- (19) Sze, S. M. *Physics of Semiconductor Devices*; Wiley: New York, 1981.