

# Long-Term, Light-Induced Changes in the Dark Conductivity of Kapton

M.S. Leung,\* M.B. Tueling,† and P.F. Mizera‡  
*The Aerospace Corporation, El Segundo, California*

The light-induced increase in dark conductivity of Kapton in space and simulated space environments has been investigated. It was found that a long-term increase in conductivity is caused by an accumulation of electrically active centers generated by solar radiation in the bulk of the material if maintained in vacuum. An analysis of the increase in conductivity as a function of light exposure time indicates that the dark conductivity of Kapton can be raised to a level at which the film can become sufficiently conductive to be antistatic simply by exposing it to solar radiation in orbit.

## Introduction

KAPTON is a polypyromellitimide film whose properties have been investigated extensively because of its wide usage in both terrestrial and space applications. Because of its low conductivity and high dielectric strength, Kapton has been used as an electrical insulator in terrestrial environments. In space, Kapton is used most commonly as the outermost surface of a spacecraft thermal control blanket. When bombarded with electrons from the hot, tenuous plasma found in space during geomagnetically disturbed times, the bare Kapton surface tends to acquire a high electrostatic potential. Several techniques have been devised in an attempt to render the surface of Kapton antistatic in order to reduce the risks arising from spacecraft charging. One such approach relies on perforating the Kapton film to allow the electrons accumulated on the front surface to drain off through the edge of the perforation to the aluminized back surface.<sup>1</sup> The most popular one involves coating the Kapton front surface completely with a transparent, conductive oxide.<sup>2</sup> In this paper we present the results of our investigation in which we found that the dark conductivity of Kapton can be raised to a level where the film itself can become sufficiently conductive to be antistatic simply by exposing it to solar radiation in orbit.

## Background

Although photoconductivity of Kapton has been studied for some time, the effect of light on the dark conductivity of Kapton in vacuum is not well understood. There were some early ground test data indicating that the dark current measured after exposure to solar radiation in vacuum appeared to be much higher than before exposure.<sup>3</sup> No explanation was given at the time for the observation. The first indication that solar exposure-induced increases in dark conductivity may be important in space came from in-situ measurements of the electrical properties of Kapton obtained by the Satellite Surface Potential Monitor (SSPM).

The SSPM was an experiment payload flown on the P78-2 Spacecraft Charging at High Altitudes (SCATHA) satellite.<sup>4</sup> The purpose of the experiment was to study the electrical behavior of typical spacecraft insulating materials in the near-

geosynchronous orbit. P78-2 was a spin-stabilized satellite with its spin axis normal to the satellite-sun line. There were three SSPM Kapton samples on board the spacecraft in different locations. Two samples were mounted in such a way that they rotated into and out of sunlight; the third was mounted in the shadow at the end of the spacecraft. On-orbit SSPM data showed that the Kapton samples that were exposed to solar radiation tended to charge less frequently and to progressively lower levels.<sup>5</sup> With the surface potential of an isolated gold-plated conductor as a reference, the data showed that the ratio of Kapton surface voltage to the reference voltage decreased monotonically as a function of time (Fig. 1). This decrease was observed only in the Kapton samples exposed to sunlight in orbit and not in the sample in the shadow of the spacecraft.

A more detailed analysis of the current vs voltage (I-V) behavior of Kapton in orbit is shown in Fig. 2.<sup>6</sup> The plot designated by triangles ( $\Delta$ ) represents the I-V curve for Kapton measured before launch. The squares ( $\square$ ) represent on-orbit I-V measurements of the SSPM Kapton samples obtained in two charging events separated by 15 months. These measurements were chosen for comparison because charging took place in rather intense but stable environments and under conditions that allow us to obtain a quasi-equilibrium I-V measurement.

In the March 28, 1979 charging event, the bulk current of Kapton showed a drastic increase when compared with the prelaunch measurements. During this event the surface charged to more than a kilovolt. This behavior indicates that the conductivity of the material two months after launch was considerably higher than expected, but still in the range where

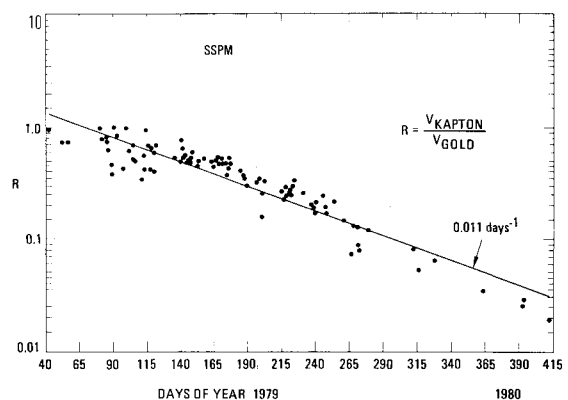


Fig. 1 Plot of the ratio of Kapton surface voltage to a reference (isolated gold plate) voltage.

Submitted Jan. 16, 1984; revision received May 7, 1984. Copyright © American Institute of Aeronautics and Astronautics, Inc., 1984. All rights reserved.

\*Section Head, Chemistry and Physics Laboratory. Member AIAA.

†Associate Technical Staff, Chemistry and Physics Laboratory.

‡Research Scientist, Space Sciences Laboratory. Associate Fellow AIAA.

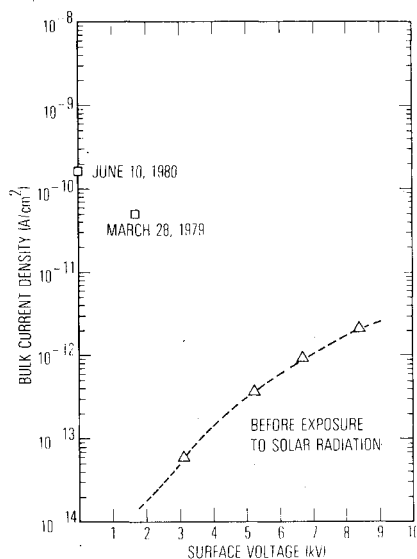


Fig. 2 I-V characteristics of Kapton samples before and after launch.

the surface charging is largely determined by the secondary electron emission. Approximately 15 months later, in the June 10, 1980 charging event, the bulk current was four times higher than that observed in the March 28, 1979 event, and at the same time the Kapton samples registered only small surface voltages. This behavior suggests that the Kapton samples exposed to the sun had become so conductive that they were no longer capable of supporting a significant surface charge buildup. A possibility exists that the conductivity of Kapton can be raised within a reasonably short time in orbit to a level where no appreciable charging can occur even in the plasmas found in periods of intense substorm activity. As a result, an experimental investigation based on ground simulation was initiated to study the change in dark conductivity of Kapton caused by exposure to solar radiation in orbit. The particular areas of interest included the solar spectral- and time-dependence of the change in conductivity.

### Experiments

Exposure to simulated solar radiation and measurement of the I-V behavior of Kapton were carried out in a vacuum chamber evacuated to  $10^{-7}$  Torr. A helium cryopump was used to maintain the pressure in the chamber. In Fig. 3, the schematic of the measurement setup is shown. All of the Kapton films used in the study were obtained from Sheldahl, Northfield, Minnesota. The samples consisted of 5- and 2-mil Kapton films aluminized on one side. The aluminized surface of each sample was attached by conductive epoxy to an etched copper circuit board. A diagram of the sample holder is given in Fig. 4. An electron gun was used to charge the unmetallized Kapton surface, while a noncontacting electrostatic potentiometer was used to measure the surface potential developed. For a 4-kV charging beam, the surface potential of Kapton was found to be 3 kV. This result agrees with our previous findings, and the difference between the changing beam potential and the Kapton surface potential is well understood.<sup>7</sup>

The procedure for carrying out the electrical measurements followed the general format given below. The specimen was irradiated in the vacuum chamber with a xenon lamp for a given period of time. Interference bandpass filters were used to isolate the particular wavelengths in the different spectral regions. The filters are designated by the wavelengths (in nm) at which the transmission maxima occur. For example, filter 425 has a transmission maximum at 425 nm. The bandwidth of these filters measured at half height is approximately 50 nm. The spectral regions chosen for study in this experiment

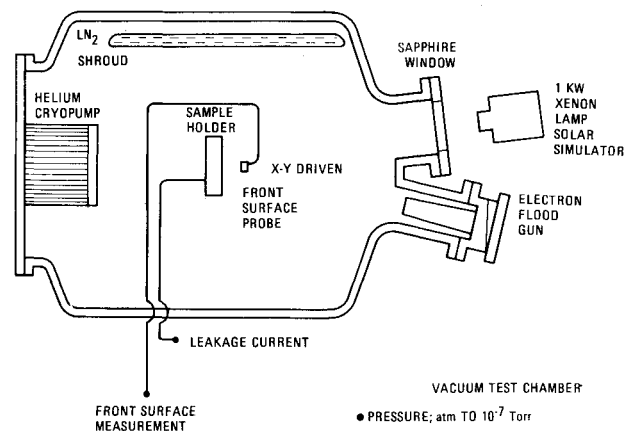


Fig. 3 Schematic of the test chamber.

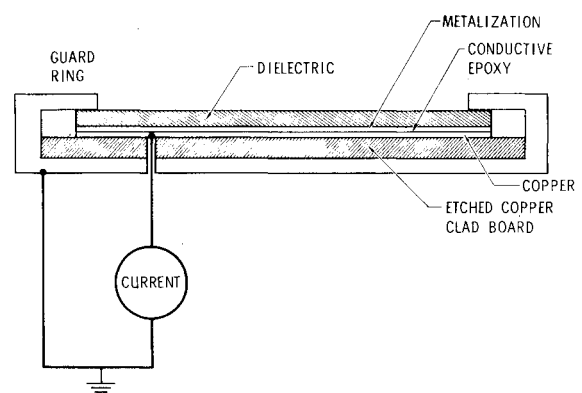


Fig. 4 Diagram of the sample holder.

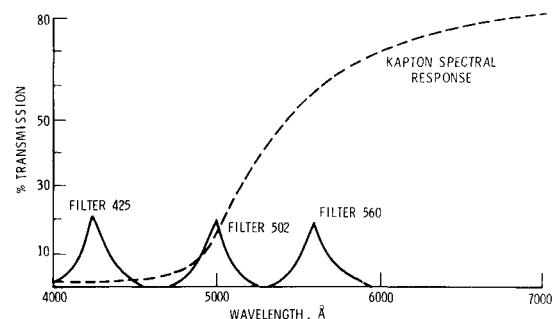


Fig. 5 Absorption characteristics of 5-mil Kapton and the filters used.

cover three separate portions of the Kapton absorption spectrum, regions where Kapton is strongly absorbing, partially absorbing, and nearly transparent. A summary of the absorption characteristics of both the filters and a 5-mil Kapton film is given in Fig. 5. The dark conductivity of the specimen was determined after each period of irradiation. In order to measure the dark conductivity, the I-V behavior of the specimen was determined in the absence of light after the specimen temperature and current were allowed sufficient time to come to equilibrium. Similar measurements were carried out on 2- and 5-mil Kapton specimens prepared from different production batches. For the exposure time dependence study, the unfiltered output of the xenon lamp was used.

### Results and Discussion

Three sets of experiments have been carried out: 1) investigation of the spectral dependence of the increase in the dark conductivity of Kapton, 2) determination of the effects

**Table 1** Change in dark current in Kapton after exposure to selected portions of the solar spectrum


	Filter	Exposure time, h	$\Delta I$ , pA	$\Delta I$ per hour, pA/h	Average	Ratio <sup>a</sup>	Adjusted <sup>b</sup> ratio
2-mil Kapton	425	15.8	15	0.95	1.10	0.11	0.15
		16.0	20	1.25			
	502	15.6	135	8.66	9.99	1.00	1.00
		16.8	1.90	11.32			
	560	15.8	75	4.74	4.25	0.43	0.40
		16.0	60	3.75			
5-mil Kapton	425	16.3	0	0.00	0.00	0.00	0.00
		16.0	0	0.00			
	502	18.4	60	3.26	3.30	1.00	1.00
		15.0	50	3.33			
	560	15.8	10	0.63	0.94	0.28	0.26
		16.0	20	1.25			

<sup>a</sup> Normalized to the largest change in bulk current. <sup>b</sup> Adjusted for filter transmission, spectral output of 1000-W xenon lamp, and relative photon flux.

of different gaseous environments on quenching the increased conductivity, and 3) determination of the dark conductivity increase as a function of exposure time. Our results indicate that photochemical reactions are ultimately responsible for the increase in dark conductivity observed in Kapton. Furthermore, our results show that Kapton can be made conductive in a much shorter time than we expected earlier. The following sections discuss our findings in detail.

### Spectral Dependence

A summary of our ground test results on spectral dependence is given in Table 1. The difference in bulk current before and after exposure is an indication of the increase in conductivity, since there was no appreciable change in the surface potential. § Filter 502 produced the largest increase in bulk current for both the 2- and 5-mil Kapton samples, as shown in Table 1. Filter 425 produced the smallest increase. Strictly speaking, from an energetics point of view, photons transmitted by filter 425 are more energetic and more likely to induce a conductivity change in the material. However, these photons are also strongly absorbed, and as a result, do not penetrate very deeply into the material. The absorption spectrum of Kapton in Fig. 5 reveals that at the wavelength where filter 425 is transmitting, less than 1% of the photons can penetrate the entire thickness of a 5-mil Kapton sample. Since the change in conductivity is measured through the film, it is critical that the photons responsible for the conductivity change should penetrate the entire thickness of the material. Consequently, although the photons have sufficient energy to cause the changes that are responsible for conductivity increase, they fail to penetrate enough to produce a significant increase in bulk current for the 5-mil Kapton sample. However for the thinner 2-mil Kapton sample, more photons can penetrate the entire thickness of the film, and a slight increase in bulk current was observed.

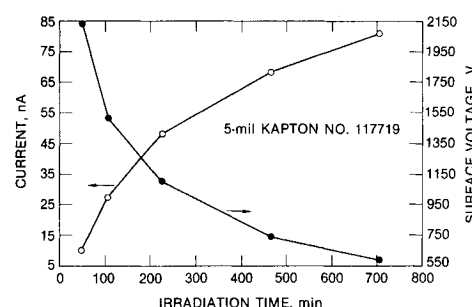**Fig. 6** Plot of I-V measurements as function of irradiation time.

On the other hand, according to the absorption spectrum of Kapton, a large percentage of photons from filter 560 can penetrate both the 2- and 5-mil Kapton films. These longer wavelength photons lack the energy required to cause the chemical changes necessary to increase the conductivity of the film. As a result, only minor increases in the bulk current were detected. Filter 502 was chosen because its transmission maximum coincided with the absorption-band edge of Kapton. The photons in this spectral region have both depth penetration and the energy appropriate for photochemical reactions. Under these conditions, electrical conductivity through the thickness of the film was found to increase dramatically.

### Quenching Study

The results we have presented so far can be explained by the formation of electrically active centers generated in the bulk of the material by photochemical reactions. In an attempt to identify which chemical species produced by the photochemical reactions are electrically active, we carried out a series of experiments in which the quenching effects of various gases were studied. In these experiments, Kapton specimens were irradiated with a 1000-W xenon lamp. After the increase in dark current was measured in a vacuum of  $10^{-7}$  Torr, a particular gas was admitted to the vacuum chamber, and the pressure of the chamber was raised to 400

§ Results of our previous studies on surface charging of insulators indicate that when the bulk current is small compared to the incident charging current, the surface potential is controlled by the secondary electron emission characteristics of the material and is not dependent on the conductivity of the material.

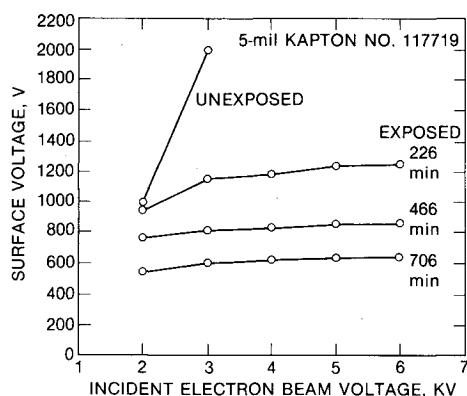


Fig. 7 Charging behavior of specimen before and after irradiation.

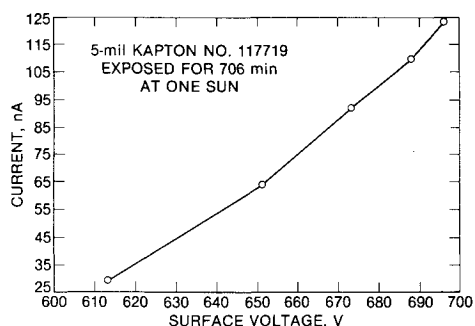


Fig. 8 I-V characteristics of specimen after 706 min of irradiation.

Torr. The specimen remained in this gaseous environment for 16 h. At the end of this period, the change in dark current was measured after the chamber had been reevacuated to a pressure of  $10^{-7}$  Torr. The gases used in this study were dry  $N_2$  and dry air. We found dry  $N_2$  had no effect on the dark current of the specimen, but dry air was extremely effective in quenching the increase in dark current.

These results suggest oxygen is responsible for deactivating the electrically active centers in the specimen. It is well known that organic radicals or radical ions are byproducts of photochemical dissociation of polymeric materials such as Kapton. Acting as donors or acceptors, these radicals are responsible for the observed increase in conductivity. When exposed to dry air, these radicals can react with oxygen to form more stable peroxy radicals that appear to be electrically inactive. As a result, the increase in conductivity is quenched. This finding is consistent with our conjecture that the conductivity increase is photochemical in origin.

Although we did not perform a long-term study to determine the stability of these electrically active centers, our results suggest that these centers appear to be stable at  $10^{-7}$  Torr. During the several weeks in which the experiment was performed, no appreciable degradation in dark conductivity of the sample was observed. This evidence is indirect, however, because the sample was continually being irradiated. A more direct experiment is needed to define the relationship between ambient oxygen partial pressure and the rate of decrease in dark current. Such a study would provide the information necessary to predict the stability of these electrically active centers in different environments.

#### Exposure Time Dependence

In order to make use of the light-induced increase in conductivity to control electrostatic charge buildup, it is essential to determine how the conductivity of Kapton varies with exposure time. A plot of the change in I-V measurements as a function of irradiation time for a 5-mil Kapton film is

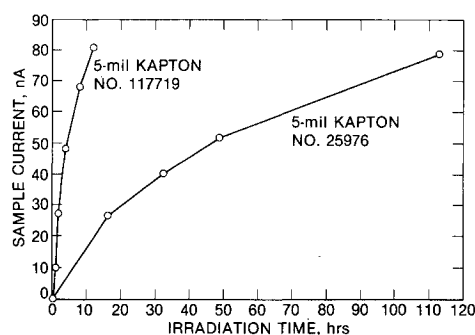


Fig. 9 I-V characteristics of specimen at various irradiation times.

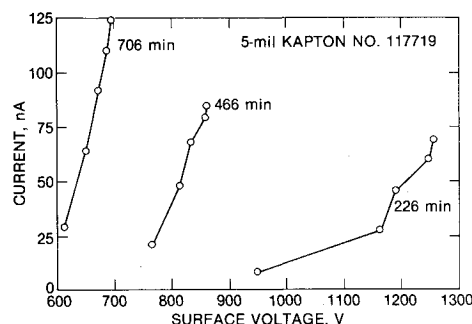


Fig. 10 Different batches of Kapton exhibiting markedly different rates of dark conductivity increase under the same irradiation conditions.

shown in Fig. 6. The electron beam voltage used in this particular case was 4 kV. The increase in the measured dark current shown in Fig. 6 is accompanied by a decrease in the surface potential indicating that the conductivity of the specimen is increasing as a result of irradiation.

Further investigation of the I-V behavior of the specimen revealed that the potential of the specimen measured after irradiation became less dependent on the incident charging beam voltage (Fig. 7). More importantly, the I-V curve shown in Fig. 8 obtained after 706 min of irradiation was found to be linear. Furthermore, the surface voltage was found to increase linearly with the incident beam current density and not the beam voltage. These results indicate that the specimen was behaving like a resistor and the electron beam was acting as a current source. This behavior represents a drastic departure from the I-V characteristics of the material before it was irradiated. Before irradiation, the surface potential varied linearly with the incident beam voltage and did not depend on the beam current density at all. This effect had been studied in detail by the authors earlier and found to be the result of secondary electron emission-controlled charging.<sup>7</sup> This phenomenon occurs only in low-conductivity materials where the major part of the incident beam current has to be balanced at the sample surface by secondary electron emission instead of conduction. For the specimen that is more conductive, the material will exhibit I-V characteristics more closely resembling those of a resistor.

In the case under study, the conductivity increases were caused by exposure to solar radiation, and we were able to follow the I-V behavior as the conductivity of the specimen was increased stepwise (Fig. 9). A detailed analysis of the I-V curves was performed to obtain an estimate of the resistance of the specimen at different exposure times. The resistivity data are summarized in Table 2. We find that the increase in conductivity is directly proportional to the increase in exposure time. This finding agrees with our earlier observation that the conductivity increase in Kapton was caused by the

Table 2 Change in dark conductivity of Kapton with exposure time

Exposure time, min	Increase in exposure time, min	Resistivity, $\rho$ ( $\Omega\text{cm}$ )	Conductivity, $\sigma$ ( $1/\Omega\text{cm}^{-1}$ )	Increase in conductivity, ( $1/\Omega\text{cm}$ )
226	240	$19.4 \times 10^{12}$	$0.5 \times 10^{-13}$	$1.5 \times 10^{-13}$
446		$5.1 \times 10^{12}$	$2.0 \times 10^{-13}$	
706		$2.9 \times 10^{12}$	$3.4 \times 10^{-13}$	

accumulation of electrically active centers produced by photochemical reactions. The agreement can be explained by examining the basic charge transport equations.

$$j = \sigma E \quad (1)$$

and

$$\sigma = en\mu \quad (2)$$

where  $j$ ,  $\sigma$ ,  $E$ ,  $e$ ,  $n$ , and  $\mu$  are current density, conductivity, electric field, electronic charge, and carrier density, and carrier mobility in Kapton, respectively. Since carrier mobility is a bulk property, it is not expected to be affected by minor chemical changes in a low-mobility polymeric material such as Kapton. Therefore, the increase in conductivity must be largely the result of an increase in the carrier density which, in turn, is controlled by the number of electrically active centers present in the material. At the same time, because the active centers are produced photochemically, the concentration of these centers should be directly proportional to the total dosage of light received by the specimen. In unimolecular photochemical reactions, the change in product concentration,  $dn/dt$ , is directly proportional to the light intensity  $I$ , or

$$\frac{dn}{dt} = \eta I \quad (3)$$

where  $\eta$  is the quantum yield for the reaction. Integrating the change over time at constant light intensity,

$$\Delta n = \eta I \Delta t \quad (4)$$

and therefore

$$\Delta \sigma = e\mu\eta I \Delta t \quad (5)$$

Hence, it is reasonable to expect the increase in conductivity of Kapton to be directly proportional to the exposure time, which is exactly what we found from our measurements.

In addition, we have uncovered a rather unexpected result from studying Kapton specimens prepared from different production batches. We found that different batches of Kapton exhibited similar increases in conductivity but differed markedly in the rate of increase under the same exposure conditions (Fig. 10). The specimen from batch number 117719 required approximately 10 times less light than the specimen from batch number 25976 in order to reach the same level of conductivity. This finding has important ramifications on the development of antistatic thermal control surfaces for future spacecraft. Our results show that the increase in conductivity of Kapton can be accelerated or inhibited by varying processing conditions or additives. More specifically, it means that the conductivity of Kapton in space can be tailored to match the requirements of specific end-use applications, provided that the basic mechanism controlling the rate of conductivity increase is known. A series of additional experiments had been conducted to investigate the chemical differences that may exist between the different batches. No extraneous differences in chemical additives were

detected in the infrared spectra of the films or in the gas chromatographic analyses of extracts from samples from the two different batches. However, the specimen from batch number 25976 appears to be darker, and the absorption spectrum shows a shift of the absorption band edge to a longer wavelength. Since no measurable difference in additives was found, we speculate that the shift in absorption could be the result of higher degree of thermal crosslinking. It was found that density, color intensity, and viscosity increased as the Kapton film received greater thermal treatment.<sup>8</sup> Kapton is a polyimide comprised of monomers derived from benzene. The polymer is yellowish brown in color because of the localization of the  $\pi$  electrons in the benzene ring. Crosslinking the polymers increases the interaction between the  $\pi$  electrons and gives rise to a more intense optical absorption band as well as a shift of the band edge to a longer wavelength. The results of the spectral dependence study show that only a narrow portion of the visible spectrum, near the onset of the absorption band, is effective in producing a conductivity increase, which means that the threshold energy for photochemical reaction is only slightly lower than the absorption band edge. Consequently, a shift of the absorption band to lower energy can reduce the number of photons available in the bulk of the material for reaction drastically, and thus has a significant effect in lowering the rate of conductivity increase. So far, this explanation is only a speculation, even though it seems to be consistent with all our previous findings.

### Summary and Conclusion

The spectral dependence of the dark conductivity of Kapton has been determined. It was found that only a very narrow portion of the solar spectrum is effective in causing an increase in the through-film dark current of Kapton. Experiments were also carried out to study the efficiency of various gaseous environments in quenching the light-induced dark current. The results indicated that the increase in the dark conductivity of Kapton is caused by an accumulation of electrically active centers produced photochemically in the bulk of the material, and these active centers should have an extremely long lifetime in the absence of oxygen. This finding suggests that the light-induced increase in conductivity of a Kapton film can persist for a long time in orbit where there is a very low density of oxygen atoms or molecules.

The increase in conductivity of Kapton as a function of exposure time has also been determined and analyzed in detail. The analysis showed that the conductivity increase is directly proportional to the exposure time. This observation is consistent with the concept that the increase in conductivity is photochemical in origin. Markedly different rates of increase in conductivity were also observed in Kapton specimens from two different production batches. The lower rate can be explained by the shift of absorption band edge to a longer wavelength. One important conclusion that can be drawn from our results thus far is that it is possible to raise the conductivity of Kapton to a level where it can be used as an antistatic spacecraft surface in a reasonably short time by

exposing Kapton to solar radiation in space. However, before Kapton can be recommended for use as an antistatic spacecraft surface, more work would be needed to determine how long the increased conductivity will persist in space.

#### Acknowledgment

This work was supported by the U.S. Air Force under Space Division Contract F04701-83-C-0084.

#### References

- <sup>1</sup>Meulenberg, A., and Robinson, P.A., "Conductive Through Punctures in Metalback Dielectrics," *Spacecraft Charging Technology 1980*, AFGL-TR-81-0270, 1981, p. 342.
- <sup>2</sup>Levadou, F., Bosma, S.J., and Paillous, A., "Materials Characterization Study of Conductive Flexible Second Surface Mirrors," *Spacecraft Charging Technology 1980*, AFGL-TR-81-0270, 1981, p. 237.
- <sup>3</sup>Coffey, H.T., Nanevic, J.E., and Adamo, R.C., *Photoconductivity of High Voltage Space Insulating Materials*, Final Report, Project 3545, Stanford Research Institute Contract NAS 3-18912, Oct. 1975.
- <sup>4</sup>Stevens, J.R. and Vampola, A.L., *Description of Space Test Program P78-2 Spacecraft and Payload*, SAMSO TR-78-24, The Aerospace Corp., El Segundo Calif, Oct. 1981.
- <sup>5</sup>Mizera, P.F., "Summary of Spacecraft Charging Results," *Journal of Spacecraft and Rockets*, Vol. 20, Sept.-Oct. 1983, p. 438.
- <sup>6</sup>Leung, M.S. and Kan, H.K.A., "Laboratory Study of the Charging of Spacecraft Materials," *Journal of Spacecraft and Rockets*, Vol. 18, Nov.-Dec. 1981, p. 510.
- <sup>7</sup>Leung, M.S., Tueling, M.B., and Schnauss, E.R., "Effects of Secondary Electron Emission on Charging," *Spacecraft Charging Technology, 1980*, AFGL-TR-81-0270, 1981, p. 163.
- <sup>8</sup>Dine-Hart, R.A., Parker, D.B.V., and Wright, W.W., *British Polymer Journal*, 3, Sept. Parts I, II, III, 1971, p. 222.

## *From the AIAA Progress in Astronautics and Aeronautics Series...*

### **MATERIALS SCIENCES IN SPACE WITH APPLICATIONS TO SPACE PROCESSING—v. 52**

*Edited by Leo Steg*

The newly acquired ability of man to project scientific instruments into space and to place himself on orbital and lunar spacecraft to spend long periods in extraterrestrial space has brought a vastly enlarged scope to many fields of science and technology. Revolutionary advances have been made as a direct result of our new space technology in astrophysics, ecology, meteorology, communications, resource planning, etc. Another field that may well acquire new dimensions as a result of space technology is that of materials science and materials processing. The environment of space is very much different from that on Earth, a fact that raises the possibility of creating materials with novel properties and perhaps exceptionally valuable uses.

We have had no means for performing trial experiments on Earth that would test the effects of zero gravity for extended durations, of a hard vacuum perhaps one million times harder than the best practical working vacuum attainable on Earth, of a vastly lower level of impurities characteristic of outer space, of sustained extra-atmospheric radiations, and of combinations of these factors. Only now, with large laboratory-style spacecraft, can serious studies be started to explore the challenging field of materials formed in space.

This book is a pioneer collection of papers describing the first efforts in this new and exciting field. They were brought together from several different sources: several meetings held in 1975-76 under the auspices of the American Institute of Aeronautics and Astronautics; an international symposium on space processing of materials held in 1976 by the Committee on Space Research of the International Council of Scientific Unions; and a number of private company reports and specially invited papers. The book is recommended to materials scientists who wish to consider new ideas in a novel laboratory environment and to engineers concerned with advanced technologies of materials processing.

*Published in 1977, 580 pp., 6×9 illus., \$25.00 Mem., \$39.00 List*

**TO ORDER WRITE: Publications Order Dept., AIAA, 1633 Broadway, New York, N.Y. 10019**