

Structurally Compliant Rocket Engine Combustion Chamber—Experimental and Analytical Validation

Robert S. Jankovsky*

NASA Lewis Research Center, Cleveland, Ohio 44135

Vinod K. Arya†

University of Akron, Akron, Ohio 44325

and

John M. Kazaroff‡ and Gary R. Halford§

NASA Lewis Research Center, Cleveland, Ohio 44135

A new, structurally compliant design for a rocket engine combustion chamber has been validated through analysis and experiment. Subscale, tubular channel chambers have been cyclically tested and analytically evaluated. Cyclic lives were determined to have a potential for 1000% increase over those of rectangular channel designs, the current state of the art. Greater structural compliance in the circumferential direction gave rise to lower thermal strains during hot firing, resulting in lower thermal strain ratcheting and longer predicted fatigue lives. Thermal, structural, and durability analyses of the combustion-chamber design, involving cyclic temperatures, strains, and low-cycle fatigue lives, have corroborated the experimental observations.

Nomenclature

A	= material constant, s^{-1}
B	= back stress, MPa
D	= drag stress, MPa
D_0	= material constant, MPa
E	= Young's modulus, MPa
H	= material constant, MPa
h	= material constant, MPa
J_2	= second invariant of effective stress
k	= Boltzmann constant, J/mol K
L	= material constant, MPa
n	= constant
r	= recovery function
S	= deviatoric stress, MPa
s	= material constant, MPa
T	= temperature, K or °C
$\Delta\epsilon$	= total strain range, mm/mm
δ	= Kronecker delta
ϵ	= strain, mm/mm
θ	= thermal diffusivity function
ν	= Poisson's ratio
Σ	= effective stress, MPa
σ	= stress, MPa

Subscripts

A	= absolute temperature, K
e	= von Mises stress or strain
i, j	= components (stress or strain)
m	= melting temperature of material, K
1, 2, 3	= principal stresses or strains

Superscript

- = derivative with respect to time

Introduction

ROCKET combustion chambers, such as the one used in the Space Shuttle main engine, operate at extremely high heat flux ($163.5 \text{ J/mm}^2 \text{ s}$) at the throat. The high heat flux results from high-temperature (3315°C), high-pressure (20 MPa) combustion gases. Active cooling of the chamber is mandatory to keep the hot-gas-side wall material from melting. The choice of materials for constructing the hot-gas-side wall is limited. Only materials with extremely high thermal conductivity can survive in these severe environments without melting or otherwise losing their structural integrity. Copper and dilute copper-base alloys offer the highest possible thermal conductivity with mechanical properties sufficient to withstand static and cyclic loading.

The mechanical durability of copper chambers can be limited by several potential failure modes: creep rupture, low-cycle thermal fatigue, and thermal-mechanical ratcheting. The useful life of the throat region of the Space Shuttle main engine, a rectangular channel chamber, is governed by thermal-mechanical ratcheting. Ratcheting takes the form of local bulging and thinning of the rectangular channel wall separating the hot-gas and coolant sides, as indicated by the "doghouse" configuration in Fig. 1 (from Ref. 1). The rate of ratcheting and wall thinning depends strongly on the severity of thermal loading (both maximum temperature and thermal gradients), the thermal and structural compliance, and the geometry of the combustion chamber, and to a lesser extent on the material strength and ductility. Elimination of the ratcheting failure mode by improving material strength and ductility is highly unlikely, because extremely large increases in material properties are required. Only incremental improvements in material properties are presently feasible. However, as seen from the results of the current experimental and analytical study, significant improvements can be made in the geometry of the cooling channels, and these considerably reduce the amount of ratcheting and thereby extend life. Unfortunately, the type of expected failure (thermal-mechanical ratcheting) cannot be analytically modeled within the present state of the art. Both thermal-mechanical ratcheting and fatigue are dominated by the strain range; therefore, it is reasonable to infer that a fatigue analysis would provide a fair estimate of the relative lives of channel geometries.

In this study the structural durabilities of a tubular channel chamber (Fig. 2) and a rectangular channel chamber were compared. Experimentally, subscale hardware was designed and tested to isolate the effects of geometry on thrust-chamber life. The experimental hardware was modeled analytically. A new viscoplastic, constitutive stress-strain model for copper was incorporated into the chamber

Received Aug. 2, 1994; revision received March 7, 1995; accepted for publication March 17, 1995. This paper is declared a work of the U.S. Government and is not subject to copyright protection in the United States.

*Aerospace Engineer, On-Board Propulsion Branch.

†Visiting Associate Professor, Department of Mathematical Sciences.

‡Senior Research Engineer (deceased).

§Senior Scientific Technologist, Structures Division.

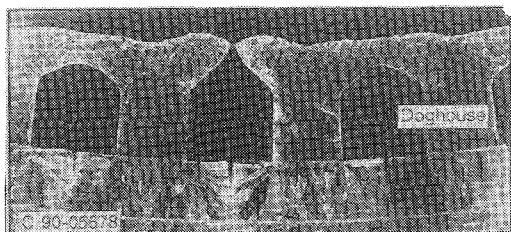
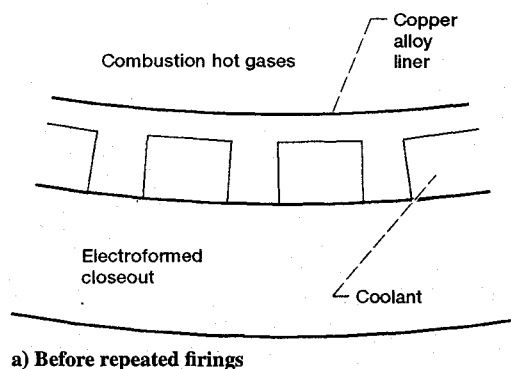


Fig. 1 Milled rectangular channel.

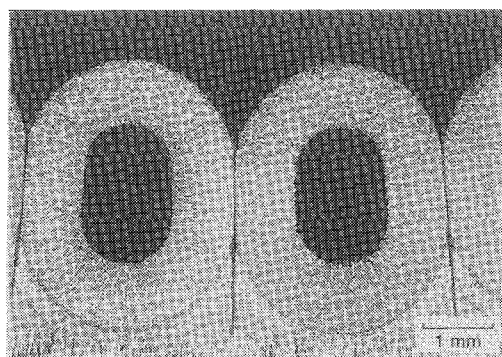


Fig. 2 "Booked" tubular channel construction.

models, and the two configurations were compared at nominal operating conditions. The experimental results from subscale chamber testing confirmed the expectations of the analyses, that significant improvements in cyclic durability can be expected from more compliant, less-constrained channel constructions.

Experimental Investigation

The testing of both chamber designs has been previously reported, i.e., rectangular channel testing¹ and the tubular channel testing.² The apparatus, test procedure, and results are summarized here.

Apparatus

A broad base of data on copper-alloy combustion chambers with rectangular channel coolant passages has been obtained on a low-cost, subscale rocket engine test apparatus, shown in Fig. 3. The apparatus is used to study the cyclic durability of rocket chamber walls, to screen candidate chamber-wall materials, and to evaluate fabrication techniques for improved life and performance. The test apparatus consists of an annular injector; a 15-cm-long, liquid-hydrogen-cooled outer cylinder, which serves as the test chamber; and a water-cooled centerbody, which forms the combustion, sonic throat, and expansion sections of an annular rocket engine. It is at the sonic throat station that the maximum heat flux is encountered, and this location is studied for fatigue. The standard test-chamber configuration has 72 rectangular coolant passages.¹

A variation of this standard configuration was used for the comparison reported herein. A new test chamber was designed with a stacked bundle of 72 oxygen-free, high-conductivity (OFHC) copper tubes as the coolant passages (Fig. 4). The same number of coolant passages is used in the standard rectangular channel chambers, thus allowing direct comparison of results. To provide a coolant-flow area equivalent to the rectangular channel configuration and to maintain the same wall thickness, round tubes were required to be "booked" (i.e., compressed to form the oval shape shown in Fig. 5).

Procedure

The test procedure for the tubular channel chambers was identical to that used for fatigue tests of the rectangular channel chambers.¹ Gaseous hydrogen and liquid oxygen were used as propellants at a nominal mixture ratio of 6.0 at a chamber pressure of 4.14 MPa. The maximum hot-gas-side wall temperature was controlled by a separate mass flow of liquid hydrogen through the coolant passages.

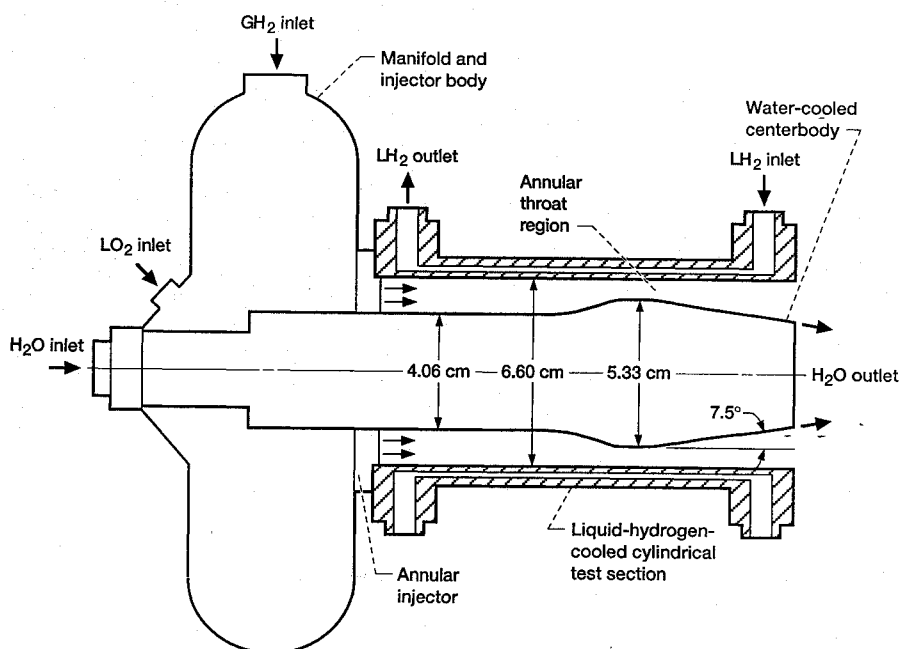


Fig. 3 Subscale rocket engine test apparatus.

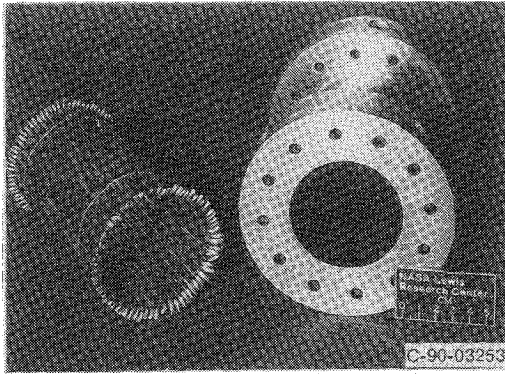


Fig. 4 Stack of OFHC copper tubes and completed subscale thrust chamber.

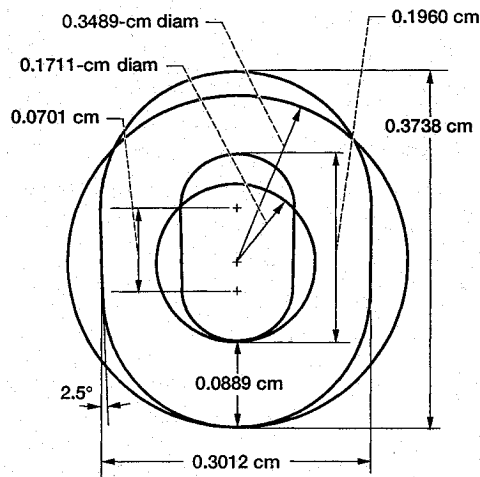


Fig. 5 Diagram of tube dimensions (round to booked).

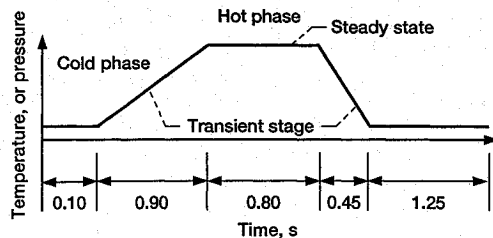


Fig. 6 Schematic cycle of loading (typical cycle history).

The chamber was fired for 1.7 s to allow it to reach thermal equilibrium and then shut down for 1.8 s while the coolant continued to flow to achieve steady-state cold conditions. The total cycle time was 3.5 s (Fig. 6). This cycle was repeated approximately 50 times. The combustion chamber was then inspected and subjected to another 50 cycles. This sequence was repeated until a combustion-chamber failure was detected by sensing a coolant passage leak.

Results

Two tubular channel chambers were tested for comparison with the rectangular channel chambers.¹ The first chamber was test fired at the nominal combustion conditions and a hot-gas-side wall temperature of 570°C. Failure occurred after 637 cycles. The second chamber was also test fired at nominal combustion conditions but was run with a hot-gas-side wall temperature of 671°C. This chamber failed after 256 cycles.²

Rectangular channel chambers were tested at the same nominal operating conditions as the tubular chambers and at a wide range of hot-gas-side wall temperatures.¹ The number of cycles to expected failure for a rectangular channel chamber of this configuration tested at 538°C is 250 cycles, and for one tested at 671°C was 117 cycles.¹ The test-fire results for the two types of chambers show two to three times more cycles to failure for the tubular chamber.

Analytical Investigation

Finite Element Thermal and Structural Analyses

Accurate predictions of the cyclic lives of the tubular and rectangular channels require accurate assessments of the inelastic response of these channels. Advanced viscoplastic models treat all the inelastic strains (including creep, plastic, relaxation, etc.) as a single entity and thus automatically include any interactions among them. Viscoplastic models, therefore, provide realistic descriptions of inelastic response. In this study, a viscoplastic model from Ref. 3 was employed to calculate the inelastic response of the channels. This viscoplastic model is described briefly in the appendix. The material constants for copper for this model are given in Table 1.

The constitutive equations of the viscoplastic model are highly nonlinear and mathematically "stiff." Applying viscoplastic models to structural engineering problems, such as the present channel comparison problem, requires the development of suitable numerical solution technologies employing, for example, the finite element method. In the present work, a numerical solution from Ref. 4 was employed. The general-purpose finite element program MARC (Ref. 5) was used to perform the finite element calculations. Time integration of the stiff constitutive equations of the viscoplastic model requires efficient and accurate integration techniques. Because an explicit integration method does not require the assembly and inversion of Jacobian matrices, a time integration strategy,⁶ based on the explicit forward Euler method, was employed here. This integration strategy has been successfully applied to numerous problems and has been found to work well for problems that involve complex thermal and/or mechanical loadings.^{7,8} The thermoviscoplastic response of structural components is also studied in Refs. 9 and 10.

The finite element models for the rectangular and tubular channels were generated by using the PATRAN program.¹¹ These models are shown in Fig. 7. Generalized plane-strain, isoparametric elements were used to model the smallest repeating segment of the chamber walls. The use of these elements facilitated quasi-three-dimensional analyses for the channels. The rectangular channel model consisted of 532 elements and 601 nodes, whereas the tubular channel model was constructed with 552 elements and 615 nodes. These finite element models were used to perform uncoupled thermal and structural analyses presented here. The finite element meshes used in the present work are fine enough to preclude the dependence of results on the mesh sizes.

Steady-state heat-transfer analyses were performed to obtain the temperature profiles for the rectangular and tubular channels. Relevant properties and boundary conditions were input to the MARC program. The steady-state temperature distributions for the rectangular and tubular channels obtained from these analyses (Fig. 8) were similar.

The cyclic thermal and mechanical loadings used in the uncoupled thermomechanical finite element analyses are shown in Fig. 6 and Table 2 (also see Ref. 12). The temperatures during the transient stage of the thermal cycle were obtained from corresponding steady-state temperatures by employing linear interpolation. The duration of a typical thermal-mechanical cycle was 3.5 s. Time-varying nodal temperatures and elemental pressure loadings were



Table 1 Material constants for copper^a

Elastic modulus E , MPa	165000 - 125 T , T in °C
Coefficient of thermal expansion α , °C ⁻¹	$15 \times 10^{-6} + 5 \times 10^{-9}T$, T in °C
Poisson's ratio ν	0.34
Constant A , s ⁻¹	50×10^6
Constant D_0 , MPa	1.5
Constant h , MPa	500
Constant H , MPa	5000
Limiting value of backstress at kinematic saturation, L , MPa	$25 \exp(-T/300)$
Constant n	5
Activation energy Q , J/mole	200,000
Constant s , MPa	14.3
Melting point T_m , K	1356
Boltzmann constant k , J/mol K	8.314


^aFrom Ref. 3.

Table 2 Cyclic temperature and pressure loading histories^a

	Wall pressure, MPa	
	Cold phase	Hot phase
Hot-gas side	0.0965	2.78
Coolant side	5.1000	6.55

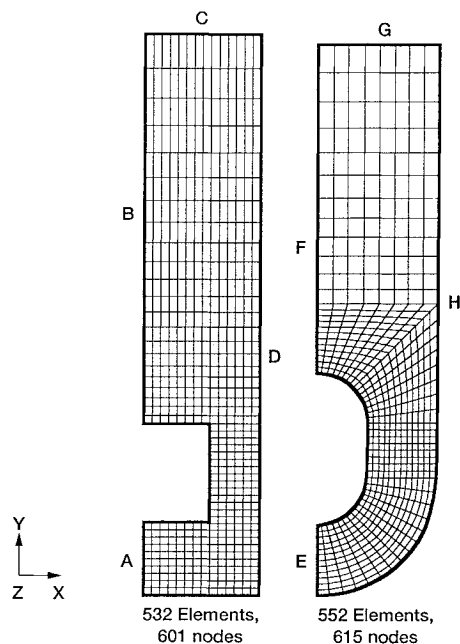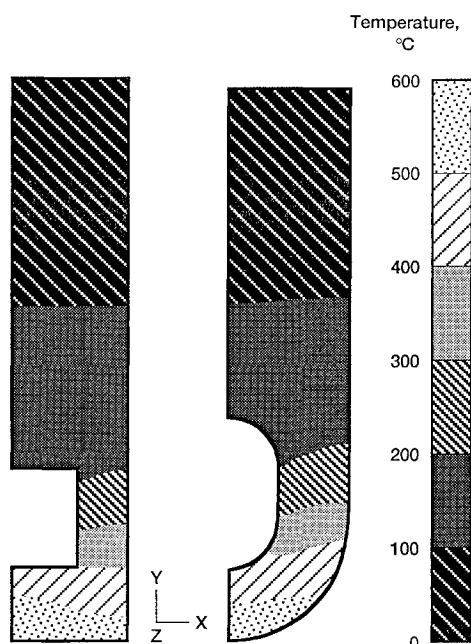^aFrom Ref. 12.**Fig. 7** Finite element models of rectangular and tubular channels.**Fig. 8** Temperature distribution in rectangular and tubular channels during fifth cycle.

applied to trace the loading cycle shown in Fig. 6. The variations in material properties with temperature (see Table 1) were taken into consideration for these computations. The boundary conditions for the structural analyses are shown in Fig. 7. The edges A, B, D of the rectangular channel and E, F, H of the tubular channel were fixed in the x direction. The edges C of rectangular channel and G of the tubular channel were fixed in the y direction.

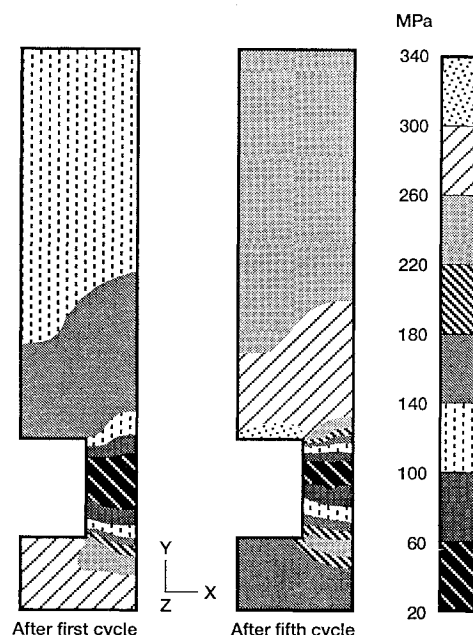**Fig. 9** Von Mises stress in rectangular channel after first and fifth cycles.

The von Mises stress distributions {stress: $\sigma_e = (1/\sqrt{2})[(\sigma_1 - \sigma_2)^2 + (\sigma_2 - \sigma_3)^2 + (\sigma_3 - \sigma_1)^2]^{1/2}$ } in the rectangular and tubular channels are shown in Figs. 9 and 10, respectively. These figures exhibit effective stress in the channels at the end of the first and fifth loading cycles. Examination of these figures reveals a significant redistribution of effective stress due to inelastic deformation. In the case of the rectangular channel, for example, at the end of the first cycle the effective stress in the lower part of the segment was higher than that in the upper part. But at the end of the fifth cycle, the effective stress in the lower part of the segment was lower than that in the upper part. Similar conclusions can be drawn for the tubular channels. The finite element thermoviscoplastic analyses were carried out only for five cycles because the stress and strain distributions in the rectangular and tubular channels were stabilized. Since the cyclic thermoviscoplastic finite element analyses are computationally intensive, an effort to perform these analyses for a few hundred cycles is impractical.

Figure 11 shows the maximum von Mises strains {strain: $\epsilon_e = (1/\sqrt{2})[(\epsilon_1 - \epsilon_2)^2 + (\epsilon_2 - \epsilon_3)^2 + (\epsilon_3 - \epsilon_1)^2]^{1/2}$ } in the rectangular and tubular channels during the fifth loading cycle. The maximum effective strain in the tubular channel was considerably lower than that in the rectangular channel. Note also from this figure that the location of maximum effective strains differed for the rectangular and tubular channels. The deformed shapes of the rectangular and tubular channels are plotted in Fig. 12 at the end of the fifth cycle. The deformations in the two channels are magnified by a factor of 1000 to facilitate visual interpretation. The figure shows a significantly larger deformation of the rectangular channel than of the tubular channel.

Figures 13 and 14 display the thinning of channel walls in the circumferential (X) and radial (Y) directions. The values plotted are at the ends of five loading cycles. The figures reveal that the rectangular channel wall thinned at a more rapid rate than did the tubular channel wall. For example, at the end of the fifth cycle the thickness of the rectangular channel wall had been reduced approximately twice as much as the tubular channel wall thickness. Looking at the deformed shapes in Fig. 12, the thinning in the radial direction is quite obvious.

It is clear from this discussion that for the same thermal-mechanical loading cycles: 1) the deformation of the tubular channel was strikingly smaller than that of the rectangular channel and 2) the thinning of the tubular channel wall in the circumferential and radial directions was much slower than that of the rectangular channel wall. It may thus be concluded that using a tubular geometry for

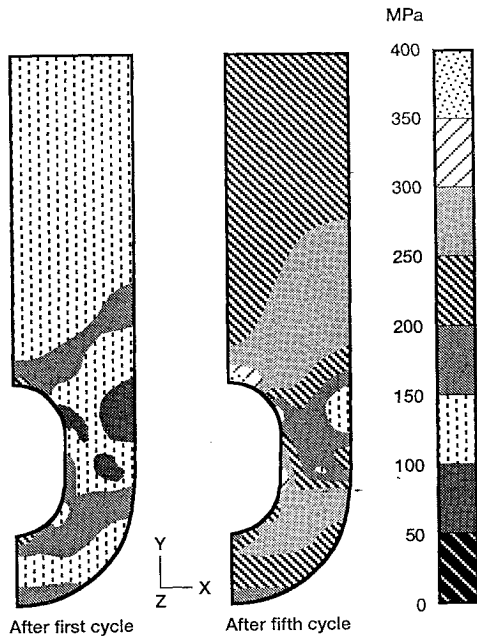


Fig. 10 Von Mises stress in tubular channel after first and fifth cycles.

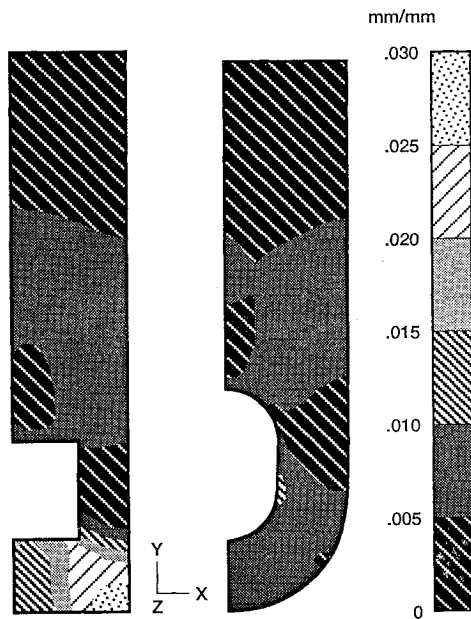


Fig. 11 Von Mises maximum strain in rectangular and tubular channels during fifth cycle.

the coolant channel can greatly increase the durability and life of thrust chambers.

Life Analyses

Life analyses of the rectangular and tubular channel combustion chambers were performed in accordance with an established procedure referred to as the "local strain" approach. The principal elements of this approach are 1) thermal and mechanical (pressure) mission loads imposed on the chamber, 2) heat transfer coefficients for the fluids and the structural components, 3) thermal conductivity and thermal expansion properties of the material, 4) cyclic elastoplastic constitutive stress-strain-temperature-time behavior of the material, and 5) low-cycle fatigue behavior of the material as represented by the cyclic effective plastic strain range vs the cyclic crack initiation life.

The first four elements are used as input to finite element analyses, which produce an output of local stresses, strains, and temperatures for each element as a function of mission operation time. Scanning the output locates the critical finite elements where temperature

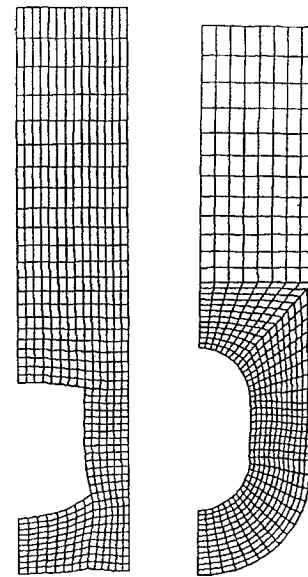


Fig. 12 Deformed shapes of rectangular and tubular channels after five cycles (magnification factor = 1000).

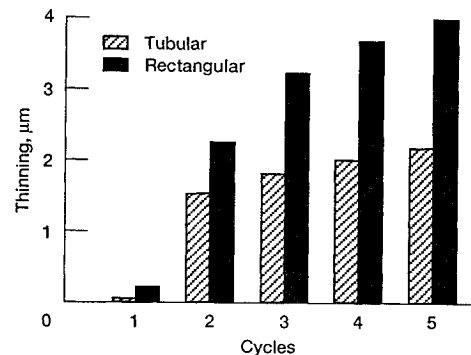


Fig. 13 Thinning in x direction of rectangular and tubular channel walls after different numbers of cycles.

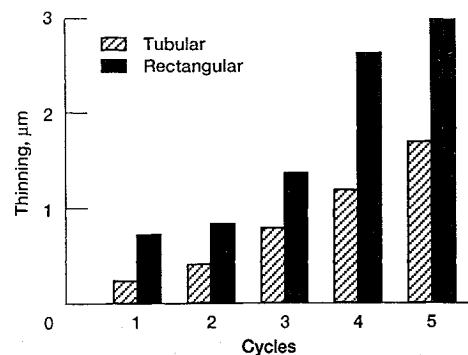



Fig. 14 Thinning in y direction of rectangular and tubular channel walls after different numbers of cycles.

extremes and strain range are largest and that hence are the most likely locations for thermal low-cycle fatigue cracks to initiate. The cyclic crack initiation life of the liner is assumed to be the same as the cyclic life of an axially loaded laboratory coupon when each is subjected to the same total effective strain range, $\Delta\epsilon_e$.

The thermal-mechanical loading cycle shown in Fig. 6 was applied repeatedly to both chamber designs. The maximum and minimum temperatures, effective strains, and effective stresses at the most critical location for each chamber design are presented in Table 3. This information evolved from the thermal and structural analyses of the chambers as they were cycled between the temperature extremes of the mission loading cycle. Supplemental

Table 3 Temperatures and ranges of stress and strain at critical locations in rectangular and tubular channels

Channel	Metal temperature, °C		Effective stress range, MPa	Effective strain range, %	
	Max.	Min.		Total	Plastic
Rectangular	538	-218	167	2.60	2.46
Tubular	445	-218	210	1.05	0.87

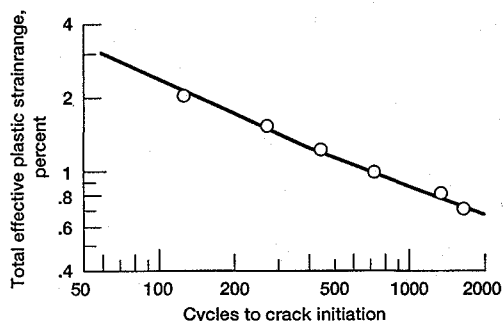**Fig. 15** Low-cycle fatigue resistance of OFHC copper at 538°C in argon at cyclic strain rate of 0.2%/s.

calculations indicated that the pressure loading, acting alone, would have a negligible effect on the deformation and life of the chambers (i.e., the pressure-induced stresses were well below the yield strength of the material at the nominal maximum operating temperature of 538°C). The associated creep rates also were small. Despite the small influence of pressure when acting alone, the simultaneous application of the pressure loading and the thermal gradients gave rise to large cyclic strains and an accelerated rate of ratcheting. The contribution to the range of total strain at the critical location due to the thermal gradient (and associated thermal constraint) was 2.6% for the rectangular channel design (of which 2.46 percentage points was plastic strain) and 1.05% for the tubular channel design (of which 0.87 percentage point was plastic strain). The time per cycle was extremely short (3.5 s), and only 2.3 s was spent at temperatures above the minimum cryogenic level. Consequently, during heating and cooling, the average strain rate was quite high (on the order of 1 to 2%/s). Because of the high strain rate, insufficient time was available for appreciable time-dependent, thermally activated creep deformation to occur. Any creep that might be present would occur most likely as stress relaxation during the brief (0.8 s) hold period at maximum temperature. Local stress relaxation of as much as 10% from the peak compressive stress would introduce a compressive creep strain of less than about 0.01%. This strain is approximately three orders of magnitude smaller than the plastic strain range and would not be expected to affect the cyclic life of the channel wall. Consequently, for nominal chamber operation there was little concern for creep-fatigue interaction during hot-fire testing of the chambers, and the life-prediction analysis was simplified to a simple cyclic elastoplastic condition.

Pertinent high-temperature, low-cycle, plastic-strain fatigue data have been reported¹³ for annealed OFHC copper at 538°C in a nonoxidizing argon atmosphere. These data are shown in Fig. 15 as total effective plastic strain range versus cycles to crack initiation. The data had been generated at a cyclic strain rate of 0.2%/s, which is about one-tenth the rates experienced in the chambers. At this cyclic strain rate the extent of time-dependent, thermally activated cyclic creep strain is negligible. Hence, the data meet an important criterion for applicability to the current analyses—negligible creep-fatigue interaction.

Another important criterion for using Conway's isothermal data is their applicability to the variable temperatures experienced throughout the mission cycle of the combustion chambers. Because the tensile ductility of OFHC copper is virtually insensitive to temperature, it is expected that the low-cycle fatigue resistance (plastic strain range versus life) will also be insensitive to temperature.¹⁴ Tensile-test reduction of area varies from 81 to 98% over the temperature

range of concern (approximately -218 to 538°C). If the fatigue failure relation is independent of temperature, and only one deformation mechanism is present (cyclic plasticity), it is reasonable to assume that the fatigue failure relation will be directly applicable to the thermal cycling conditions being considered. In other words, one curve, determined at any isothermal temperature within the cyclic range of -218 to 538°C, should be applicable to all temperatures within the range if the strains in the cycle are predominantly plastic. The latter was the case for both the isothermal fatigue test data and the strains occurring at the critical locations within the chambers. Note that environmental oxidation interaction was precluded by use of an inert argon atmosphere for coupon testing and by the hydrogen-rich, reducing atmosphere present during chamber testing. Note also that OFHC copper is not embrittled by the presence of hydrogen.¹⁵

For temperatures far above 538°C, however, creep and associated creep damage cannot be ignored, because they increase with temperature at an exponential rate. Some of the chamber tests experienced temperatures as high as 671°C; therefore, creep strain due to the internal channel pressure acting alone would become (based on a simple Larson-Miller parameter¹⁶) nearly three orders of magnitude greater than at 538°C. Consequently, the time-dependent deformation would become a nonnegligible fraction of the plastic strain, with a resultant loss in cyclic life expectancy. Quantitatively acceptable calculations of the creep-strain contributions were not possible without performing three-dimensional finite element viscoplasticity analyses for the highest-temperature chamber tests. Qualitatively, a large decrease (approaching an order of magnitude in life) in cyclic durability could be expected.

Predicting fatigue-crack initiation life for the tubular and rectangular chamber designs under nominal thermal and mechanical loading conditions is a rather simple task. The two equivalent plastic strain ranges of 2.46 and 0.87% were entered into the Manson-Coffin law shown in Fig. 15, and the respective cyclic lives of 70 to 750 cycles to failure were determined. The greater fatigue life of the tubular than the rectangular channel design is significant. A more than tenfold improvement in predicted low-cycle fatigue life is due directly to the reduction of the thermally induced strain range in the tubular channel design.

Discussion

This effort showed that the strain levels for the tubular channel were significantly lower than those for the rectangular channel. Strain range was used to predict a significant increase in mission life. The analyses predicted a reduction in strain range from 2.6% in the rectangular channel to 1.05% in the tubular channel. Such a dramatic reduction in strain range was expected to provide a tenfold increase in life by the "local-strain approach." The test results, however, only showed a two- to threefold increase in life.

Both analyses and tests showed that significant improvements in life can be achieved by accommodating strain instead of resisting it, but the amounts of improvement differed. This difference was principally the result of our inability to accurately include all effects of the real environment. Because of this reality, only relative comparisons could be made. The difference in life indicated by the analyses and the tests was due primarily to two reasons. First, a fatigue analysis was performed to estimate the lives of the tubular and rectangular channel designs. Thermal-mechanical ratcheting, not fatigue, is the failure mode of these types of chambers. But both fatigue and thermal-mechanical ratcheting are dominated by the magnitude of the strain range. Therefore, it is reasonable to assume that a fatigue analysis would provide a good, but not exact, indicator of relative life improvement. Second, there was a difference in operating versus assumed temperatures. The analyses used a maximum wall temperature of 538°C for both chamber configurations so that a direct comparison could be made. In testing the two configurations it was difficult to achieve an exact temperature of 538°C. The tubular channel was run slightly hotter than the analysis temperature (on the order of 571°C). Consequently, some of the potential improvement in durability because of a more compliant geometry was offset by a higher temperature with attendant higher rates of damage due to the probable introduction of

cyclic creep strain. Furthermore, because of the nominally higher temperature of the tubular channel, greater surface roughening was observed. This phenomenon, known as blanching,¹⁷ escalated the tubular wall temperature to an estimated value of 830°C at the time testing was suspended. This additional increase in temperature of the tubular channel chamber reduced its life even further relative to both the tubular channel analysis and the experimental results of the rectangular channel chamber. It is obvious from the results of both the testing and analyses that a tubular channel geometry reduces the strain range and therefore increases the life of a rocket thrust chamber.

Conclusions

Presently, advanced hydrogen-oxygen rocket combustion chambers have a limited life due to thermal-mechanical fatigue and ratcheting. This ratcheting is a strong function of the material strength and the strain range. In the past numerous attempts have been made to extend the useful life of rocket combustion chambers by improving the chamber material strength. These efforts resulted in little life improvement because the strain levels at the high heat fluxes present in rocket combustion chambers are in the range 2 to 4%. This level of strain is roughly an order of magnitude greater than the yield strain of copper or copper alloys.

The work herein takes steps to dramatically improve combustion chamber life by reducing the strain range the material experiences. This reduction is accomplished by modifying the geometry of the hot-gas-side surface of the combustion chamber. The tubular geometry reduces the compressive strain, thus reducing the total strain range and extending life.

The viscoplastic analysis, durability analysis, and test results reported herein verified that the more compliant tubular construction extends the life of the combustion chamber. The viscoplastic analysis found that the total strain range of the tubular channel was reduced to 1.05% from 2.6% in the rectangular channel. The durability analysis found that the reduction in strain range could extend the life of the combustion chamber by as much as 1000%. The test results found that the compliant chamber extends life by 300%.

Appendix: Viscoplastic Model

The viscoplastic model³ in the present work incorporates two internal state variables—a tensorial backstress B_{ij} and a scalar drag stress D . The kinematic, or flow-induced, anisotropic hardening is incorporated through the backstress B_{ij} , and the isotropic hardening is incorporated through the drag stress D . There is no yield surface in the model, and it employs a small-deformation and small-strain formulation. The assumption of uncoupled dynamic and static recovery terms provides a simpler mathematical structure for the model.

The total strain rate $\dot{\epsilon}_{ij}$ is assumed to be the sum of elastic $\dot{\epsilon}_{ij}^{el}$, inelastic $\dot{\epsilon}_{ij}^{in}$, and thermal $\dot{\epsilon}_{ij}^{th}$ strain-rate components. This can be written as

$$\dot{\epsilon}_{ij} = \dot{\epsilon}_{ij}^{el} + \dot{\epsilon}_{ij}^{in} + \dot{\epsilon}_{ij}^{th} \quad (i, j = 1, 2, 3) \quad (A1)$$

Note that the inelastic strain in a viscoplastic formulation includes plasticity, creep, relaxation, etc., and their interactions.

The material is assumed to be isotropic, and Hooke's law is used to relate the stress rate $\dot{\sigma}_{ij}$ to the elastic strain rate $\dot{\epsilon}_{ij}^{el}$, that is,

$$\dot{\epsilon}_{ij}^{el} = \frac{1+\nu}{E} \dot{\sigma}_{ij} - \frac{\nu}{E} \dot{\sigma}_{kk} \delta_{ij} \quad (A2)$$

Following the usual summation convention, the repeated subscripts in the preceding equation and elsewhere imply summation.

We define the deviatoric stress S_{ij} as

$$S_{ij} = \sigma_{ij} - \frac{1}{3} \sigma_{kk} \delta_{ij} \quad (A3)$$

Denoting the backstress as B_{ij} , the effective stress Σ_{ij} is defined as

$$\Sigma_{ij} = S_{ij} - B_{ij} \quad (A4)$$

The second invariant of effective stress J_2 is

$$J_2 = \frac{1}{2} \Sigma_{ij} \Sigma_{ij} \quad (A5)$$

and the function F is defined by

$$F = (J_2/D) \quad (A6)$$

The constitutive equations of the model now follow. We first define the thermal diffusivity function θ , which contains the temperature dependence of the model. It is given by

$$\theta = \begin{cases} \exp\left(-\frac{Q}{kT_A}\right), & T_A \geq 0.5T_m \\ \exp\left\{-\frac{2Q}{kT_m} \left[\ln\left(\frac{T_m}{2T_A}\right) + 1\right]\right\}, & T_A \leq 0.5T_m \end{cases} \quad (A7)$$

in which Q is the activation energy, T_A is the absolute temperature, and T_m is the melting point of the material.

The function Z , called the Zener-Hollomon parameter, has the following expressions:

$$Z = \begin{cases} AF^n, & F \leq 1 \\ A \exp[n(F-1)], & F \geq 1 \end{cases} \quad (A8)$$

The flow law is now given by

$$\dot{\epsilon}_{ij} = \theta Z \frac{\Sigma_{ij}}{J_2} \quad (A9)$$

The differential equations governing the growth of the internal state variables B_{ij} and D are

$$\dot{B}_{ij} = H \left(\dot{\epsilon}_{ij}^{in} - \frac{B_{ij}}{L} I_2 \right) \quad (A10)$$

and

$$\dot{D} = h \left[\frac{I_2}{G} - \theta r(G) \right] \quad (A11)$$

where

$$I_2 = \theta Z \quad (A12)$$

In the above equations H , L , and h are inelastic material constants. The constant L denotes the limiting value of the backstress at kinematic saturation (Ref. 3).

The following expressions then define the recovery function r :

$$r(G) = \begin{cases} 0, & D = D_0 \\ R(G), & D > D_0 \end{cases} \quad (A13)$$

$$R(G) = \begin{cases} AG^{n-1}, & G \leq 1 \\ AG^{-1} \exp[n(G-1)], & G \geq 1 \end{cases} \quad (A14)$$

and

$$G = \frac{L}{s-D} \quad (A15)$$

The function r is constrained by the following dissipativity condition:

$$r \geq Z \left[\frac{1}{G} - 2 \left(F + \frac{B_2^2}{LD} \right) \right] \quad (A16)$$

where

$$B_2 = \frac{1}{2} B_{ij} B_{ij} \quad (A17)$$

This condition must be satisfied for the theory to be thermodynamically admissible. The material constants for this model characterized for copper are listed in Table 1.

References

- ¹Quentmeyer, R. J., "Experimental Fatigue Life Investigation of Cylindrical Thrust Chambers," NASA TM X-73665, July 1977.
- ²Kazaroff, J. M., Jankovsky, R. J., and Pavli, A. J., "Hot Fire Test Results of Subscale Tubular Combustion Chambers," NASA TP-3222, Nov. 1992.
- ³Freed, A. D., and Verrilli, M. J., "A Viscoplastic Theory Applied to Copper," NASA TM-100831, Aug. 1988.
- ⁴Arya, V. K., and Kaufman, A., "Finite Element Implementation of Robinson's Viscoplastic Model and Its Application to Some Uniaxial and Multiaxial Problems," *Engineering Computations*, Vol. 6, No. 3, 1989, pp. 537-547.
- ⁵Anon., *MARC General Purpose Finite Element Program*, Vols. A-D, MARC Research Analysis Corp., Palo Alto, CA, 1994.
- ⁶Arya, V. K., Hornberger, K., and Stamm, H., "On the Numerical Integration of Viscoplastic Models," Kernforschungszentrum, Rept. 4082, Karlsruhe, Germany, May 1986.
- ⁷Arya, V. K., "Analytical and Finite Element Solutions of Some Problems Using a Viscoplastic Model," *Computers & Structures*, Vol. 33, No. 4, 1989, pp. 957-967.
- ⁸Arya, V. K., "Finite Element Analysis of Structural Components by Using Viscoplastic Models with Application to a Cowl Lip Problem," *Journal of Materials at High Temperatures*, Vol. 9, No. 4, 1991, pp. 201-208.
- ⁹Thornton, E. A., Oden, J. T., Tworzydlo, W. W., and Youn, S.-K., "Thermoviscoplastic Analysis of Hypersonic Structures Subjected to Severe Aerodynamic Heating," *Journal of Aircraft*, Vol. 27, No. 9, 1990, pp. 826-835.
- ¹⁰Thornton, E. A., and Kolenski, J. D., "Viscoplastic Response of Structures for Intense Local Heating," *Journal of Aerospace Engineering*, Vol. 7, No. 1, 1994, pp. 50-71.
- ¹¹Anon., *PATRAN II User Manual*, PDA Engineering, Santa Ana, CA, 1984.
- ¹²Armstrong, W. H., "Structural Analysis of Cylindrical Thrust Chambers—Final Report," Vol. 1, Lockheed Missiles and Space Co., LMSC-HREC-TR-D568827-VOL-1, NASA Contract NAS3-21361, NASA CR-159522, 1979.
- ¹³Conway, J. B., Stentz, R. H., and Berling, J. T., "High Temperature, Low-Cycle Fatigue of Copper-Base Alloys in Argon; Part I—Preliminary Results for 12 Alloys at 1000°F (538°C)," NASA CR-121259, 1973.
- ¹⁴Halford, G. R., Hirschberg, M. H., and Manson, S. S., "Temperature Effects on the Strainrange Partitioning Approach for Creep Fatigue Analysis. Fatigue at Elevated Temperatures," American Society for Testing and Materials, ASTM STP-520, 1973, pp. 658-669.
- ¹⁵Anon., *Metals Handbook*, 8th ed., Vol. 1, American Society for Metals, Novelty, OH, 1961, p. 996.
- ¹⁶Larson, F. R., and Miller, J., "A Time-Temperature Relationship for Rupture and Creep Stresses," *Transactions of the American Society of Mechanical Engineers*, Vol. 74, No. 5, 1952, pp. 765-775.
- ¹⁷Morgan, D. B., and Franklin, J. E., "Hot-Fire Test Investigation of Copper Combustion Chamber Blanching," *The 1989 JANNAF Propulsion Meeting*, edited by D. S. Eggleston and K. L. Strange, Publication 515, Vol. 3, Chemical Propulsion Information Agency, 1989, pp. 417-426.

E. A. Thornton
Associate Editor