


# Graphene Film Growth on Polycrystalline Metals

REBECCA S. EDWARDS AND KARL S. COLEMAN\*

*Department of Chemistry, Durham University, South Road, Durham DH1 3LE, U.K.*

RECEIVED ON APRIL 30, 2012

## CONSPECTUS

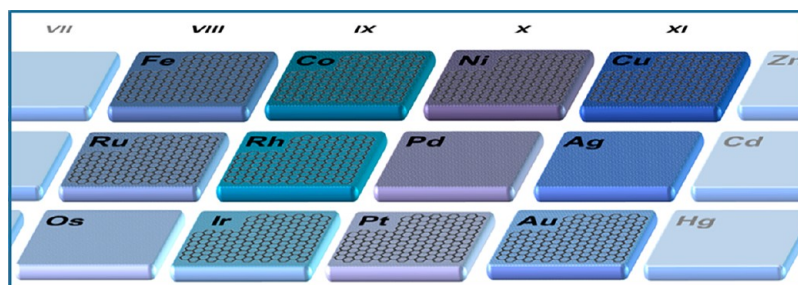

Graphene, a true wonder material, is the newest member of the nanocarbon family. The continuous network of hexagonally arranged carbon atoms gives rise to exceptional electronic, mechanical, and thermal properties, which could result in the application of graphene in next generation electronic components, energy-storage materials such as capacitors and batteries, polymer nanocomposites, transparent conducting electrodes, and mechanical resonators. With one particularly attractive application, optically transparent conducting electrodes or films, graphene has the potential to rival indium tin oxide (ITO) and become a material for producing next generation displays, solar cells, and sensors.

Typically, graphene has been produced from graphite using a variety of methods, but these techniques are not suitable for growing large-area graphene films. Therefore researchers have focused much effort on the development of methodology to grow graphene films across extended surfaces. This Account describes current progress in the formation and control of graphene films on polycrystalline metal surfaces. Researchers can grow graphene films on a variety of polycrystalline metal substrates using a range of experimental conditions. In particular, group 8 metals (iron and ruthenium), group 9 metals (cobalt, rhodium, and iridium), group 10 metals (nickel and platinum), and group 11 metals (copper and gold) can support the growth of these films. Stainless steel and other commercial copper–nickel alloys can also serve as substrates for graphene film growth. The use of copper and nickel currently predominates, and these metals produce large-area films that have been efficiently transferred and tested in many electronic devices. Researchers have grown graphene sheets more than 30 in. wide and transferred them onto display plastic ready for incorporation into next generation displays. The further development of graphene films in commercial applications will require high-quality, reproducible growth at ambient pressure and low temperature from cheap, readily available carbon sources. The growth of graphene on metal surfaces has drawbacks: researchers must transfer the graphene from the metal substrate or remove the metal by etching. Further research is needed to overcome these transfer and removal challenges.

## 1. Introduction

Graphene is a single layer of graphite and is the newest member of the nanocarbon family. The continuous network of hexagonally arranged carbon atoms gives rise to some exceptional electronic, mechanical, and thermal properties, which could see the application of graphene in new generation electronic components, energy-storage materials such as capacitors and batteries, polymer nanocomposites, transparent conducting electrodes, and mechanical resonators.<sup>1–3</sup> Graphene can be prepared using “top-down” approaches from graphite such as micromechanical

cleavage, oxidation, and thermal expansion followed by reduction, and by extensive sonication in solvent systems with surface energies that match that of graphite.<sup>1,4</sup> “Bottom-up” methods of graphene synthesis, which are perhaps more amenable to scale, have included decomposition of ethanol in a microwave plasma<sup>5</sup> and the spray pyrolysis of sodium ethoxide.<sup>6</sup> It is also possible to obtain graphene by the longitudinal cutting of carbon nanotubes.<sup>7</sup> All of these methods produce platelets of graphene. However, this Account will focus on the synthesis, mainly by chemical vapor deposition (CVD) and temperature-programmed

growth (TPG), of large area graphene films. This is a highly relevant topic given the excitement around producing optically transparent conducting films that could rival indium tin oxide (ITO) and be used in next generation displays, solar cells, and sensors or that could even be patterned to make new electronic components and devices. It is worth mentioning that graphene films can be grown on silicon carbide wafers by high-temperature reduction and it represents a very active area of research in electronic devices, which has been reviewed recently and will not be discussed here.<sup>8</sup> This Account details current progress in the formation and control of graphene films on polycrystalline metal surfaces.

**1.1. Introduction to Growth on Metal Surfaces.** There are a number of factors that affect the potential of a metal to produce high-quality graphene films; from an industrial point of view cost is important because metals are normally etched during the transfer process, but more fundamental differences between the metals also play a big part in their selection. Metals can promote graphene formation by a surface growth mechanism, where the metal catalyzes the decomposition of a carbon feedstock promoting carbon fragmentation at the metal surface, or by segregation where carbon is absorbed in the metal at high temperature and then segregates to the surface forming graphene on cooling. Many of the inferences about graphene growth on metals have been made based on information gained from density function theory (DFT) calculations and experimental observations from single-crystal systems.<sup>9</sup> While these studies provide valuable insight into the effect of interaction strength and lattice mismatch on graphene growth along with the mechanism of formation, single-crystal systems are not suitable for the production of large-scale graphene films. This is primarily due to the difficulty in growing large single-crystal metals. Instead the future of large-scale graphene film production lies with polycrystalline metal films, which can be deposited on substrates of variable size using techniques such as sputtering or evaporation.

In order for applications to develop, it is important that graphene films formed on metal surfaces can be removed or transferred to other substrates, in particular plastics on which it is difficult to grow graphene directly. Typical methods of film transfer have included stamping using poly(methyl methacrylate) (PMMA) or polydimethylsiloxane (PDMS),<sup>10,11</sup> where the polymer is added to the graphene surface, the metal is removed via chemical etching, the graphene/polymer is stamped onto a second substrate, and the polymer is removed. It is also possible to use rolling or "roll-to-roll" processes that are compatible with industry techniques,

where graphene grown on flexible metal films is rolled onto flexible substrates, followed by removal of the metal layer to yield bare graphene on the substrate surface.<sup>12</sup> The transfer of 30 in. graphene films grown on Cu has been achieved using the roll-to-roll process.<sup>13</sup>

## 2. Large-Area Growth of Graphene on Polycrystalline Metal Surfaces

The growth of large-area graphene films requires large metal surfaces, which are generally prepared by sputter coating or electron beam evaporation of the desired metal. This results in metal films with multiple grains that are then typically annealed to improve surface roughness or to promote formation of a particular metal facet. Selecting metals suitable for large-scale graphene growth is complicated by a number of additional considerations that are not relevant for growth on single crystals. Key to this is the behavior of graphene toward grain boundaries in the underlying metal. Growth over grain boundaries or large metal grain sizes is favorable for high-quality graphene because underlying grain boundaries often result in graphene defects including nucleation of multilayer graphene.<sup>14</sup> Grain size is ultimately related to the metal film thickness,<sup>15</sup> with larger grains forming for thicker films; however because metal thickness is also a key factor for graphene growth over certain metals,<sup>16</sup> enlarging grain size by using thicker metal films is not appropriate in all cases. Larger grains can be promoted by annealing at high temperatures but surface defects such as pits can be formed during this process that can degrade the quality of the graphene.<sup>16,17</sup>


A study on engineering polycrystalline Ni films to achieve improved uniformity of CVD grown graphene highlights a number of additional factors that affect metal grain size, including the temperature and pressure conditions during the initial metal deposition and the method used to prepare the underlying SiO<sub>2</sub>/Si substrate.<sup>17</sup> Furthermore improved graphene uniformity for metal films deposited on *c*-plane sapphire rather than SiO<sub>2</sub>/Si has been reported for multiple metals due to preferred single crystal metal growth over sapphire.<sup>18–21</sup> It is also important to reduce the number of graphene nucleation sites because defects can form at graphene domain boundaries due to misalignment of the carbon atoms.<sup>22</sup> For surface-catalyzed reactions, the number of graphene nucleation sites can be controlled not only by the reduction of surface defects of the metal but also by the rate of carbon exposure, where slower rates result in fewer nucleation sites and hence larger graphene domains.<sup>23</sup> This prolonged exposure to the growth temperature to reduce

graphene nucleation must be balanced with the detrimental effect that prolonged exposure may have on the metal surface and the graphene quality.

Graphene growth on single crystals should provide some insight into the expected growth of graphene on polycrystalline surfaces with regard to the number of layers anticipated. However, care must be taken because many of the single crystal studies are performed under ultrahigh vacuum (UHV) conditions, whereas atmospheric pressure conditions are generally more favorable for growth at the industrial scale due to cost of maintaining low pressure systems. Graphene growth has been seen to alter with pressure; for example, while growth on Cu has been found to be “self-limiting” to monolayer graphene at UHV, few layer graphene has been observed for atmospheric pressure growth.<sup>24</sup>

**2.1. Group 8. 2.1.1. Iron.** Studies on polycrystalline Fe generally report the growth of multilayer graphene via CVD at low pressures and relatively low temperatures (600–800 °C). The exposure to acetylene is found to be important to graphene formation, with both reduced surface coverage and reduced graphene thickness being observed at lower exposures.<sup>25</sup> Graphene thickness can also be controlled using Fe film thickness,<sup>26</sup> with thinner graphene forming on thicker Fe. Interestingly for Fe films 6–20 nm thick, multilayer graphene grew on-top of carbon nanotubes (CNTs), while for films <5 nm, CNTs were formed exclusively. Increasing growth temperature is found to increase graphene thickness but reduce the number of defects,<sup>25</sup> so growth of thin, high-quality graphene on Fe requires careful balancing of conditions.


**2.1.2. Ruthenium.** Growth of graphene on Ru sputter-coated on SiO<sub>2</sub>,<sup>27</sup> fused silica,<sup>28</sup> and sapphire<sup>18</sup> has been reported. The Ru films deposited on SiO<sub>2</sub> and fused silica have a columnar structure with strongly aligned grains exposing flat (0001) surface facets, whereas on sapphire the Ru is described as being “single crystalline” Ru(0001). Exposure to ethylene at high temperatures (800 °C,<sup>28</sup> 950 °C<sup>18,27</sup>) followed by slow cooling in UHV affords uniform monolayer graphene that is continuous across grain boundaries and is “slightly wavy” in appearance.<sup>27</sup> Etching of the underlying Ru deposited on sapphire, using an aqueous solution of ceric ammonium nitrate and acetic acid, has been demonstrated for monolayer graphene with domains <60 μm in size,<sup>18</sup> where the growth is halted prior to formation of the continuous graphene film. The etchant is said to etch down between the graphene domains then sideways underneath them to release the graphene, so it may not be suitable for continuous films where access to the underlying Ru would be restricted.

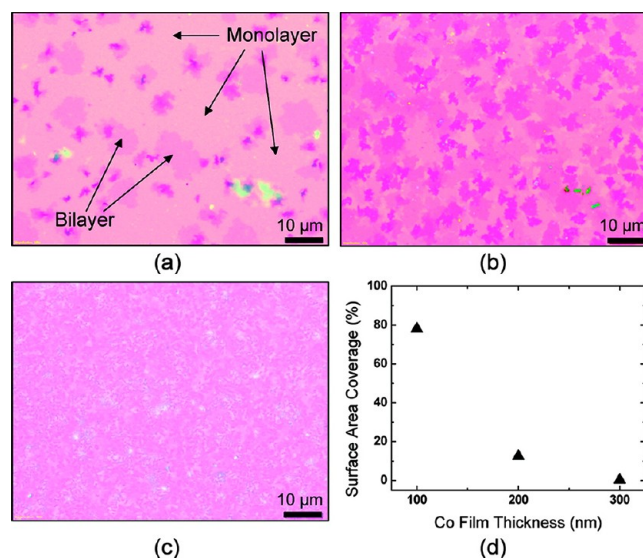

**FIGURE 1.** Optical micrographs of graphene grown on (a) 100 nm Co film, showing large monolayer area along with small domains of bi- and multilayer area, and (b) 200 and (c) 300 nm Co films. (d) Percentage surface area coverage by monolayer graphene as a function of Co film thickness. Reproduced from ref 16. Copyright 2011 American Chemical Society.

**2.2. Group 9. 2.2.1. Cobalt.** A number of studies have been undertaken for the growth of graphene on polycrystalline Co deposited on SiO<sub>2</sub>/Si,<sup>16,29,30</sup> along with growth over c-plane sapphire.<sup>19</sup> CVD of methane at high temperature affords a uniform monolayer of graphene for Co deposited over sapphire (single-crystalline Co) but an inhomogeneous film containing both monolayer and multilayer graphene flakes for Co deposited over SiO<sub>2</sub>/Si (polycrystalline Co, grain size <3 μm). This is attributed to the high density of Co grain boundaries in the SiO<sub>2</sub>/Si based sample, Figure 1.

Nonuniform graphene of varying thickness has been reported for CVD of acetylene over Co at low pressures and moderate to high temperatures (800–1000 °C). Graphene thickness is seen to decrease with shorter growth times and increased temperature, which can be attributed to reduced carbon exposure and the increased desorption coefficient of carbon at higher temperatures.<sup>29</sup> Co film thickness is also found to be an important factor as the percentage of multilayer graphene decreases with decreasing Co thickness,<sup>16</sup> resulting in 80% monolayer graphene for 100 nm Co films. Thinner Co films (~60 nm) agglomerated and formed surface pits so entirely monolayer growth could not be achieved. Multilayer graphene is seen to nucleate at grain boundaries,<sup>30</sup> and growth of uniform monolayer graphene has been reported for single crystalline Co deposited over sapphire.<sup>19</sup> Etching of Co to release

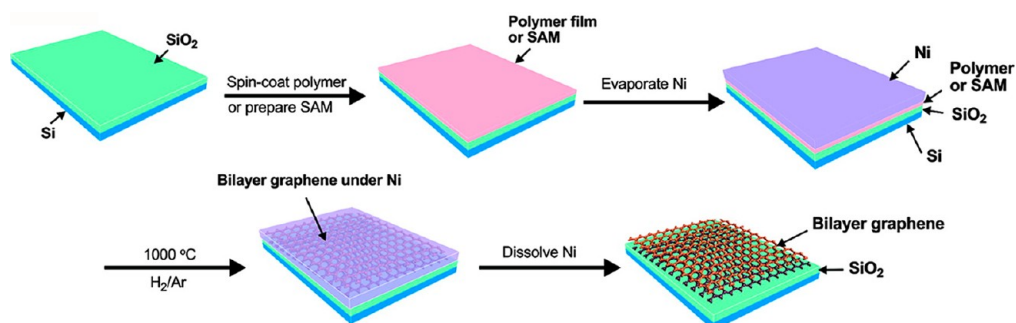


**FIGURE 2.** Schematic of bilayer graphene formation from Ni coated polymers or SAMs on SiO<sub>2</sub>/Si substrates after annealing at high temperature under hydrogen. Reproduced from ref 41. Copyright 2011 American Chemical Society.

graphene has been demonstrated using aqueous solutions of FeCl<sub>3</sub> and HCl.<sup>19,29</sup>

**2.2.2. Rhodium.** Graphene formation on Rh foils, repeatedly annealed under UHV to promote the emergence of the Rh(111) face, has been reported.<sup>31</sup> Growth via carbon segregation occurs after exposure of the metal surface to benzene vapor, where graphene islands begin to form upon reaching the carbon solubility limit of Rh. These islands coalesce resulting in complete surface coverage of monolayer graphene. However, multilayer graphene forms upon cooling due to further segregation of carbon from the bulk metal, highlighting the importance of growth temperature for the control of graphene thickness.

**2.2.3. Iridium.** Graphene growth has been reported on single crystalline Ir(111) films deposited on sapphire and yttria-stabilized zirconium oxide (YSZ) by pulsed laser deposition and electron beam evaporation, respectively.<sup>20,32</sup> On sapphire, high-quality monolayer graphene was grown via CVD of ethylene at 677 °C under UHV conditions and found to cover >95% of the surface for 10 min carbon exposure. For YSZ temperature-programmed growth (TPG) of Ir(111) exposed to acetone (the carbon source), graphene formation begins around 327 °C and proceeds to a well-ordered graphene monolayer upon heating to 727 °C.

**2.3. Group 10. 2.3.1. Nickel.** CVD growth of graphene over polycrystalline Ni has primarily been performed at atmospheric pressure, yielding graphene that extends across nickel grain boundaries to form continuous films.<sup>33,34</sup> Slow annealing of the polycrystalline nickel<sup>35</sup> or increase in deposition temperature<sup>17</sup> promotes large grain sizes of Ni(111) over Ni(100) improving graphene film quality. A study on the effect of growth temperature, gas mixing ratio, and growth time on the CVD of acetylene/hydrogen shows that high temperature, high hydrogen concentration, and short growth time are important for producing few-layer graphene with minimal defects.<sup>36</sup> A similar study involving

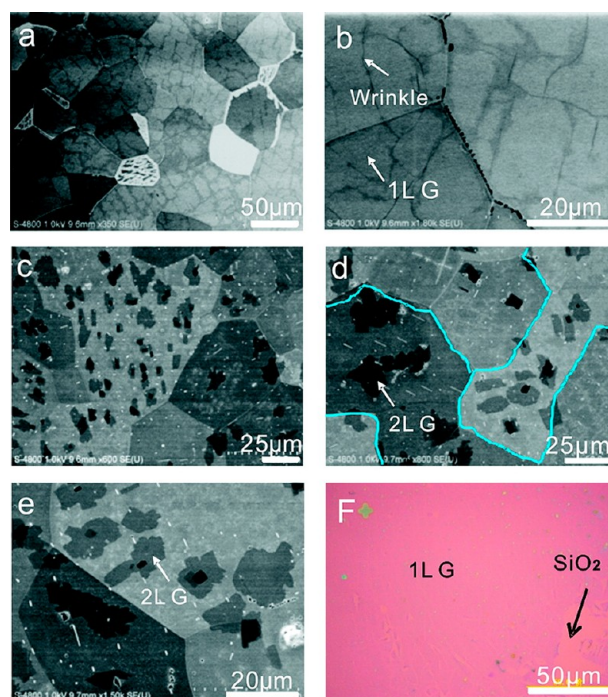

**FIGURE 3.** SEM image of single-layer graphene grown on Pt foils (a,b). SEM images (c–e) show sequential growth of bilayer flakes with orthogonal and irregular boundaries on Pt domains (brighter SEM contrast). (f) Optical image of monolayer graphene transferred onto a 300 nm SiO<sub>2</sub>/Si substrate. Reproduced from ref 44. Copyright 2011 American Chemical Society.


methane showed the importance of cooling rate and short growth times for reducing graphene thickness to grow primarily single and bilayer graphene films.<sup>14,37</sup> Etching of nickel to release graphene has been widely demonstrated using aqueous FeCl<sub>3</sub>,<sup>37</sup> enabling the study of nickel-grown graphene in a number of electronic devices.<sup>38</sup>

Growth of graphene on nickel surfaces has also been demonstrated based on diffusion and segregation of carbon from underlying amorphous carbon or nanodiamond films.<sup>39,40</sup> Conversely nickel films have been shown to transform the underlying carbon source to graphene at high

temperature, forming bilayer graphene films directly on insulating substrates from polymers or self-assembled monolayers (SAMs) at low pressure conditions<sup>41</sup> and few-layer graphene on SiO<sub>2</sub>/Si from SAMs at atmospheric pressure,<sup>42</sup> Figure 2.

**2.3.2. Platinum.** The growth of uniform monolayer and bilayer graphene films has been achieved for CVD of methane at low pressures and high temperatures (1000–1050 °C) on Pt surfaces. Temperature is found to be an important factor for controlling graphene thickness, with thicker films (>5 layers) being produced at higher temperatures.<sup>43</sup> Graphene uniformity is seen to alter with carbon exposure, forming irregularly shaped islands of bilayer graphene upon increasing growth time or flow rate of carbon sources, Figure 3.<sup>44</sup>

**2.4. Group 11. 2.4.1. Copper.** Graphene growth on Cu foils has been extensively studied under both low and ambient pressure conditions, and has been reviewed recently.<sup>45</sup> An early study reported the growth of centimeter scale graphene films on Cu foils via high-temperature CVD of methane under UHV conditions.<sup>46</sup> These films were characterized as ~95% monolayer with small regions of bi- and multilayer graphene and were found to be “self-limiting”, producing similar films for short and long methane exposures. Graphene thickness is found to be independent of copper thickness, with similar graphene films being observed for foils of thickness between 12.5 and 50 mm. A similar method has been utilized for the production of >95% monolayer films on Cu foils with a diagonal length up to 30 in.<sup>13</sup> Here curving of the Cu foils around a 7.5 in. quartz tube is necessary to combat graphene inhomogeneity brought about due to the temperature gradient across the radius of the tubular reactor. For both of these studies, higher quality graphene is observed for larger grain sizes. The effect of Cu purity and pretreatment on UHV graphene growth have been investigated along with the effect of hydrocarbon concentration.<sup>47</sup> Sonication in acetone prior to annealing and the reduction of annealing pressure from 80 to 20 mbar were found to be beneficial to graphene uniformity, while Cu purity was found to impact graphene thickness, with monolayer graphene reported on 99.999% Cu foil and bilayer graphene being reported for 99.8%. Hydrocarbon concentration can also impact graphene uniformity due to its effect on the number of graphene nucleation sites; with few sites, and hence more uniform graphene, being produced at lower hydrocarbon concentrations. Growth of graphene with average domain sizes of ~140 μm<sup>2</sup> has been reported for a low-pressure CVD using carefully controlled hydrocarbon exposures.<sup>23</sup> Methane exposure is kept low at the beginning

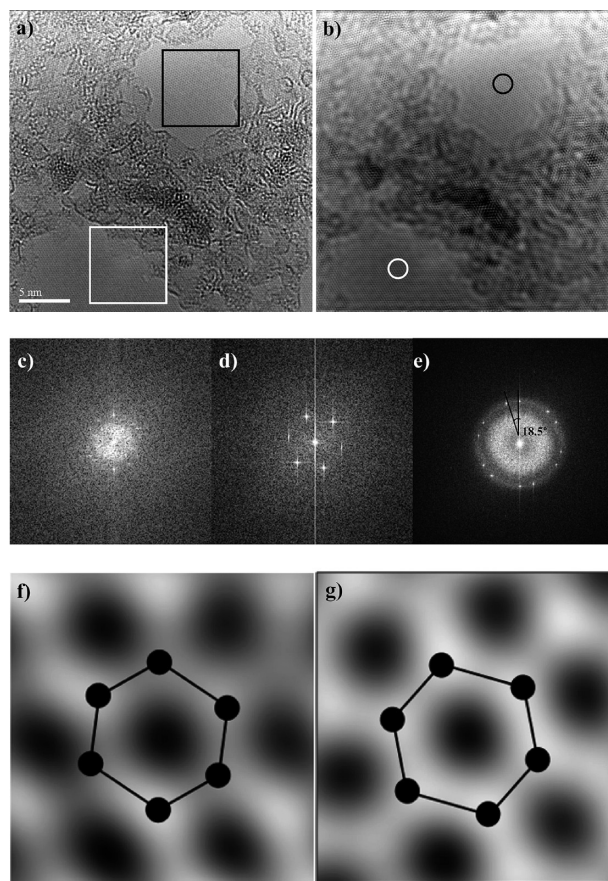

**FIGURE 4.** (a) TEM bright field image of monolayer graphene grown on Cu at a domain boundary, (b) mask-filtered image of panel a, (c,d) fast Fourier transform (FFT) from area in white and black box, respectively, in panel a, which show that the monolayer graphene has two different crystal orientations at each respective area, (e) FFT of the whole image in panel a, which shows two sets of hexagonal FFT spots misoriented by approximately 18.5° from one another, and (f,g) high-resolution image cropped from white and black circled regions in panel b, respectively. Reproduced from ref 23. Copyright 2010 American Chemical Society.

of the process to reduce the number of graphene nucleation sites and then increased during the reaction to promote continuous graphene coverage, Figure 4.


Under ambient pressure conditions, graphene growth on large polycrystalline Cu films using methane as the carbon source occurs readily<sup>48,49</sup> and is continuous across Cu grain boundaries.<sup>50</sup> Under these conditions, predominately mono- and bilayer graphene is formed when Cu (700 nm) deposited on SiO<sub>2</sub>/Si is used.<sup>48</sup> When electropolished Cu foils are used, 95% monolayer coverage can be obtained under low methane concentrations, while increasing the methane concentration affords thicker graphitic regions.<sup>49</sup> Similarly, chemical mechanical polishing of Cu foils results in improved graphene films compared with unpolished samples. This can be attributed to the reduction in graphene nucleation sites on the smoother metal surfaces.<sup>51</sup>

An alternative method of graphene growth on Cu foils involves depositing the carbon source on the metal surface prior to heating to high temperatures. By this method, growth of monolayer graphene has been achieved by annealing Cu foils with an amorphous carbon coating at 1035 °C under a flow of hydrogen.<sup>52</sup> The flow of hydrogen was also found to be important for growth of graphene at 800 °C on Cu foils coated with PMMA, where graphene thickness was controlled by adjusting argon and hydrogen flow rates, forming monolayer graphene at higher hydrogen flows.<sup>53</sup> Monolayer growth for Cu covered with sucrose and fluorene has also been reported under the same conditions. The growth of monolayer graphene can even be achieved by heating “food”, “insects”, or “waste” deposited on Cu to 1050 °C.<sup>54</sup> Etching of copper has been reported using aqueous solutions of iron chloride,<sup>49</sup> ammonium salts,<sup>47</sup> or Cu etchant solution (CE-100, Transene).<sup>51</sup>

**2.4.2. Gold.** Ambient pressure CVD growth of graphene on gold has been reported for Au foils 25  $\mu\text{m}$  thick.<sup>55</sup> The partially (111) orientated gold surfaces exposed to methane at 850–1050 °C produce a high percentage of monolayer graphene. Temperature has a minimal effect on graphene thickness and defect concentration for this range, but higher temperatures resulted in the formation of highly defective multilayer graphene. Etching of the gold to allow film transfer is readily achieved using the commercial gold etchant TFA from Transene Co. Inc., which contains a KI–I<sub>2</sub> complex.

**2.5. Alloys. 2.5.1. Stainless Steel.** Inhomogeneous growth of graphene films has been reported by CVD at moderate temperature (800–850 °C) in both low and ambient pressure conditions. The rate of cooling is found to be an important factor, with no graphene being detected for high cooling rates  $\geq 140$  °C/min and graphite-like material being formed for very slow cooling rates.<sup>56</sup> Interestingly, the duration of carbon exposure has a less marked influence on mono-, bi-, or multilayer graphene formation, although it is noted that longer exposure times resulted in higher quality graphene and significantly shorter exposure times resulted in discontinuous graphene growth.<sup>57</sup>

**2.5.2. Copper–Nickel Alloy.** Cu–Ni alloys can be used for graphene growth where the substrates are initially prepared as Cu/Ni/SiO<sub>2</sub>/Si sandwich structures,<sup>58,59</sup> and the Cu–Ni alloy formed in situ upon high-temperature annealing under UHV, Figure 5. Carbon impurities in the nickel film ( $\sim 2.6$  atom %) act as the carbon source, diffusing along with the Ni atoms during the high-temperature annealing, resulting in graphene formation on the surfaces of the Cu–Ni binary

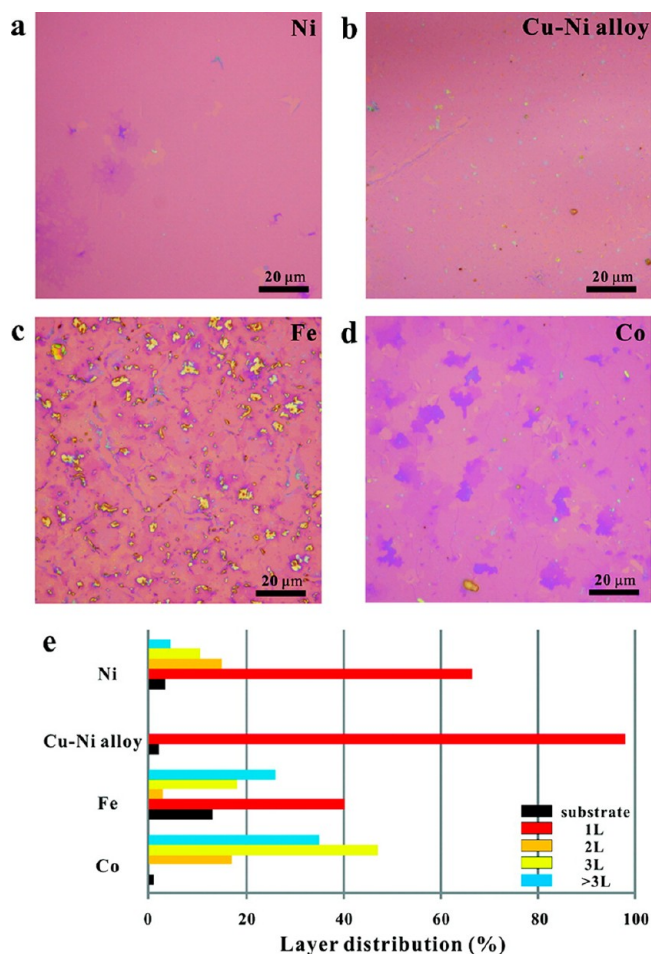

**FIGURE 5.** CVD growth and segregation behavior of graphene on Ni (a), Cu–Ni alloy (b) (5.5 at % Ni), Fe (c), and Co (d) and the corresponding layer thickness distributions at optimized growth temperature, 1100, 900, 1000, and 1000 °C, respectively (e). The graphene was transferred to 300 nm SiO<sub>2</sub>/Si substrates for taking the optical microscope images. Reproduced from ref 58. Copyright 2011 American Chemical Society.

alloys. The number of graphene layers synthesized varied depending on the thickness of the Ni layer deposited; for 20 nm Ni (5.5 atom % Ni),  $\sim 95\%$  of the surface was covered with monolayer graphene, and for 40 nm Ni (10.4 atom % Ni),  $\sim 90\%$  of the surface was covered with bilayer graphene. At higher atom % of Ni, graphene growth becomes inhomogeneous, forming randomly distributed regions of multilayer graphene. Graphene growth also occurs on commercial polycrystalline Cu–Ni alloy films 200 nm thick (67.8 wt % Cu and 31 wt % Ni) using methane as the carbon source.<sup>60,61</sup>

**2.5.3. Gold–Nickel Alloy.** Au–Ni alloys prepared by from Au films (0–10 nm) thermally evaporated onto polycrystalline Ni films ( $\sim 550$  nm) on SiO<sub>2</sub>/Si substrates can be used to grow graphene with acetylene as the carbon source.<sup>62</sup> Graphene films with  $\sim 74\%$  monolayer coverage and

domain sizes  $>15 \mu\text{m}$  are achieved for growth over the Ni–Au (5 nm Au) based alloy at 450 °C under low pressure conditions. Preannealing at 600 °C (under hydrogen) is vital for graphene formation. Successful etching away of the alloy can be achieved using a two-step process involving aqueous solutions of  $\text{FeCl}_3$  and  $\text{KI/I}_2$ .

**2.5.4. Nickel–Molybdenum Alloy.** Growth of entirely monolayer graphene with 100% surface coverage can be achieved from CVD of methane at 1000 °C over a Ni–Mo alloy.<sup>63</sup> The alloy was prepared by deposition of Ni (200 nm) onto Mo foils (25 or 200  $\mu\text{m}$ ) and annealed at 900 °C prior to graphene growth. Graphene formation proceeds via a surface-catalyzed process rather than from carbon segregation because carbon dissolved in the bulk is “trapped” as molybdenum carbide.

### 3. Summary

Graphene film growth on a variety of polycrystalline metals and metal alloys has been demonstrated across a range of experimental conditions, providing insight into the key factors effecting growth and the potential of different metals to produce high-quality graphene. At present Cu and Ni dominate the field, producing large area films that have already been efficiently transferred and tested in a number of electronic devices. Looking to the future high-quality, reproducible growth at ambient pressure and low temperature from cheap, readily available carbon sources will be important for the realization of graphene films in commercial applications. A further important advancement will be high-quality graphene growth directly on insulating substrates, which is an area of growing interest in the field.

*This research was supported by Durham University and the EPSRC (studentship RSE).*

#### BIOGRAPHICAL INFORMATION

**Rebecca Edwards** received her MChem from Durham University in 2010. She is currently studying for a Ph.D. in chemistry, researching the synthesis and chemistry of graphene, in the nano-carbon group at Durham University led by Karl Coleman.

**Karl Coleman** is a Reader in Nanomaterials in the Department of Chemistry at Durham University. He has extensive experience in the chemistry of carbon nanotubes and is interested in the synthesis and chemistry of graphene. He was named the Royal Society of Chemistry Entrepreneur of the Year in 2011 for his development of new intellectual property for the production of graphene and its commercial exploitation. He is the cofounder of the Chemical Nanosciences and Nanotechnology subject group of the Royal Society of Chemistry.

#### FOOTNOTES

\*Corresponding author. E-mail: k.s.coleman@durham.ac.uk.  
The authors declare no competing financial interest.

#### REFERENCES

- Rao, C. N. R.; Sood, A. K.; Subrahmanyam, K. S.; Govindaraj, A. Graphene: The New Two-Dimensional Nanomaterial. *Angew. Chem., Int. Ed.* **2009**, *48*, 7752–7777.
- Geim, A. K. Graphene: Status and Prospects. *Science* **2009**, *324*, 1530–1534.
- Avouris, P. Graphene: Electronic and Photonic Properties and Devices. *Nano Lett.* **2010**, *10*, 4285–4294.
- Hernandez, Y.; Nicolosi, V.; Lotya, M.; Blighe, F. M.; Sun, Z.; De, S.; McGovern, I. T.; Holland, B.; Byrne, M.; Gun'ko, Y. K.; Boland, J. J.; Niraj, P.; Duesberg, G.; Krishnamurthy, S.; Goodhue, R.; Hutchison, J.; Scardaci, V.; Ferrari, A. C.; Coleman, J. N. High-Yield Production of Graphene by Liquid-Phase Exfoliation of Graphite. *Nat. Nanotechnol.* **2008**, *3*, 563–568.
- Dato, A.; Radmilovic, V.; Lee, Z.; Phillips, J.; Frenklach, M. Substrate-Free Gas-Phase Synthesis of Graphene Sheets. *Nano Lett.* **2008**, *8*, 2012–2016.
- Herron, C. R.; Coleman, K. S.; Edwards, R. S.; Mendis, B. G. Simple and Scalable Route for the 'Bottom-Up' Synthesis of Few-Layer Graphene Platelets and Thin Films. *J. Mater. Chem.* **2011**, *21*, 3378–3383.
- Kosynkin, D. V.; Higginbotham, A. L.; Sinitskii, A.; Lomeda, J. R.; Dimiev, A.; Price, B. K.; Tour, J. M. Longitudinal Unzipping of Carbon Nanotubes to Form Graphene Nanoribbons. *Nature* **2009**, *458*, 872–876.
- Riedl, C.; Coletti, C.; Starke, U. Structural and Electronic Properties of Epitaxial Graphene on SiC(0001): A Review of Growth, Characterization, Transfer Doping and Hydrogen Intercalation. *J. Phys. D: Appl. Phys.* **2010**, *43*, No. 374009.
- Batzill, M. The Surface Science of Graphene: Metal Interfaces, CVD Synthesis, Nanoribbons, Chemical Modifications, and Defects. *Surf. Sci. Rep.* **2012**, *67*, 83–115.
- Liang, X.; Sperling, B. A.; Calizo, I.; Cheng, G.; Hacker, C. A.; Zhang, Q.; Obeng, Y.; Yan, K.; Peng, H.; Li, Q.; Zhu, X.; Yuan, H.; Walker, A. R. H.; Liu, Z.; Peng, L.-m.; Richter, C. A. Toward Clean and Crackless Transfer of Graphene. *ACS Nano* **2011**, *5*, 9144–9153.
- Liu, N.; Pan, Z.; Fu, L.; Zhang, C.; Dai, B.; Liu, Z. The Origin of Wrinkles on Transferred Graphene. *Nano Research* **2011**, *4*, 996–1004.
- Juang, Z.-Y.; Wu, C.-Y.; Lu, A.-Y.; Su, C.-Y.; Leou, K.-C.; Chen, F.-R.; Tsai, C.-H. Graphene Synthesis by Chemical Vapor Deposition and Transfer by a Roll-to-Roll Process. *Carbon* **2010**, *48*, 3169–3174.
- Bae, S.; Kim, H.; Lee, Y.; Xu, X.; Park, J.-S.; Zheng, Y.; Balakrishnan, J.; Lei, T.; Kim, H. R.; Song, Y. I.; Kim, Y.-J.; Kim, K. S.; Ozyilmaz, B.; Ahn, J.-H.; Hong, B. H.; Iijima, S. Roll-to-Roll Production of 30-in. Graphene Films for Transparent Electrodes. *Nat. Nanotechnol.* **2010**, *5*, 574–578.
- Reina, A.; Thiele, S.; Jia, X.; Bhaviripudi, S.; Dresselhaus, M. S.; Schaefer, J. A.; Kong, J. Growth of Large-Area Single- and Bi-Layer Graphene by Controlled Carbon Precipitation on Polycrystalline Ni Surfaces. *Nano Res.* **2009**, *2*, 509–516.
- Thompson, C. V. Grain Growth in Thin Films. *Annu. Rev. Mater. Sci.* **1990**, *20*, 245–268.
- Ramon, M. E.; Gupta, A.; Corbet, C.; Ferrer, D. A.; Mowva, H. C. P.; Carpenter, G.; Colombo, L.; Bourianoff, G.; Doczy, M.; Akinwande, D.; Tutuc, E.; Banerjee, S. K. CMOS-Compatible Synthesis of Large-Area, High-Mobility Graphene by Chemical Vapor Deposition of Acetylene on Cobalt Thin Films. *ACS Nano* **2011**, *5*, 7198–7204.
- Thiele, S.; Reina, A.; Healey, P.; Kedzierski, J.; Wyatt, P.; Hsu, P.-L.; Keast, C.; Schaefer, J.; Kong, J. Engineering Polycrystalline Ni Films to Improve Thickness Uniformity of the Chemical-Vapor-Deposition-Grown Graphene Films. *Nanotechnology* **2010**, *21*, No. 015601.
- Sutter, P. W.; Albrecht, P. M.; Sutter, E. A. Graphene Growth on Epitaxial Ru Thin Films on Sapphire. *Appl. Phys. Lett.* **2010**, *97*, No. 213101.
- Ago, H.; Ito, Y.; Mizuta, N.; Yoshida, K.; Hu, B.; Orofeo, C. M.; Tsuji, M.; Ikeda, K.-i.; Mizuno, S. Epitaxial Chemical Vapor Deposition Growth of Single-Layer Graphene over Cobalt Film Crystallized on Sapphire. *ACS Nano* **2010**, *4*, 7407–7414.
- Vo-Van, C.; Kimouche, A.; Reserbat-Plantey, A.; Fruchart, O.; Bayle-Guillemaud, P.; Bendjab, N.; Coraux, J. Epitaxial Graphene Prepared by Chemical Vapor Deposition on Single Crystal Thin Iridium Films on Sapphire. *Appl. Phys. Lett.* **2011**, *98*, No. 181903.
- Hu, B.; Ago, H.; Ito, Y.; Kawahara, K.; Tsuji, M.; Magome, E.; Sumitani, K.; Mizuta, N.; Ikeda, K.-i.; Mizuno, S. Epitaxial Growth of Large-Area Single-Layer Graphene over Cu(111)/Sapphire by Atmospheric Pressure CVD. *Carbon* **2012**, *50*, 57–65.
- Kim, K.; Lee, Z.; Regan, W.; Kisielowski, C.; Crommie, M. F.; Zettl, A. Grain Boundary Mapping in Polycrystalline Graphene. *ACS Nano* **2011**, *5*, 2142–2146.
- Li, X.; Magnuson, C. W.; Venugopal, A.; An, J.; Suk, J. W.; Han, B.; Borysiak, M.; Cai, W.; Velamakanni, A.; Zhu, Y.; Fu, L.; Vogel, E. M.; Voelkl, E.; Colombo, L.; Ruoff, R. S. Graphene Films with Large Domain Size by a Two-Step Chemical Vapor Deposition Process. *Nano Lett.* **2010**, *10*, 4328–4334.

- 24 Bhaviripudi, S.; Jia, X.; Dresselhaus, M. S.; Kong, J. Role of Kinetic Factors in Chemical Vapor Deposition Synthesis of Uniform Large Area Graphene Using Copper Catalyst. *Nano Lett.* **2010**, *10*, 4128–4133.
- 25 An, H.; Lee, W.-J.; Jung, J. Graphene Synthesis on Fe Foil Using Thermal CVD. *Curr. Appl. Phys.* **2011**, *11*, S81–S85.
- 26 Kondo, D.; Yagi, K.; Sato, M.; Nihei, M.; Awano, Y.; Sato, S.; Yokoyama, N. Selective Synthesis of Carbon Nanotubes and Multi-Layer Graphene by Controlling Catalyst Thickness. *Chem. Phys. Lett.* **2011**, *514*, 294–300.
- 27 Sutter, E.; Albrecht, P.; Sutter, P. Graphene Growth on Polycrystalline Ru Thin Films. *Appl. Phys. Lett.* **2009**, *95*, No. 133109.
- 28 Sutter, E.; Albrecht, P.; Camino, F. E.; Sutter, P. Monolayer Graphene As Ultimate Chemical Passivation Layer for Arbitrarily Shaped Metal Surfaces. *Carbon* **2010**, *48*, 4414–4420.
- 29 Zhan, N.; Wang, G.; Liu, J. Cobalt-Assisted Large-Area Epitaxial Graphene Growth in Thermal Cracker Enhanced Gas Source Molecular Beam Epitaxy. *Appl. Phys. A: Mater. Sci. Process.* **2011**, *105*, 341–345.
- 30 Wang, S. M.; Pei, Y. H.; Wang, X.; Wang, H.; Meng, Q. N.; Tian, H. W.; Zheng, X. L.; Zheng, W. T.; Liu, Y. C. Synthesis of Graphene on a Polycrystalline Co Film by Radio-Frequency Plasma-Enhanced Chemical Vapor Deposition. *J. Phys. D: Appl. Phys.* **2010**, *43*, No. 455402.
- 31 Rut'kov, E. V.; Kuz'michev, A. V.; Gall, N. R. Carbon Interaction with Rhodium Surface: Adsorption, Dissolution, Segregation, Growth of Graphene Layers. *Phys. Solid State* **2011**, *53*, 1092–1098.
- 32 Mueller, F.; Grandthyll, S.; Zeitz, C.; Jacobs, K.; Huefner, S.; Gsell, S.; Schreck, M. Epitaxial Growth of Graphene on Ir(111) by Liquid Precursor Deposition. *Phys. Rev. B* **2011**, *84*, No. 075472.
- 33 Reina, A.; Jia, X.; Ho, J.; Nezich, D.; Son, H.; Bulovic, V.; Dresselhaus, M. S.; Kong, J. Large Area, Few-Layer Graphene Films on Arbitrary Substrates by Chemical Vapor Deposition. *Nano Lett.* **2009**, *9*, 30–35.
- 34 De Arco, L. G.; Zhang, Y.; Schlenker, C. W.; Ryu, K.; Thompson, M. E.; Zhou, C. Continuous, Highly Flexible, and Transparent Graphene Films by Chemical Vapor Deposition for Organic Photovoltaics. *ACS Nano* **2010**, *4*, 2865–2873.
- 35 Zhang, Y.; Gomez, L.; Ishikawa, F. N.; Madaria, A.; Ryu, K.; Wang, C.; Badmaev, A.; Zhou, C. Comparison of Graphene Growth on Single-Crystalline and Polycrystalline Ni by Chemical Vapor Deposition. *J. Phys. Chem. Lett.* **2010**, *1*, 3101–3107.
- 36 Chae, S. J.; Guenes, F.; Kim, K. K.; Kim, E. S.; Han, G. H.; Kim, S. M.; Shin, H.-J.; Yoon, S.-M.; Choi, J.-Y.; Park, M. H.; Yang, C. W.; Pribat, D.; Lee, Y. H. Synthesis of Large-Area Graphene Layers on Poly-Nickel Substrate by Chemical Vapor Deposition: Wrinkle Formation. *Adv. Mater.* **2009**, *21*, 2328–2333.
- 37 Kim, K. S.; Zhao, Y.; Jang, H.; Lee, S. Y.; Kim, J. M.; Kim, K. S.; Ahn, J.-H.; Kim, P.; Choi, J.-Y.; Hong, B. H. Large-Scale Pattern Growth of Graphene Films for Stretchable Transparent Electrodes. *Nature* **2009**, *457*, 706–710.
- 38 Liu, W.; Jackson, B. L.; Zhu, J.; Miao, C.-Q.; Chung, C.-H.; Park, Y.-J.; Sun, K.; Woo, J.; Xie, Y.-H. Large Scale Pattern Graphene Electrode for High Performance in Transparent Organic Single Crystal Field-Effect Transistors. *ACS Nano* **2010**, *4*, 3927–3932.
- 39 Zheng, M.; Takei, K.; Hsia, B.; Fang, H.; Zhang, X.; Ferralis, N.; Ko, H.; Chueh, Y.-L.; Zhang, Y.; Maboudian, R.; Javey, A. Metal-Catalyzed Crystallization of Amorphous Carbon to Graphene. *Appl. Phys. Lett.* **2010**, *96*, No. 063110.
- 40 Garcia, J. M.; He, R.; Jiang, M. P.; Kim, P.; Pfeiffer, L. N.; Pinczuk, A. Multilayer Graphene Grown by Precipitation upon Cooling of Nickel on Diamond. *Carbon* **2011**, *49*, 1006–1012.
- 41 Yan, Z.; Peng, Z.; Sun, Z.; Yao, J.; Zhu, Y.; Liu, Z.; Ajayan, P. M.; Tour, J. M. Growth of Bilayer Graphene on Insulating Substrates. *ACS Nano* **2011**, *5*, 8187–8192.
- 42 Shin, H.-J.; Choi, W. M.; Yoon, S.-M.; Han, G. H.; Woo, Y. S.; Kim, E. S.; Chae, S. J.; Li, X.-S.; Benayad, A.; Duong Dinh, L.; Gunes, F.; Lee, Y. H.; Choi, J.-Y. Transfer-Free Growth of Few-Layer Graphene by Self-Assembled Monolayers. *Adv. Mater.* **2011**, *23*, 4392–4397.
- 43 Kang, B. J.; Mun, J. H.; Hwang, C. Y.; Cho, B. J. Monolayer Graphene Growth on Sputtered Thin Film Platinum. *J. Appl. Phys.* **2009**, *106*, No. 104309.
- 44 Gao, T.; Xie, S.; Gao, Y.; Liu, M.; Chen, Y.; Zhang, Y.; Liu, Z. Growth and Atomic-Scale Characterizations of Graphene on Multifaceted Textured Pt Foils Prepared by Chemical Vapor Deposition. *ACS Nano* **2011**, *5*, 9194–9201.
- 45 Mattevi, C.; Kim, H.; Chhowalla, M. A Review of Chemical Vapour Deposition of Graphene on Copper. *J. Mater. Chem.* **2011**, *21*, 3324–3334.
- 46 Li, X.; Cai, W.; An, J.; Kim, S.; Nah, J.; Yang, D.; Piner, R.; Velamakanni, A.; Jung, I.; Tutuc, E.; Banerjee, S. K.; Colombo, L.; Ruoff, R. S. Large-Area Synthesis of High-Quality and Uniform Graphene Films on Copper Foils. *Science* **2009**, *324*, 1312–1314.
- 47 Liu, W.; Li, H.; Xu, C.; Khatami, Y.; Banerjee, K. Synthesis of High-Quality Monolayer and Bilayer Graphene on Copper Using Chemical Vapor Deposition. *Carbon* **2011**, *49*, 4122–4130.
- 48 Lee, Y.; Bae, S.; Jang, H.; Jang, S.; Zhu, S.-E.; Sim, S. H.; Song, Y. I.; Hong, B. H.; Ahn, J.-H. Wafer-Scale Synthesis and Transfer of Graphene Films. *Nano Lett.* **2010**, *10*, 490–493.
- 49 Luo, Z.; Lu, Y.; Singer, D. W.; Berck, M. E.; Somers, L. A.; Goldsmith, B. R.; Johnson, A. T. C. Effect of Substrate Roughness and Feedstock Concentration on Growth of Wafer-Scale Graphene at Atmospheric Pressure. *Chem. Mater.* **2011**, *23*, 1441–1447.
- 50 Yu, Q.; Jauregui, L. A.; Wu, W.; Colby, R.; Tian, J.; Su, Z.; Cao, H.; Liu, Z.; Pandey, D.; Wei, D.; Chung, T. F.; Peng, P.; Guisinger, N. P.; Stach, E. A.; Bao, J.; Pei, S.-S.; Chen, Y. P. Control and Characterization of Individual Grains and Grain Boundaries in Graphene Grown by Chemical Vapor Deposition. *Nat. Mater.* **2011**, *10*, 443–449.
- 51 Han, G. H.; Guenes, F.; Bae, J. J.; Kim, E. S.; Chae, S. J.; Shin, H.-J.; Choi, J.-Y.; Pribat, D.; Lee, Y. H. Influence of Copper Morphology in Forming Nucleation Seeds for Graphene Growth. *Nano Lett.* **2011**, *11*, 4144–4148.
- 52 Ji, H.; Hao, Y.; Ren, Y.; Charlton, M.; Lee, W. H.; Wu, Q.; Li, H.; Zhu, Y.; Wu, Y.; Piner, R.; Ruoff, R. S. Graphene Growth Using a Solid Carbon Feedstock and Hydrogen. *ACS Nano* **2011**, *5*, 7656–7661.
- 53 Sun, Z.; Yan, Z.; Yao, J.; Beitler, E.; Zhu, Y.; Tour, J. M. Growth of Graphene from Solid Carbon Sources. *Nature* **2010**, *468*, 549–552.
- 54 Ruan, G.; Sun, Z.; Peng, Z.; Tour, J. M. Growth of Graphene from Food, Insects, and Waste. *ACS Nano* **2011**, *5*, 7601–7607.
- 55 Oznucler, T.; Pince, E.; Polat, E. O.; Balci, O.; Salihoglu, O.; Kocabas, C. Synthesis of Graphene on Gold. *Appl. Phys. Lett.* **2011**, *98*, No. 183101.
- 56 John, R.; Ashokreddy, A.; Vijayan, C.; Pradeep, T. Single- and Few-Layer Graphene Growth on Stainless Steel Substrates by Direct Thermal Chemical Vapor Deposition. *Nanotechnology* **2011**, *22*, No. 165701.
- 57 Gullapalli, H.; Reddy, A. L. M.; Kilpatrick, S.; Dubey, M.; Ajayan, P. M. Graphene Growth via Carburization of Stainless Steel and Application in Energy Storage. *Small* **2011**, *7*, 1697–1700.
- 58 Liu, N.; Fu, L.; Dai, B.; Yan, K.; Liu, X.; Zhao, R.; Zhang, Y.; Liu, Z. Universal Segregation Growth Approach to Wafer-Size Graphene from Non-Noble Metals. *Nano Lett.* **2011**, *11*, 297–303.
- 59 Liu, X.; Fu, L.; Liu, N.; Gao, T.; Zhang, Y.; Liao, L.; Liu, Z. Segregation Growth of Graphene on Cu-Ni Alloy for Precise Layer Control. *J. Phys. Chem. C* **2011**, *115*, 11976–11982.
- 60 Chen, S.; Brown, L.; Levendorf, M.; Cai, W.; Ju, S.-Y.; Edgeworth, J.; Li, X.; Magnuson, C. W.; Velamakanni, A.; Piner, R. D.; Kang, J.; Park, J.; Ruoff, R. S. Oxidation Resistance of Graphene-Coated Cu and Cu/Ni Alloy. *ACS Nano* **2011**, *5*, 1321–1327.
- 61 Chen, S.; Cai, W.; Piner, R. D.; Suk, J. W.; Wu, Y.; Ren, Y.; Kang, J.; Ruoff, R. S. Synthesis and Characterization of Large-Area Graphene and Graphite Films on Commercial Cu-Ni Alloy Foils. *Nano Lett.* **2011**, *11*, 3519–3525.
- 62 Weatherup, R. S.; Bayer, B. C.; Blume, R.; Ducati, C.; Baetz, C.; Schlögl, R.; Hofmann, S. In Situ Characterization of Alloy Catalysts for Low-Temperature Graphene Growth. *Nano Lett.* **2011**, *11*, 4154–4160.
- 63 Dai, B.; Fu, L.; Zou, Z.; Wang, M.; Xu, H.; Wang, S.; Liu, Z. Rational Design of a Binary Metal Alloy for Chemical Vapor Deposition Growth of Uniform Single-Layer Graphene. *Nat. Commun.* **2011**, *2*, 522.