

Synthesis, Crystal Growth and Structure Investigations of Rare-Earth Disilicates and Rare-Earth Oxyapatites

A. Nørlund Christensen,^{*,a} R. G. Hazell^a and A. W. Hewat^b

^aDepartment of Inorganic Chemistry, Aarhus University, DK-8000 Aarhus C, Denmark and ^bMax von Laue–Paul Langevin Institute, PO Box 156, F-38042 Grenoble 9, France

Christensen, A. N., Hazell, R. G. and Hewat, A. W., 1997. Synthesis, Crystal Growth and Structure Investigations of Rare-Earth Disilicates and Rare-Earth Oxyapatites. – Acta Chem. Scand. 51: 37–43. © Acta Chemica Scandinavica 1997.

The rare-earth disilicates RE₂Si₂O₇ (RE=La, Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er and Y) and the rare-earth oxyapatites RE_{9.33}□_{0.67}(SiO₄)₆O₂ (RE=La, Nd and Eu) were synthesized in solid-state reactions at temperatures from 1050 to 1500 °C. Single crystals of the disilicates Ho₂Si₂O₇, Er₂Si₂O₇ and Y₂Si₂O₇ and of the oxyapatites Eu_{9.33}□_{0.67}(SiO₄)₆O₂ and Dy_{9.33}□_{0.67}(SiO₄)₆O₂ were grown in a flux growth mode in the temperature interval 1260–960 °C from a flux containing Bi₂O₃ and V₂O₅. Purity of single crystals and reaction products was investigated by X-ray single-crystal and powder-diffraction techniques.

X-Ray single-crystal diffraction analyses are reported on Ho₂Si₂O₇ and EuVO₄. Ho₂Si₂O₇ type *D* is monoclinic *P*2₁/*c* with *Z*=4 and *a*=4.6868(5), *b*=10.8618(12), *c*=5.5872(5) Å, β=95.993(7)°. EuVO₄ is tetragonal. *I*4₁/*amd* with *Z*=4 and *a*=7.2480(9), *c*=6.3778(10) Å.

Neutron powder diffraction analyses are reported on Er₂Si₂O₇, Ho₂Si₂O₇ and Y₂Si₂O₇ all of type *D* structure and on the oxyapatites La_{9.33}□_{0.67}(SiO₄)₆O₂ and Nd_{9.33}□_{0.67}(SiO₄)₆O₂. The type *D* structure is monoclinic with *P*2₁/*c* and *Z*=4. Er₂Si₂O₇ has *a*=4.6943(4), *b*=10.8097(10), *c*=5.5646(4) Å, β=96.037(4)°. Ho₂Si₂O₇ has *a*=4.6929(5), *b*=10.8627(12), *c*=5.5895(5) Å, β=96.017(4)°. Y₂Si₂O₇ has *a*=4.6916(4), *b*=10.8521(10), *c*=5.5872(5) Å, β=96.040(3)°. The rare-earth oxyapatite structure is hexagonal with *P*6₃/*m* and *Z*=1. La_{9.33}□_{0.67}(SiO₄)₆O₂ has *a*=9.7259(10) and *c*=7.1899(3) Å, and Nd_{9.33}□_{0.67}(SiO₄)₆O₂ has *a*=9.5731(8) and *c*=7.0336(2) Å.

The synthesis of high-temperature phases of the rare-earth disilicates RE₂Si₂O₇ (RE=La, Ce, Pr, Nd, Sm, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu and Y) from the melt, using a crucible-free technique, was reported recently.¹ The technique used was to melt the end of a ceramic rod of RE₂Si₂O₇ and to collect the droplets of the compound on a tray of BN, on which they froze to the silicate. However, some of the samples made in this way contained rather large quantities of impurity phases which were, as examples, Ho_{9.33}□_{0.67}(SiO₄)₆O₂ in the Ho₂Si₂O₇ sample and Y_{9.33}□_{0.67}(SiO₄)₆O₂ in the sample of Y₂Si₂O₇.¹ The traditional way of synthesis for the rare-earth disilicates is to apply solid-state sintering reaction in which pellets of the oxide mixtures are kept at temperatures in the range 1200–1600 °C for time periods up to 100 h. These heat treatments are repeated a number of times for each sample after grinding and formation of new pellets after each treatment to insure homogeneity. This synthesis technique was applied in the present work.

Four high-temperature forms of RE₂Si₂O₇ have been reported.² The structure type *G* is monoclinic for RE=

La to Sm, type *F* is triclinic for RE=Sm and Eu, type *E* is orthorhombic for RE=Eu to Ho, and type *D* is monoclinic for RE=Ho and Er and exists also for Y. In addition, type *C* is monoclinic for RE=Ho to Lu and is most likely stable at high as well as at low temperatures for RE=Tm to Lu. The geometry in the Si₂O₇⁶⁻ ions in the different structure types is so that the Si–O–Si angle is 180° in the type *C* and *D* structures, determined by the symmetry of the space groups of the two structure types. The Si–O–Si angle in the type *G* structures cluster around 132°, and are in the type *E* structures found in the interval 150–160°. The type *F* structure is not known in detail.

In the type *E* structures of Ho₂Si₂O₇ and Y₂Si₂O₇ it was found from profile analysis of neutron diffraction powder patterns that the Si–μ–O distances (μ–O denotes the bridge oxygen atom) were longer than reported earlier for the type *E* structure of Y₂Si₂O₇³ and Gd₂Si₂O₇.⁴ To clarify this ambiguity a detailed structure analysis of the type *E* structures of RE₂Si₂O₇ (RE=Gd, Tb, Dy, Ho, and Y) is planned. Single crystals of RE₂Si₂O₇ (RE=Ho, Er, and Tm for type *C*, RE=Ho and Er for type *D*, and RE=Dy for type *E* structure) have been obtained

* To whom correspondence should be addressed.

in a flux growth method.⁵ The single crystals were obtained by slow cooling of melts containing Bi₂O₃ and V₂O₅. Crystal growth by a flux method has been made for the compounds Ho₂Si₂O₇ (type *D*) Er₂Si₂O₇ (type *C*), Y₂Si₂O₇ (type *D*), Eu_{9.33}□_{0.67}(SiO₄)₆O₂, and Dy_{9.33}□_{0.67}(SiO₄)₆O₂ to obtain samples for single-crystal structure analysis and the results of the growth experiments are reported below.

Experimental

Solid-state synthesis and crystal growth. The following chemicals were used in the synthesis: SiO₂, kieselgur, V₂O₅ (Merck), La₂O₃ (Johnson Matthey), Ho₂O₃, Er₂O₃, Bi₂O₃ (Fluka), Sm₂O₃, Eu₂O₃, Ho₂O₃, Y₂O₃ (Auer Remy), and Nd₂O₃, Eu₂O₃, Gd₂O₃, Tb₄O₇, Dy₂O₃, Ho₂O₃, Er₂O₃ (Rhone-Poulenc). Stoichiometric mixtures of the rare-earth oxides and kieselgur were pressed into 10 or 25 mm diameter pellets in moulds of cemented carbides and heated twice or up to five times in an electric furnace with intermediate grindings and pressing into new tablets in the solid-state sintering reactions. The experimental conditions listing temperature and time for the first and last heat treatment are listed in Table 1. The tablets were placed in Al₂O₃ crucibles or on blocks of Al₂O₃. In some cases, minor reactions between the pellets and the Al₂O₃ support were observed. The mass of the reaction mixture was typically about 20 g for each charge. To obtain a sample of the type *F* structure of Sm₂Si₂O₇ a 10 mm diameter sample of the compound was heated in an RF heating coil with a graphite susceptor in a He atmosphere.⁶ The sintering temperature for this experiment could not be recorded.

The experimental conditions for the flux growth experiments are listed in Table 2. The melt was kept in a 50 ml platinum crucible placed in a 150 ml Al₂O₃ crucible on a support of granulated ZrO₂. The growth furnace used has been described previously.⁷ Crystal growth by a self-nucleation was achieved by a slow cooling from the maximum to minimum temperature listed in Table 2. From the latter temperature the furnace was cooled fast to room temperature. To remove the V₂O₅–Bi₂O₃ flux from the grown crystals the platinum crucible was placed upside down on a porous support of magnesium oxide in a platinum bowl and heated to the minimum temperature (see above) in a furnace for 5 h. By this treatment, the flux was sucked into the magnesium oxide support and the grown single crystals could easily be removed from the platinum crucible.

X-Ray diffraction. X-Ray powder patterns were recorded at 25 °C of the samples from the solid-state synthesis and from the crystal growth experiments on a Stoe–Stadi powder diffractometer with a position-sensitive detector. The diffractometer was calibrated with a silicon standard ($a = 5.430\ 50\ \text{Å}$) and Cu $K_{\alpha 1}$ radiation was used ($\lambda = 1.540\ 598\ \text{Å}$). The phases identified from the powder patterns are listed in Tables 1 and 2.

Three-dimensional single-crystal X-ray diffraction data were measured on a Huber four-circle diffractometer on a crystal of Ho₂Si₂O₇ type *D* and on a crystal of EuVO₄, and experimental conditions and crystallographic data for these two structures are displayed in Table 3.

Neutron powder diffraction. The neutron diffraction powder patterns were measured of the rare-earth silicates at 27 °C on the powder diffractometer D1A at Institut Laue-Langevin, Grenoble. Experimental conditions for the measurements and unit cells and space groups for the five compounds are listed in Table 4.

Results and discussion

The purpose of the solid-state synthesis was to produce samples of RE_{9.33}□_{0.67}(SiO₄)₆O₂ and RE₂Si₂O₇ for further structure investigations by neutron powder diffraction technique. In the cases of Eu₂Si₂O₇ and Sm₂Si₂O₇ the goal was to produce samples of the structure type *F* for detailed structure analysis using X-ray powder diffraction data. The purpose of the crystal growth synthesis was to test the possibility of growing single crystals of the high-temperature phases from a flux. Of special interest was the possible growth of single crystals of Eu₂Si₂O₇ type *F*.

Oxide mixtures with a stoichiometric composition to produce the apatite forms RE_{9.33}□_{0.67}(SiO₄)₆O₂ formed readily these compounds at 1400 °C (Table 1). This was also the case for oxide mixtures with a composition to produce RE₂Si₂O₇ (Table 1) except in the cases of Sm and Eu, for which a strong tendency to produce the apatite forms was observed in a number of the experiments. This may be related to the position of Sm and Eu in the row of lanthanides where at least Eu²⁺ ions may be formed in reduction of Eu³⁺, or to the fact that the two rare-earth oxides reacted with the Al₂O₃ crucibles.

In the binary system Ho₂O₃–SiO₂ a phase with the composition Ho₂Si₆O₁₅ has been reported,⁸ but a structure of a holmium silicate with this composition has not been reported. Attempts were made to synthesize the holmium silicate reported to have the composition Ho₂Si₆O₁₅(Ho₂O₃·6SiO₂).⁸ As Y³⁺ has approximately the same ionic radius as Ho³⁺, attempts were also made to make an yttrium silicate with the composition Y₂Si₆O₁₅. Pellets of the two oxides and SiO₂ (kieselgur) with the nominal composition Ho₂O₃·6SiO₂ and Y₂O₃·6SiO₂ and a pellet of SiO₂ (kieselgur) were placed in a boat of Al₂O₃ and kept in a furnace at 1100 °C for 68 days (Table 1). X-Ray powder patterns of the SiO₂ pellets showed that it was cristobalite, those of the Y₂O₃·6SiO₂ pellet showed that it was a mixture of Y₂Si₂O₇ type *C* and cristobalite, and those of the Ho₂O₃·6SiO₂ pellet showed that it was a mixture of Ho₂Si₂O₇ type *B* and cristobalite. The X-ray powder pattern listed in Ref. 8, Table 5, for the compound Ho₂O₃·6SiO₂ is indeed very similar to that of Ho₂Si₂O₇

Table 1. Experimental conditions for the solid-state synthesis of polycrystalline samples of rare-earth silicates.

| Stoichiometric mixtures to produce RE _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | | | | | | | | |
|---|--------------------------------|-------------------|-------------------------|------------------------|-----------------|--|----------------------|----------------------|
| Quantities/g | RE ₂ O ₃ | SiO ₂ | First heat treatment/°C | Last heat treatment/°C | Reaction time/h | Product | Structure type | Impurity phase |
| La ₂ O ₃ | 20.63 | 4.89 | 1400 | 1400 | 125 | La _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | Apatite | None |
| Nd ₂ O ₃ | 4.89 | 1.12 | 1400 | 1400 | 200 | Nd _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | Apatite | None |
| Eu ₂ O ₃ | 4.93 | 1.08 | 1300 | 1400 | 100 | Eu _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | Apatite | None |
| Stoichiometric mixtures to produce RE ₂ Si ₆ O ₁₅ | | | | | | | | |
| Quantities/g | RE ₂ O ₃ | SiO ₂ | Heat treatment/°C | | Reaction time/d | Product | Structure type | Impurity phase |
| Ho ₂ O ₃ | 5.67 | 5.41 | 1100 | | 68 | Ho ₂ Si ₂ O ₇ | <i>B</i> | Cristobalite |
| Y ₂ O ₃ | 4.52 | 7.21 | 1100 | | 68 | Y ₂ Si ₂ O ₇ | <i>C</i> | Cristobalite |
| | | 5.50 | 1100 | | 68 | Cristobalite | | |
| Stoichiometric mixtures to produce RE ₂ Si ₂ O ₇ | | | | | | | | |
| Quantities/g | RE ₂ O ₃ | SiO ₂ | First heat treatment/°C | Last heat treatment/°C | Reaction time/h | Product | Structure type | Impurity phase |
| La ₂ O ₃ | 27.54 | 10.78 | 1350 | 1400 | 150 | La ₂ Si ₂ O ₇ | <i>G</i> | None |
| Nd ₂ O ₃ | 15.52 | 5.54 | 1300 | 1400 | 125 | Nd ₂ Si ₂ O ₇ | <i>A</i> | None |
| Eu ₂ O ₃ | 19.84 | 6.78 | 1350 | 1400 | 200 | Eu ₂ Si ₂ O ₇ | <i>E</i> | None |
| Eu ₂ O ₃ | 9.15 | 3.12 | 1400 | 1050 | 150 | Eu _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | Apatite | None |
| Eu ₂ O ₃ | 9.15 | 3.12 | 1300 | 1050 | 150 | Eu _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | Apatite | None |
| Sm ₂ O ₃ | 5.67 | 1.96 | 1300 | 1400 | 250 | Sm ₂ Si ₂ O ₇ | <i>A^c</i> | None |
| Sm ₂ O ₃ | 20.14 | 6.94 | 1350 | 1400 | 200 | Sm ₂ Si ₂ O ₇ | <i>A</i> | None |
| Sm ₂ O ₃ | 17.51 | 6.03 | 1300 | | | | | |
| Gd ₂ O ₃ | 5.17 | 1.76 | 1300 | 1400 | 150 | Gd ₂ Si ₂ O ₇ | <i>E</i> | None |
| Tb ₄ O ₇ | 25.26 | 8.12 | 1300 | 1400 ^a | 150 | Tb ₂ Si ₂ O ₇ | <i>E</i> | None |
| Dy ₂ O ₃ | 15.01 | 4.83 | 1300 | 1400 | 150 | Dy ₂ Si ₂ O ₇ | <i>B</i> | None |
| Dy ₂ O ₃ | 25.25 | 8.14 | 1300 | 1400 ^a | 150 | Dy ₂ Si ₂ O ₇ | <i>E</i> | None |
| Ho ₂ O ₃ | 4.19 | 2.00 ^b | 1400 | 1130 | 100 | Ho ₂ Si ₂ O ₇ | <i>D</i> | Formation of a glass |
| Ho ₂ O ₃ | 11.34 | 3.61 | 1450 | 1450 | 200 | Ho ₂ Si ₂ O ₇ | <i>D</i> | None |
| Er ₂ O ₃ | 14.02 | 4.40 | 1450 | 1400 | 225 | Er ₂ Si ₂ O ₇ | <i>D</i> | None |
| Y ₂ O ₃ | 6.77 | 3.60 | 1450 | 1450 | 200 | Y ₂ Si ₂ O ₇ | <i>D</i> | None |
| Y ₂ O ₃ | 34.57 | 18.39 | 1400 | 1500 | 200 | Y ₂ Si ₂ O ₇ | <i>D</i> | None |

^a The temperature control failed in these experiments and the actual temperature in the furnace may have been higher than the reported value of 1400 °C. ^b To produce a silicate with the composition Ho₂Si₃O₉ (reported in Ref. 8). ^c Converted to type *F* when heated in ADL high-frequency furnace.

Table 2. Experimental conditions for the flux growth experiments using the molar ratios: 7.14 RE₂O₃: 21.43 SiO₂: 57.15 Bi₂O₃: 14.28 V₂O₅.

| Quantities/g | RE ₂ O ₃ | SiO ₂ | Bi ₂ O ₃ | V ₂ O ₅ | T _{max} /°C | T _{min} /°C | Cooling rate/ °C h ⁻¹ | Main product | Structure type | Impurity phase |
|--------------------------------|--------------------------------|------------------|--------------------------------|-------------------------------|----------------------|----------------------|-------------------------------------|--|----------------|-------------------|
| Eu ₂ O ₃ | 3.77 | 1.93 | 39.94 | 3.90 | 1260 | 960 | 1.5 | Eu _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | | EuVO ₄ |
| Dy ₂ O ₃ | 3.99 | 1.93 | 39.94 | 3.90 | 1260 | 960 | 1.5 | Dy _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ | | None |
| Ho ₂ O ₃ | 4.05 | 1.93 | 39.94 | 3.90 | 1260 | 960 | 1.5 | Ho ₂ Si ₂ O ₇ | Type <i>D</i> | None |
| Er ₂ O ₃ | 4.10 | 1.93 | 39.94 | 3.90 | 1260 | 960 | 1.5 | Er ₂ Si ₂ O ₇ | Type <i>C</i> | None |
| Y ₂ O ₃ | 2.42 | 1.93 | 39.94 | 3.90 | 1260 | 1140 | 1.5 | Y ₂ Si ₂ O ₇ | Type <i>D</i> | None |

type *B*. Two powder patterns are listed in Ref. 8 for two modifications of a holmium silicate with the composition Ho₂O₃·3SiO₂. The pattern listed for the low-temperature modification of this compound (Ref. 8, Table 3) is indeed similar to that of Ho₂Si₂O₇, type *C*, and the pattern listed for the high-temperature modification of the compound (Ref. 8, Table 4) is the same as that of Ho₂Si₂O₇,

type *D*. The phase diagram reported for the system Ho₂O₃–SiO₂ in Ref. 8 has thus most likely severe errors. Attempts were also made in this investigation to synthesize a holmium silicate with the composition Ho₂O₃·3SiO₂. This resulted in formation of samples of Ho₂Si₂O₇, type *D*, containing the surplus SiO₂ as cristobalite (Table 1).

Table 3. Experimental data and unit cell parameters for EuVO_4 and for $\text{Ho}_2\text{Si}_2\text{O}_7$, type D.

| | EuVO_4 | $\text{Ho}_2\text{Si}_2\text{O}_7$ |
|---|--|--|
| $a/\text{\AA}$ | 7.2480(9) | 4.6868(5) |
| $b/\text{\AA}$ | 7.2480(9) | 10.8618(12) |
| $c/\text{\AA}$ | 6.3778(10) | 5.5872(5) |
| $\alpha/^\circ$ | 90.0 | 90.0 |
| $\beta/^\circ$ | 90.0 | 95.993(7) |
| $\gamma/^\circ$ | 90.0 | 90.0 |
| Cell volume/ \AA^3 | 335 | 283 |
| Space group | $I4_1/amd$ | $P2_1/c$ |
| Z | 4 | 4 |
| Density (calc)/ g cm^{-3} | 5.29 | 5.85 |
| Size of crystal/mm | 0.250×0.033 $\times 0.094$ | 0.150×0.220 $\times 0.080$ |
| Linear absorption coefficient, μ/cm^{-1} | 215 | 151 |
| Transmission between | 0.16–0.56 | 0.09–0.23 |
| No. of measured reflections (including two standards) | 2655 | 4717 |
| R_{intern} of reflections (%) | 4.8 | 1.9 |
| No. of independent reflections | 2544 | 4250 |
| No. of reflections with $I > 3\sigma(I)$ | 304 | 1112 |
| Scan method | ω -2 θ | ω -2 θ |
| $\theta_{\text{max}}/^\circ$ | 36 | 36 |
| T/K | 298 | 298 |
| Wavelength/ \AA | 0.7107 | 0.56090 |

The crystal growth experiments from a Bi_2O_3 - V_2O_5 flux resulted in formation of single crystals of the high-temperature forms, type D, of $\text{Ho}_2\text{Si}_2\text{O}_7$ and $\text{Y}_2\text{Si}_2\text{O}_7$, which again illustrates the similarity between the Ho^{3+} and Y^{3+} ions. The type D structures were also obtained of the two compounds in the solid-state sintering reactions at 1450 °C (Table 1). However, the rare-earth disilicates were not obtained in the crystal growth experiments of Eu and Dy where the apatite forms $\text{Eu}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$ and $\text{Dy}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$ were the single crystals obtained. In addition, well formed single crystals of europium vanadate, EuVO_4 were formed in the europium silicate crystal growth experi-

ment. It is remarkable that the two apatite compounds are formed instead of the rare-earth disilicates. The composition of the flux may favour the formation of one silicate or modification of a rare-earth silicate to other compounds.⁵ However, in the solid-state sintering experiments the tendency of the formation of $\text{Eu}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$ was strong, also from stoichiometric mixtures to produce $\text{Eu}_2\text{Si}_2\text{O}_7$.

Single-crystal X-ray diffraction investigation of the structures of EuVO_4 and $\text{Ho}_2\text{Si}_2\text{O}_7$, type D.

Structure determination of EuVO_4 . A needle-shaped single crystal of EuVO_4 was selected using the polarising microscope, and precession photographs confirmed the space group $I4_1/amd$. The X-ray diffractometer data were collected on a Huber four-circle diffractometer. Unit cell parameters and other experimental data are listed in Table 3.

The structure was solved by direct methods using the SHELX86 program.⁹ This gave the position of all the atoms of the structure and a difference Fourier map did not indicate any additional electron density. The model of the structure was refined using the least squares program LINUS,¹⁰ with scattering contributions from neutral atoms,¹¹ and with correction for anomalous dispersions.¹² The weights used in the refinements were $1/\sigma(I)$ with $\sigma(I) = [\sigma_{\text{count}}(F^2) + 1.03F^2]^{1/2} - |F|$ and $\sigma_{\text{count}}(F^2)$ is (number of counts)^{1/2}. The final R -values were $R_F = 2.1\%$ and $R_w = 3.5\%$. Atomic coordinates and displacement parameters are listed in Table 5 and interatomic distances and bond angles are in Table 6. All the rare-earth vanadates and that of yttrium can have the zircon structure,¹³ and the crystal structures of YVO_4 and of ErVO_4 have been reported.^{14,15} The interatomic distances found in the structure of EuVO_4 have a higher precision than the distances reported previously for the structures of YVO_4 and ErVO_4 .

Structure determination of $\text{Ho}_2\text{Si}_2\text{O}_7$, type D. A single crystal of $\text{Ho}_2\text{Si}_2\text{O}_7$ was selected using the polarising microscope, and precession photographs confirmed the

Table 4. Experimental data and unit-cell parameters for rare-earth silicates measured at the neutron powder diffractometer.

| Compound ^a | A | B | C | D | E |
|--|----------|----------|-------------|-------------|-------------|
| Diffractometer | D1A | D1A | D1A | D1A | D1A |
| $2\theta_{\text{min}}/^\circ$ | 10.0 | 10.0 | 10.0 | 10.0 | 24.1 |
| $2\theta_{\text{max}}/^\circ$ | 147.0 | 147.0 | 147.0 | 147.0 | 147.0 |
| $\Delta 2\theta/^\circ$ | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 |
| $\lambda/\text{\AA}$ | 1.909 | 1.909 | 1.909 | 1.909 | 1.909 |
| Max. $\sin \theta/\lambda/\text{\AA}^{-1}$ | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 |
| Diameter of vanadium can/mm | 16 | 12 | 12 | 12 | 12 |
| $a/\text{\AA}$ | 9.726(1) | 9.573(1) | 4.6943(4) | 4.6925(5) | 4.6916(4) |
| $b/\text{\AA}$ | 9.726(1) | 9.573(1) | 10.8097(10) | 10.8627(12) | 10.8521(10) |
| $c/\text{\AA}$ | 7.190(1) | 7.034(1) | 5.5646(4) | 5.5895(5) | 5.5872(5) |
| $\beta/^\circ$ | | | 96.037(4) | 96.017(4) | 96.040(3) |
| Space group | $P6_3/m$ | $P6_3/m$ | $P2_1/c$ | $P2_1/c$ | $P2_1/c$ |

^aA: $\text{La}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$; B: $\text{Nd}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$; C: $\text{Er}_2\text{Si}_2\text{O}_7$, type D; D: $\text{Ho}_2\text{Si}_2\text{O}_7$, type D; E: $\text{Y}_2\text{Si}_2\text{O}_7$, type D.

Table 5. Atomic coordinates and displacement parameters for EuVO₄.

| Atom | Site | x/a | y/b | z/c | U ₁₁ | U ₂₂ | U ₃₃ | U ₁₃ |
|------|------|-----|-----------|-----------|-----------------|-----------------|-----------------|-----------------|
| Eu | 4a | 0 | 3/4 | 1/8 | 67(1) | 67(1) | 51(2) | 0 |
| V | 4b | 0 | 3/4 | 5/8 | 70(3) | 70(3) | 56(5) | 0 |
| O | 16h | 0 | 0.4315(4) | 0.2036(5) | 83(9) | 181(11) | 90(10) | 12(8) |

The U-values are multiplied by 10⁴.

Table 6. Interatomic distances (in Å) in the zircon structure of EuVO₄, YVO₄ and ErVO₄.

| EuVO ₄ | YVO ₄ (Ref. 14) | ErVO ₄ (Ref. 15) |
|-------------------|----------------------------|-----------------------------|
| Eu-O | 2.363(3) | Y-O 2.299 ± 8 |
| Eu-O | 2.474(3) | Y-O 2.443 ± 8 |
| V-O | 1.710(3) | V-O 1.706 ± 8 |

space group *P2₁/c*. X-Ray diffraction data were measured as reported for EuVO₄, and cell parameters are listed in Table 3. Structure solution and refinement was also made as reported for EuVO₄. The final *R*-values were *R_F* = 5.4% and *R_w* = 7.1%. Table 7 is a list of atomic coordinates and displacement parameters, and interatomic distances and bond lengths are in Table 8. Figure 1 is a stereoscopic drawing of the structure of Ho₂Si₂O₇, type *D*. A Fourier map calculation showed that the bridge oxygen atom O3 showed a rather large displacement perpendicular to the Si-O-Si bond direction shaped as a disc with its center 0.13 Å off the atomic position of O3. If the oxygen atom is placed in the centre, the Si-O-Si angle would be 172° in contrast to the value of 180° reported previously.⁴

Table 7. Structure parameters for Ho₂Si₂O₇, type *D* from X-ray single-crystal diffraction data. Monoclinic space group *P2₁/c*. Occupancy of O3 is 0.5. The equivalent isotropic thermal parameters are listed.

| Atom | Site | x/a | y/b | z/c | U _{eq} ^a |
|------|------|------------|-------------|------------|------------------------------|
| Ho | 4e | 0.88855(3) | 0.84940(2) | 0.09314(3) | 0.0049(3) |
| Si | 4e | 0.6389(2) | 0.1114(1) | 0.3566(2) | 0.0044(9) |
| O1 | 4e | 0.7923(7) | 0.0517(3) | 0.1346(6) | 0.010(3) |
| O2 | 4e | 0.8752(7) | 0.1823(3) | 0.5390(6) | 0.008(3) |
| O3 | 4e | 0.5064(31) | -0.0075(13) | 0.4866(24) | 0.013(2) |
| O4 | 4e | 0.3793(7) | 0.2016(3) | 0.2491(6) | 0.009(3) |

$$^a U_{eq} = (1/3) \sum_i \sum_j U_{ij} a_i^* a_j^* a_i a_j$$

Table 8. Interatomic distances (in Å) in the structure of Ho₂Si₂O₇, type *D*.

| | | | |
|-------|----------|-------|----------|
| Ho-O4 | 2.245(4) | Si-O1 | 1.632(4) |
| Ho-O2 | 2.257(4) | Si-O2 | 1.619(4) |
| Ho-O1 | 2.260(4) | Si-O4 | 1.627(3) |
| Ho-O4 | 2.272(4) | Si-O3 | 1.622(4) |
| Ho-O2 | 2.288(4) | Si-O3 | 1.636(4) |
| Ho-O1 | 2.325(4) | | |

Neutron powder diffraction investigations of the rare-earth silicates.

Structure investigation of the apatites RE_{9.33}□_{0.67}(SiO₄)₆O₂. The crystal structures of the rare-earth oxyapatites RE_{9.33}□_{0.67}(SiO₄)₆O₂ were reported for Gd by Smolin and Shepelev¹⁶ and for Ce and Dy by Belokoneva *et al.*,¹⁷ respectively. These investigations were made with X-ray single-crystal diffraction data. The structures have two independent RE atoms, one in site 6h and one in site 4f with three 1/3 RE atoms statistically distributed in the fourfold site. Model calculations were made with neutron powder diffraction data of La_{9.33}□_{0.67}(SiO₄)₆O₂ and Nd_{9.33}□_{0.67}(SiO₄)₆O₂ using the published atomic coordinates¹⁷ as starting parameters, and the least-squares profile refinement program FullProf.¹⁸ The final parameters for the two structures are listed in Table 9. Interatomic distances for the REO_x coordination polyhedra and for the SiO₄⁴⁻ ion are in Table 10, and Fig. 2 is a projection of the structure of Nd_{9.33}□_{0.67}(SiO₄)₆O₂ along [001]. The La1 and Nd1 atoms are seven-coordinated with six oxygen atoms from

Table 9. Structure parameters for La_{9.33}□_{0.67}(SiO₄)₆O₂ and Nd_{9.33}□_{0.67}(SiO₄)₆O₂ from neutron powder diffraction data. Hexagonal space group *P6₃/m*.

| Atom | Site | x/a | y/b | z/c | B/Å ² |
|---|------|-----------|-----------|-----------|------------------|
| La _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ ^a | | | | | |
| La1 | 6h | 0.9844(5) | 0.2274(4) | 1/4 | 0.7(1) |
| La2 | 4f | 1/3 | 2/3 | 0.0058(8) | 0.8(1) |
| Si | 6h | 0.3719(7) | 0.4050(8) | 1/4 | 0.2(1) |
| O1 | 6h | 0.4830(7) | 0.3209(6) | 1/4 | 1.8(1) |
| O2 | 6h | 0.4684(6) | 0.5947(6) | 1/4 | 1.3(1) |
| O3 | 12i | 0.2571(5) | 0.3472(5) | 0.0683(4) | 2.0(1) |
| O4 | 2a | 0 | 0 | 1/4 | 3.5(2) |
| Nd _{9.33} □ _{0.67} (SiO ₄) ₆ O ₂ ^b | | | | | |
| Nd1 | 6h | 0.9881(4) | 0.2306(3) | 1/4 | 0.4(1) |
| Nd2 | 4f | 1/3 | 2/3 | 0.0013(6) | 0.9(1) |
| Si | 6h | 0.3697(5) | 0.3998(6) | 1/4 | 0.6(1) |
| O1 | 6h | 0.4842(4) | 0.3186(4) | 1/4 | 1.4(1) |
| O2 | 6h | 0.4722(4) | 0.5969(4) | 1/4 | 1.4(1) |
| O3 | 12i | 0.2513(4) | 0.3421(3) | 0.0680(3) | 1.7(1) |
| O4 | 2a | 0 | 0 | 1/4 | 1.6(1) |

Profile parameters and *R*-values from the program FullProf. ^a*U* = 0.202(5), *V* = -0.586(5), *W* = 0.550(7). Asymmetry parameters: 0.26(3), 0.09(1), 0.14(4). *R_p* = 7.4%, *R_{WP}* = 9.9%, *R_F* = 9.2%. ^b*U* = 0.202, *V* = -0.557(4), *W* = 0.517(6). Asymmetry parameters: 0.43(2), 0.07(1), -0.20(3). *R_p* = 4.9%, *R_{WP}* = 5.8%, *R_F* = 6.5%.

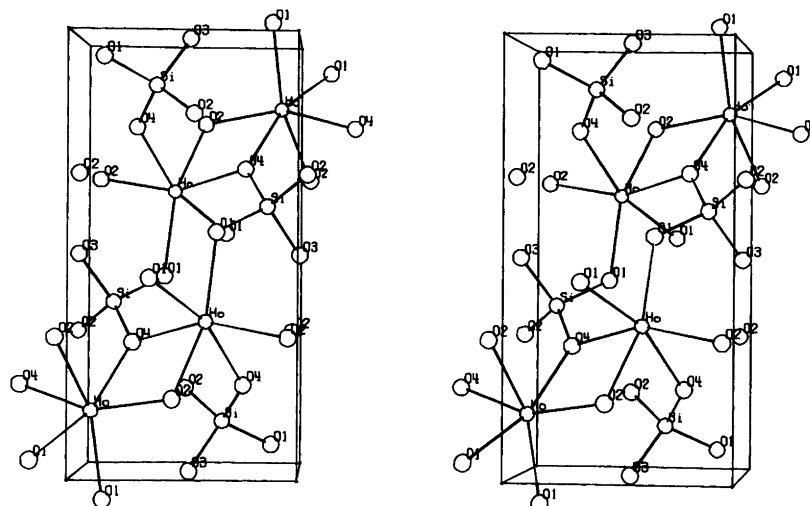


Fig. 1. View of the structure of $\text{Ho}_2\text{Si}_2\text{O}_7$, type D along [100]. The b -axis is along the page.

Table 10. Interatomic distances in the structures of $\text{La}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$ and in $\text{Nd}_{9.33}\square_{0.67}(\text{SiO}_4)_6\text{O}_2$.

| | | | | | |
|--------|------|--------|------|-------|------|
| La1-O4 | 2.29 | La2-O2 | 2.49 | Si-O2 | 1.60 |
| La1-O3 | 2.46 | La2-O2 | 2.49 | Si-O3 | 1.63 |
| La1-O3 | 2.46 | La2-O2 | 2.49 | Si-O3 | 1.63 |
| La1-O2 | 2.56 | La2-O1 | 2.52 | Si-O1 | 1.65 |
| La1-O3 | 2.65 | La2-O1 | 2.52 | | |
| La1-O3 | 2.65 | La2-O1 | 2.52 | | |
| La1-O1 | 2.71 | La2-O3 | 2.85 | | |
| | | La2-O3 | 2.85 | | |
| | | La2-O3 | 2.85 | | |
| Nd1-O4 | 2.27 | Nd2-O1 | 2.44 | Si-O3 | 1.61 |
| Nd1-O3 | 2.40 | Nd2-O1 | 2.44 | Si-O3 | 1.61 |
| Nd1-O3 | 2.40 | Nd2-O1 | 2.44 | Si-O1 | 1.63 |
| Nd1-O2 | 2.47 | Nd2-O2 | 2.48 | Si-O2 | 1.64 |
| Nd1-O3 | 2.54 | Nd2-O2 | 2.48 | | |
| Nd1-O2 | 2.54 | Nd2-O2 | 2.48 | | |
| Nd1-O1 | 2.68 | Nd2-O3 | 2.84 | | |
| | | Nd2-O3 | 2.84 | | |
| | | Nd2-O3 | 2.84 | | |

the silicate ions, and with the free oxygen atom O4. The coordination polyhedron is a deformed version of the YO_7 coordination polyhedron found in the structure of YOOD .¹⁹ The La2 and Nd2 atoms are nine-coordinated with oxygen atoms from the silicate ions. The coordination polyhedron is slightly deformed and of the same type as found in the structure of $\text{Y}(\text{OH})_3$.²⁰ The La-O and Nd-O interatomic distances are within the expected range of distances, which is also the case for the Si-O distances of the SiO_4^{4-} ions in the two structures. The standard deviations found for the interatomic distances in the two structures are smaller than the errors reported in Ref. 16.

Structure investigation of $\text{RE}_2\text{Si}_2\text{O}_7$, Type D. Starting parameters for the model calculations using the neutron diffraction powder patterns of $\text{Er}_2\text{Si}_2\text{O}_7$, $\text{Ho}_2\text{Si}_2\text{O}_7$ and $\text{Y}_2\text{Si}_2\text{O}_7$ and the profile refinement program FullProf¹⁸ were the parameters arrived at in the single-crystal structure analysis of $\text{Ho}_2\text{Si}_2\text{O}_7$ (see above). The final para-

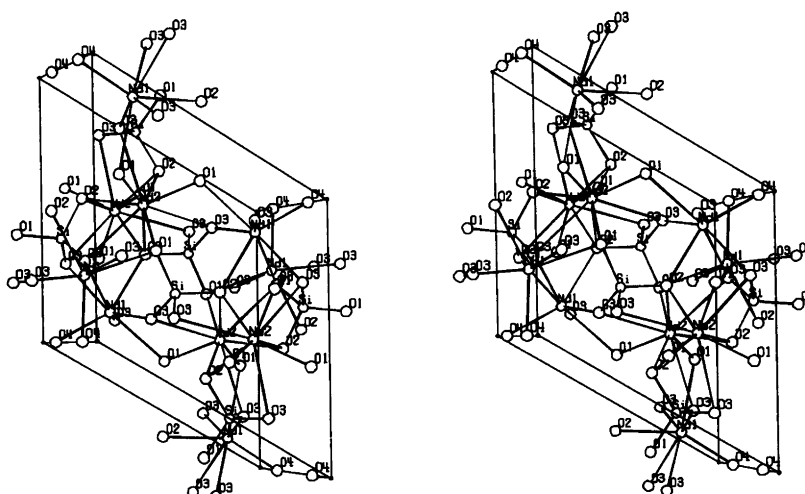


Fig. 2. View of the structure of $\text{Nd}_{9.33}\square_{0.67}(\text{SiO}_6)_4\text{O}_2$ along [001]. The a -axis is along the page.

Table 11. Structure parameters for RE₂Si₂O₇, type D from neutron powder diffraction data. Monoclinic space group P2₁/c; occupancy for O3 is 0.5.

| Atom | Site | x/a | y/b | z/c | B/Å ² |
|---|------|------------|-------------|------------|------------------|
| Er ₂ Si ₂ O ₇ ^a | | | | | |
| Er | 4e | 0.8913(12) | 0.8495(4) | 0.0941(10) | 0.0(1) |
| Si | 4e | 0.6436(28) | 0.1154(9) | 0.3676(22) | 1.3(2) |
| O1 | 4e | 0.7885(14) | 0.0493(6) | 0.1354(13) | 0.4(2) |
| O2 | 4e | 0.8676(14) | 0.1830(6) | 0.5373(11) | 0.0(1) |
| O3 | 4e | 0.5285(37) | -0.0148(16) | 0.4857(32) | 0.0(2) |
| O4 | 4e | 0.3802(16) | 0.2031(6) | 0.2501(14) | 0.9(2) |
| Y ₂ Si ₂ O ₇ ^b | | | | | |
| Y | 4e | 0.8904(11) | 0.8495(4) | 0.0941(9) | 0.4(1) |
| Si | 4e | 0.6445(2) | 0.1136(8) | 0.3696(17) | 1.1(2) |
| O1 | 4e | 0.7933(13) | 0.0502(6) | 0.1358(11) | 0.6(1) |
| O2 | 4e | 0.8670(12) | 0.1822(5) | 0.5371(10) | 0.0(1) |
| O3 | 4e | 0.5340(32) | -0.0106(16) | 0.4976(32) | 0.0(2) |
| O4 | 4e | 0.3792(16) | 0.2017(6) | 0.2513(14) | 2.0(2) |
| Ho ₂ Si ₂ O ₇ ^c | | | | | |
| Ho | 4e | 0.8950(13) | 0.8492(4) | 0.0964(11) | 0.0(1) |
| Si | 4e | 0.6506(29) | 0.1157(11) | 0.3826(27) | 1.8(3) |
| O1 | 4e | 0.7922(18) | 0.0487(8) | 0.1374(15) | 0.8(2) |
| O2 | 4e | 0.8645(15) | 0.1841(6) | 0.5358(12) | 0.0(2) |
| O3 | 4e | 0.5445(32) | -0.0095(19) | 0.5059(33) | 0.0(3) |
| O4 | 4e | 0.3826(23) | 0.2021(9) | 0.2549(21) | 2.6(3) |

Profile parameters and R-values from the program FullProf. ^aU=0.198, V=-0.554(5), W=0.553(9). Asymmetry parameters: 0.24(6), 0.03(2), -0.02(7). R_p=6.8%, R_{WP}=8.9%, R_F=14.0%. ^bU=0.198(4), V=-0.539(5), W=0.537(8). Asymmetry parameters: 0.31(5), 0.01(1), -0.21(7). R_p=11.5%, R_{WP}=14.6%, R_F=12.5%. ^cU=0.206(5), V=-0.559(5), W=0.554(11). Asymmetry parameters: 0.36(5), 0.04(2), -0.13(7). R_p=6.8%, R_{WP}=9.1%, R_F=16.0%.

Table 12. Interatomic distances in the type D structures of Ho₂Si₂O₇, Er₂Si₂O₇ and Y₂Si₂O₇.

| Ho ₂ Si ₂ O ₇ | | Er ₂ Si ₂ O ₇ | | Y ₂ Si ₂ O ₇ | |
|--|------|--|------|---|------|
| Ho-O1 | 2.24 | Er-O1 | 2.23 | Y-O1 | 2.24 |
| Ho-O2 | 2.27 | Er-O4 | 2.26 | Y-O4 | 2.26 |
| Ho-O4 | 2.27 | Er-O4 | 2.26 | Y-O4 | 2.27 |
| Ho-O2 | 2.28 | Er-O2 | 2.26 | Y-O2 | 2.27 |
| Ho-O4 | 2.31 | Er-O2 | 2.29 | Y-O2 | 2.30 |
| Ho-O1 | 2.34 | Er-O1 | 2.34 | Y-O1 | 2.33 |
| Si-O2 | 1.45 | Si-O2 | 1.52 | Si-O2 | 1.52 |
| Si-O3 | 1.62 | Si-O3 | 1.63 | Si-O3 | 1.62 |
| Si-O4 | 1.67 | Si-O4 | 1.64 | Si-O4 | 1.65 |
| Si-O1 | 1.74 | Si-O1 | 1.68 | Si-O1 | 1.69 |

meters for the structures of the three compounds are listed in Table 11, and interatomic distances and bond angles are listed in Table 12.

In the RE₂Si₂O₇ type D structure the RE atoms are

six-coordinated to oxygen atoms in a slightly deformed octahedron. In the disilicate ions the Si-O_{bridge} distances are not significantly longer than the Si-O_{terminal} distances. With the O_{bridge} atom placed statistically in site 4e the Si-O-Si angles cluster around the value 172°.

Acknowledgements. The Danish Natural Science Research Council has supported this investigation with a grant. *Carlsbergfondet* is thanked for a high temperature furnace used in the synthesis. The Max von Laue-Paul Langevin Institute is acknowledged for the use of the neutron powder diffractometer D1A. Mrs. M. A. Chevallier, Mrs. C. Secher, Mr. A. Lindahl and Mr. N. J. Hansen are acknowledged for valuable assistance.

References

- Christensen, A. N. *Z. Kristallogr.* 209 (1994) 7.
- Felsche, J. *J. Less-Common Met.* 21 (1970) 1.
- Dias, H. W., Glasser, F. P., Gunawardane, R. P. and Howie, R. A. *Z. Kristallogr.* 191 (1990) 117.
- Smolin, Yu. I. and Shepelev, Yu. F. *Acta Crystallogr., Sect. B26* (1970) 484.
- Maqsood, A., Wanklyn, B. M. and Garton, G. *J. Cryst. Growth* 46 (1979) 671.
- Christensen, A. N. and Hazell, R. G. *Acta Chem. Scand.* 45 (1991) 226.
- Christensen, A. N. *Acta Chem. Scand.* 46 (1992) 909.
- Montorsi, M. *J. Less-Common Met.* 84 (1982) 25.
- Sheldrick, G. *SHELX86, Program for the Solution of Crystal Structures.* University of Göttingen, Germany 1986.
- Busing, W. R., Martin, K. O. and Levy, H. A. *ORFLS, A Fortran Crystallographic Least Squares Program*, Report ORNL-TM 305. Oak Ridge National Laboratory, Oak Ridge, TN, 1962. LINUS is a 1971 version of ORFLS.
- Cromer, D. T. and Waber, J. T. Report LA-3056, Los Alamos Scientific Laboratory of the University of California, Los Alamos, NM 1964.
- Eds. MacGillavry, C.H., Rieck, G.D. and Lonsdale, K. *International Tables for X-Ray Crystallography*, The Kynoch Press, Birmingham, UK 1962, Vol. III, p. 213.
- Schwarz, H. *Z. Anorg. Chem.* 323 (1963) 44.
- Baglio, J. A. and Gashurov, G. *Acta Crystallogr., Sect. B24* (1968) 292.
- Patscheke, E., Fuess, H. and Will, G. *Chem. Phys. Lett.* 2 (1968) 47.
- Smolin, Yu. I. and Shepelev, Yu. F. *Izv. Akad. Nauk SSSR Neorg. Mat.* 5 (1969) 1823.
- Belokoneva, E. L., Petrova, T. L., Simonov, M. A. and Belov, N. V. *Sov. Phys. Crystallogr.* 17 (1972) 429.
- Rodriguez-Carvajal, J. *FullProf* Version 3.0.0. Apr. 95-LLBJRC. Laboratoire Léon Brillouin (CEA-CNRS), Saclay, France.
- Christensen, A. N. and von Heidenstam, O. *Acta Chem. Scand.* 20 (1966) 2658.
- Christensen, A. N., Hazell, R. G. and Nilsson, Å. *Acta Chem. Scand.* 21 (1967) 481.

Received March 11, 1996.