

Revision of the structure of $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ leucite as orthorhombic *Pbca*A. M. T. Bell,^{a,*} K. S. Knight,^b
C. M. B. Henderson^{a,c} and A. N. Fitch^d^aDepartment of Photon Sciences, STFC Daresbury Laboratory, Warrington WA4 4AD, England, ^bISIS, STFC Rutherford Appleton Laboratory, Didcot OX11 0QX, England, ^cSchool of Earth, Atmospheric and Environmental Sciences, University of Manchester, Manchester M13 9PL, England, and ^dESRF, 6 Rue Jules Horowitz, BP 220, 38043 Grenoble Cedex 9, France

* Current address: HASYLAB, Deutsches Elektronen-Synchrotron, Notkestrasse 85, 22607 Hamburg, Germany.

Correspondence e-mail: ynotlleb1@mac.com

The crystal structure of a hydrothermally synthesized leucite analogue $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ has been determined and refined using the Rietveld method from high-resolution synchrotron X-ray and neutron powder diffraction data. This structure is based on the topology and cation-ordering scheme of the *Pbca* leucite structure of $\text{Cs}_2\text{CdSi}_5\text{O}_{12}$, and exhibits five ordered Si sites and one ordered Cu tetrahedrally coordinated (*T*) site. This structure for $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ is topologically identical to other known leucite structures and is different from that originally proposed by Heinrich & Baerlocher [(1991), *Acta Cryst. C* **47**, 237–241] in the tetragonal space group *P4₁2₁2*. The crystal structure of a dry-synthesized leucite analogue $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ has also been refined; this has the *Ia $\bar{3}d$* cubic pollucite structure with disordered *T* sites.

Received 11 September 2009

Accepted 21 December 2009

1. Introduction

The crystal structure of end-member leucite (KAlSi_2O_6) consists of a three-dimensional framework of silicate tetrahedra in which one third of the Si atoms are replaced by Al, with the larger (*W*) channels through the framework being occupied by the cavity-filling cation K^+ , while the smaller (*S*) channels are vacant. The framework is propagated in three dimensions by linking four and six rings of TO_4 tetrahedra. This crystal structure has the tetragonal *I4₁/a* space group at ambient temperature and pressure (Mazzi *et al.*, 1976), but is found to undergo a displacive phase transition to the cubic space group *Ia $\bar{3}d$* at ~ 923 K (Wyart, 1940; Taylor & Henderson, 1968). The structure of pollucite, the naturally occurring Cs-rich analogue of leucite ($\text{Cs}_{12}\text{Na}_4\text{Al}_{16}\text{Si}_{32}\text{O}_{96}\cdot 4\text{H}_2\text{O}$), has been determined by Beger (1969) in *Ia $\bar{3}d$* , but another natural pollucite sample has recently been refined in the monoclinic space group *C2/c* (Kamiya *et al.*, 2008). In both of these structures Cs and H_2O occupy the *W* sites, and Na the *S* sites. The synthetic end-member pollucite ($\text{CsAlSi}_2\text{O}_6$) has the *Ia $\bar{3}d$* leucite aristotype structure under ambient conditions with Cs occupying the *W* sites and with the *S* sites vacant. Tetragonal and cubic leucite structures may also occur if some *T*-site atoms are replaced by trivalent transition elements or divalent cations. These analogues have the stoichiometries ACSi_2O_6 and $\text{A}_2\text{BSi}_5\text{O}_{12}$, where *A* is an alkali metal cation (K, Rb, Cs), *B* is a divalent metal cation (Be, Mg, Fe^{2+} , Co, Ni, Zn, Cd), and *C* is a trivalent metal cation (Al, Fe^{3+} ; Torres-Martinez & West, 1986, 1989; Bell & Henderson, 1994*a,b*; Bell, Henderson *et al.*, 1994; Henderson *et al.*, 1998). All of these structures have disordered framework cations on the tetrahedrally coordinated (*T*) sites.

However, a synchrotron X-ray powder diffraction, electron diffraction and ^{29}Si MAS NMR study of a leucite analogue with the stoichiometry $\text{K}_2\text{MgSi}_5\text{O}_{12}$ (Bell, Henderson *et al.*,

1994) showed that, while a dry-synthesized sample has the $Ia\bar{3}d$ aristotype structure with disordered T cations (Mg and Si), a hydrothermally synthesized sample had a previously unrecorded $P2_1/c$ monoclinic leucite structure. This monoclinic sample has a unit cell with 24 independent oxygen sites, 12 independent T sites [two with Si surrounded by four SiO_4 tetrahedra (denoted Q4Si(4Si) sites), eight with Si surrounded by three SiO_4 and one MgO_4 (Q4Si(3Si,1Mg)), and two with Mg surrounded by four SiO_4 tetrahedra (Q4Mg(4Si)]. In addition, four symmetry-independent extra-framework, cavity cation sites are occupied by K. A similar synchrotron X-ray powder diffraction and ^{29}Si MAS NMR study of the $\text{Cs}_2\text{CdSi}_5\text{O}_{12}$ leucite phase (Bell, Redfern *et al.*, 1994) determined another previously unrecorded structure type belonging to the orthorhombic $Pbca$ space group. The unit cell for this structure has 12 independent oxygen sites, six independent T sites [one Q4Si(4Si), four Q4(3Si,1Mg) and one Q4Mg(4Si)] and two independent Cs sites. Two types of four rings occur, one with four Q4Si(3Si,1Cd) and the other with the arrangement Q4Si(4Si)–Q4Si(3Si,1Cd)–Q4Cd(4Si)–Q4Si(3Si,1Cd). One type of six-ring occurs with the linkages Q4Si(4Si)–Q4Si(3Si,1Cd)–Q4Si(3Si,1Cd)–Q4Cd(4Si)–Q4Si(3Si,1Cd)–Q4Si(3Si,1Cd). Rietveld refinement (Bell & Henderson, 1996, 2009) showed that this ordered $Pbca$ structure is also found for dry-synthesized leucite analogues with stoichiometries $\text{Cs}_2\text{CoSi}_5\text{O}_{12}$, $\text{Cs}_2\text{NiSi}_5\text{O}_{12}$ and $\text{Cs}_2\text{ZnSi}_5\text{O}_{12}$, and for hydrothermally synthesized leucite analogues with stoichiometries $\text{Rb}_2\text{CdSi}_5\text{O}_{12}$, $\text{Cs}_2\text{MnSi}_5\text{O}_{12}$, $\text{Cs}_2\text{MgSi}_5\text{O}_{12}$ and $\text{Rb}_2\text{MgSi}_5\text{O}_{12}$. A high-temperature, X-ray powder diffraction study (Redfern & Henderson, 1996) showed that the crystal structure of hydrothermal $\text{K}_2\text{MgSi}_5\text{O}_{12}$ exhibits an unquenchable displacive transition from the $P2_1/c$ monoclinic phase to the $Pbca$ orthorhombic phase at 622 K in which five pairs of Si (ten sites) and one pair of Mg (two sites)

merge to form five Si sites [one Q4Si(4Si), four Q4Si(3Si,1Mg)] and one Mg [Q4Mg(4Si) site], while two pairs of K sites merge to form one pair in the $Pbca$ polymorph. In both of these polymorphs each Mg atom is separated by two Si atoms from the next nearest Mg.

The crystal structures of the different leucite analogues described above are all topologically identical and the space groups $I4_1/a$, $Pbca$ and $P2_1/c$ are all isotropy subgroups of the aristotype phase in the space group $Ia\bar{3}d$. All structural varieties have frameworks built up by linking four and six rings of TO_4 tetrahedra. The topology of the $Pbca$ structure is shown in Fig. 1 for $\text{Cs}_2\text{CdSi}_5\text{O}_{12}$ leucite viewed down [010]; note that Q4Si(4Si), Q4Si(3Si,1Cd) and Q4Cd(4Si) tetrahedral sites are distinguished with different colours.

A very different cation-ordering scheme has been determined (Heinrich & Baerlocher, 1991) for a hydrothermally synthesized pollucite analogue with the stoichiometry $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$. This structure was refined in the tetragonal space group $P4_12_12$ with the lattice parameters $a = 13.5776$ (1) and $c = 13.6189$ (2) Å. However, in this crystal structure the cation-ordering scheme is topologically different to all the other analogous leucite structures and was reported to have a unit cell with 12 independent O sites, a seven T -site ordered framework with six Si sites [three Q4Si(4Si), two Q4Si(3Si,1Cu) one Q4Si(2Si,2Cu)] and one Cu site [Q4Cu(4Si)]; Cu sites are separated by only one Si. This structure also has three distinct Cs sites. In contrast to the $Pbca$ leucites this structure has three different four rings with the arrangements [Q4Si(4Si)–Q4Si(3Si,1Cu)–Q4Si(4Si)–Q4Si(3Si,1Cu)], [Q4Si(4Si)–Q4Si(3Si,1Cu)–Q4Cu(4Si)–Q4Si(3Si,1Cu)] and [Q4Si(4Si)–Q4Si(2Si,2Cu)–Q4Cu(4Si)–

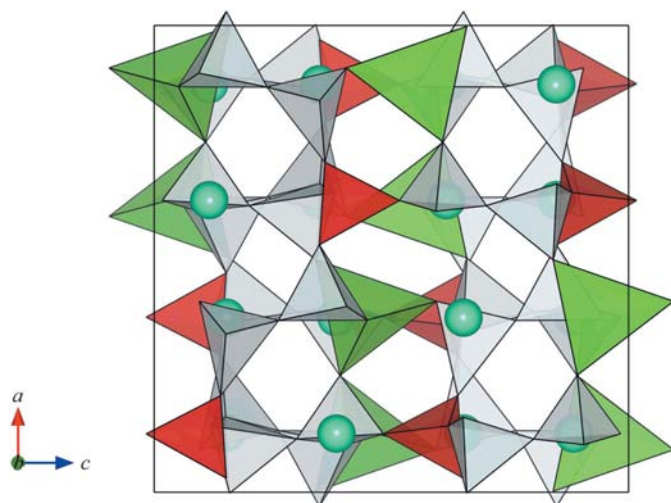


Figure 1
Plot of $Pbca$ crystal structure of $\text{Cs}_2\text{CdSi}_5\text{O}_{12}$ (Bell & Henderson, 1994b) down [010]. Cs^+ cations are indicated by light blue circles, CdO_4 [Q4Cd(4Si)] by green tetrahedra, Q4Si(4Si) by red tetrahedra and Q4Si(3Si,1Cd) by light grey tetrahedra. Crystal structure plots produced using VESTA (Momma & Izumi, 2008).

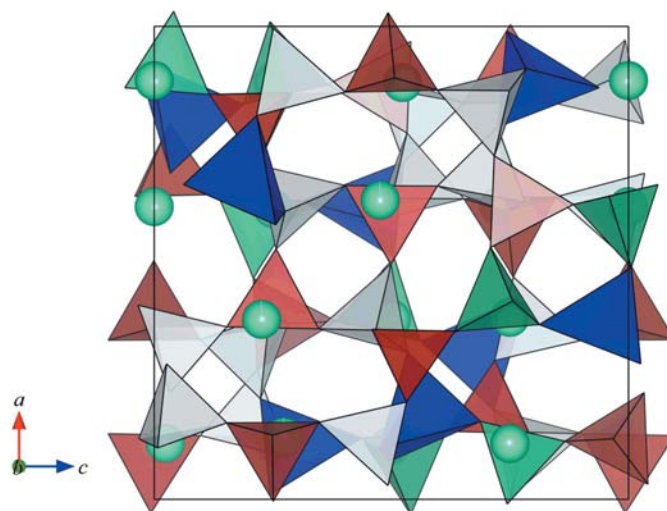


Figure 2
Plot of $P4_12_12$ crystal structure of $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ (Heinrich & Baerlocher, 1991) down [010]. Cs^+ cations are indicated by light blue circles, CuO_4 [Q4Cu(4Si)] by blue tetrahedra, Q4Si(4Si) by red tetrahedra, Q4Si(3Si,1Cu) by light grey tetrahedra, and Q4Si(2Si,2Cu) by dark green tetrahedra. Note the different arrangement of the Q4Cu(4Si) tetrahedra (blue in this figure) compared with the Q4Cd(4Si) (green) tetrahedra in Fig. 1. The origin is shifted by (1/4, 1/2, 1/8) compared with that for Fig. 1. Crystal structure plots produced using VESTA (Momma & Izumi, 2008).

Q4Si(2Si,2Cu)] and has two six rings with the different linkages [Q4Si(4Si)–Q4Si(2Si,2Cu)–Q4Cu(4Si)–Q4Si(3Si,1Cu)–Q4Si(4Si)–Q4Si(3Si,1Cu)] and [Q4Si(4Si)–Q4Si(3Si,1Cu)–Q4Si(4Si)–Q4Si(2Si,2Cu)–Q4Si(4Si)–Q4Si(3Si,1Cu)]. Fig. 2 shows the structure for $P4_12_12$ Cs₂CuSi₅O₁₂ leucite viewed down [010]. The very different framework topologies for Q4Si tetrahedra (Figs. 1 and 2) and for CdO₄ (Fig. 1) and CuO₄ (Fig. 2) tetrahedra are obvious. Note that the origin of the tetragonal crystal structure is displaced from the origin of the aristotype phase in the space group $Ia\bar{3}d$ (and that of the $Pbca$ phase) by $(1/4, 1/2, 1/8)$ (Stokes & Hatch, 1988).

In order to assess the likelihood of such fundamentally different structural arrangements for stoichiometrically similar leucite analogues we have synthesized a new sample of hydrothermal Cs₂CuSi₅O₁₂ and have determined its crystal structure using both neutron and synchrotron powder diffraction methods. The fact that the sample is dimensionally very close to cubic ($c/a = 1.0036$) complicates the powder structure determination and necessitates the use of the highest resolution diffraction techniques possible. In addition, another Cs₂CuSi₅O₁₂ sample was synthesized under dry conditions at 1 atm. and its structure was determined using synchrotron powder diffraction methods.

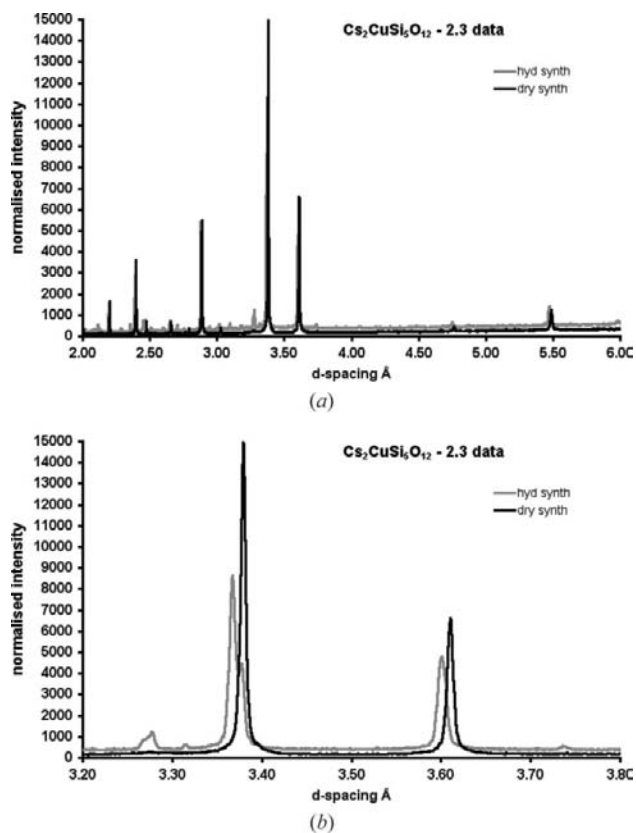


Figure 3
High-resolution powder diffraction data collected on station 2.3 for the dry and hydrothermally synthesized Cs₂CuSi₅O₁₂ samples. Fig. 3(a) shows data between 2 and 6 Å and Fig. 3(b) data between 3.2 and 3.8 Å.

Table 1
Interatomic Cs–O distances for hydrothermal Cs₂CuSi₅O₁₂ (Å).

| | | | |
|---------|------------------------|---------|-----------|
| Cs1–O1 | 3.999 (6) [†] | Cs2–O1 | 3.444 (6) |
| Cs1–O2 | 3.613 (5) | Cs2–O2 | 3.958 (6) |
| Cs1–O3 | 3.852 (6) | Cs2–O3 | 3.301 (6) |
| Cs1–O4 | 3.434 (5) | Cs2–O4 | 2.918 (6) |
| Cs1–O5 | 3.254 (6) | Cs2–O5 | 3.413 (5) |
| Cs1–O6 | 3.626 (5) | Cs2–O6 | 3.735 (7) |
| Cs1–O7 | 3.152 (6) | Cs2–O7 | 3.326 (6) |
| Cs1–O8 | 3.175 (6) | Cs2–O8 | 3.786 (6) |
| Cs1–O9 | 3.306 (6) | Cs2–O9 | 3.043 (6) |
| Cs1–O10 | 3.589 (6) | Cs2–O10 | 3.587 (6) |
| Cs1–O11 | 3.028 (5) | Cs2–O11 | 3.616 (7) |
| Cs1–O12 | 3.324 (7) | Cs2–O12 | 3.523 (6) |

[†] Numbers in brackets are 1σ errors in last place(s).

2. Experimental

2.1. Sample preparation

High-purity Cs₂CO₃, CuO and SiO₂ were mixed in stoichiometric proportions and heated in a platinum crucible overnight at 873 K to decompose the carbonate. This mixture was reground, returned to the crucible and melted at 1473 K for 30 min before quenching by dipping the base of the crucible into water. The turquoise-coloured glass was finely ground and used to synthesize the leucite analogues. One sample (denoted CsCu1) was crystallized dry at 1 atm by heating in a platinum crucible for 3 weeks at 873 K; this product had a turquoise colour similar to that of the glass starting material. The hydrothermal sample (CsCu2) was prepared in four separate ~1 gm batches by sealing in platinum capsules (6 mm diameter, ~25 mm long) with ~2% added water, and run in cold-seal pressure vessels under the identical conditions of 683 K, 500 bars pressure, for 6 d. Weights of capsules did not change during the experiments showing that they were properly sealed and each sample 'slug' was evenly beige-coloured along its length. X-ray powder diffraction patterns for each of the four batches were identical and the separate samples were then mixed to provide a sufficient sample for neutron diffraction study. Earlier synthesis experiments involved the use of gold capsules (following the method of Heinrich & Baerlocher, 1991), but resulted in very heterogeneous products with dark and light grey, yellow-grey and red regions and these were discarded.

The dry and hydrothermal samples gave similar laboratory X-ray powder diffraction patterns, although the latter had narrower peak shapes indicating better crystallinity. The composition of the hydrothermal sample was determined using electron microprobe methods giving a cell formula (average of 17 spot analyses) of Cs_{2.02}Cu_{1.00}Si_{4.98}O₁₂, therefore a stoichiometry of Cs₂CuSi₅O₁₂ was assumed.

2.2. Initial synchrotron X-ray powder diffraction

High-resolution synchrotron X-ray powder diffraction data were collected on both the dry synthesized (CsCu1) and hydrothermally synthesized (CsCu2) samples of Cs₂CuSi₅O₁₂. Samples were mounted on a flat-plate sample holder and data were collected using the powder diffractometer on station 2.3

of the Daresbury Synchrotron Radiation Source with a synchrotron X-ray wavelength of 1.7974 Å (Cernik *et al.*, 1990; Collins *et al.*, 1992).

Figs. 3(a) and (b) show plots of these powder data for the two Cs₂CuSi₅O₁₂ samples. Note that the dry sample has fewer Bragg peaks than the hydrothermal sample. Fig. 3(b) shows Bragg reflections close to 3.38 Å, where the 400/040/004 multiplet would be observed. This is a single peak for the dry sample and a doublet for the hydrothermal sample. This indicates that these two samples do not have the same crystal structures, with the extra Bragg peaks observed for the hydrothermal sample suggesting that this sample has a lower symmetry crystal structure than the dry sample.

2.3. Neutron and higher-resolution synchrotron X-ray powder diffraction

Owing to the very close overlap of Bragg reflections in the 2.3 synchrotron X-ray powder diffraction data for the hydrothermally synthesized sample it was not possible to carry out a Rietveld structure refinement for this sample with either the *Pbca* leucite structure or the *P*4₁2₁2 Cs₂CuSi₅O₁₂ structure as starting models. Therefore, more powder diffraction data were

Table 2

Interatomic T–O (T1 = Cu, T2–6 = Si) distances for hydrothermal Cs₂CuSi₅O₁₂ (Å).

| | | | |
|--------|------------|--------|-----------|
| T1–O4 | 1.945 (6)† | T4–O2 | 1.639 (5) |
| T1–O7 | 1.919 (5) | T4–O3 | 1.595 (5) |
| T1–O9 | 1.940 (5) | T4–O4 | 1.623 (5) |
| T1–O11 | 1.853 (5) | T4–O12 | 1.604 (5) |
| T2–O1 | 1.597 (5) | T5–O5 | 1.634 (5) |
| T2–O3 | 1.610 (5) | T5–O7 | 1.612 (5) |
| T2–O5 | 1.630 (5) | T5–O8 | 1.620 (5) |
| T2–O10 | 1.611 (5) | T5–O12 | 1.645 (5) |
| T3–O1 | 1.622 (5) | T6–O6 | 1.629 (5) |
| T3–O2 | 1.613 (5) | T6–O8 | 1.607 (5) |
| T3–O6 | 1.574 (5) | T6–O9 | 1.645 (5) |
| T3–O11 | 1.574 (5) | T6–O10 | 1.606 (5) |

† Numbers in brackets are 1σ errors in last place(s).

collected with higher-resolution instruments for the hydrothermal sample CsCu₂.

A sample was loaded into an 11 mm outer diameter vanadium can for neutron powder-diffraction data collection using the high-resolution powder diffraction (HRPD) instrument at the ISIS spallation neutron source. Data were collected in time-of-flight mode between 15–215 ms, normalized to the

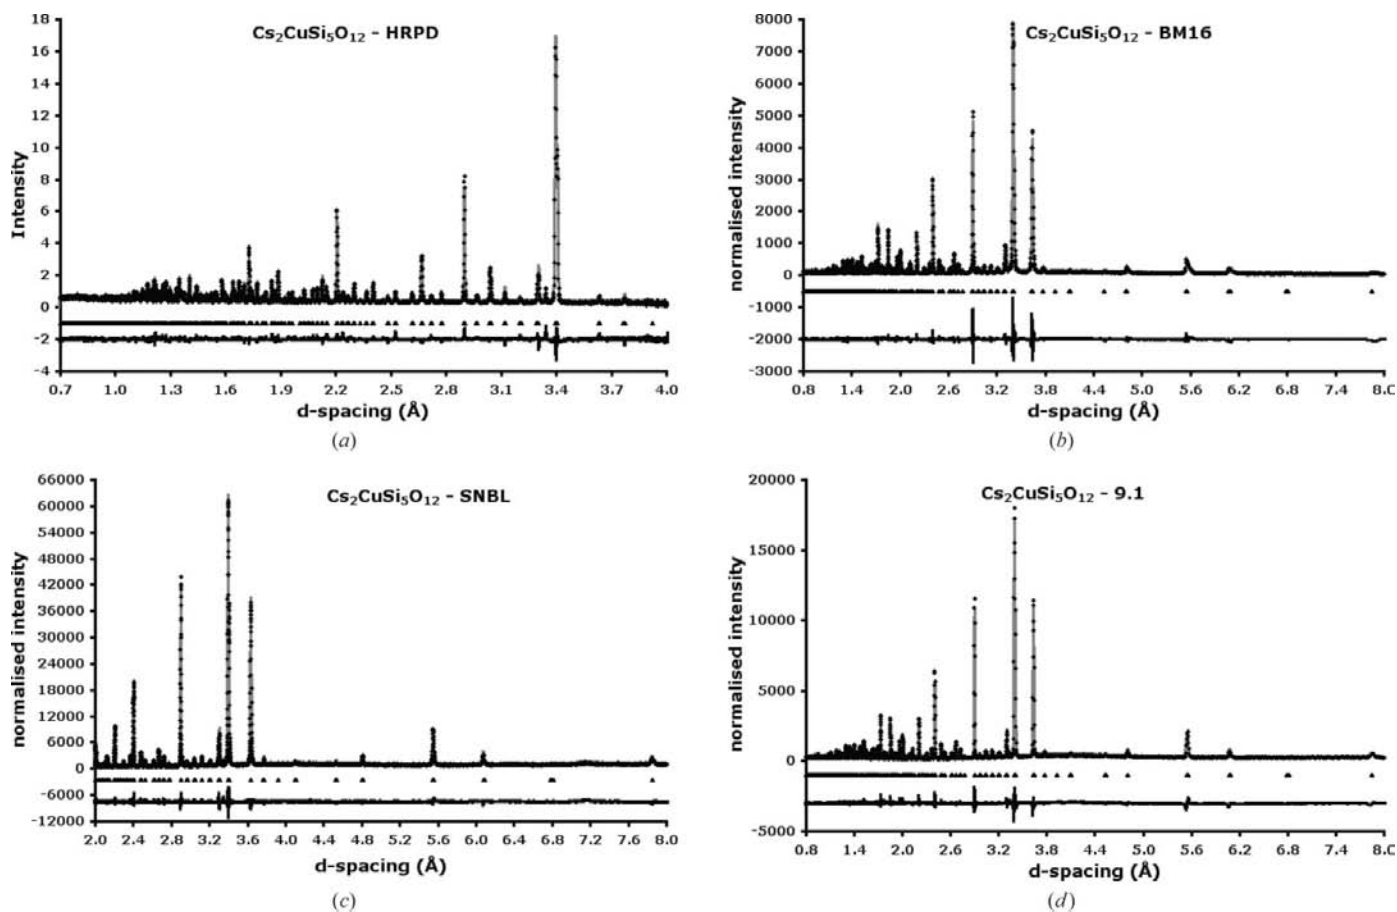


Figure 4 Rietveld difference plots for hydrothermally synthesized Cs₂CuSi₅O₁₂, *Pbca* crystal structure. Observed data are indicated by black points, calculated data by a light grey line and the difference plot by a black line. The positions of *Pbca* Bragg reflections are indicated by triangles. Plots are given for data collected on (a) HRPD (ISIS), (b) BM16 (ESRF), (c) SNBL (ESRF) and (d) 9.1 (SRS).

Table 3

Interatomic O—T—O (T1 = Cu, T2–6 = Si) angles (°) for hydrothermal Cs₂CuSi₅O₁₂.

| | | | | | |
|-----------|-----------|-----------|-----------|-----------|-----------|
| O4—T1—O7 | 92.3 (2)† | O1—T3—O2 | 114.7 (4) | O5—T5—O7 | 112.9 (4) |
| O4—T1—O9 | 115.1 (3) | O1—T3—O6 | 94.3 (3) | O5—T5—O8 | 101.1 (3) |
| O4—T1—O11 | 123.7 (3) | O1—T3—O11 | 108.6 (4) | O5—T5—O12 | 110.0 (4) |
| O7—T1—O9 | 111.8 (3) | O2—T3—O6 | 111.3 (4) | O7—T5—O8 | 110.9 (4) |
| O7—T1—O11 | 118.9 (3) | O2—T3—O11 | 110.0 (4) | O7—T5—O12 | 111.1 (4) |
| O9—T1—O11 | 96.3 (3) | O6—T3—O11 | 117.3 (4) | O8—T5—O12 | 110.4 (4) |
| O1—T2—O3 | 115.6 (4) | O2—T4—O3 | 103.5 (4) | O6—T6—O8 | 108.7 (4) |
| O1—T2—O5 | 103.8 (4) | O2—T4—O4 | 113.1 (4) | O6—T6—O9 | 102.4 (4) |
| O1—T2—O10 | 110.4 (4) | O2—T4—O12 | 106.9 (4) | O6—T6—O10 | 115.3 (4) |
| O3—T2—O5 | 107.6 (4) | O3—T4—O4 | 117.8 (4) | O8—T6—O9 | 112.4 (4) |
| O3—T2—O10 | 112.6 (4) | O3—T4—O12 | 100.2 (4) | O8—T6—O10 | 104.6 (4) |
| O5—T2—O10 | 106.0 (4) | O4—T4—O12 | 114.0 (4) | O9—T6—O10 | 113.6 (4) |

† Numbers in brackets are 1σ errors in last place(s).

Table 4

Interatomic T—O—T (T1 = Cu, T2–6 = Si) angles (°) for hydrothermal Cs₂CuSi₅O₁₂.

| | | | |
|-----------|------------|--------------|-----------|
| T2—O1—T3 | 140.8 (4)† | T1—O11—T3 | 129.3 (4) |
| T3—O2—T4 | 143.5 (4) | T4—O12—T5 | 137.4 (5) |
| T2—O3—T4 | 141.6 (4) | Mean Si—O—Si | 144.5 |
| T1—O4—T4 | 126.4 (4) | Mean T1—O—T | 130.8 |
| T2—O5—T5 | 138.6 (4) | Mean T2—O—T | 144.1 |
| T3—O6—T6 | 156.5 (4) | Mean T3—O—T | 142.5 |
| T1—O7—T5 | 139.3 (4) | Mean T4—O—T | 137.2 |
| T5—O8—T6 | 142.3 (5) | Mean T5—O—T | 140.2 |
| T1—O9—T6 | 128.1 (4) | Mean T6—O—T | 145.6 |
| T2—O10—T6 | 155.3 (5) | | |

† Numbers in brackets are 1σ errors in last place(s).

incident flux and corrected for detector efficiency before being rebinned at a resolution suitable for the sample.

Samples were also loaded into 0.5 mm diameter borosilicate glass capillaries for high-resolution synchrotron X-ray powder diffraction data collection. Data were collected on the

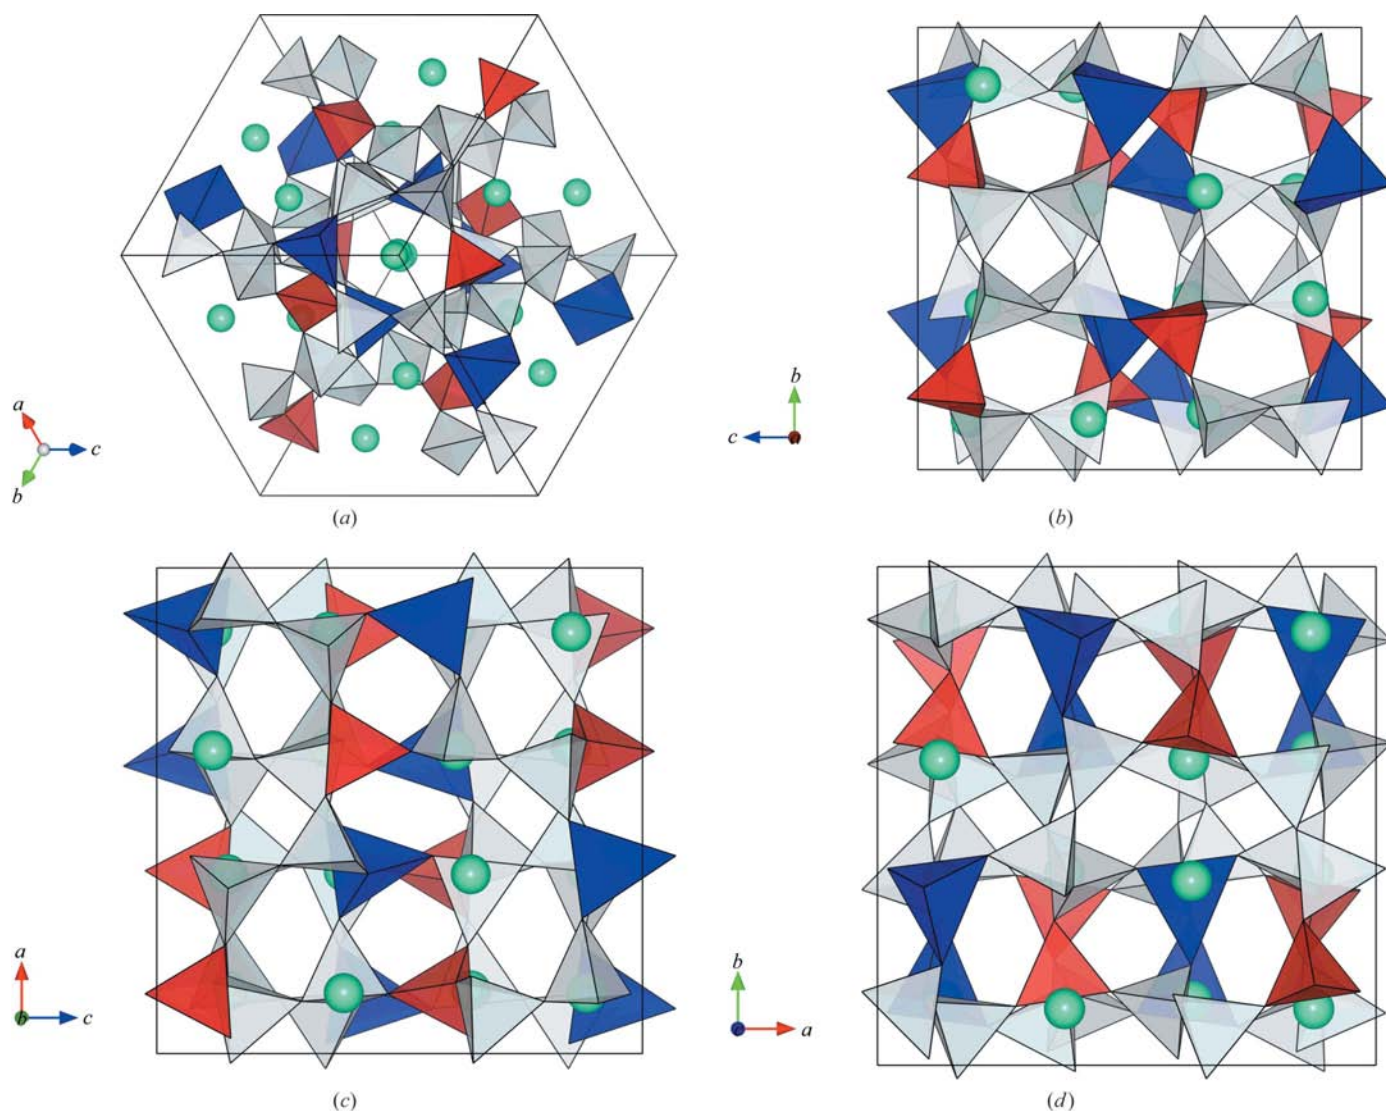


Figure 5

Plot of *Pbca* crystal structure of hydrothermal Cs₂CuSi₅O₁₂. Cs⁺ cations are indicated by light blue circles, CuO₄ by turquoise tetrahedra, Q4Si(4Si) by red tetrahedra and Q4Si(3Si,1Cu) by light grey tetrahedra: (a) down [111]; (b) on (100); (c) on (010); (d) on (001). Crystal structure plots produced using VESTA (Momma & Izumi, 2008).

Table 5

Mean Cs—O and T—O bond distances (Å), O—T—O and T—O—T angles (°) and tetrahedral site (T-site) distortion parameters (deg²) for *Pbca* Cs₂CuSi₅O₁₂ (1σ errors in brackets); T1 = Cu, T2–6 = Si.

| | T—O | O—T—O | T—O—T | T-site distortion index (Robinson <i>et al.</i> , 1971) | T-site NNN connectivity |
|---------------|------------------|-----------------|-----------------|---|-------------------------|
| T1—O | 1.915 (0.042) | 109.6 (12.6) | 130.8 (5.8) | 159.5 | Q4Cu(4Si) |
| T2—O | 1.612 (0.014) | 109.3 (4.4) | 142.1 (11.2) | 19.2 | Q4Si (4Si) |
| T3—O | 1.597 (0.025) | 109.4 (8.0) | 142.5 (11.2) | 64.5 | Q4Si(3Si,1Cu) |
| T4—O | 1.615 (0.019) | 109.3 (6.7) | 137.2 (7.7) | 46.3 | Q4Si (3Si,1Cu) |
| T5—O | 1.628 (0.015) | 109.4 (4.2) | 139.4 (2.1) | 17.4 | Q4Si (3Si,1Cu) |
| T6—O | 1.621 (0.019) | 109.5 (5.1) | 145.6 (13.3) | 26.8 | Q4Si (3Si,1Cu) |
| Mean T(2–6)—O | 1.615 (0.012) | | 141.4 (3.2) | 34.8 (20.2) | |
| Mean Si—O—Si | | | 144.5 (7.3) | | |
| Mean Si—O—Cu | | | 130.8 (5.8) | | |
| Mean Cs1—O | 3.446 (0.295) | | | | |
| Mean Cs2—O | 3.471 (0.299) | | | | |

following powder diffraction instruments: BM16 ($\lambda = 0.354841$ Å) and the Swiss–Norwegian beamline (SNBL; $\lambda = 0.80196$ Å) at the European Synchrotron Radiation Facility and station 9.1 ($\lambda = 0.993773$ Å) of the Daresbury Synchrotron Radiation Source.

2.3.1. Rietveld refinement, hydrothermal sample.

Combined neutron and synchrotron X-ray Rietveld (Rietveld, 1969) refinements were carried out using *GSAS* (Larson & Von Dreele, 2004; Toby, 2001). A first refinement was carried out using the *Pbca* structure of Cs₂CdSi₅O₁₂ (Bell, Redfern *et al.*, 1994) as a starting model with Cu replacing Cd on the ordered T1 tetrahedral site. Si—O distances were restrained to be 1.62 ± 0.02 Å. No other bond lengths or angles were restrained. Chemically sensible, positive isotropic displacement factors were refined for each site; all five silicon sites were constrained to have the same displacement factor and all 12 oxygen sites were constrained to have the same displacement factor. This refinement converged with $R_{wp} = 0.0977$, $R_p = 0.0712$ and $\chi^2 = 5.018$. Bond lengths are given in Tables 1 and 2 and interatomic angles in Tables 3 and 4. Mean bond lengths, angles and distortion parameters for the tetrahedral units are given in Table 5. Fig. 4 shows individual Rietveld difference plots from this refinement and Fig. 5 shows plots of the refined *Pbca* crystal structure for Cs₂CuSi₅O₁₂.¹

In order to assess if the Cu had been placed on the correct T site, refinements in the space group *Pbca* were also carried out with Cu ordered onto each of the other T sites (T2–T6) in

¹ Supplementary data for this paper are available from the IUCr electronic archives (Reference: HW5006). Services for accessing these data are described at the back of the journal.

turn. In each case the isotropic displacement factor for the site containing Cu refined to very large values and those for the sites occupied by Si became negative. As a final test Cu and Si were disordered over the six tetrahedral sites (Si:Cu = 5:1) and the structure was refined with the T—O distance restrained to 1.62 Å. In this refinement the T1—O bond distance increased but those for the other T sites showed little variation. Thus, the refinement carried out using the Cs₂CdSi₅O₁₂ starting model (Cu on T1) has the lowest R factor and is clearly the most reliable *Pbca* structure for our sample of Cs₂CuSi₅O₁₂.

We also refined the crystal structure using the synchrotron and neutron diffraction data sets for our sample of Cs₂CuSi₅O₁₂ using the *P4₁2₁2* model of Heinrich & Baerlocher (1991), again restraining the Si—O distance to 1.62 Å. This refinement eventually converged with $R_{wp} = 0.1318$, $R_p = 0.0957$ and $\chi^2 = 9.233$, but had a negative isotropic displacement factor for the copper site. Based on the quality of fits we believe that the *Pbca* structure model is the correct one for this leucite analogue.

Experimental details for this combined and synchrotron X-ray refinement for the hydrothermal sample are given in Table 6.

Experimental details for this combined and synchrotron X-ray refinement for the hydrothermal sample are given in Table 6.

2.3.2. Rietveld refinement on dry sample. The 2.3 powder data collected on the dry sample could be indexed as a single *Ia $\bar{3}d$* cubic phase similar to the structure of pollucite (Beger, 1969), synthetic leucites Rb₂ZnSi₅O₁₂, CsFeSi₂O₆ and dry-synthesized K₂MgSi₅O₁₂ (Bell & Henderson, 1994*a,b*; Bell, Henderson *et al.*, 1994).

A Rietveld refinement (Rietveld, 1969) was carried out using *GSAS* (Larson & Von Dreele, 2004; Toby, 2001). The *Ia $\bar{3}d$* cubic structure of Rb₂ZnSi₅O₁₂ (Bell & Henderson, 1994*a*) was used as a starting model with Cs replacing Rb as the extra-framework cation and Cu replacing Zn as the disordered framework cation. T—O distances (T = disordered Cu and Si) were restrained to be 1.6625 ± 0.02 Å. No other bond lengths or angles were restrained. Chemically sensible positive isotropic displacement factors were refined for each site; disordered Si and Cu were constrained to have the same displacement factors. This refinement converged with $R_{wp} = 0.1110$, $R_p = 0.0824$ and $\chi^2 = 2.714$. Refined structural parameters for this sample are given in Table 7. Fig. 6(*a*) shows the Rietveld difference plot for this refinement and Fig. 6(*b*) shows a plot of the crystal structure.

Experimental details for this synchrotron X-ray refinement for the dry sample are also given in Table 6.

Table 6

Experimental details.

Column of parameters for the Cs₂CuSi₅O₁₂ hydrothermal synthesized sample is for a combined neutron and synchrotron refinement. Cells in the table are split into four rows corresponding to the four histograms in the GSAS Rietveld refinement. Histogram 1 was for neutron powder data collected on HRPD at ISIS. Histogram 2 was for synchrotron X-ray powder diffraction data collected on the Swiss–Norwegian Beam Line at the ESRF. Histogram 3 was for synchrotron X-ray powder diffraction data collected on BM16 at the ESRF. Histogram 4 was for synchrotron X-ray powder diffraction data collected on station 9.1 at the Daresbury SRS. For the cell labelled ‘*R* factors and goodness of fit’ overall *R* factors are given above those for the four individual histograms.

| | Cs ₂ CuSi ₅ O ₁₂ hydrothermal synthesized | Cs ₂ CuSi ₅ O ₁₂ dry synthesized |
|---|---|--|
| Crystal data | | |
| Chemical formula | Cs ₂ CuO ₁₂ Si ₅ | C ₈ Cu ₄ O ₄₈ Si ₂₀ |
| <i>M_r</i> | 661.77 | 2647.08 |
| Crystal system, space group | Orthorhombic, <i>Pbca</i> | Cubic, <i>Ia$\bar{3}d$</i> |
| <i>a</i> , <i>b</i> , <i>c</i> (Å) | 13.58943 (6), 13.57355 (5), 13.62296 (4) | 13.6322 (4), 13.6322, 13.6322 |
| <i>V</i> (Å ³) | 2512.847 (13) | 2533.4 (2) |
| <i>Z</i> | 8 | 2 |
| Radiation type | Neutron time-of-flight Synchrotron X-ray, $\lambda = 0.80196$ Å Synchrotron X-ray, $\lambda = 0.354841$ Å Synchrotron X-ray, $\lambda = 0.993773$ Å | Synchrotron X-ray, $\lambda = 1.7974$ Å |
| μ (mm ⁻¹) | 0.049915 Unknown –0.59688E-02 0.75240E-03 | N/A flat plate sample |
| Specimen shape, size (mm) | Cylinder 11 mm diameter, height not known Capillary, 0.5 mm diameter Capillary, 0.5 mm diameter Capillary, 40 mm long, 0.7 mm diameter | Flat sheet, 25 × 0.5 |
| Data collection | | |
| Diffraction | In-house design In-house design In-house design In-house design | In-house design |
| Specimen mounting | Vanadium sample can Capillary Capillary Capillary | ‘Silicon flat-plate sample holder’ |
| Data collection mode | Transmission | Reflection |
| Data collection method | Time-of-flight Step Step Step | Step |
| Absorption correction | Debye–Scherrer absorption correction No correction Debye–Scherrer absorption correction Debye–Scherrer absorption correction | No correction |
| No. of measured, independent and observed reflections | Unknown | – |
| 2 θ values (°) | Time of flight 2 $\theta_{\min} = 5.000$, 2 $\theta_{\max} = 40.406$, 2 $\theta_{\text{step}} = 0.002$ 2 $\theta_{\min} = 1.002$, 2 $\theta_{\max} = 45.762$, 2 $\theta_{\text{step}} = 0.003$ 2 $\theta_{\min} = 2.01$, 2 $\theta_{\max} = 80$, 2 $\theta_{\text{step}} = 0.01$ | 2 $\theta_{\min} = 15.02$, 2 $\theta_{\max} = 80$, 2 $\theta_{\text{step}} = 0.01$ |
| Refinement | | |
| <i>R</i> factors and goodness-of-fit | <i>R_p</i> = 0.0712, <i>R_{wp}</i> = 0.0977, $\chi^2 = 5.018$ <i>R_p</i> = 0.0833, <i>R_{wp}</i> = 0.0914, <i>R_{exp}</i> = 0.0285, <i>R</i> (<i>F</i> ²) = 0.17158 <i>R_p</i> = 0.069, <i>R_{wp}</i> = 0.0918, <i>R_{exp}</i> = 0.0614, <i>R</i> (<i>F</i> ²) = 0.0386 <i>R_p</i> = 0.083, <i>R_{wp}</i> = 0.1035, <i>R_{exp}</i> = 0.0444, <i>R</i> (<i>F</i> ²) = 0.0928 <i>R_p</i> = 0.0773, <i>R_{wp}</i> = 0.1088, <i>R_{exp}</i> = 0.0520, <i>R</i> (<i>F</i> ²) = 0.11985 | <i>R_p</i> = 0.0824, <i>R_{wp}</i> = 0.1110, <i>R_{exp}</i> = 0.067, <i>R</i> (<i>F</i> ²) = 0.05163, $\chi^2 = 2.714$ |
| No. of reflections/data points | 3977/6236 257/17704 2956/14921 2850/7800 | 43/6499 |

3. Results and discussion

3.1. Hydrothermally synthesized Cs₂CuSi₅O₁₂

The structural data obtained for hydrothermally synthesized Cs₂CuSi₅O₁₂ based on the four datasets is of a strikingly high quality (owing to the combination of high-resolution synchrotron and neutron data) for a powder diffraction determination with absolute errors of ~ 0.005 Å for individual cation–O bond lengths (relative errors of 0.33% for Si, 0.25% for Cu and 0.2% for Cs). Absolute errors for bond angles are ~ 0.4° (relative errors of 0.4% for O–T–O and 0.3% for T–O–T angles). These errors are ~ 3 to 8 times smaller than previously published powder structural data for leucite bond lengths, and ~ 3–6 times smaller than equivalent bond angles (e.g. Bell, Henderson *et al.*, 1994; Bell & Henderson, 1996; Heinrich & Baerlocher, 1991; Bell & Henderson, 2009). We are confident, therefore, that the data for Cs₂CuSi₅O₁₂ provide a good basis for characterizing the detailed structural properties of Cs-leucite analogues with ordered *T* cations.

Fig. 5 displays the *Pbca* structure of Cs₂CuSi₅O₁₂ projected down [111] (Fig. 5*a*) and down [100], [010] and [001] (Figs. 5*b*, *c* and *d*, respectively). Fig. 5(*a*) shows that the channels in the framework occupied by the large alkali cations are defined by six rings of tetrahedra with Q4Cu(4Si) and Q4Si(4Si) opposite each other and separated by two pairs of connected Q4Si(3Si,1Cu) tetrahedra. The other structure projections show that the framework is built up by linking four and six rings of tetrahedra. The four rings aligned approximately in the (100) plane (shaded grey in Fig. 5*b*) contain only Q4Si(3Si,1Cu) tetrahedra.

Table 6 (continued)

| | Cs ₂ CuSi ₅ O ₁₂ hydrothermal synthesized | Cs ₂ CuSi ₅ O ₁₂ dry synthesized |
|-------------------|--|---|
| No. of parameters | 110 | 20 |
| No. of restraints | 20 | 8 |

Computer programs: local software, *GSAS* (Larson & Von Dreele, 2004), *EXPGUI* (Toby, 2001), *VESTA* (Momma & Izumi, 2008), *enCIFer* (CCDC, 2008).

Table 7

Refined interatomic distances and angles for dry-synthesized Cs₂CuSi₅O₁₂.

T = disordered Cu (occ = 1/6) and Si (occ = 5/6).

| | | | |
|----------|---------------|------------|---------------|
| Cs—O × 6 | 3.363 (5)† | O—T—O | 106.4 |
| Cs—O × 6 | 3.528 (5) | O—T—O | 112.0 (3) × 2 |
| T—O × 2 | 1.631 (4) | O—T—O | 101.3 (4) |
| T—O × 2 | 1.652 (5) | Mean O—T—O | 109.5 |
| O—T—O | 112.6 (3) × 2 | T—O—T | 142.9 (3) |

† Numbers in brackets are 1σ errors in last place(s).

In contrast, the four rings approximately parallel to (010) and (001) (Figs. 5*b* and *c*) contain one CuO₄ tetrahedron (blue) opposite a Q4Si(4Si) tetrahedron (red), separated by Q4Si(3Si,1Cu) tetrahedra. The fact that the CuO₄ tetrahedron is significantly larger than SiO₄ tetrahedra leads to the four rings in Figs. 5(*c*) and (*d*) being more distorted than the almost square, Cu-free, four-rings shown in Fig. 5(*b*) (cf. Cs₂CdSi₅O₁₂; Bell, Redfern *et al.*, 1994).

The mean bond distances and bond angles, and tetrahedral distortion parameters (Robinson *et al.*, 1971) for the *Pbca* structure for Cs₂CuSi₅O₁₂ are given in Table 5. The mean Cs—O bond lengths for both alkali sites are identical within error and average 3.46 Å; this defines the lower end of the range of mean Cs—O distances reported for Cs₂BSi₅O₁₂ leucites with *B* = Mg, Zn, Cd, Mn, Ni and Co (3.46–3.54 Å; Bell *et al.*, 1994; Bell & Henderson, 1996, 2009). The well defined value of 3.46 Å is equivalent to an ionic radius for Cs⁺ of 2.1 Å, which is 10% larger than Shannon's (1976) value of 1.88 Å for 12-coordinated Cs⁺. Note that our value is close to the mean Cs—O distance of 3.48 Å to the 12 closest O atoms for pollucite (Beger, 1969; Palmer *et al.*, 1997).

The mean Cu—O distance of 1.915 Å is equivalent to an ionic radius of 0.565 Å for Cu²⁺ in fourfold coordination matching the value of 0.57 Å given by Shannon (1976). The individual Si—O distances for T₂–T₆ sites cover the range 1.57–1.65 Å and fall just outside the range usually found in silicate structures (1.59–1.63 Å; *International Tables for X-ray Crystallography*, 1985, Vol. III, Table 4.1.1). Based on these more precise data for Cs₂CuSi₅O₁₂ it seems likely that Si—O values reported for other Cs₂BSi₅O₁₂, which are outside this range (e.g. 1.51 and 1.67 Å in Cs₂CdSi₅O₁₂; Bell, Redfern *et al.*, 1994) are likely to reflect higher experimental errors.

The CuO₄ tetrahedron has a significantly higher O—T—O tetrahedral angle variance (160 deg², Table 5; Robinson *et al.*, 1971) than those for BO₄ tetrahedra in other Cs₂BSi₅O₁₂ leucites, but this relationship is not simply related to ionic size [cf. Cd 94 (Bell, Redfern *et al.*, 1994); Mn 58, Co 60, Ni 47 (Bell

& Henderson, 1996); Mg 80 deg² (Bell & Henderson, 2009)]. The O—T—O angle variance for the CuO₄ tetrahedron is also substantially higher than the variances for all the SiO₄ tetrahedra in Cs₂CuSi₅O₁₂ leucite [range 17.4–64.5 deg² (mean

34.8), Table 5], which is opposite the relationships found for other Cs 3*d* transition-element (Mn, Co, Ni) leucites (Bell & Henderson, 1996). Based on the higher quality of the data for Cs₂CuSi₅O₁₂ leucite, especially where neutron diffraction data will define the positions of O atoms more reliably than X-ray methods, it seems likely that our earlier determinations suggesting that SiO₄ tetrahedra are more distorted than BO₄ tetrahedra are likely to be in error.

The mean Si—O—Si angle for Cs₂CuSi₅O₁₂ has a larger value (144.5°) than that for Si—O—Cd (130.8°) and this is the same relationship found for other Cs₂BSi₅O₁₂ leucites: *i.e.* for *B* = Cd (147 and 127°); Mn (137, 133°); Co (137, 135°); Ni (142, 134°); and for Mg (146, 143°). In all cases *B*—O distances are larger than those for Si—O and Si—O—*B* angles are smaller than Si—O—Si angles. In addition, the largest mean *B*—O

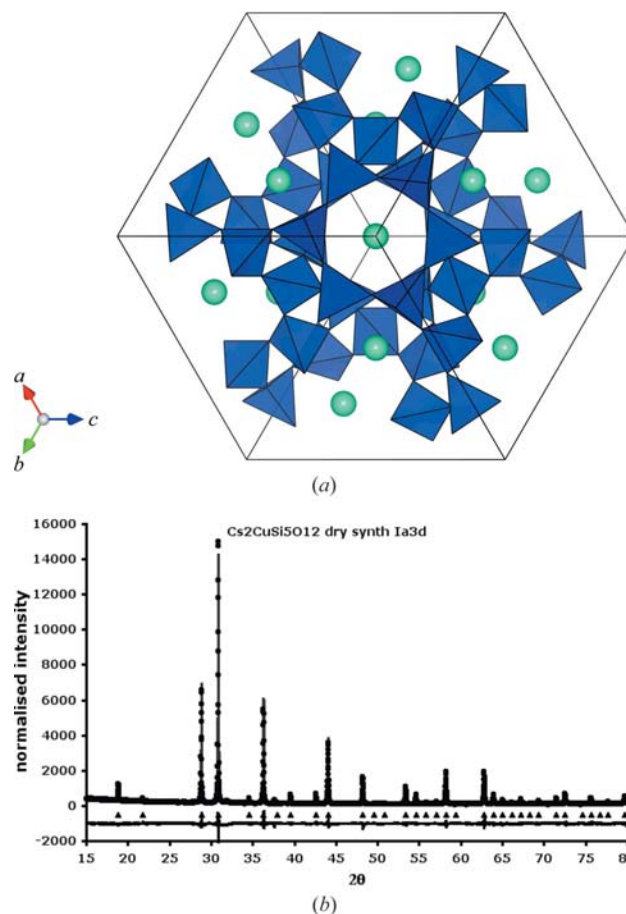


Figure 6
(a) Rietveld difference plot for dry-synthesized Cs₂CuSi₅O₁₂. Crystal structure plots produced using *VESTA* (Momma & Izumi, 2008). (b) Plot of *Iα3d* crystal structure down [111].

distance ($\text{Cd}-\text{O} = 2.24 \text{ \AA}$) has the smallest $T-\text{O}-T$ (127°) and the smallest $B-\text{O}$ ($\text{Mg}-\text{O} = 1.87 \text{ \AA}$) has the largest $T-\text{O}-T$ (143°). These trends are in agreement with the inverse relationship between mean $T-\text{O}$ bond length and mean $T-\text{O}-T$ angle shown by framework silicates (Hill & Gibbs, 1979).

3.2. Dry synthesized $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$

The refined crystal structure for the dry-synthesized $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ sample is similar to that for other $Ia\bar{3}d$ leucites with disordered T -site cations. It should be noted that the unit-cell volume for this disordered polymorph [$V = 2533.4$ (2) \AA^3] is larger than the unit-cell volume for the ordered hydrothermally synthesized polymorph [$V = 2512.85$ (1) \AA^3]. A similar effect was observed in $\text{K}_2\text{MgSi}_5\text{O}_{12}$ [Bell, Henderson *et al.*, 1994; dry sample has $V = 2416.33$ (5) \AA^3 , and hydrothermal sample $V = 2348$ (2) \AA^3]. The structures with the ordered cations have more collapsed tetrahedral frameworks and hence smaller unit-cell volumes. As expected, the larger framework collapse for $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ is reflected in the mean $T-\text{O}-T$ angle for the hydrothermal sample (139.9°) being smaller than that for the less-collapsed dry sample (142.9°); this is the same relationship as in $\text{K}_2\text{MgSi}_5\text{O}_{12}$ leucites with values of 137.4 and 144.5° (Bell, Henderson *et al.*, 1994).

4. Conclusions

Rietveld refinement of high resolution, neutron and synchrotron X-ray powder diffraction data for a sample of hydrothermally synthesized $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ shows that its crystal structure can be better described by the $Pbca$ structure rather than by the $P4_12_12$ structure of Heinrich & Baerlocher (1991), which has a much more complicated tetrahedral framework topology. Thus, the tetrahedral cations in $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ are fully ordered on six T sites, in agreement with the structures of $Pbca$ leucites of varying compositions and consistent with the structure of monoclinic $P2_1/c$ leucites with 12 T sites (e.g. $\text{K}_4\text{Mg}_2\text{Si}_{10}\text{O}_{24}$), which show displacive transitions to $Pbca$ polymorphs at elevated temperature. This conclusion follows the famous Ockham's razor dictum 'pluralitas non est ponenda sine necessitate'.

Finally, we note that the space group $Pbca$ allows a hypothetical phase transition to the cubic space group $Pa\bar{3}$ at higher temperature. Unlike the phase transition from $P2_1/c$ to $Pbca$, a structural phase transition to $Pa\bar{3}$ from $Pbca$ is not permitted to be continuous through either Landau theory or renormalization-group theory (Stokes & Hatch, 1988) and requires the ordered divalent tetrahedral site to become disordered in the cubic space group. We have generated a possible starting model for such a phase using distance least-squares modelling (Baerlocher *et al.*, 1977); this model structure has two independent Cs sites, two independent T sites (disordered Cu and Si) and four independent O sites.

Rietveld refinement of synchrotron X-ray powder diffraction data for a sample of dry synthesized $\text{Cs}_2\text{CuSi}_5\text{O}_{12}$ shows

that the structure can be described by the $Ia\bar{3}d$ pollucite structure. In this structure Cu and Si are disordered over the T sites. A high-temperature crystallographic study carried out using high-resolution powder diffraction to assess whether T -site disordering might be associated with a phase transition to either $Pa\bar{3}$ or $Ia\bar{3}d$ would be worthwhile.

We wish to acknowledge the use of the Chemical Database Service at Daresbury (Fletcher *et al.* 1996) and thank John Charnock for carrying out the electron microprobe analysis.

References

- Baerlocher, C., Hepp, A. & Meier, W. M. (1977). DLS-76, <http://www.crystal.mat.ethz.ch/Software>.
- Beger, R. M. (1969). *Z. Kristallogr.* **129**, 280–302.
- Bell, A. M. T. & Henderson, C. M. B. (1994a). *Acta Cryst.* **C50**, 984–986.
- Bell, A. M. T. & Henderson, C. M. B. (1994b). *Acta Cryst.* **C50**, 1531–1536.
- Bell, A. M. T. & Henderson, C. M. B. (1996). *Acta Cryst.* **C52**, 2132–2139.
- Bell, A. M. T. & Henderson, C. M. B. (2009). *Acta Cryst.* **B65**, 435–444.
- Bell, A. M. T., Henderson, C. M. B., Redfern, S. A. T., Cernik, R. J., Champness, P. E., Fitch, A. N. & Kohn, S. C. (1994). *Acta Cryst.* **B50**, 31–41.
- Bell, A. M. T., Redfern, S. A. T., Henderson, C. M. B. & Kohn, S. C. (1994). *Acta Cryst.* **B50**, 560–566.
- CCDC (2005). *enCIFer*. Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge, England.
- Cernik, R. J., Murray, P. K., Pattison, P. & Fitch, A. N. (1990). *J. Appl. Cryst.* **23**, 292–296.
- Collins, S. P., Cernik, R. J., Pattison, P., Bell, A. M. T. & Fitch, A. N. (1992). *Rev. Sci. Instrum.* **63**, 1013–1014.
- Fletcher, D. A., McMeeking, R. F. & Parkin, D. J. (1996). *Chem. Inf. Comput. Sci.* **36**, 746–749.
- Heinrich, A. R. & Baerlocher, Ch. (1991). *Acta Cryst.* **C47**, 237–241.
- Henderson, C. M. B., Bell, A. M. T., Kohn, S. C. & Page, C. S. (1998). *Mineral. Mag.* **62**, 165–178.
- Hill, R. J. & Gibbs, G. V. (1979). *Acta Cryst.* **B35**, 25–30.
- Kamiya, N., Nishi, K. & Yokomori, Y. (2008). *Z. Kristallogr.* **223**, 584–590.
- Larson, A. C. & Von Dreele, R. B. (2004). *GSAS*, Report LAUR 86–748. Los Alamos National Laboratory, New Mexico, USA.
- Mazzi, F., Galli, E. & Gottardi, G. (1976). *Am. Mineral.* **61**, 108–115.
- Momma, K. & Izumi, F. (2008). *J. Appl. Cryst.* **41**, 653–658.
- Palmer, D. C., Dove, M. T., Ibberson, R. M. & Powell, B. M. (1997). *Am. Mineral.* **82**, 16–29.
- Redfern, S. A. T. & Henderson, C. M. B. (1996). *Am. Mineral.* **81**, 369–374.
- Robinson, K., Gibbs, G. V. & Ribbe, P. H. (1971). *Science*, **172**, 567–570.
- Rietveld, H. M. (1969). *J. Appl. Cryst.* **2**, 65–71.
- Shannon, R. D. (1976). *Acta Cryst.* **A32**, 751–767.
- Stokes, H. T. & Hatch, D. M. (1988). *Isotropy Subgroups of the 230 Crystallographic Space Groups*. Singapore: World Scientific.
- Taylor, D. & Henderson, C. M. B. (1968). *Am. Mineral.* **53**, 1476–1489.
- Toby, B. H. (2001). *J. Appl. Cryst.* **34**, 210–213.
- Torres-Martinez, L. M. & West, A. R. (1986). *Z. Kristallogr.* **175**, 1–7.
- Torres-Martinez, L. M. & West, A. R. (1989). *Z. Anorg. Allg. Chem.* **573**, 223–230.
- Wyart, M. J. (1940). *Bull. Soc. Miner. Crist.* **63**, 5–17.