

**Sr<sub>3</sub>ZnPtO<sub>6</sub> and Sr<sub>3</sub>CdPtO<sub>6</sub>**

Mark D. Smith and Hans-Conrad zur Loye\*

Department of Chemistry and Biochemistry, University of South Carolina, Columbia,  
South Carolina 29208, USA  
Correspondence e-mail: zurloye@sc.edu

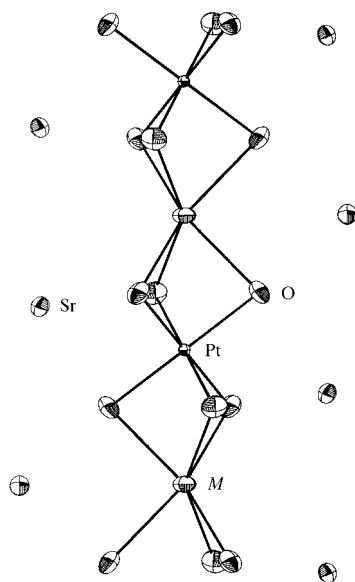
Received 6 September 2000

Accepted 11 December 2000

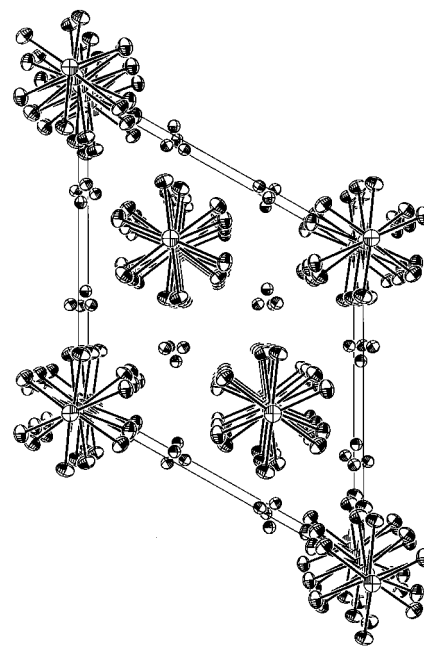
The flux synthesis of single crystals of the isostructural compounds tristrontium zinc platinum hexaoxide, Sr<sub>3</sub>ZnPtO<sub>6</sub>, and tristrontium cadmium platinum hexaoxide, Sr<sub>3</sub>CdPtO<sub>6</sub>, is reported. The compounds adopt the pseudo-one-dimensional rhombohedral K<sub>4</sub>CdCl<sub>6</sub> structure type, and feature chains of face-shared distorted ZnO<sub>6</sub> or CdO<sub>6</sub> trigonal prisms and PtO<sub>6</sub> octahedra, surrounded by columns of Sr<sup>2+</sup> ions. All transition metals are located on the threefold axis of symmetry, while the Sr<sup>2+</sup> cations lie on twofold axes.

**Comment**

Interest in detailed structural and magnetic measurements on oxides adopting the K<sub>4</sub>CdCl<sub>6</sub> structure type (Bergerhoff & Schmitz-Dumont, 1956) has been great during recent years, mostly due to the low-dimensional nature and compositional flexibility of this large class of oxides. Though the work to date has involved predominantly powder studies, a few single-crystal studies of platinates of this type have been reported, beginning with Sr<sub>4</sub>PtO<sub>6</sub> in 1959 (Randall & Katz, 1959) and

**Figure 1**

A section of the face-shared MPtO<sub>6</sub> (*M* is Zn or Cd) chains in the title compounds. Displacement ellipsoids are drawn (*M* = Cd) at the 80% probability level.

**Figure 2**

A view of Sr<sub>3</sub>MPtO<sub>6</sub> (*M* is Zn or Cd) along [001].

including Sr<sub>3</sub>CuPtO<sub>6</sub> (Wilkinson *et al.*, 1991), Sr<sub>3</sub>NiPtO<sub>6</sub> (Nguyen *et al.*, 1997) and Ca<sub>4</sub>PtO<sub>6</sub> (Claridge *et al.*, 1997). During the course of investigations into preparing single crystals of compositions related to Sr<sub>3</sub>MPtO<sub>6</sub>, we have grown single crystals of Sr<sub>3</sub>ZnPtO<sub>6</sub>, (I), and Sr<sub>3</sub>CdPtO<sub>6</sub>, (II), from potassium hydroxide fluxes at high temperatures, employing the Pt<sup>4+</sup>-containing precursor (NH<sub>4</sub>)<sub>2</sub>PtCl<sub>6</sub>. While (I) has been determined previously by X-ray powder diffraction (Lampe-Önnerud & zur Loye, 1996), (II) has not been reported.

The structures of the title compounds consist of chains of slightly distorted face-shared ZnO<sub>6</sub> [in (I)] or CdO<sub>6</sub> [in (II)] trigonal prisms which alternate with rhombohedrally elongated PtO<sub>6</sub> octahedra along [001] (Fig. 1). The distortion of the trigonal prisms consists of a rotation of the opposite triangular faces away from ideal eclipsed geometry [12.3° for (I) and 13.6° for (II)]. The chains are surrounded by six spiral columns of Sr<sup>2+</sup> ions, and the Sr<sup>2+</sup> columns are in turn surrounded by three polyhedral chains (Fig. 2). The Sr<sup>2+</sup> ions occupy an irregular eight-coordinate position, just off the threefold axis on a position of site symmetry 2.

The Zn—O bond distance in (I) is essentially identical to the value determined previously from powder data [2.199 (4) Å; Lampe-Önnerud & zur Loye, 1996]. The Cd—O distance in (II) also agrees with the few known bond lengths for Cd in a trigonal prismatic coordination, *i.e.* 2.302 (6) Å in Sr<sub>3</sub>CdIrO<sub>6</sub> (Segal *et al.*, 1996) and 2.338 (4) Å in Sr<sub>3</sub>CdRhO<sub>6</sub> (Smith & zur Loye, 2000). The Pt—O distances (Tables 1 and 2) in both compounds are typical of octahedral Pt<sup>4+</sup> in platinates.

**Experimental**

(NH<sub>4</sub>)<sub>2</sub>PtCl<sub>6</sub> was prepared according to Kaufman (1967). Subsequently, SrCO<sub>3</sub> (Alfa, 99.95%), ZnO (Alfa, 99.99%) or CdO (Alfa, 99.99%), and (NH<sub>4</sub>)<sub>2</sub>PtCl<sub>6</sub> (stoichiometric amounts, *ca* 1 g total reagent mass) and KOH (Fisher, reagent grade; ~10 times by mass the total reagent amount) were loaded into a covered alumina

**Table 1**

Selected geometric parameters (Å) for (I).

Sr—O <sup>i</sup>	2.476 (4) × 2	Zn—O	2.200 (4) × 6
Sr—O <sup>ii</sup>	2.645 (4) × 2	Zn—Pt	2.8073 (3) × 2
Sr—O <sup>iii</sup>	2.668 (4) × 2	Pt—O	2.029 (4) × 6
Sr—O <sup>iv</sup>	2.718 (4) × 2		

 Symmetry codes: (i)  $-x + y, -x, z$ ; (ii)  $\frac{2}{3} + x - y, \frac{1}{3} + x, \frac{1}{3} - z$ ; (iii)  $\frac{2}{3} - y, \frac{1}{3} + x - y, \frac{1}{3} + z$ ; (iv)  $\frac{2}{3} - x, \frac{1}{3} - y, \frac{1}{3} - z$ .

crucible. The mixture was heated at 1273 K for 2 h and cooled to 1023 K at a rate of 1 K h<sup>-1</sup>, at which point the furnace was shut off and allowed to cool radiatively to room temperature. The KOH matrix was dissolved with distilled water, leaving numerous blue-green hexagonal prisms and less abundant brown crystals with a rhombohedral habit. Both morphologies were determined to be rhombohedral Sr<sub>3</sub>MPTiO<sub>6</sub> by powder X-ray diffraction. However, all of the blue-green hexagonal rods displayed obverse-reverse rhombohedral twinning, and therefore the brown crystals were selected for analysis.

## Compound (I)

### Crystal data

Sr <sub>3</sub> ZnPtO <sub>6</sub>	Mo K $\alpha$ radiation
$M_r = 619.32$	Cell parameters from 823 reflections
Trigonal, $R\bar{3}c$	$\theta = 4.23\text{--}36.20^\circ$
$a = 9.6267 (7) \text{ \AA}$	$\mu = 53.564 \text{ mm}^{-1}$
$c = 11.2292 (11) \text{ \AA}$	$T = 293 (2) \text{ K}$
$V = 901.23 (13) \text{ \AA}^3$	Fragment, brown
$Z = 6$	$0.11 \times 0.05 \times 0.03 \text{ mm}$
$D_x = 6.847 \text{ Mg m}^{-3}$	

### Data collection

Bruker SMART APEX CCD diffractometer	493 independent reflections
$\omega$ scans	$R_{\text{int}} = 0.045$
Absorption correction: multi-scan (SADABS; Bruker, 1999)	$\theta_{\text{max}} = 36.32^\circ$
$T_{\text{min}} = 0.054, T_{\text{max}} = 0.211$	$h = -13 \rightarrow 15$
2881 measured reflections	$k = -13 \rightarrow 15$
	$l = -18 \rightarrow 17$

### Refinement

Refinement on $F^2$	$w = 1/[\sigma^2(F_o^2) + (0.0272P)^2]$
$R[F^2 > 2\sigma(F^2)] = 0.029$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.059$	$(\Delta/\sigma)_{\text{max}} < 0.001$
$S = 0.981$	$\Delta\rho_{\text{max}} = 6.49 \text{ e \AA}^{-3}$
493 reflections	$\Delta\rho_{\text{min}} = -4.57 \text{ e \AA}^{-3}$
20 parameters	Extinction correction: SHELXL97
	Extinction coefficient: 0.00027 (5)

## Compound (II)

### Crystal data

Sr <sub>3</sub> CdPtO <sub>6</sub>	Mo K $\alpha$ radiation
$M_r = 666.35$	Cell parameters from 1517 reflections
Trigonal, $R\bar{3}c$	$\theta = 4.23\text{--}36.22^\circ$
$a = 9.6413 (4) \text{ \AA}$	$\mu = 51.286 \text{ mm}^{-1}$
$c = 11.5935 (7) \text{ \AA}$	$T = 293 (2) \text{ K}$
$V = 933.29 (8) \text{ \AA}^3$	Chunk, brown
$Z = 6$	$0.09 \times 0.04 \times 0.03 \text{ mm}$
$D_x = 7.114 \text{ Mg m}^{-3}$	

### Data collection

Bruker SMART APEX CCD diffractometer	505 independent reflections
$\omega$ scans	$R_{\text{int}} = 0.036$
Absorption correction: multi-scan (SADABS; Bruker, 1999)	$\theta_{\text{max}} = 36.35^\circ$
$T_{\text{min}} = 0.091, T_{\text{max}} = 0.360$	$h = -15 \rightarrow 8$
2632 measured reflections	$k = -16 \rightarrow 15$
	$l = -19 \rightarrow 9$

**Table 2**

Selected geometric parameters (Å) for (II).

Sr—O <sup>i</sup>	2.529 (4) × 2	Cd—O	2.328 (4) × 6
Sr—O <sup>ii</sup>	2.622 (4) × 2	Cd—Pt	2.89837 (18) × 2
Sr—O <sup>iii</sup>	2.635 (4) × 2	Pt—O	2.039 (4) × 6
Sr—O <sup>iv</sup>	2.739 (4) × 2		

 Symmetry codes: (i)  $-x + y, -x, z$ ; (ii)  $\frac{2}{3} + x - y, \frac{1}{3} + x, \frac{1}{3} - z$ ; (iii)  $\frac{2}{3} - y, \frac{1}{3} + x - y, \frac{1}{3} + z$ ; (iv)  $\frac{2}{3} - x, \frac{1}{3} - y, \frac{1}{3} - z$ .

### Refinement

Refinement on $F^2$	$w = 1/[\sigma^2(F_o^2) + (0.0463P)^2 + 3.1434P]$
$R[F^2 > 2\sigma(F^2)] = 0.030$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.072$	$(\Delta/\sigma)_{\text{max}} < 0.001$
$S = 1.086$	$\Delta\rho_{\text{max}} = 5.05 \text{ e \AA}^{-3}$
505 reflections	$\Delta\rho_{\text{min}} = -3.56 \text{ e \AA}^{-3}$
19 parameters	

Systematic absences in the data sets for both compounds confirmed a  $c$  glide operation, indicating the space groups  $R\bar{3}c$  and  $R\bar{3}c$ . Preliminary powder X-ray diffraction showed the compounds to be isostructural with K<sub>4</sub>CdCl<sub>6</sub> (space group  $R\bar{3}c$ ); therefore, the expected centrosymmetric space group was chosen and confirmed by the solution. The largest difference peaks were both located less than 0.8 Å from the Zn and Cd atoms. The relatively large values of  $\Delta\rho_{\text{max}}$  in the vicinity of Zn<sup>I</sup> and Cd<sup>II</sup> suggest a small fraction of these atoms may be located off the threefold axis. However, refinement of the Zn or Cd site-occupancy factors for each structure did not lead to a significant deviation from unity and refinements including off-axis contributions were unstable.

For both compounds, data collection: SMART (Bruker, 1999); cell refinement: SAINT (Bruker, 1999); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 1997); program(s) used to refine structure: SHELXL97 (Sheldrick, 1997); molecular graphics: SHELXTL (Bruker, 1999).

Funding was provided by the National Science Foundation through grant DMR:9873570. The Bruker SMART APEX diffractometer was purchased using funds provided by the NSF IMR Program through grant DMR:9975623.

Supplementary data for this paper are available from the IUCr electronic archives (Reference: BR1306). Services for accessing these data are described at the back of the journal.

## References

- Bergerhoff, G. & Schmitz-Dumont, O. (1956). *Z. Anorg. Allg. Chem.* **284**, 10–19.
- Bruker (1999). SMART (Version 5.611), SAINT (Version 6.02a), SHELXTL (Version 5.10) and SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.
- Claridge, J. B., Layland, R. C. & zur Loye, H.-C. (1997). *Acta Cryst.* **C53**, 1740–1741.
- Kaufman, G. S. (1967). *Inorganic Syntheses*, Vol. 9, edited by S. Y. Tyree Jr, pp. 182–185. New York: McGraw-Hill.
- Lampe-Önnerud, C. & zur Loye, H.-C. (1996). *Inorg. Chem.* **35**, 2155–2156.
- Nguyen, T. N., Giaquinta, D. M. & zur Loye, H.-C. (1997). *Chem. Mater.* **6**, 1642–1646.
- Randall, J. J. Jr & Katz, L. (1959). *Acta Cryst.* **12**, 519–521.
- Segal, N., Vente, J. F., Bush, T. S. & Battle, P. D. (1996). *J. Mater. Chem.* **6**, 395–401.
- Sheldrick, G. M. (1997). SHELXS97 and SHELXL97. University of Göttingen, Germany.
- Smith, M. D. & zur Loye, H.-C. (2000). Unpublished results.
- Wilkinson, A. P., Cheetham, A. K., Kunman, W. & Kvik, A. (1991). *Eur. J. Solid State Inorg. Chem.* **28**, 453–459.