

**Eu<sub>1.8</sub>La<sub>0.2</sub>BaZnO<sub>5</sub>: a Rietveld refinement using X-ray powder diffraction**José Apuleyo Hernández-Pérez,<sup>a</sup>  
María-Elena Villafuerte-  
Castrejón<sup>a\*</sup> and Lauro Bucio<sup>b</sup><sup>a</sup>Instituto de Investigaciones en Materiales,  
Universidad Nacional Autónoma de México,  
AP 70-360, 04510 México, DF, Mexico, and<sup>b</sup>Instituto de Física, Universidad Nacional  
Autónoma de México, AP 20-364, 01000  
México, DF, MexicoCorrespondence e-mail:  
mevc@servidor.unam.mx

The families of oxides with stoichiometry  $RE_2BaMO_5$  (where  $RE$  is a trivalent rare earth, and  $M$  is  $Co^{2+}$ ,  $Ni^{2+}$ ,  $Cu^{2+}$ ,  $Zn^{2+}$ ,  $Pd^{2+}$  or  $Pt^{2+}$ ) are known as the green phases in studies of Y–Ba–Cu–O superconductor ceramics. These oxides are not superconductors but nevertheless present interesting structural types. In this work, the synthesis and structural characterization using the Rietveld method applied to X-ray powder diffraction data for  $Eu_{1.8}La_{0.2}BaZnO_5$  (europium lanthanum barium zinc oxide) are presented. The compound is isostructural with  $Y_2BaZnO_5$ . The two sites for  $Y^{3+}$  are occupied by  $Eu^{3+}$ , while  $La^{3+}$  ions partially occupy one of these sites.

Received 17 January 2005

Accepted 26 January 2005

Online 5 February 2005

**Key indicators**


Powder X-ray study

 $T = 300\text{ K}$ Mean  $\sigma(Zn-O) = 0.014\text{ \AA}$  $R$  factor = 0.091 $wR$  factor = 0.12


Data-to-parameter ratio = 23.3

For details of how these key indicators were  
automatically derived from the article, see  
<http://journals.iucr.org/e>.**Comment**

$Eu_2BaZnO_5$  belongs to the family of mixed oxides with general stoichiometry  $RE_2BaMO_5$ , in which four different structural types are possible depending on the  $RE^{3+}$  and/or  $M^{2+}$  ions present in the crystal structure. Each of them is characterized by different coordination polyhedra around the  $M^{2+}$  cation (Burdett & Mitchell, 1990; Saez-Puche & Hernandez-Velazco, 1994; Lavat *et al.*, 1992). For type I ( $Sm_2BaCuO_5$  type), the  $M^{2+}$  ions form isolated  $MO_5$  square-pyramidal units in an orthorhombic unit cell, space group  $Pnma$ , and  $Z = 4$ . For type II ( $Nd_2BaNiO_5$  type), the  $M^{2+}$  ions form infinite chains of  $MO_6$  octahedra, running parallel to the  $a$  axis and also with an orthorhombic unit cell, with space group  $Immm$  and  $Z = 2$ . In the case of type III ( $Nd_2BaPtO_5$  type), the symmetry is tetragonal, space group  $P4/mbm$ ,  $Z = 2$ , in which  $M^{2+}$  ions are in isolated  $MO_4$  square-planar environments. For the last type, type IV ( $Nd_2BaZnO_5$  type), the symmetry is also tetragonal, with space group  $I4/mcm$  and  $Z = 4$ . In that structure, the  $M^{2+}$  ions are in isolated  $MO_4$  tetra-

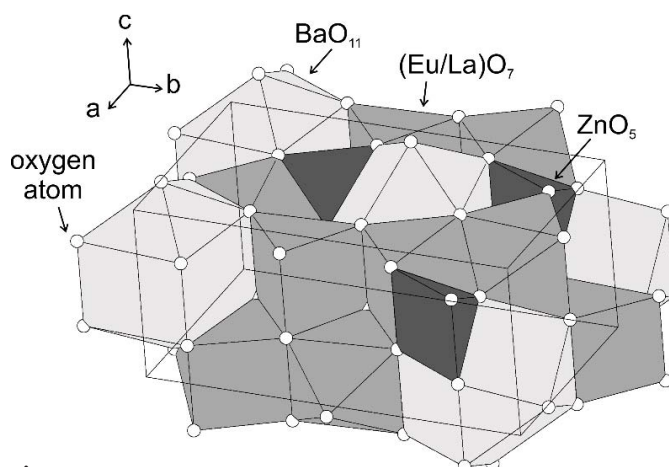

**Figure 1**  
The unit-cell contents of  $Eu_{1.8}La_{0.2}BaZnO_5$ .

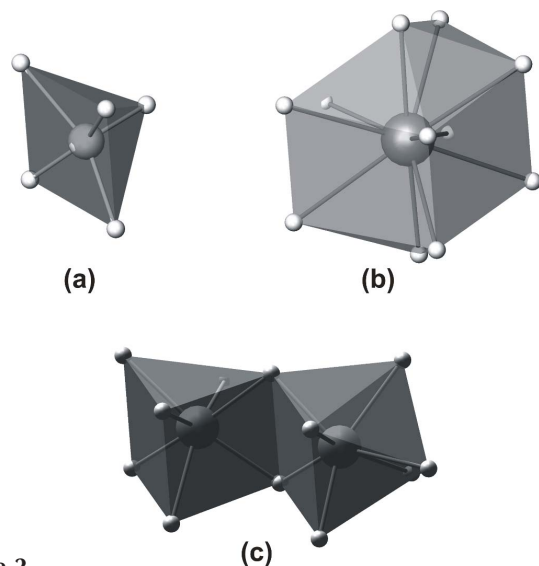


**Figure 2**  
The coordination polyhedra present in  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$ . (a)  $\text{ZnO}_5$ , distorted square-based pyramid. (b)  $\text{BaO}_{11}$ , a type of distorted tricapped quadrangular prism. (c)  $\text{EuO}_7$  and  $\text{Eu/LaO}_7$  non-equivalent distorted monocapped quadrangular prisms.

hedra. Due to their structural features and interesting properties, this family of compounds has previously been studied and characterized. However, no report exists to date on the crystallographic characterization of the solid solution of  $\text{Eu}_2\text{BaZnO}_5$  with  $\text{La}^{3+}$ , which we report here for the case of  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$ .

The replacement mechanism seems to be given by  $\text{Eu}^{3+} \longleftrightarrow \text{La}^{3+}$ . According to this mechanism, the solid solution has the formula  $\text{Eu}_{2-x}\text{La}_x\text{BaZnO}_5$  with  $0 < x < 0.3$ . The solubility range is small, taking into account our preliminary X-ray diffraction analysis: the cell parameters for  $x = 0, 0.2$  and  $0.3$  decrease with  $x$  content, following Vegard's law.

The crystal structure of  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  is shown in Fig. 1, which also shows a view of the unit-cell contents. The introduction of the  $\text{La}^{3+}$  ions generates changes in the unit-cell parameters compared with the data reported by Kaduk *et al.* (1999) for  $\text{Eu}_2\text{BaZnO}_5$ :  $a = 7.1789$  (1) Å,  $b = 12.53575$  (17) Å,  $c = 5.79103$  (8) Å and  $V = 521.15$  Å<sup>3</sup> (Kaduk *et al.*, 1999); parameters from the present work for  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$ :  $a = 7.1952$  (1) Å,  $b = 12.5720$  (2) Å,  $c = 5.8035$  (1) Å and  $V = 524.97$  (1) Å<sup>3</sup>.

The structure of  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  exhibits three different coordination polyhedra, namely a distorted square-based pyramidal  $\text{ZnO}_5$  (Fig. 2a), a type of distorted tricapped quadrangular prismatic  $\text{BaO}_{11}$ , in which Ba ions are surrounded by 11 O atoms (Fig. 2b), and two non-equivalent distorted monocapped trigonal prisms (Fig. 2c), one of them completely occupied by  $\text{Eu}^{3+}$  (the  $\text{EuO}_7$  polyhedron) and the other with partial substitution of  $\text{La}^{3+}$  ions (the  $\text{Eu/LaO}_7$  polyhedron). This last fact can be supported by the following observations. The average bond distance for  $\text{EuO}_7$  polyhedra is 2.35 Å, very close to the sum of the ionic radii reported by Shannon (1976) ( $r_{\text{Eu}} + r_{\text{O}} = 1.01 + 1.38 = 2.39$  Å). In the second monocapped trigonal prism,  $\text{Eu/LaO}_7$ , the average bond is

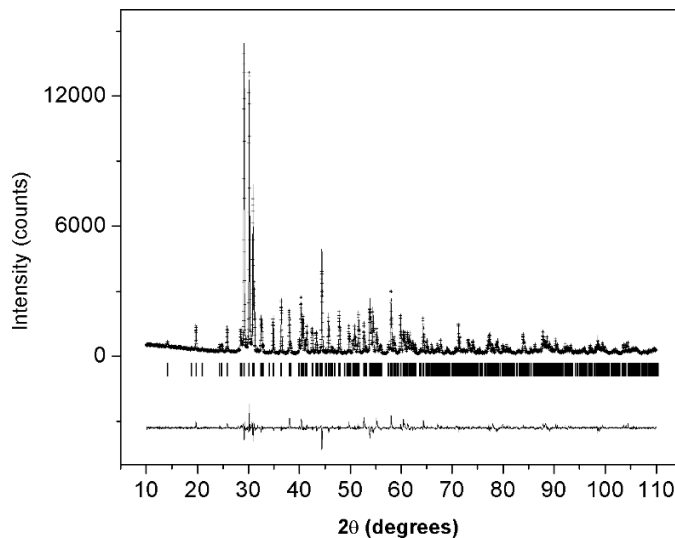

**Figure 3**  
A comparison of observed (cross symbols) and calculated (solid line) intensities for  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$ . The difference pattern appears below. The Bragg peak positions for  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  and  $\text{PtO}_2$  are represented as vertical marks.

longer (2.38 Å). This distortion is due to the incorporation of the  $\text{La}^{3+}$  ions on this site. In the same way, the average bond distances found in  $\text{BaO}_{11}$  and  $\text{ZnO}_5$  polyhedra fit reasonably well with the sum of their ionic radii: mean  $\text{Ba}-\text{O} = 3.08$  Å, compared with  $r_{\text{Ba}} + r_{\text{O}} = 2.95$  Å, and mean  $\text{Zn}-\text{O} = 2.07$  Å, compared with  $r_{\text{Zn}} + r_{\text{O}} = 2.06$  Å. These average bond distances are similar to those reported for  $\text{Eu}_2\text{BaZnO}_5$  by Kaduk *et al.* (1999).

## Experimental

The title compound was synthesized by a solid-state reaction. Stoichiometric quantities of 0.6093, 0.4595, 2.7834 and 1.1478 g for the starting reactants  $\text{Eu}_2\text{O}_3$  (99.99%, Aldrich),  $\text{La}_2\text{O}_3$  (99.99%, Aldrich),  $\text{BaCO}_3$  (99.99%, Aldrich) and  $\text{ZnO}$  (99.99%, Aldrich), respectively, with a total weight of 5 g, were mixed with acetone for at least 10 min and then powdered in an agate mortar. The powder was heated for a few hours in air at 973 K using a platinum crucible in order to expel  $\text{CO}_2$ . Finally, the compound was fired at 1473 K for 2–3 d. Because  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  can be easily hydrated, it was kept in a desiccator.

### Crystal data

$\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$   
 $M_r = 584.03$   
 Orthorhombic, *Pbnm*  
 $a = 7.1952$  (1) Å  
 $b = 12.5720$  (2) Å  
 $c = 5.8035$  (1) Å  
 $V = 524.97$  (1) Å<sup>3</sup>  
 $Z = 4$   
 $D_x = 7.4$  (1) Mg m<sup>-3</sup>

Cu  $K\alpha$  radiation  
 $\mu = 226.2$  mm<sup>-1</sup>  
 $T = 300$  K  
 Specimen shape: flat sheet  
 $20 \times 20 \times 0.2$  mm  
 Specimen prepared at 1473 K  
 Particle morphology: homogeneous  
 micrometric particles, pale yellow

### Data collection

Siemens D5000 diffractometer  
 Specimen mounting: packed powder  
 sample container  
 Specimen mounted in reflection  
 mode

$h = 0 \rightarrow 9$   
 $k = 0 \rightarrow 16$   
 $l = 0 \rightarrow 7$   
 $2\theta_{\text{min}} = 10, 2\theta_{\text{max}} = 110^\circ$   
 Increment in  $2\theta = 0.02^\circ$

## Refinement

Refinement on  $I_{\text{net}}$  $R_p = 0.091$  $R_{\text{wp}} = 0.12$  $R_B = 0.071$  $S = 1.67$  $2\theta_{\text{min}} = 10.0248$ ,  $2\theta_{\text{max}} = 110.0248^\circ$ Increment in  $2\theta = 0.02^\circ$ Profile function: pseudo-Voigt,  
modified by Thompson *et al.*  
(1987)

791 reflections

34 parameters

Weighting scheme based on  
measured s.u. valuesPreferred orientation correction:  
none

Table 1

Selected bond lengths (Å).

Eu1—O1	2.28 (2)	Ba—O1 <sup>ix</sup>	3.38 (1)
Eu1—O1 <sup>i</sup>	2.28 (2)	Ba—O1 <sup>x</sup>	3.38 (1)
Eu1—O2	2.37 (1)	Ba—O1 <sup>xi</sup>	3.24 (1)
Eu1—O2 <sup>ii</sup>	2.39 (1)	Ba—O2 <sup>ix</sup>	2.96 (1)
Eu1—O2 <sup>iii</sup>	2.39 (1)	Ba—O2 <sup>xii</sup>	3.07 (1)
Eu1—O2 <sup>j</sup>	2.37 (1)	Ba—O2 <sup>xiii</sup>	3.07 (1)
Eu1—O3	2.40 (2)	Ba—O2 <sup>x</sup>	2.96 (1)
La—O1 <sup>iv</sup>	2.31 (1)	Ba—O3 <sup>xiv</sup>	2.78 (2)
La—O1 <sup>v</sup>	2.47 (2)	Ba—O3 <sup>xii</sup>	2.904 (1)
La—O1 <sup>vi</sup>	2.47 (2)	Ba—O3 <sup>xv</sup>	2.904 (1)
La—O1 <sup>vii</sup>	2.31 (1)	Zn—O1 <sup>xv</sup>	2.00 (1)
La—O2	2.43 (1)	Zn—O1 <sup>xvi</sup>	2.00 (1)
La—O2 <sup>i</sup>	2.43 (1)	Zn—O2 <sup>xii</sup>	2.15 (1)
La—O3	2.25 (2)	Zn—O2 <sup>xiii</sup>	2.15 (1)
Ba—O1 <sup>viii</sup>	3.24 (1)	Zn—O3 <sup>xviii</sup>	2.05 (2)

Symmetry codes: (i)  $x, y, \frac{1}{2} - z$ ; (ii)  $x - \frac{1}{2}, \frac{1}{2} - y, 1 - z$ ; (iii)  $x - \frac{1}{2}, \frac{1}{2} - y, z - \frac{1}{2}$ ; (iv)  $\frac{1}{2} + x, \frac{1}{2} - y, -z$ ; (v)  $\frac{1}{2} - x, y - \frac{1}{2}, \frac{1}{2} - z$ ; (vi)  $\frac{1}{2} - x, y - \frac{1}{2}, z$ ; (vii)  $\frac{1}{2} + x, \frac{1}{2} - y, \frac{1}{2} + z$ ; (viii)  $\frac{1}{2} + x, \frac{3}{2} - y, -z$ ; (ix)  $\frac{3}{2} - x, \frac{1}{2} + y, \frac{1}{2} - z$ ; (x)  $\frac{3}{2} - x, \frac{1}{2} + y, z$ ; (xi)  $\frac{1}{2} + x, \frac{3}{2} - y, \frac{1}{2} + z$ ; (xii)  $1 - x, 1 - y, z - \frac{1}{2}$ ; (xiii)  $1 - x, 1 - y, 1 - z$ ; (xiv)  $1 + x, 1 + y, z$ ; (xv)  $1 - x, 1 - y, \frac{1}{2} + z$ ; (xvi)  $1 - x, 1 - y, -z$ ; (xvii)  $\frac{1}{2} - x, \frac{1}{2} + y, \frac{1}{2} - z$ .

The starting set of parameters to perform a Rietveld refinement for  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  was taken from the data reported by Kaduk *et al.* (1999) for the isostructural compound  $\text{Eu}_2\text{BaZnO}_5$ . The structure was refined against the powder diffraction data by the Rietveld method, using a pseudo-Voigt function modified by Thompson *et al.* (1987) to generate the line shape of the diffraction peaks. The background was initially refined by means of a linear interpolation between 70 background points with refinable heights. At the end of the refinement, the values for all of these background heights were fixed. The refinement was performed by describing the symmetry in the space group  $Pbnm$  (No. 62), which is a non-standard setting (*cab* axis reordering) for the standard symbol  $Pnma$ . We used this setting in order to facilitate a comparison with other previously reported isostructural compounds, in which the  $Pbnm$  setting was also used, *e.g.*  $\text{Y}_2\text{BaZnO}_5$  (Michel & Raveau, 1983),  $\text{Dy}_2\text{BaZnO}_5$  (Mueller-Buschbaum & Rabbow, 1993),  $\text{Ho}_2\text{BaZnO}_5$  and  $\text{Er}_2\text{BaZnO}_5$  (Wong-Ng *et al.*, 1998), and  $\text{Eu}_2\text{BaZnO}_5$ ,  $\text{Sm}_2\text{BaZnO}_5$ ,  $\text{Gd}_2\text{BaZnO}_5$  and  $\text{Tm}_2\text{BaZnO}_5$  (Kaduk *et al.*, 1999). The following parameters were refined: zero point, scale factor, unit-cell dimensions, half-width, pseudo-Voigt parameters for the peak shape, and positional and isotropic displacement parameters. For the occupation factors, we started the refinement considering the amount of  $\text{La}^{3+}$ , equally distributed over the two  $\text{Eu}^{3+}$  sites in  $\text{Eu}_2\text{BaZnO}_5$  (*i.e.* 0.9 and 0.1 for  $\text{Eu}^{3+}$  and  $\text{La}^{3+}$ , respectively, in each of the two sites). Keeping the

occupation factors fixed, we found unreasonable isotropic displacement parameters, *i.e.* very high on one site and very low (almost negative) on the other. Because atomic sites corresponding to smaller or negative values of displacement parameters can be interpreted as sites in which elements of higher atomic numbers should be located, we tried to improve our results by placing all the  $\text{La}^{3+}$  cations in the site with the higher displacement parameter (with occupation factors of 0.8 for  $\text{Eu}^{3+}$  and 0.2 for  $\text{La}^{3+}$ ), keeping the other site with  $\text{Eu}^{3+}$  cations only (occupation factor of 1.0). In this way, we found reasonable displacement parameters. Refinement of the occupation factors was not included in the final refinement because it did not allow the attainment of stable behaviour, so convergence was not reached. The fixed occupation factors for the  $\text{Eu}^{3+}$  and  $\text{La}^{3+}$  cations cited above were assigned according to the data estimated from the composition of the reactants used. These findings are in agreement with the longer bonds found on the site with incorporated  $\text{La}^{3+}$  cations, as mentioned in the *Comment* section. A small quantity of  $\text{PtO}_2$  was refined as a secondary phase, a product of a chemical reaction with the crucible employed. The data for the refinement of this secondary phase were obtained from the data reported for  $\beta\text{-PtO}_2$  by Siegel *et al.* (1969). According to the refinement, the weight fractions for  $\text{Eu}_{1.8}\text{La}_{0.2}\text{BaZnO}_5$  and  $\text{PtO}_2$  were 99.5 (1) and 0.5 (1)%, respectively. The results of the Rietveld refinement are shown in Fig. 3.

Data collection: *DIFFRAC/AT* (Siemens, 1993); cell refinement: *DICVOL91* (Boultif & Louer, 1991); program(s) used to refine structure: *FULLPROF* (Rodríguez-Carvajal, 1990); molecular graphics: *ATOMS* (Dowty, 2000); software used to prepare material for publication: *ATOMS*.

The authors are grateful for the financial support extended by DGAPA, UNAM, and PAPIIT Nos. IN-103603 and IN-1138114/15.

## References

- Burdett, J. K. & Mitchell, J. F. (1990). *J. Am. Chem. Soc.* **112**, 6571–6579.  
 Boultif, A. & Louër, D. (1991). *J. Appl. Cryst.* **24**, 987–993.  
 Dowty, E. (2000). *ATOMS for Windows*. Version 5.1. Shape Software, 521 Hidden Valley Road, Kingsport, TN 37663, USA.  
 Kaduk, J. A., Wong-Ng, W., Greenwood, W., Dillingham, J. & Toby, B. H. (1999). *J. Res. Natl. Inst. Stand. Technol.* **104**, 147–171.  
 Lavat, A., Baran, E. J., Saez-Puche, R., Salinas-Sanchez, A. & Matin-Llorente, M. J. (1992). *Vibr. Spectrosc.* **3**, 290–298.  
 Michel, C. & Raveau, B. (1983). *J. Solid State Chem.* **49**, 150–156.  
 Mueller-Buschbaum H. & Rabbow, C. (1993). *Z. Anorg. Allg. Chem.* **619**, 529–533.  
 Rodríguez-Carvajal, J. (1990). *FULLPROF. Abstracts of the Satellite Meeting on Powder Diffraction of the XV Congress of the IUCr*, p. 127, Toulouse, France.  
 Saez-Puche, R. & Hernandez-Velazco, J. (1994). *Adv. Mater. Res.* **1–2**, 65–82.  
 Shannon, R. D. (1976). *Acta Cryst.* **A32**, 751–767.  
 Siegel, S., Hoekstra, H. R. & Tani, B. S. (1969). *J. Inorg. Nucl. Chem.* **31**, 3803–3807.  
 Siemens (1993). *DIFFRAC/AT*. Version 3.2. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.  
 Thompson, P., Cox, D. E. & Hastings, J. B. (1987). *J. Appl. Cryst.* **20**, 79–83.  
 Wong-Ng, W., Toby, B. & Greenwood, W. (1998). *Powder Diffract.* **13**, 144–151.