

Goethite, α -FeO(OH), from single-crystal dataHexiong Yang,* Ren Lu,
Robert T. Downs and Gelu
CostinUniversity of Arizona, Department of
Geosciences, 1040 East 4th Street, Tucson,
AZ 85721-0077, USA

Correspondence e-mail: hyang@u.arizona.edu

Key indicators

Single-crystal X-ray study

T = 273 K

Mean $\sigma(e-O) = 0.001 \text{ \AA}$

R factor = 0.019

wR factor = 0.052

Data-to-parameter ratio = 21.0

For details of how these key indicators were
automatically derived from the article, see
<http://journals.iucr.org/e>.

This is the first reported structure refinement of goethite, α -FeO(OH), on the basis of a single-crystal X-ray diffraction study. The structure of goethite, isostructural with diaspore, AlO(OH), and groutite, MnO(OH), can be described in terms of a slightly distorted hexagonal close-packed O-atom arrangement with Fe atoms occupying one-half of the octahedral interstices, and with all atoms located on mirror planes. There are two distinct O sites, O1 and O2, each bonded to three Fe atoms, with O2 additionally bonded to an H atom. The O2—H···O1 donor–acceptor distance in goethite is significantly longer than that in diaspore or groutite, indicating that the hydrogen bonding in goethite is the weakest of the three minerals. Analysis of refinement data for the three isostructural compounds reveals rigid-body thermal motion behavior of the octahedral groups.

Comment

Goethite, α -FeO(OH), is one of the most widespread forms of iron oxides in terrestrial soils, sediments and ore deposits (Cornell & Schwertmann, 2003; Strucki *et al.* 1988), as well as a common weathering product in rocks of all types (Ozdemir & Dunlop, 2000). It transforms to hematite (α -Fe₂O₃) between 453 and 543 K through dehydrogenation and has been used extensively in the preparation of maghemite (γ -Fe₂O₃) in magnetic storage media. The crystal structure of goethite was first determined by Goldsztaub (1935) and Hoppe (1940) using X-ray diffraction photographic techniques. Forsyth *et al.* (1968) and Szytula *et al.* (1968) examined the magnetic structure of goethite with neutron powder diffraction on both natural and synthetic samples and found that it is anti-ferromagnetic below about 373 K (the Néel point). The structural behavior of goethite as a function of temperature and pressure was investigated by Gualtieri & Venturelli (1999) and Nagai *et al.* (2003), respectively, by means of synchrotron X-ray powder diffraction. However, despite both its mineralogical and technological interest, no detailed structural information, such as anisotropic atomic displacement parameters, are available for goethite because of the lack of a single-crystal X-ray diffraction structure analysis.

Goethite is isostructural with diaspore, AlO(OH), and groutite, MnO(OH) (Forsyth *et al.*, 1968; Szytula *et al.*, 1968). Its structure can be described in terms of a slightly distorted hexagonal close-packed O-atom arrangement with Fe atoms occupying one-half of the octahedral interstices. The Fe³⁺O₆ octahedra share edges to form double chains running parallel to *c*, which are further linked to form a three-dimensional structure by sharing vertices (Fig. 1). There are two distinct O sites, O1 and O2, both coordinated to three Fe atoms, with O2 additionally bonded to an H atom. In spite of the same ionic

Received 11 October 2006

Accepted 8 November 2006

radius of 0.645 Å for six-coordinated Fe³⁺ and Mn³⁺ ions (Shannon, 1976), the average M³⁺–O bond length within the Fe³⁺O₆ octahedron in goethite (2.026 Å) is slightly shorter than that within the Mn³⁺O₆ octahedron in groutite (2.039 Å), due to the obvious Jahn–Teller effect of Mn³⁺.

A translational–librational–screw (TLS) rigid-body analysis (Schomaker & Trueblood, 1968; Downs, 2000) was conducted on the FeO₆, AlO₆ and MnO₆ octahedral groups in goethite, diasporite (Hill, 1979) and groutite (Kohler *et al.*, 1997), respectively. The atomic displacement parameters reveal rigid-body behavior with differences in the mean-square displacement amplitudes along the M–O bonds of less than 0.001 Å². The librational angles are small, at 1.7, 1.3 and 1.5° for goethite, diasporite and groutite, respectively. These magnitudes result in a very small thermal effect on the bond lengths. They are consistent with high-quality diffraction data, and with the edge-sharing topology of the double octahedral chains.

Hydrogen bonding is found between atom O2 of one FeO₆ octahedron and an O1 atom in an adjacent one, with an O2–H distance of 0.88 Å and an O2–H···O1ⁱ angle of 161 (3)°. This value is comparable with that in diasporite [160.8 (1)°; Hill, 1979] but notably smaller than that in groutite [171 (4)°; Kohler *et al.*, 1997]. The non-linear hydrogen bonding in goethite is known to be of moderate strength and represents the most common type of hydrogen bond (Jeffrey, 1997). Nevertheless, the donor–acceptor O2–H···O1ⁱ distance in goethite [2.747 (1) Å] is significantly longer than those in diasporite [2.649 (1) Å; Hill, 1979] or groutite [2.619 (1) Å; Kohler *et al.*, 1997], indicating that the hydrogen bonding in goethite is the weakest of the three minerals. This observation is consistent with the IR spectroscopic measurements; the ν_{OH} stretching bands decrease from 3100 cm⁻¹ in goethite to 2950 cm⁻¹ in diasporite (Libowitzky & Rossman, 1997) and to 2685 cm⁻¹ in groutite (Kohler *et al.*, 1997).

Experimental

The goethite crystal used in this study is a natural sample from Park County, Colorado, USA (RRUFF project collection, R050142; <http://ruff.info>). Within experimental uncertainty, the chemical composition determined with an electron microprobe is that of ideal FeO(OH).

Crystal data

FeO(OH)	Z = 4
M _r = 88.86	D _x = 4.275 Mg m ⁻³
Orthorhombic, <i>Pbnm</i>	Mo Kα radiation
a = 4.5979 (2) Å	μ = 10.30 mm ⁻¹
b = 9.9510 (5) Å	T = 273 (2) K
c = 3.0178 (1) Å	Block, brown
V = 138.08 (1) Å ³	0.09 × 0.09 × 0.08 mm

Data collection

Bruker SMART APEX2 CCD area-detector diffractometer	2197 measured reflections
φ and ω scans	483 independent reflections
Absorption correction: multi-scan (SADABS; Sheldrick, 2005)	458 reflections with I > 2σ(I)
T _{min} = 0.410, T _{max} = 0.441	R _{int} = 0.017
	θ _{max} = 40.5°

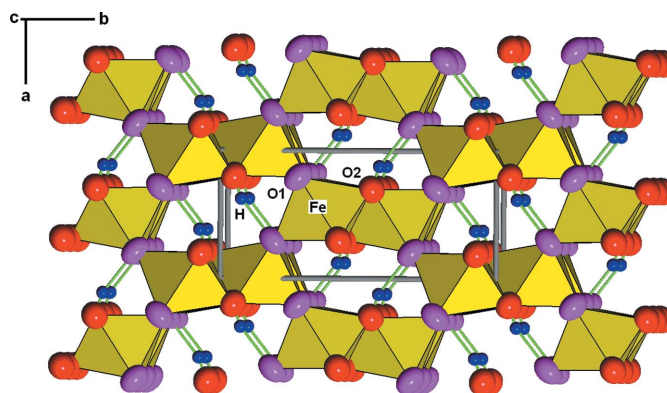


Figure 1

The crystal structure of goethite, α-FeO(OH). O atoms are drawn with anisotropic displacement ellipsoids at the 90% probability level and H atoms with arbitrary radii. Hydrogen bonding is indicated with green lines.

Refinement

Refinement on F^2
 $R[F^2 > 2\sigma(F^2)] = 0.019$
 $wR(F^2) = 0.052$
 $S = 1.15$
 483 reflections
 23 parameters
 All H-atom parameters refined

$w = 1/[\sigma^2(F_o^2) + (0.034P)^2]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} = 0.001$
 $\Delta\rho_{\max} = 0.98 \text{ e } \text{Å}^{-3}$
 $\Delta\rho_{\min} = -1.00 \text{ e } \text{Å}^{-3}$
 Extinction correction: *SHELXL97* (Sheldrick, 1997)
 Extinction coefficient: 0.087 (9)

Table 1

Selected bond lengths (Å).

Fe–O1 ⁱ	1.9325 (9)	Fe–O2 ⁱⁱⁱ	2.0996 (9)
Fe–O1 ⁱⁱ	1.9560 (6)	Fe–O2 ^{iv}	2.1063 (7)

Symmetry codes: (i) $-x + \frac{1}{2}, y + \frac{1}{2}, z$; (ii) $-x + 1, -y + 1, -z + 1$; (iii) $x, y + 1, z$; (iv) $-x, -y + 1, -z$.

Consistent with previous studies, the non-standard setting *Pbnm* of space group *Pnma* was used. The H atom was located in a difference Fourier map and its position was refined freely.

Data collection: *SMART* (Bruker, 2003); cell refinement: *SAINTE* (Bruker, 2005); data reduction: *SAINTE*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 1997); program(s) used to refine structure: *SHELXL97* (Sheldrick, 1997); molecular graphics: Xtal-Draw (Downs & Hall-Wallace, 2003); software used to prepare material for publication: *SHELXTL* (Bruker, 1997).

The authors thank Dave Bunk Minerals for the donation of the sample.

References

- Bruker (1997). *SHELXTL*. Version 5.10. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bruker (2003). *SMART*. Version 6.0. Bruker AXS Inc., Madison, Wisconsin, USA.
- Bruker (2005). *SAINTE*. Version 6.0. Bruker AXS Inc., Madison, Wisconsin, USA.
- Cornell, R. M. & Schwertmann, U. (2003). *The Iron Oxides*, pp. 2–10. Weinheim: VCH Verlag.
- Downs, R. T. (2000). *Rev. Mineral. Geochem.* **41**, 61–87.
- Downs, R. T. & Hall-Wallace, M. (2003). *Am. Mineral.* **88**, 247–250.
- Forsyth, J. B., Hedley, I. G. & Johnson, C. E. (1968). *J. Phys. C*, **1**, 179–188.
- Goldsztaub, M. S. (1935). *Bull. Soc. Fr. Mineral.* **58**, 6–67.
- Gualtieri, A. F. & Venturelli, P. (1999). *Am. Mineral.* **84**, 895–904.

- Hill, R. J. (1979). *Phys. Chem. Miner.* **5**, 179–200.
- Hoppe, V. W. (1940). *Z. Kristallogr.* **103**, 73–89.
- Jeffrey, G. A. (1997). *An Introduction to Hydrogen Bonding*, pp. 56–78. New York: Oxford University Press.
- Kohler, T., Armbruster, T. & Libowitzky, E. (1997). *J. Solid State Chem.* **133**, 486–500.
- Libowitzky, E. & Rossman, G. R. (1997). *Am. Mineral.* **82**, 1111–1115.
- Nagai, T., Kagi, H. & Yamanaka, T. (2003). *Am. Mineral.* **88**, 1423–1427.
- Ozdemir, O. & Dunlop, D. J. (2000). *Earth Planet. Sci. Lett.* **177**, 59–67.
- Schomaker, V. & Trueblood, K. N. (1968). *Acta Cryst.* **B24**, 63–76.
- Shannon, R. D. (1976). *Acta Cryst.* **A32**, 751–767.
- Sheldrick, G. M. (1997). *SHELXS97* and *SHELXL97*. University of Göttingen, Germany.
- Sheldrick, G. M. (2005). *SADABS*. Version 2.10. University of Göttingen, Germany.
- Strucki, J. W., Goodman, B. A. & Schwertmann, U. (1988). *Iron in Soils and Clay Minerals*. NATO ASI Series C217. Boston: Reidel Publishing Company.
- Szytula, A., Burewicz, A., Dimitrijevic, Z., Krasnicki, S., Rzany, H., Todorovic, J., Wanic, A. & Wolski, W. (1968). *Phys. Status Solidi*, **26**, 429–434.