

Poly[bis(acetone- κ O)bis{ μ_3 -1-[(5-chloro-2-oxidophenyl)diazenyl]-2-naphtholato- κ^4 O:O,O':O'}sodium(I)chromium(III)]

Shinpei Ito,^a Yohei Sato^b and Jin Mizuguchi^{b*}

^aDepartment of Applied Physics, Faculty of Engineering, Yokohama National University, Tokiwadai 79-5, Hodogaya-ku, Yokohama 240-8501, Japan, and

^bDepartment of Applied Physics, Graduate School of Engineering, Yokohama National University, Tokiwadai 79-5, Hodogaya-ku, Yokohama 240-8501, Japan
Correspondence e-mail: mizu-j@ynu.ac.jp


Received 16 December 2007; accepted 7 January 2008

Key indicators: single-crystal X-ray study; $T = 93$ K; mean $\sigma(\text{C}-\text{C}) = 0.008$ Å; R factor = 0.110; wR factor = 0.318; data-to-parameter ratio = 13.9.

The title compound, $[\text{CrNa}(\text{C}_6\text{H}_9\text{ClN}_2\text{O}_2)_2(\text{C}_3\text{H}_6\text{O})_2]_n$, is an azo- Cr^{III} complex polymer that is used as a charge-control agent in electrophotography. The monomeric unit is composed of octahedral Cr^{III} and Na^{I} units, and is characterized by twofold rotation symmetry. The Cr^{III} atom is chelated by two N and four O atoms from two [(5-chloro-2-oxidophenyl)diazenyl]-2-naphtholate ligands. The ligand anion exists in the *cis* form. The Na^{I} atom is coordinated by two phenoxy O atoms from a neighboring Cr^{III} unit, two naphthoxy O atoms from another neighboring Cr^{III} unit and two O atoms from acetone molecules. The dinuclear complex forms a one-dimensional polymer running along the c axis.

Related literature

For general background to charge-control agents, see: Tanaka (1995). For the preparation of the title compound, see: Yasumatsu *et al.* (2006). For related structures, see: Mizuguchi, Sato, Uta & Sato (2007); Mizuguchi *et al.* (2007*a,b*); Mizuguchi, Uta & Sato (2007); Sato *et al.* (2008).

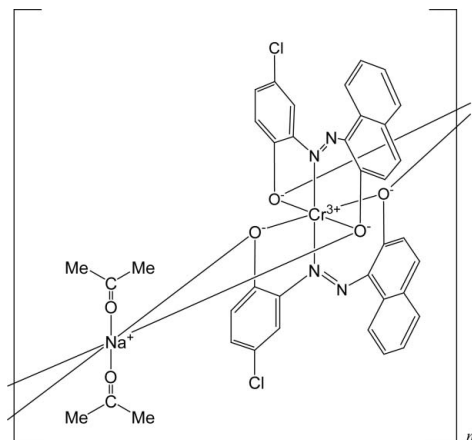

Experimental

Crystal data

$[\text{CrNa}(\text{C}_{16}\text{H}_9\text{ClN}_2\text{O}_2)_2(\text{C}_3\text{H}_6\text{O})_2]$
 $M_r = 784.55$
 Orthorhombic, $Pnna$
 $a = 18.5082$ (17) Å
 $b = 26.199$ (3) Å
 $c = 7.1726$ (6) Å
 $V = 3478.0$ (6) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 0.55$ mm⁻¹
 $T = 93$ K
 $0.26 \times 0.10 \times 0.09$ mm

Data collection

Rigaku R-Axis RAPID diffractometer
 Absorption correction: multi-scan (ABSCOR; Higashi, 1995)
 $T_{\text{min}} = 0.890$, $T_{\text{max}} = 0.947$
 22709 measured reflections
 3314 independent reflections
 1916 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.153$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.110$
 $wR(F^2) = 0.318$
 $S = 1.03$
 3314 reflections
 238 parameters
 H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 2.03$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.59$ e Å⁻³

Table 1

Selected geometric parameters (Å, °).

Cr1—O1	1.948 (4)	Na1—O1	2.708 (4)
Cr1—O1 ⁱ	1.948 (4)	Na1—O1 ⁱⁱ	2.708 (4)
Cr1—O2	1.993 (4)	Na1—O2 ⁱⁱⁱ	2.547 (4)
Cr1—O2 ⁱ	1.993 (4)	Na1—O2 ⁱ	2.547 (4)
Cr1—N1	2.021 (5)	Na1—O3	2.274 (5)
Cr1—N1 ⁱ	2.021 (5)	Na1—O3 ⁱⁱ	2.274 (5)
Cl1—Cl	1.752 (7)		
O1—Cr1—O1 ⁱ	91.84 (19)	O1—Na1—O2 ⁱⁱⁱ	168.44 (17)
O1—Cr1—O2	169.0 (2)	O1—Na1—O2 ⁱ	64.50 (13)
O1—Cr1—O2 ⁱ	90.83 (18)	O1—Na1—O3	82.45 (16)
O1—Cr1—N1	87.12 (19)	O1—Na1—O3 ⁱⁱ	91.90 (16)
O1—Cr1—N1 ⁱ	90.86 (19)	O2 ⁱⁱⁱ —Na1—O2 ⁱ	124.4 (2)
O2—Cr1—O2 ⁱ	88.56 (19)	O2 ⁱⁱⁱ —Na1—O3	89.00 (17)
O2—Cr1—N1	82.2 (2)	O2 ⁱⁱⁱ —Na1—O3 ⁱⁱ	95.46 (17)
O2—Cr1—N1 ⁱ	100.0 (2)	O3—Na1—O3 ⁱⁱ	170.4 (2)
N1—Cr1—N1 ⁱ	177.1 (2)	Cr1—O1—Na1	99.77 (18)
O1—Na1—O1 ⁱⁱ	107.84 (18)	Cr1—O2—Na1 ^{iv}	104.03 (19)

Symmetry codes: (i) $x, -y + \frac{1}{2}, -z + \frac{1}{2}$; (ii) $x, -y + \frac{1}{2}, -z - \frac{1}{2}$; (iii) $x, y, z - 1$; (iv) $x, y, z + 1$.

Data collection: *PROCESS-AUTO* (Rigaku, 1998); cell refinement: *PROCESS-AUTO*; data reduction: *CrystalStructure* (Rigaku/MSO, 2006); program(s) used to solve structure: *SIR2004* (Burla *et al.*, 2005); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP3* (Burnett & Johnson, 1996); software used to prepare material for publication: *CrystalStructure*.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: IS2268).

References

- Burla, M. C., Caliandro, R., Camalli, M., Carrozzini, B., Cascarano, G. L., De Caro, L., Giacovazzo, C., Polidori, G. & Spagna, R. (2005). *J. Appl. Cryst.* **38**, 381–388.
 Burnett, M. N. & Johnson, C. K. (1996). *ORTEP3*. Report ORNL-6895. Oak Ridge National Laboratory, Tennessee, USA.
 Higashi, T. (1995). *ABSCOR*. Rigaku Corporation, Tokyo, Japan.
 Mizuguchi, J., Sato, Y. & Uta, K. (2007*a*). *Acta Cryst.* **E63**, m1327–m1328.
 Mizuguchi, J., Sato, Y. & Uta, K. (2007*b*). *Acta Cryst.* **E63**, m1377–m1378.
 Mizuguchi, J., Sato, Y., Uta, K. & Sato, K. (2007). *Acta Cryst.* **E63**, o2509–o2510.

- Mizuguchi, J., Uta, K. & Sato, Y. (2007). *Acta Cryst.* **E63**, m1329–m1330.
- Rigaku (1998). *PROCESS-AUTO*. Rigaku Corporation, Tokyo, Japan.
- Rigaku/MSC (2006). *CrystalStructure*. Version 3.8. Rigaku/MSC, The Woodlands, Texas, USA.
- Sato, Y., Uta, K. & Mizuguchi, J. (2008). *Acta Cryst.* **E64**, m240–m241.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Tanaka, K. (1995). *J. Electrostatics (Jpn. Version)*, **19**, 15–21.
- Yasumatsu, M., Kuroda, K., Yamate, O., Sato, K., Hikata, J. & Yushina, H. (2006). JP Patent 2006-113576A.

supplementary materials

Acta Cryst. (2008). E64, m333-m334 [doi:10.1107/S1600536808000433]

Poly[bis(acetone- κO)bis $\{\mu_3$ -1-[(5-chloro-2-oxidophenyl)diazenyl]-2-naphtholato- $\kappa^4 O:O,O':O'\}$ sodium(I)chromium(III)]

S. Ito, Y. Sato and J. Mizuguchi

Comment

The title compound, (I), is an azo-Cr complex polymer that is used as a charge- control agent (CCA) of the negative type in electrophotography (Tanaka, 1995). The purpose of the investigation has been set out in our previous paper (Mizuguchi, Sato, Uta & Sato, 2007). We have previously reported the structure of a methanol-solvated azo-Fe complex with an ammonium cation (Mizuguchi *et al.*, 2007a) and its acetone solvate (Mizuguchi, Uta & Sato, 2007). Further structural analysis was carried out on the same azo-Fe complex but with a different cation, *i.e.* sodium one in place of the ammonium ion. The compound was recrystallized from an acetone (Mizuguchi *et al.*, 2007b) or acetonitrile solution (Sato, Uta & Mizuguchi, 2007). The present paper reports an azo-Cr complex polymer whose monomeric unit comprises an octahedral Cr^{III} unit and an octahedral Na^I one.

Figure 1 shows the *ORTEP* plot (Burnett & Johnson, 1996) of the monomeric unit of (I). The unit is composed of an octahedral Cr^{III} unit and an octahedral Na^I one. The anion complex exists in *cis*-form, just as in the ordinary azo-Fe complexes described in the above paragraph. Each Cr^{III} atom is chelated by the N and two O atoms from two [(5-chloro-2-oxidophenyl) diazenyl]-2-naphtholate ligands. On the other hand, the Na^I cation coordinates to a phenoxy O atom from the two ligands of each octahedral Cr^{III} unit, a naphthoxy O atom from the two ligands of each neighboring Cr^{III} unit and two acetone molecules. The octahedral Cr^{III} unit and the octahedral Na^I one are repeated alternately to form a one dimensional polymer along *c* through the four O ligands in common (Fig. 2). The polymer formation contributes to a significant stabilization of (I) whose property is pre-requisite for the CCA application in electrophotography.

Experimental

The title compound was prepared according to the previously reported method (Yasumatsu *et al.*, 2006). Single crystals were recrystallized from an acetone solution. After 48 h, a number of single crystals were obtained in the form of blocks. Since the single crystals were found to include two solvent molecules according to the thermogravimetric analysis, reflection data were collected at 93 K.

Refinement

All H atoms were placed in geometrically idealized positions (C—H = 0.93 or 0.96 Å) and constrained to ride on their parent atoms, with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$ or $1.5U_{\text{eq}}(\text{methyl C})$. *R*-merge for the reflection data was 15.3%. This indicates poor crystal quality resulting in a rather high value of the *R* factor. The highest electron density (2.03 e Å⁻³) is located 0.64 Å from Cr1.

Figures

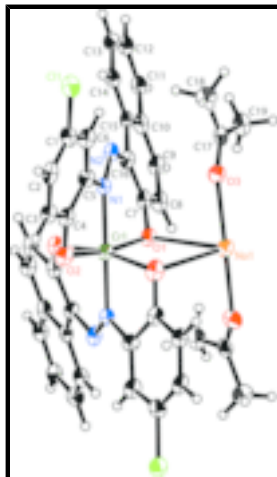


Fig. 1. A view of the monomeric structure of the title compound, showing 50% displacement ellipsoids. Unlabelled atoms except for C17—C19 and O3 are related to labelled atoms by the symmetry operation $(x, 1/2 - y, 1/2 - z)$, whereas those for C17—C19 and O3 by the symmetry operation $(x, 1/2 - y, -1/2 - z)$.

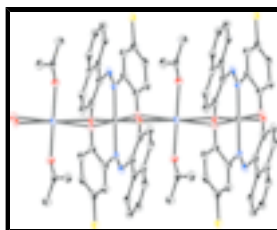


Fig. 2. Polymeric structure of the title compound along the c axis.

Poly[bis(acetone)bis(μ_3 -1-[(5-chloro-2-oxidophenyl)diazenyl]-2-naphtholato- $\kappa^4 O:O,O':O'$)}sodium(I)chromium(III)]

Crystal data

$[\text{CrNa}(\text{C}_{16}\text{H}_9\text{ClN}_2\text{O}_2)_2(\text{C}_3\text{H}_6\text{O})_2]$

$M_r = 784.55$

Orthorhombic, $Pnna$

Hall symbol: $-P\ 2a\ 2bc$

$a = 18.5082(17)\ \text{\AA}$

$b = 26.199(3)\ \text{\AA}$

$c = 7.1726(6)\ \text{\AA}$

$V = 3478.0(6)\ \text{\AA}^3$

$Z = 4$

$F_{000} = 1612.00$

$D_x = 1.498\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation

$\lambda = 0.71075\ \text{\AA}$

Cell parameters from 14701 reflections

$\theta = 3.7\text{--}26.1^\circ$

$\mu = 0.55\ \text{mm}^{-1}$

$T = 93\ \text{K}$

Block, black

$0.26 \times 0.10 \times 0.09\ \text{mm}$

Data collection

Rigaku R-AXIS RAPID
diffractometer

Detector resolution: $10.00\ \text{pixels mm}^{-1}$

ω scans

Absorption correction: multi-scan
(*ABSCOR*; Higashi, 1995)

1916 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.153$

$\theta_{\text{max}} = 26.0^\circ$

$h = -22 \rightarrow 22$

$T_{\min} = 0.890$, $T_{\max} = 0.947$
 22709 measured reflections
 3314 independent reflections

$k = -32 \rightarrow 31$
 $l = -8 \rightarrow 8$

Refinement

Refinement on F^2

$R[F^2 > 2\sigma(F^2)] = 0.110$

$wR(F^2) = 0.318$

$S = 1.04$

3314 reflections

238 parameters

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.2P)^2]$
 where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 2.03 \text{ e } \text{\AA}^{-3}$

$\Delta\rho_{\min} = -0.59 \text{ e } \text{\AA}^{-3}$

Extinction correction: none

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Cr1	0.80893 (8)	0.2500	0.2500	0.0380 (5)
Cl1	0.63892 (10)	0.02267 (8)	0.4102 (2)	0.0539 (6)
Na1	0.7960 (2)	0.2500	-0.2500	0.0467 (9)
O1	0.8822 (2)	0.24781 (18)	0.0550 (6)	0.0435 (11)
O2	0.7318 (2)	0.2380 (2)	0.4390 (6)	0.0513 (12)
O3	0.8062 (2)	0.1638 (2)	-0.2260 (6)	0.0512 (12)
N1	0.8117 (2)	0.1729 (2)	0.2488 (6)	0.0351 (11)
N2	0.8617 (2)	0.1418 (2)	0.2019 (6)	0.0407 (13)
C1	0.6658 (3)	0.0867 (2)	0.4209 (8)	0.0462 (16)
C2	0.6242 (3)	0.1212 (3)	0.5099 (8)	0.0461 (17)
C3	0.6441 (3)	0.1722 (2)	0.5183 (9)	0.0437 (15)
C4	0.7078 (3)	0.1896 (2)	0.4309 (8)	0.0407 (15)
C5	0.7492 (3)	0.1516 (2)	0.3324 (9)	0.0426 (15)
C6	0.7292 (3)	0.1006 (2)	0.3330 (9)	0.0435 (15)
C7	0.9324 (3)	0.2119 (2)	0.0575 (7)	0.0396 (15)
C8	1.0020 (3)	0.2267 (3)	-0.0206 (8)	0.0451 (15)
C9	1.0569 (3)	0.1937 (2)	-0.0250 (8)	0.0461 (16)
C10	1.0507 (3)	0.1422 (2)	0.0373 (7)	0.0434 (16)

supplementary materials

C11	1.1093 (3)	0.1072 (3)	0.0275 (8)	0.0458 (16)
C12	1.1004 (3)	0.0574 (2)	0.0811 (8)	0.0462 (16)
C13	1.0341 (3)	0.0416 (2)	0.1532 (8)	0.0457 (15)
C14	0.9764 (3)	0.0742 (2)	0.1681 (8)	0.0445 (16)
C15	0.9825 (3)	0.1249 (2)	0.1113 (7)	0.0371 (14)
C16	0.9246 (3)	0.1624 (2)	0.1233 (7)	0.0385 (14)
C17	0.8410 (4)	0.1242 (3)	-0.2542 (7)	0.0484 (17)
C18	0.8125 (4)	0.0736 (3)	-0.1908 (11)	0.0583 (19)
C19	0.9106 (3)	0.1238 (3)	-0.3583 (10)	0.0561 (19)
H2	0.5815	0.1107	0.5665	0.055*
H3	0.6151	0.1953	0.5824	0.052*
H6	0.7580	0.0761	0.2753	0.052*
H8	1.0082	0.2595	-0.0678	0.054*
H9	1.1013	0.2048	-0.0706	0.055*
H11	1.1540	0.1182	-0.0156	0.055*
H12	1.1383	0.0343	0.0695	0.055*
H13	1.0289	0.0080	0.1924	0.055*
H14	0.9329	0.0624	0.2165	0.053*
H18A	0.8513	0.0536	-0.1406	0.087*
H18B	0.7913	0.0560	-0.2948	0.087*
H18C	0.7764	0.0789	-0.0965	0.087*
H19A	0.9490	0.1139	-0.2759	0.084*
H19B	0.9202	0.1573	-0.4066	0.084*
H19C	0.9076	0.0999	-0.4595	0.084*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cr1	0.0287 (8)	0.0449 (9)	0.0405 (8)	0.0000	0.0000	0.0033 (5)
Cl1	0.0448 (10)	0.0658 (13)	0.0511 (10)	-0.0180 (8)	0.0053 (7)	-0.0007 (7)
Na1	0.046 (2)	0.048 (2)	0.046 (2)	0.0000	0.0000	0.0035 (15)
O1	0.032 (2)	0.058 (3)	0.040 (2)	-0.001 (2)	-0.0023 (18)	0.0069 (19)
O2	0.024 (2)	0.077 (3)	0.053 (2)	0.007 (2)	-0.001 (2)	0.005 (2)
O3	0.045 (3)	0.056 (3)	0.052 (2)	0.006 (2)	-0.019 (2)	-0.002 (2)
N1	0.027 (2)	0.043 (3)	0.035 (2)	0.001 (2)	0.001 (2)	-0.001 (2)
N2	0.023 (2)	0.065 (4)	0.033 (2)	0.002 (2)	0.0005 (19)	0.007 (2)
C1	0.034 (3)	0.063 (4)	0.042 (3)	-0.009 (3)	-0.008 (2)	-0.001 (3)
C2	0.021 (3)	0.076 (5)	0.041 (3)	-0.017 (3)	-0.002 (2)	0.002 (3)
C3	0.021 (3)	0.059 (4)	0.051 (3)	0.005 (2)	0.001 (2)	0.012 (3)
C4	0.020 (2)	0.057 (4)	0.044 (3)	-0.004 (2)	-0.001 (2)	0.007 (2)
C5	0.023 (3)	0.055 (4)	0.050 (3)	-0.005 (2)	-0.008 (2)	0.006 (3)
C6	0.025 (3)	0.058 (4)	0.048 (3)	-0.001 (2)	0.002 (2)	0.005 (3)
C7	0.018 (2)	0.070 (4)	0.031 (2)	-0.002 (2)	-0.001 (2)	-0.003 (2)
C8	0.023 (3)	0.076 (4)	0.037 (3)	-0.002 (3)	-0.003 (2)	0.003 (3)
C9	0.027 (3)	0.071 (4)	0.040 (3)	0.003 (3)	-0.003 (2)	0.005 (3)
C10	0.018 (2)	0.080 (5)	0.032 (2)	-0.001 (2)	0.001 (2)	-0.002 (3)
C11	0.033 (3)	0.070 (5)	0.034 (3)	0.002 (3)	0.002 (2)	-0.004 (3)
C12	0.039 (3)	0.062 (4)	0.037 (3)	0.010 (3)	0.007 (2)	-0.003 (3)

C13	0.045 (4)	0.049 (4)	0.043 (3)	0.006 (3)	-0.008 (3)	-0.001 (3)
C14	0.032 (3)	0.060 (4)	0.041 (3)	0.006 (3)	-0.001 (2)	-0.003 (3)
C15	0.026 (3)	0.054 (4)	0.031 (2)	-0.005 (2)	0.002 (2)	-0.004 (2)
C16	0.022 (3)	0.057 (4)	0.037 (2)	-0.003 (2)	-0.004 (2)	0.008 (2)
C17	0.048 (4)	0.062 (5)	0.035 (3)	-0.002 (3)	-0.009 (2)	-0.007 (3)
C18	0.039 (4)	0.066 (5)	0.070 (4)	-0.007 (3)	0.010 (3)	0.007 (4)
C19	0.040 (4)	0.078 (5)	0.050 (3)	-0.013 (3)	0.000 (3)	-0.005 (3)

Geometric parameters (Å, °)

Cr1—O1	1.948 (4)	C6—H6	0.930
Cr1—O1 ⁱ	1.948 (4)	C7—C8	1.458 (8)
Cr1—O2	1.993 (4)	C7—C16	1.386 (9)
Cr1—O2 ⁱ	1.993 (4)	C8—C9	1.336 (10)
Cr1—N1	2.021 (5)	C8—H8	0.930
Cr1—N1 ⁱ	2.021 (5)	C9—C10	1.426 (10)
Cl1—C1	1.752 (7)	C9—H9	0.930
Na1—O1	2.708 (4)	C10—C11	1.421 (9)
Na1—O1 ⁱⁱ	2.708 (4)	C10—C15	1.443 (8)
Na1—O2 ⁱⁱⁱ	2.547 (4)	C11—C12	1.371 (10)
Na1—O2 ⁱ	2.547 (4)	C11—H11	0.930
Na1—O3	2.274 (5)	C12—C13	1.394 (9)
Na1—O3 ⁱⁱ	2.274 (5)	C12—H12	0.930
O1—C7	1.323 (7)	C13—C14	1.372 (9)
O2—C4	1.345 (8)	C13—H13	0.930
O3—C17	1.238 (9)	C14—C15	1.393 (9)
N1—N2	1.278 (7)	C14—H14	0.930
N1—C5	1.418 (7)	C15—C16	1.456 (8)
N2—C16	1.403 (7)	C17—C18	1.497 (11)
C1—C2	1.349 (9)	C17—C19	1.488 (10)
C1—C6	1.381 (9)	C18—H18A	0.960
C2—C3	1.386 (10)	C18—H18B	0.960
C2—H2	0.930	C18—H18C	0.960
C3—C4	1.411 (8)	C19—H19A	0.960
C3—H3	0.930	C19—H19B	0.960
C4—C5	1.440 (9)	C19—H19C	0.960
C5—C6	1.387 (9)		
O1—Cr1—O1 ⁱ	91.84 (19)	C3—C4—C5	116.0 (6)
O1—Cr1—O2	169.0 (2)	N1—C5—C4	111.7 (5)
O1—Cr1—O2 ⁱ	90.83 (18)	N1—C5—C6	126.7 (5)
O1—Cr1—N1	87.12 (19)	C4—C5—C6	121.6 (5)
O1—Cr1—N1 ⁱ	90.86 (19)	C1—C6—C5	118.7 (6)
O1 ⁱ —Cr1—O2	90.83 (18)	C1—C6—H6	120.6
O1 ⁱ —Cr1—O2 ⁱ	169.0 (2)	C5—C6—H6	120.6
O1 ⁱ —Cr1—N1	90.86 (19)	O1—C7—C8	115.1 (6)
O1 ⁱ —Cr1—N1 ⁱ	87.12 (19)	O1—C7—C16	126.7 (5)

supplementary materials

O2—Cr1—O2 ⁱ	88.56 (19)	C8—C7—C16	118.2 (5)
O2—Cr1—N1	82.2 (2)	C7—C8—C9	120.6 (7)
O2—Cr1—N1 ⁱ	100.0 (2)	C7—C8—H8	119.7
O2 ⁱ —Cr1—N1	100.0 (2)	C9—C8—H8	119.7
O2 ⁱ —Cr1—N1 ⁱ	82.2 (2)	C8—C9—C10	122.9 (6)
N1—Cr1—N1 ⁱ	177.1 (2)	C8—C9—H9	118.5
O1—Na1—O1 ⁱⁱ	107.84 (18)	C10—C9—H9	118.5
O1—Na1—O2 ⁱⁱⁱ	168.44 (17)	C9—C10—C11	122.2 (5)
O1—Na1—O2 ⁱ	64.50 (13)	C9—C10—C15	118.9 (5)
O1—Na1—O3	82.45 (16)	C11—C10—C15	118.9 (6)
O1—Na1—O3 ⁱⁱ	91.90 (16)	C10—C11—C12	120.6 (6)
O1 ⁱⁱ —Na1—O2 ⁱⁱⁱ	64.50 (13)	C10—C11—H11	119.7
O1 ⁱⁱ —Na1—O2 ⁱ	168.44 (17)	C12—C11—H11	119.7
O1 ⁱⁱ —Na1—O3	91.90 (16)	C11—C12—C13	119.5 (6)
O1 ⁱⁱ —Na1—O3 ⁱⁱ	82.45 (16)	C11—C12—H12	120.3
O2 ⁱⁱⁱ —Na1—O2 ⁱ	124.4 (2)	C13—C12—H12	120.3
O2 ⁱⁱⁱ —Na1—O3	89.00 (17)	C12—C13—C14	121.9 (6)
O2 ⁱⁱⁱ —Na1—O3 ⁱⁱ	95.46 (17)	C12—C13—H13	119.0
O2 ⁱ —Na1—O3	95.46 (17)	C14—C13—H13	119.0
O2 ⁱ —Na1—O3 ⁱⁱ	89.00 (17)	C13—C14—C15	120.5 (6)
O3—Na1—O3 ⁱⁱ	170.4 (2)	C13—C14—H14	119.7
Cr1—O1—Na1	99.77 (18)	C15—C14—H14	119.7
Cr1—O1—C7	120.0 (3)	C10—C15—C14	118.5 (5)
Na1—O1—C7	116.1 (3)	C10—C15—C16	116.9 (6)
Cr1—O2—Na1 ^{iv}	104.03 (19)	C14—C15—C16	124.5 (5)
Cr1—O2—C4	110.9 (3)	N2—C16—C7	125.6 (5)
Na1 ^{iv} —O2—C4	107.9 (3)	N2—C16—C15	112.0 (5)
Na1—O3—C17	149.7 (4)	C7—C16—C15	122.4 (5)
Cr1—N1—N2	131.1 (4)	O3—C17—C18	120.5 (6)
Cr1—N1—C5	111.7 (4)	O3—C17—C19	122.6 (7)
N2—N1—C5	116.8 (5)	C18—C17—C19	116.9 (6)
N1—N2—C16	117.4 (5)	C17—C18—H18A	109.5
C11—C1—C2	120.0 (5)	C17—C18—H18B	109.5
C11—C1—C6	118.3 (5)	C17—C18—H18C	109.5
C2—C1—C6	121.7 (6)	H18A—C18—H18B	109.5
C1—C2—C3	120.9 (6)	H18A—C18—H18C	109.5
C1—C2—H2	119.5	H18B—C18—H18C	109.5
C3—C2—H2	119.5	C17—C19—H19A	109.5
C2—C3—C4	120.9 (6)	C17—C19—H19B	109.5
C2—C3—H3	119.5	C17—C19—H19C	109.5
C4—C3—H3	119.5	H19A—C19—H19B	109.5
O2—C4—C3	124.2 (6)	H19A—C19—H19C	109.5
O2—C4—C5	119.8 (5)	H19B—C19—H19C	109.5
O1—Cr1—O1 ⁱ —C7 ⁱ	55.3 (4)	O3—Na1—O1 ⁱⁱ —C7 ⁱⁱ	-135.0 (4)

O1 ⁱ —Cr1—O1—Na1	-176.84 (18)	O1 ⁱⁱ —Na1—O3 ⁱⁱⁱ —C17 ⁱⁱ	-80.9 (8)
O1 ⁱ —Cr1—O1—C7	55.3 (4)	O3 ⁱⁱⁱ —Na1—O1 ⁱⁱ —C7 ⁱⁱ	37.2 (4)
O1—Cr1—O2—C4	-3.6 (12)	O2 ⁱⁱⁱ —Na1—O2 ⁱ —Cr1	165.00 (18)
O1—Cr1—O2—Na1 ^{iv}	112.2 (9)	O2 ⁱⁱⁱ —Na1—O2 ⁱ —C4 ⁱ	-77.2 (4)
O2—Cr1—O1—Na1	79.2 (10)	O2 ⁱ —Na1—O2 ⁱⁱⁱ —Cr1 ⁱⁱⁱ	165.00 (18)
O2—Cr1—O1—C7	-48.7 (12)	O2 ⁱ —Na1—O2 ⁱⁱⁱ —C4 ⁱⁱⁱ	-77.2 (4)
O1—Cr1—O2 ⁱ —C4 ⁱ	-107.6 (4)	O2 ⁱⁱⁱ —Na1—O3—C17	91.2 (8)
O1—Cr1—O2 ⁱ —Na1	8.1 (2)	O3—Na1—O2 ⁱⁱⁱ —Cr1 ⁱⁱⁱ	-99.1 (2)
O2 ⁱ —Cr1—O1—Na1	-7.5 (2)	O3—Na1—O2 ⁱⁱⁱ —C4 ⁱⁱⁱ	18.7 (3)
O2 ⁱ —Cr1—O1—C7	-135.4 (4)	O2 ⁱⁱⁱ —Na1—O3 ⁱⁱ —C17 ⁱⁱ	-144.3 (8)
O1—Cr1—N1—N2	25.7 (4)	O3 ⁱⁱ —Na1—O2 ⁱⁱⁱ —Cr1 ⁱⁱⁱ	72.5 (2)
O1—Cr1—N1—C5	-161.3 (3)	O3 ⁱⁱ —Na1—O2 ⁱⁱⁱ —C4 ⁱⁱⁱ	-169.7 (3)
N1—Cr1—O1—Na1	92.39 (18)	O2 ⁱ —Na1—O3—C17	-144.3 (8)
N1—Cr1—O1—C7	-35.5 (4)	O3—Na1—O2 ⁱ —Cr1	72.5 (2)
O1—Cr1—N1 ⁱ —N2 ⁱ	-66.1 (4)	O3—Na1—O2 ⁱ —C4 ⁱ	-169.7 (3)
O1—Cr1—N1 ⁱ —C5 ⁱ	106.9 (3)	O2 ⁱ —Na1—O3 ⁱⁱ —C17 ⁱⁱ	91.2 (8)
N1 ⁱ —Cr1—O1—Na1	-89.70 (18)	O3 ⁱⁱ —Na1—O2 ⁱ —Cr1	-99.1 (2)
N1 ⁱ —Cr1—O1—C7	142.4 (4)	O3 ⁱⁱ —Na1—O2 ⁱ —C4 ⁱ	18.7 (3)
O1 ⁱ —Cr1—O2—C4	-107.6 (4)	Cr1—O1—C7—C8	-148.7 (4)
O1 ⁱ —Cr1—O2—Na1 ^{iv}	8.1 (2)	Cr1—O1—C7—C16	32.3 (7)
O2—Cr1—O1 ⁱ —C7 ⁱ	-135.4 (4)	Na1—O1—C7—C8	91.2 (5)
O1 ⁱ —Cr1—O2 ⁱ —C4 ⁱ	-3.6 (12)	Na1—O1—C7—C16	-87.7 (6)
O1 ⁱ —Cr1—O2 ⁱ —Na1	112.2 (9)	Cr1—O2—C4—C3	-166.3 (5)
O2 ⁱ —Cr1—O1 ⁱ —C7 ⁱ	-48.7 (12)	Cr1—O2—C4—C5	15.4 (6)
O1 ⁱ —Cr1—N1—N2	-66.1 (4)	Na1 ^{iv} —O2—C4—C3	80.3 (6)
O1 ⁱ —Cr1—N1—C5	106.9 (3)	Na1 ^{iv} —O2—C4—C5	-98.0 (5)
N1—Cr1—O1 ⁱ —C7 ⁱ	142.4 (4)	Na1—O3—C17—C18	178.8 (6)
O1 ⁱ —Cr1—N1 ⁱ —N2 ⁱ	25.7 (4)	Na1—O3—C17—C19	-3.9 (12)
O1 ⁱ —Cr1—N1 ⁱ —C5 ⁱ	-161.3 (3)	Cr1—N1—N2—C16	-5.7 (7)
N1 ⁱ —Cr1—O1 ⁱ —C7 ⁱ	-35.5 (4)	Cr1—N1—C5—C4	-12.3 (6)
O2—Cr1—O2 ⁱ —C4 ⁱ	83.4 (4)	Cr1—N1—C5—C6	170.9 (5)
O2—Cr1—O2 ⁱ —Na1	-160.9 (2)	N2—N1—C5—C4	161.7 (5)
O2 ⁱ —Cr1—O2—C4	83.4 (4)	N2—N1—C5—C6	-15.0 (8)
O2 ⁱ —Cr1—O2—Na1 ^{iv}	-160.9 (2)	C5—N1—N2—C16	-178.4 (4)
O2—Cr1—N1—N2	-156.8 (4)	N1—N2—C16—C7	-13.7 (8)
O2—Cr1—N1—C5	16.2 (3)	N1—N2—C16—C15	168.4 (4)
N1—Cr1—O2—C4	-16.9 (3)	Cl1—C1—C2—C3	-179.3 (4)
N1—Cr1—O2—Na1 ^{iv}	98.9 (2)	Cl1—C1—C6—C5	176.7 (4)
O2—Cr1—N1 ⁱ —N2 ⁱ	116.1 (4)	C2—C1—C6—C5	-1.8 (9)
O2—Cr1—N1 ⁱ —C5 ⁱ	-71.0 (3)	C6—C1—C2—C3	-0.8 (9)
N1 ⁱ —Cr1—O2—C4	165.2 (3)	C1—C2—C3—C4	1.2 (9)

supplementary materials

N1 ⁱ —Cr1—O2—Na1 ^{iv}	-79.1 (2)	C2—C3—C4—O2	-177.5 (5)
O2 ⁱ —Cr1—N1—N2	116.1 (4)	C2—C3—C4—C5	0.9 (9)
O2 ⁱ —Cr1—N1—C5	-71.0 (3)	O2—C4—C5—N1	-2.0 (8)
N1—Cr1—O2 ⁱ —C4 ⁱ	165.2 (3)	O2—C4—C5—C6	175.0 (5)
N1—Cr1—O2 ⁱ —Na1	-79.1 (2)	C3—C4—C5—N1	179.6 (5)
O2 ⁱ —Cr1—N1 ⁱ —N2 ⁱ	-156.8 (4)	C3—C4—C5—C6	-3.5 (9)
O2 ⁱ —Cr1—N1 ⁱ —C5 ⁱ	16.2 (3)	N1—C5—C6—C1	-179.6 (5)
N1 ⁱ —Cr1—O2 ⁱ —C4 ⁱ	-16.9 (3)	C4—C5—C6—C1	4.0 (9)
N1 ⁱ —Cr1—O2 ⁱ —Na1	98.9 (2)	O1—C7—C8—C9	179.7 (5)
O1—Na1—O1 ⁱⁱ —C7 ⁱⁱ	-52.4 (4)	O1—C7—C16—N2	-0.9 (9)
O1 ⁱⁱ —Na1—O1—Cr1	177.19 (16)	O1—C7—C16—C15	176.9 (5)
O1 ⁱⁱ —Na1—O1—C7	-52.4 (4)	C8—C7—C16—N2	-179.8 (5)
O1—Na1—O2 ⁱⁱⁱ —Cr1 ⁱⁱⁱ	-56.8 (9)	C8—C7—C16—C15	-2.1 (8)
O1—Na1—O2 ⁱⁱⁱ —C4 ⁱⁱⁱ	61.0 (10)	C16—C7—C8—C9	-1.2 (8)
O2 ⁱⁱⁱ —Na1—O1—Cr1	-135.9 (8)	C7—C8—C9—C10	2.8 (9)
O2 ⁱⁱⁱ —Na1—O1—C7	-5.5 (10)	C8—C9—C10—C11	178.5 (6)
O1—Na1—O2 ⁱ —Cr1	-6.48 (17)	C8—C9—C10—C15	-1.0 (9)
O1—Na1—O2 ⁱ —C4 ⁱ	111.3 (3)	C9—C10—C11—C12	-177.2 (5)
O2 ⁱ —Na1—O1—Cr1	6.53 (17)	C9—C10—C15—C14	178.7 (5)
O2 ⁱ —Na1—O1—C7	137.0 (4)	C9—C10—C15—C16	-2.1 (8)
O1—Na1—O3—C17	-80.9 (8)	C11—C10—C15—C14	-0.8 (8)
O3—Na1—O1—Cr1	-93.2 (2)	C11—C10—C15—C16	178.4 (5)
O3—Na1—O1—C7	37.2 (4)	C15—C10—C11—C12	2.3 (8)
O1—Na1—O3 ⁱⁱ —C17 ⁱⁱ	26.8 (8)	C10—C11—C12—C13	-2.8 (9)
O3 ⁱⁱ —Na1—O1—Cr1	94.5 (2)	C11—C12—C13—C14	1.7 (9)
O3 ⁱⁱ —Na1—O1—C7	-135.0 (4)	C12—C13—C14—C15	-0.2 (7)
O1 ⁱⁱ —Na1—O2 ⁱⁱⁱ —Cr1 ⁱⁱⁱ	-6.48 (17)	C13—C14—C15—C10	-0.2 (7)
O1 ⁱⁱ —Na1—O2 ⁱⁱⁱ —C4 ⁱⁱⁱ	111.3 (3)	C13—C14—C15—C16	-179.3 (5)
O2 ⁱⁱⁱ —Na1—O1 ⁱⁱ —C7 ⁱⁱ	137.0 (4)	C10—C15—C16—N2	-178.3 (4)
O1 ⁱⁱ —Na1—O2 ⁱ —Cr1	-56.8 (9)	C10—C15—C16—C7	3.7 (8)
O1 ⁱⁱ —Na1—O2 ⁱ —C4 ⁱ	61.0 (9)	C14—C15—C16—N2	0.8 (8)
O2 ⁱ —Na1—O1 ⁱⁱ —C7 ⁱⁱ	-5.5 (10)	C14—C15—C16—C7	-177.2 (5)
O1 ⁱⁱ —Na1—O3—C17	26.8 (8)		

Symmetry codes: (i) $x, -y+1/2, -z+1/2$; (ii) $x, -y+1/2, -z-1/2$; (iii) $x, y, z-1$; (iv) $x, y, z+1$.

Fig. 1

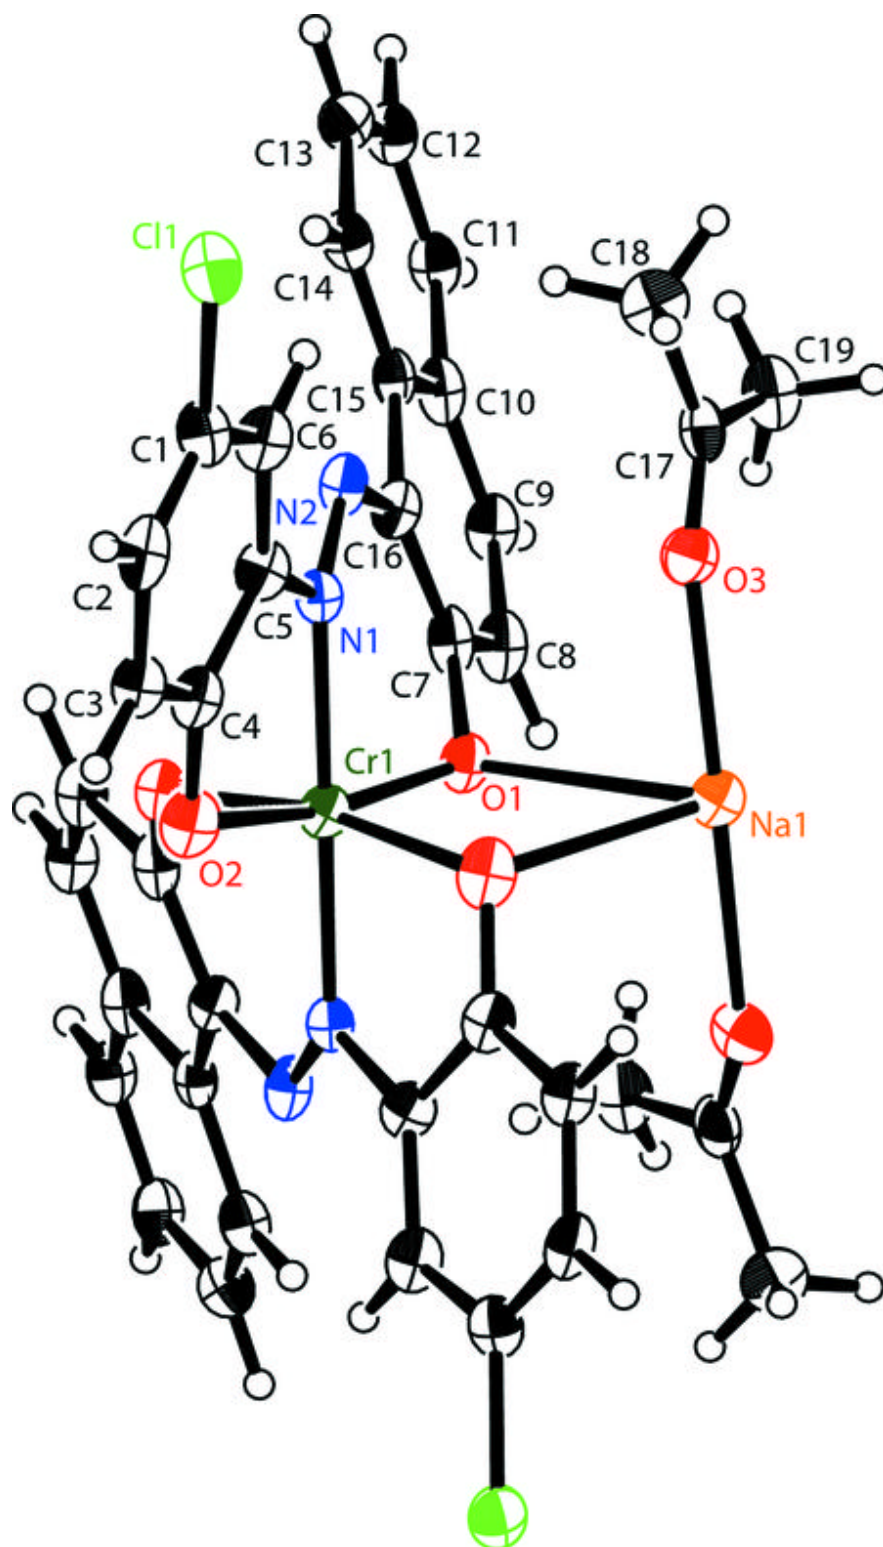


Fig. 2

