

Poly[tris(μ_4 -5-aminoisophthalato)diaqua-dilanthanum(III)]

Tham Weng-Thim,^a Rohana Adnan,^a Hoong-Kun Fun^{b*} and Samuel Robinson Jebas^{b‡}

^aSchool of Chemical Science, Universiti Sains Malaysia, 11800 USM, Penang, Malaysia, and ^bX-ray Crystallography Unit, School of Physics, Universiti Sains Malaysia, 11800 USM, Penang, Malaysia

Correspondence e-mail: hkfun@usm.my


Received 31 May 2008; accepted 22 June 2008

Key indicators: single-crystal X-ray study; $T = 100$ K; mean $\sigma(\text{C}-\text{C}) = 0.002$ Å; R factor = 0.025; wR factor = 0.074; data-to-parameter ratio = 37.1.

The title compound, $[\text{La}_2(\text{C}_8\text{H}_5\text{NO}_4)_3(\text{H}_2\text{O})_2]_n$, is a three-dimensional network coordination polymer in which each La^{III} ion is nine-coordinated by eight carboxylate O atoms from six 5-aminoisophthalate ligands and one O atom from a water molecule. One organic ligand lies on a twofold rotation axis. $\text{O}-\text{H}\cdots\text{O}$, $\text{O}-\text{H}\cdots\text{N}$ and $\text{N}-\text{H}\cdots\text{O}$ hydrogen bonds are observed in the crystal structure.

Related literature

For related literature on metal carboxylate complexes, see: Eddaoudi *et al.* (2002); Tao *et al.* (2000); Zheng *et al.* (2004). For related literature on aromatic polycarboxylic acids, see: Eddaoudi *et al.* (2000); Li *et al.* (1999); Lo *et al.* (2000); Qu *et al.* (2005); Rosi *et al.* (2002). For the coordination modes of lanthanides, see: Bond *et al.* (2000); Saleh *et al.* (1998). For bond length and angle data, see: Glunnlugson *et al.* (2004); Zheng *et al.* (2003); Drew *et al.* (2000).

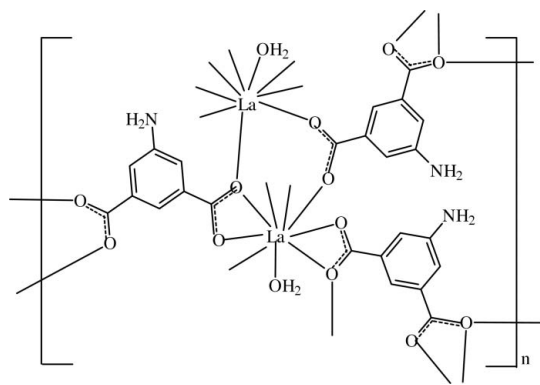

‡ Permanent address: Department of Physics, Karunya University, Karunya Nagar, Coimbatore 641 114, India.

Experimental

Crystal data

$[\text{La}_2(\text{C}_8\text{H}_5\text{NO}_4)_3(\text{H}_2\text{O})_2]$
 $M_r = 851.24$
 Orthorhombic, $Pbcn$
 $a = 12.2525$ (3) Å
 $b = 8.0521$ (2) Å
 $c = 25.6820$ (6) Å
 $V = 2533.74$ (11) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 3.41$ mm⁻¹
 $T = 100.0$ (1) K
 $0.36 \times 0.31 \times 0.06$ mm

Data collection

Bruker SMART APEXII CCD area-detector diffractometer
 Absorption correction: multi-scan (SADABS; Bruker, 2005)
 $T_{\text{min}} = 0.313$, $T_{\text{max}} = 0.822$
 68438 measured reflections
 7718 independent reflections
 6892 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.040$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.025$
 $wR(F^2) = 0.074$
 $S = 1.16$
 7718 reflections
 208 parameters
 5 restraints

H atoms treated by a mixture of independent and constrained refinement

$\Delta\rho_{\text{max}} = 1.54$ e Å⁻³
 $\Delta\rho_{\text{min}} = -1.24$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
$\text{O1W}-\text{H1OW}\cdots\text{O5}^{\text{i}}$	0.84	2.02	2.8354 (16)	164
$\text{O1W}-\text{H2OW}\cdots\text{N1}^{\text{ii}}$	0.84	2.02	2.817 (2)	157
$\text{N1}-\text{H1N1}\cdots\text{O4}^{\text{iii}}$	0.90 (1)	2.28 (2)	3.0929 (17)	150 (3)
$\text{N2}-\text{H1N2}\cdots\text{O4}^{\text{iv}}$	0.84 (1)	2.60 (2)	3.1953 (12)	129 (2)

Symmetry codes: (i) $-x + \frac{1}{2}, y + \frac{1}{2}, z$; (ii) $x + 1, y, z$; (iii) $-x - \frac{1}{2}, y - \frac{1}{2}, z$; (iv) $x + \frac{1}{2}, y + \frac{1}{2}, -z + \frac{1}{2}$.

Data collection: *APEX2* (Bruker, 2005); cell refinement: *APEX2*; data reduction: *SAINT* (Bruker, 2005); program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *SHELXTL*; software used to prepare material for publication: *SHELXTL* and *PLATON* (Spek, 2003).

FKH and SRJ thank the Malaysian Government and Universiti Sains Malaysia for the Science Fund grant No. 305/PFIZIK/613312. SRJ thanks Universiti Sains Malaysia for a post-doctoral fellowship.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: CI2610).

References

- Bond, D. L., Clark, D. L., Donohoe, R. J., Gordon, J. C., Gordon, P. L., Keogh, D. W., Scott, B. L., Tait, C. D. & Watkin, J. G. (2000). *Inorg. Chem.* **39**, 3934–3937.
 Bruker (2005). *APEX2*, *SAINT* and *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
 Drew, M. G. B., Hudson, M. J., Iveson, P. B., Madic, C. & Russel, M. L. (2000). *J. Chem. Soc. Dalton Trans.* pp. 2711–2720.
 Eddaoudi, M., Kim, J., Rosi, N., Vodak, D., Wochter, J., O'Keeffe, M. & Yaghi, O. (2002). *Mater. Sci.* **295**, 469–472.
 Eddaoudi, M., Li, H. & Yaghi, O. M. (2000). *J. Am. Chem. Soc.* **122**, 1391–1397.
 Glunnlugson, T., Leonard, J. P., Mulready, S. & Nieuwenhuyzen, M. (2004). *Tetrahedron*, **60**, 105–113.

- Li, H., Eddaoudi, M., O'Keeffe, M. & Yaghi, O. M. (1999). *Nature (London)*, **402**, 276–279.
- Lo, S. M. F., Chui, S. S. Y., Shek, L. Y., Lin, Z., Zhang, X. X., Wen, G. H. & Williams, I. D. (2000). *J. Am. Chem. Soc.* **122**, 6293–6294.
- Qu, Y. L., Ke, Y. X., Lu, S. M., Fan, R., Pan, G. Q. & Li, J. M. (2005). *J. Mol. Struct.* **734**, 7–13.
- Rosi, N. L., Eddaoudi, M., Kim, J., O'Keeffe, M. & Yaghi, O. M. (2002). *Angew. Chem.* **41**, 284–287.
- Saleh, M. I., Salhin, A., Saad, B., Zain, S. M., Rahman, N. A. & Ariffin, Z. (1998). *J. Mol. Struct.* **448**, 63–68.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Spek, A. L. (2003). *J. Appl. Cryst.* **36**, 7–13.
- Tao, J., Tong, M. L., Shi, J. X., Chen, X. M. & Ng, S. W. (2000). *Chem. Commun.* pp. 2043–2044.
- Zheng, X.-J. & Jin, L.-P. (2003). *Polyhedron*, **22**, 2617–2624.
- Zheng, S. L., Yang, J. H., Yu, X. L., Chen, X. M. & Wong, W. T. (2004). *Inorg. Chem.* **43**, 830–838.

supplementary materials

Acta Cryst. (2008). E64, m971-m972 [doi:10.1107/S1600536808018849]

Poly[tris(μ_4 -5-aminoisophthalato)diaquadilanthanum(III)]

T. Weng-Thim, R. Adnan, H.-K. Fun and S. R. Jebas

Comment

In recent years, interest has been focused on metal carboxylate complexes due to their potential applications as material for molecular recognition, ion exchange, catalysis and luminescence (Eddaoudi *et al.*, 2002; Tao *et al.*, 2000; Zheng *et al.*, 2004). Aromatic polycarboxylic acids such as 1,4-benzenedicarboxylic acid and 1,3-benzenedicarboxylic acid are used extensively in the synthesis of this type of coordination polymer (Eddaoudi *et al.*, 2000; Li *et al.*, 1999; Lo *et al.*, 2000; Qu *et al.*, 2005; Rosi *et al.*, 2002).

Aminoisophthalic acid is a potential multidentate ligand with trifunctional group that may generate structures of higher dimensions containing networks or channels. Its two carboxylic groups may be completely or partially deprotonated and thus results in versatile coordination modes. Meanwhile, lanthanide ions are known for their ability to display diverse coordination modes and high coordination number (Bond *et al.*, 2000; Saleh *et al.*, 1998). In addition to that, hard acid lanthanide ions prefer to coordinate with carboxyl groups belonging to hard base. In this paper, we report the crystal structure of a polymeric coordination complex formed from hydrothermal reaction between trivalent lanthanum ion and aminoisophthalic acid.

In the crystal structure of the title compound, each La^{III} ion is nine-coordinated by eight carboxylate O atoms from six 5-aminoisophthalate ligands and one O atom from a water molecule. The La—O bond lengths [2.4076 (11) Å–2.8015 (12) Å] and bond angles around the La^{III} ion agree well with the values reported for related lanthanum complexes (Glunlaugson *et al.*, 2004; Zheng *et al.*, 2003; Drew *et al.*, 2000).

The O—H \cdots O, O—H \cdots N and N—H \cdots O hydrogen bonds are observed in the crystal structure (Fig. 2).

Experimental

A mixture of 5-aminoisophthalic acid (0.273 g, 1.5 mmol), sodium hydroxide (0.120 g, 3 mmol) and distilled water (20 ml) was heated till boiling. The solution was left to cool and then poured into a 40 ml Teflon tube with La(NO₃).6H₂O (0.433 g, 1.0 mmol). The Teflon tube was sealed and heated at 403 K for 60 h, and then allowed to cool to room temperature. Pale clear-pink crystals obtained were filtered, washed with distilled water and left to dry in air (yield: 52% based on La).

Refinement

H atoms of the water molecule were located initially in a difference Fourier map and then constrained to ride on the parent O atom, with O—H = 0.84 Å and $U_{\text{iso}}(\text{H}) = 0.018 \text{ \AA}^2$. The amino H atoms were located in a difference map and were refined with a N—H distance restraint of 0.85 (1) or 0.90 (1) Å. The remaining H atoms were positioned geometrically [C—H = 0.93 Å] and refined using a riding model with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The highest residual density peak is located 0.61 Å from La1 and the deepest hole is located 0.57 Å from La1.

Figures

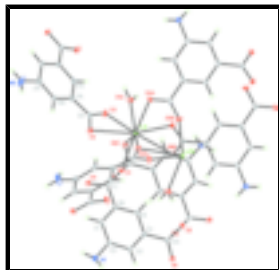


Fig. 1. Part of the three-dimensional coordination polymer, showing the coordination environment of the La^{III} ion. Displacement ellipsoids are drawn at the 50% probability level [symmetry codes: (A) $1/2-x, -1/2+y, z$; (B) $1/2+x, 1/2-y, -z$; (C) $-x, 1-y, -z$.]

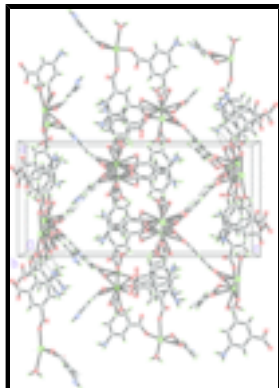


Fig. 2. A view of part of the coordination polymer of the title compound. Hydrogen bonds are shown as dashed lines.

Poly[tris(μ_4 -5-aminoisophthalato)diaquadilanthanum(III)]

Crystal data

$[\text{La}_2(\text{C}_8\text{H}_5\text{NO}_4)_3(\text{H}_2\text{O})_2]$

$M_r = 851.24$

Orthorhombic, *Pbcn*

Hall symbol: -P 2n 2ab

$a = 12.2525$ (3) Å

$b = 8.0521$ (2) Å

$c = 25.6820$ (6) Å

$V = 2533.74$ (11) Å³

$Z = 4$

$F_{000} = 1640$

$D_x = 2.221$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71073$ Å

Cell parameters from 9864 reflections

$\theta = 2.3\text{--}45.2^\circ$

$\mu = 3.41$ mm⁻¹

$T = 100.0$ (1) K

Plate, pink

$0.36 \times 0.31 \times 0.06$ mm

Data collection

Bruker SMART APEXII CCD area-detector diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 100.0$ (1) K

φ and ω scans

Absorption correction: multi-scan (SADABS; Bruker, 2005)

7718 independent reflections

6892 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.040$

$\theta_{\text{max}} = 40.0^\circ$

$\theta_{\text{min}} = 1.6^\circ$

$h = -22 \rightarrow 21$

$T_{\min} = 0.313$, $T_{\max} = 0.822$
68438 measured reflections

$k = -14 \rightarrow 14$
 $l = -45 \rightarrow 44$

Refinement

Refinement on F^2	Secondary atom site location: difference Fourier map
Least-squares matrix: full	Hydrogen site location: inferred from neighbouring sites
$R[F^2 > 2\sigma(F^2)] = 0.025$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.074$	$w = 1/[\sigma^2(F_o^2) + (0.0368P)^2 + 1.5159P]$
$S = 1.16$	where $P = (F_o^2 + 2F_c^2)/3$
7718 reflections	$(\Delta/\sigma)_{\max} = 0.001$
208 parameters	$\Delta\rho_{\max} = 1.54 \text{ e } \text{\AA}^{-3}$
5 restraints	$\Delta\rho_{\min} = -1.24 \text{ e } \text{\AA}^{-3}$
Primary atom site location: structure-invariant direct methods	Extinction correction: none

Special details

Experimental. The data was collected with the Oxford Cyrosystem Cobra low-temperature attachment.

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
La1	0.305761 (5)	0.465168 (9)	0.094499 (3)	0.00725 (3)
O1	0.11915 (9)	0.55822 (16)	0.09118 (5)	0.01427 (19)
O2	0.29520 (8)	0.76545 (14)	0.14936 (5)	0.01260 (17)
O3	0.36750 (11)	0.54193 (13)	0.18450 (5)	0.0161 (2)
O4	0.03641 (8)	0.77482 (13)	0.12749 (5)	0.01283 (17)
O5	-0.11694 (8)	0.16092 (13)	-0.01083 (4)	0.01261 (17)
O6	-0.27525 (9)	0.27524 (13)	-0.03252 (4)	0.01193 (16)
O1W	0.48255 (8)	0.60804 (14)	0.07751 (5)	0.01474 (18)
H1OW	0.5115	0.6313	0.0488	0.018*
H2OW	0.5309	0.6145	0.1009	0.018*
N1	-0.35537 (11)	0.53130 (17)	0.15151 (6)	0.0164 (2)
N2	0.5000	1.2332 (3)	0.2500	0.0265 (5)
C1	-0.16182 (11)	0.57505 (17)	0.13169 (6)	0.0116 (2)

supplementary materials

H1	-0.1544	0.6421	0.1610	0.014*
C2	-0.26282 (11)	0.50210 (18)	0.12013 (6)	0.0117 (2)
C3	-0.27434 (10)	0.40880 (17)	0.07446 (6)	0.0112 (2)
H3	-0.3426	0.3692	0.0647	0.013*
C4	-0.18356 (10)	0.37549 (16)	0.04371 (6)	0.0102 (2)
C5	-0.08197 (11)	0.44158 (16)	0.05646 (6)	0.0108 (2)
H5	-0.0209	0.4155	0.0365	0.013*
C6	-0.07239 (11)	0.54677 (16)	0.09915 (6)	0.0100 (2)
C7	0.03462 (10)	0.63224 (16)	0.10726 (6)	0.01037 (19)
C8	0.35819 (11)	0.69799 (17)	0.18250 (6)	0.0111 (2)
C9	0.42765 (11)	0.80015 (16)	0.21813 (6)	0.0114 (2)
C10	0.42555 (12)	0.97334 (16)	0.21897 (6)	0.0123 (2)
H10	0.3747	1.0303	0.1989	0.015*
C11	0.5000	1.0623 (3)	0.2500	0.0135 (3)
C12	0.5000	0.7136 (2)	0.2500	0.0124 (3)
H12	0.5000	0.5981	0.2500	0.015*
C13	-0.19263 (10)	0.26435 (17)	-0.00240 (6)	0.0099 (2)
H1N1	-0.399 (2)	0.443 (2)	0.1564 (11)	0.023 (7)*
H1N2	0.5414 (19)	1.281 (3)	0.2714 (9)	0.028 (7)*
H2N1	-0.342 (2)	0.571 (3)	0.1839 (6)	0.018 (6)*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
La1	0.00651 (4)	0.00736 (4)	0.00789 (4)	-0.00013 (2)	0.00015 (2)	-0.00035 (2)
O1	0.0076 (4)	0.0187 (5)	0.0165 (5)	0.0020 (3)	0.0003 (3)	-0.0007 (4)
O2	0.0128 (4)	0.0130 (4)	0.0120 (5)	0.0016 (3)	-0.0042 (3)	0.0008 (3)
O3	0.0223 (5)	0.0101 (4)	0.0160 (5)	0.0014 (3)	-0.0076 (4)	-0.0013 (3)
O4	0.0122 (4)	0.0111 (4)	0.0153 (5)	-0.0026 (3)	-0.0004 (3)	-0.0009 (3)
O5	0.0127 (4)	0.0129 (4)	0.0122 (5)	0.0030 (3)	-0.0022 (3)	-0.0024 (3)
O6	0.0107 (4)	0.0133 (4)	0.0118 (5)	0.0004 (3)	-0.0025 (3)	-0.0001 (3)
O1W	0.0108 (4)	0.0170 (5)	0.0163 (5)	-0.0029 (3)	0.0008 (3)	0.0023 (4)
N1	0.0108 (5)	0.0231 (6)	0.0153 (6)	-0.0028 (4)	0.0031 (4)	-0.0054 (4)
N2	0.0457 (13)	0.0095 (7)	0.0244 (11)	0.000	-0.0211 (10)	0.000
C1	0.0093 (5)	0.0122 (5)	0.0133 (6)	-0.0010 (3)	0.0002 (4)	-0.0023 (4)
C2	0.0098 (5)	0.0130 (5)	0.0123 (6)	-0.0006 (4)	0.0004 (4)	-0.0012 (4)
C3	0.0098 (4)	0.0119 (5)	0.0120 (6)	-0.0009 (3)	-0.0003 (4)	-0.0010 (4)
C4	0.0109 (5)	0.0092 (5)	0.0104 (6)	-0.0003 (3)	-0.0007 (4)	-0.0009 (4)
C5	0.0102 (4)	0.0107 (5)	0.0114 (6)	-0.0003 (3)	-0.0001 (4)	-0.0004 (4)
C6	0.0086 (5)	0.0095 (5)	0.0120 (6)	-0.0004 (3)	-0.0008 (4)	-0.0002 (4)
C7	0.0088 (4)	0.0114 (5)	0.0109 (5)	-0.0007 (3)	-0.0011 (4)	0.0010 (4)
C8	0.0119 (5)	0.0113 (5)	0.0101 (5)	0.0013 (3)	-0.0021 (4)	-0.0015 (4)
C9	0.0133 (5)	0.0108 (5)	0.0102 (5)	0.0003 (3)	-0.0032 (4)	-0.0008 (4)
C10	0.0164 (5)	0.0093 (5)	0.0113 (6)	0.0018 (3)	-0.0036 (4)	-0.0004 (4)
C11	0.0190 (8)	0.0098 (7)	0.0116 (8)	0.000	-0.0038 (6)	0.000
C12	0.0144 (7)	0.0098 (7)	0.0129 (8)	0.000	-0.0046 (6)	0.000
C13	0.0106 (5)	0.0100 (5)	0.0093 (5)	-0.0003 (3)	-0.0004 (4)	-0.0001 (4)

Geometric parameters (Å, °)

La1—O1	2.4076 (11)	N1—H2N1	0.91 (1)
La1—O2 ⁱ	2.4701 (11)	N2—C11	1.377 (3)
La1—O1W	2.4912 (10)	N2—H1N2	0.84 (1)
La1—O3	2.5093 (12)	C1—C6	1.397 (2)
La1—O5 ⁱⁱ	2.5585 (11)	C1—C2	1.4016 (19)
La1—O4 ⁱ	2.6089 (10)	C1—H1	0.93
La1—O6 ⁱⁱⁱ	2.6538 (11)	C2—C3	1.400 (2)
La1—O6 ⁱⁱ	2.6955 (11)	C3—C4	1.3902 (19)
La1—O2	2.8015 (12)	C3—H3	0.93
O1—C7	1.2643 (18)	C4—C5	1.3927 (18)
O2—C8	1.2708 (17)	C4—C13	1.489 (2)
O2—La1 ^{iv}	2.4701 (11)	C5—C6	1.390 (2)
O3—C8	1.2628 (17)	C5—H5	0.93
O4—C7	1.2604 (17)	C6—C7	1.4953 (18)
O4—La1 ^{iv}	2.6089 (10)	C8—C9	1.4961 (19)
O5—C13	1.2651 (17)	C9—C12	1.3933 (17)
O5—La1 ^v	2.5585 (11)	C9—C10	1.3949 (19)
O6—C13	1.2771 (17)	C10—C11	1.4071 (18)
O6—La1 ⁱⁱⁱ	2.6538 (11)	C10—H10	0.93
O6—La1 ^v	2.6955 (11)	C11—C10 ^{vi}	1.4071 (18)
O1W—H1OW	0.84	C12—C9 ^{vi}	1.3933 (17)
O1W—H2OW	0.84	C12—H12	0.93
N1—C2	1.411 (2)	C13—La1 ^v	3.0017 (14)
N1—H1N1	0.90 (1)		
O1—La1—O2 ⁱ	75.36 (4)	C2—N1—H1N1	115.5 (19)
O1—La1—O1W	132.52 (4)	C2—N1—H2N1	116.3 (18)
O2 ⁱ —La1—O1W	146.72 (4)	H1N1—N1—H2N1	105 (2)
O1—La1—O3	104.02 (4)	C11—N2—H1N2	117 (2)
O2 ⁱ —La1—O3	77.64 (4)	C6—C1—C2	119.84 (13)
O1W—La1—O3	77.61 (4)	C6—C1—H1	120.1
O1—La1—O5 ⁱⁱ	116.44 (4)	C2—C1—H1	120.1
O2 ⁱ —La1—O5 ⁱⁱ	113.96 (4)	C3—C2—C1	119.43 (12)
O1W—La1—O5 ⁱⁱ	73.40 (4)	C3—C2—N1	119.13 (12)
O3—La1—O5 ⁱⁱ	139.45 (4)	C1—C2—N1	121.25 (13)
O1—La1—O4 ⁱ	153.93 (4)	C4—C3—C2	119.92 (12)
O2 ⁱ —La1—O4 ⁱ	78.67 (3)	C4—C3—H3	120.0
O1W—La1—O4 ⁱ	71.56 (4)	C2—C3—H3	120.0
O3—La1—O4 ⁱ	67.80 (4)	C3—C4—C5	120.51 (13)
O5 ⁱⁱ —La1—O4 ⁱ	76.42 (4)	C3—C4—C13	120.55 (11)
O1—La1—O6 ⁱⁱⁱ	66.41 (4)	C5—C4—C13	118.91 (12)
O2 ⁱ —La1—O6 ⁱⁱⁱ	141.66 (3)	C6—C5—C4	119.58 (13)

supplementary materials

O1W—La1—O6 ⁱⁱⁱ	69.74 (4)	C6—C5—H5	120.2
O3—La1—O6 ⁱⁱⁱ	113.64 (3)	C4—C5—H5	120.2
O5 ⁱⁱ —La1—O6 ⁱⁱⁱ	82.01 (4)	C5—C6—C1	120.32 (12)
O4 ⁱ —La1—O6 ⁱⁱⁱ	139.64 (3)	C5—C6—C7	117.66 (12)
O1—La1—O6 ⁱⁱ	81.54 (4)	C1—C6—C7	121.98 (12)
O2 ⁱ —La1—O6 ⁱⁱ	71.63 (4)	O4—C7—O1	123.35 (13)
O1W—La1—O6 ⁱⁱ	123.26 (4)	O4—C7—C6	119.47 (12)
O3—La1—O6 ⁱⁱ	146.29 (3)	O1—C7—C6	117.12 (12)
O5 ⁱⁱ —La1—O6 ⁱⁱ	49.86 (3)	O3—C8—O2	120.49 (13)
O4 ⁱ —La1—O6 ⁱⁱ	92.45 (3)	O3—C8—C9	118.09 (12)
O6 ⁱⁱⁱ —La1—O6 ⁱⁱ	99.18 (3)	O2—C8—C9	121.33 (12)
O1—La1—O2	72.86 (4)	O3—C8—La1	55.20 (8)
O2 ⁱ —La1—O2	104.59 (4)	O2—C8—La1	68.49 (8)
O1W—La1—O2	74.31 (4)	C9—C8—La1	157.57 (9)
O3—La1—O2	48.55 (3)	C12—C9—C10	120.17 (13)
O5 ⁱⁱ —La1—O2	141.45 (3)	C12—C9—C8	116.50 (12)
O4 ⁱ —La1—O2	112.21 (3)	C10—C9—C8	123.28 (13)
O6 ⁱⁱⁱ —La1—O2	67.38 (3)	C9—C10—C11	120.37 (14)
O6 ⁱⁱ —La1—O2	154.13 (3)	C9—C10—H10	119.8
C7—O1—La1	155.94 (10)	C11—C10—H10	119.8
C8—O2—La1 ^{iv}	164.67 (10)	N2—C11—C10	120.59 (9)
C8—O2—La1	86.55 (8)	N2—C11—C10 ^{vi}	120.59 (9)
La1 ^{iv} —O2—La1	107.35 (4)	C10—C11—C10 ^{vi}	118.81 (18)
C8—O3—La1	100.39 (9)	C9 ^{vi} —C12—C9	119.99 (18)
C7—O4—La1 ^{iv}	114.46 (9)	C9 ^{vi} —C12—H12	120.0
C13—O5—La1 ^v	97.67 (9)	C9—C12—H12	120.0
C13—O6—La1 ⁱⁱⁱ	121.94 (9)	O5—C13—O6	121.52 (13)
C13—O6—La1 ^v	90.94 (8)	O5—C13—C4	118.50 (12)
La1 ⁱⁱⁱ —O6—La1 ^v	105.27 (4)	O6—C13—C4	119.99 (12)
La1—O1W—H1OW	128.6	O5—C13—La1 ^v	57.64 (7)
La1—O1W—H2OW	120.9	O6—C13—La1 ^v	63.88 (8)
H1OW—O1W—H2OW	108.3	C4—C13—La1 ^v	175.99 (9)
O2 ⁱ —La1—O1—C7	81.4 (3)	La1—O3—C8—O2	21.93 (16)
O1W—La1—O1—C7	-77.4 (3)	La1—O3—C8—C9	-154.83 (11)
O3—La1—O1—C7	8.5 (3)	La1 ^{iv} —O2—C8—O3	-174.7 (3)
O5 ⁱⁱ —La1—O1—C7	-168.8 (2)	La1—O2—C8—O3	-19.25 (14)
O4 ⁱ —La1—O1—C7	76.4 (3)	La1 ^{iv} —O2—C8—C9	1.9 (5)
O6 ⁱⁱⁱ —La1—O1—C7	-101.5 (3)	La1—O2—C8—C9	157.41 (13)
O6 ⁱⁱ —La1—O1—C7	154.5 (3)	La1 ^{iv} —O2—C8—La1	-155.5 (4)
O2—La1—O1—C7	-29.2 (3)	O1—La1—C8—O3	120.56 (10)
C13 ⁱⁱ —La1—O1—C7	172.0 (3)	O2 ⁱ —La1—C8—O3	45.09 (10)
C8—La1—O1—C7	-13.0 (3)	O1W—La1—C8—O3	-104.47 (10)

O1—La1—O2—C8	138.62 (9)	O5 ⁱⁱ —La1—C8—O3	-97.27 (11)
O2 ⁱ —La1—O2—C8	69.33 (7)	O4 ⁱ —La1—C8—O3	-33.35 (10)
O1W—La1—O2—C8	-76.18 (9)	O6 ⁱⁱⁱ —La1—C8—O3	-173.07 (10)
O3—La1—O2—C8	10.99 (8)	O6 ⁱⁱ —La1—C8—O3	58.48 (19)
O5 ⁱⁱ —La1—O2—C8	-110.23 (9)	O2—La1—C8—O3	159.76 (15)
O4 ⁱ —La1—O2—C8	-14.18 (9)	C13 ⁱⁱ —La1—C8—O3	-82.2 (2)
O6 ⁱⁱⁱ —La1—O2—C8	-150.35 (9)	O1—La1—C8—O2	-39.20 (9)
O6 ⁱⁱ —La1—O2—C8	147.23 (9)	O2 ⁱ —La1—C8—O2	-114.68 (7)
C13 ⁱⁱ —La1—O2—C8	-148.28 (9)	O1W—La1—C8—O2	95.77 (9)
O1—La1—O2—La1 ^{iv}	-47.98 (4)	O3—La1—C8—O2	-159.76 (15)
O2 ⁱ —La1—O2—La1 ^{iv}	-117.27 (6)	O5 ⁱⁱ —La1—C8—O2	102.97 (9)
O1W—La1—O2—La1 ^{iv}	97.22 (5)	O4 ⁱ —La1—C8—O2	166.88 (8)
O3—La1—O2—La1 ^{iv}	-175.61 (7)	O6 ⁱⁱⁱ —La1—C8—O2	27.17 (8)
O5 ⁱⁱ —La1—O2—La1 ^{iv}	63.17 (6)	O6 ⁱⁱ —La1—C8—O2	-101.28 (16)
O4 ⁱ —La1—O2—La1 ^{iv}	159.22 (4)	C13 ⁱⁱ —La1—C8—O2	118.03 (17)
O6 ⁱⁱⁱ —La1—O2—La1 ^{iv}	23.04 (4)	O1—La1—C8—C9	-159.9 (3)
O6 ⁱⁱ —La1—O2—La1 ^{iv}	-39.37 (10)	O2 ⁱ —La1—C8—C9	124.7 (3)
C13 ⁱⁱ —La1—O2—La1 ^{iv}	25.12 (10)	O1W—La1—C8—C9	-24.9 (2)
C8—La1—O2—La1 ^{iv}	173.40 (11)	O3—La1—C8—C9	79.6 (3)
O1—La1—O3—C8	-62.50 (10)	O5 ⁱⁱ —La1—C8—C9	-17.7 (3)
O2 ⁱ —La1—O3—C8	-133.75 (10)	O4 ⁱ —La1—C8—C9	46.2 (3)
O1W—La1—O3—C8	68.68 (10)	O6 ⁱⁱⁱ —La1—C8—C9	-93.5 (3)
O5 ⁱⁱ —La1—O3—C8	113.71 (10)	O6 ⁱⁱ —La1—C8—C9	138.1 (2)
O4 ⁱ —La1—O3—C8	143.60 (11)	O2—La1—C8—C9	-120.7 (3)
O6 ⁱⁱⁱ —La1—O3—C8	7.57 (11)	C13 ⁱⁱ —La1—C8—C9	-2.6 (4)
O6 ⁱⁱ —La1—O3—C8	-158.30 (8)	O3—C8—C9—C12	1.7 (2)
O2—La1—O3—C8	-11.23 (8)	O2—C8—C9—C12	-175.02 (12)
C13 ⁱⁱ —La1—O3—C8	152.93 (9)	La1—C8—C9—C12	-64.5 (3)
C6—C1—C2—C3	-3.4 (2)	O3—C8—C9—C10	179.15 (15)
C6—C1—C2—N1	-178.49 (14)	O2—C8—C9—C10	2.4 (2)
C1—C2—C3—C4	6.3 (2)	La1—C8—C9—C10	112.9 (2)
N1—C2—C3—C4	-178.49 (14)	C12—C9—C10—C11	3.2 (2)
C2—C3—C4—C5	-3.4 (2)	C8—C9—C10—C11	-174.17 (12)
C2—C3—C4—C13	174.65 (13)	C9—C10—C11—N2	178.42 (11)
C3—C4—C5—C6	-2.5 (2)	C9—C10—C11—C10 ^{vi}	-1.58 (11)
C13—C4—C5—C6	179.43 (13)	C10—C9—C12—C9 ^{vi}	-1.58 (11)
C4—C5—C6—C1	5.4 (2)	C8—C9—C12—C9 ^{vi}	175.93 (14)
C4—C5—C6—C7	-172.14 (13)	La1 ^v —O5—C13—O6	0.96 (15)
C2—C1—C6—C5	-2.4 (2)	La1 ^v —O5—C13—C4	-178.75 (10)
C2—C1—C6—C7	174.99 (13)	La1 ⁱⁱⁱ —O6—C13—O5	-109.60 (13)
La1 ^{iv} —O4—C7—O1	29.15 (18)	La1 ^v —O6—C13—O5	-0.90 (14)
La1 ^{iv} —O4—C7—C6	-147.91 (10)	La1 ⁱⁱⁱ —O6—C13—C4	70.10 (15)

supplementary materials

La1—O1—C7—O4	42.8 (3)	La1 ^v —O6—C13—C4	178.80 (11)
La1—O1—C7—C6	-140.0 (2)	La1 ⁱⁱⁱ —O6—C13—La1 ^v	-108.70 (8)
C5—C6—C7—O4	147.88 (14)	C3—C4—C13—O5	-138.65 (14)
C1—C6—C7—O4	-29.6 (2)	C5—C4—C13—O5	39.5 (2)
C5—C6—C7—O1	-29.36 (19)	C3—C4—C13—O6	41.6 (2)
C1—C6—C7—O1	153.14 (14)	C5—C4—C13—O6	-140.26 (14)

Symmetry codes: (i) $-x+1/2, y-1/2, z$; (ii) $x+1/2, -y+1/2, -z$; (iii) $-x, -y+1, -z$; (iv) $-x+1/2, y+1/2, z$; (v) $x-1/2, -y+1/2, -z$; (vi) $-x+1, y, -z+1/2$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O1W—H1OW \cdots O5 ^{iv}	0.84	2.02	2.8354 (16)	164
O1W—H2OW \cdots N1 ^{vii}	0.84	2.02	2.817 (2)	157
N1—H1N1 \cdots O4 ^{viii}	0.90 (1)	2.28 (2)	3.0929 (17)	150 (3)
N2—H1N2 \cdots O4 ^{ix}	0.84 (1)	2.60 (2)	3.1953 (12)	129 (2)

Symmetry codes: (iv) $-x+1/2, y+1/2, z$; (vii) $x+1, y, z$; (viii) $-x-1/2, y-1/2, z$; (ix) $x+1/2, y+1/2, -z+1/2$.

Fig. 1

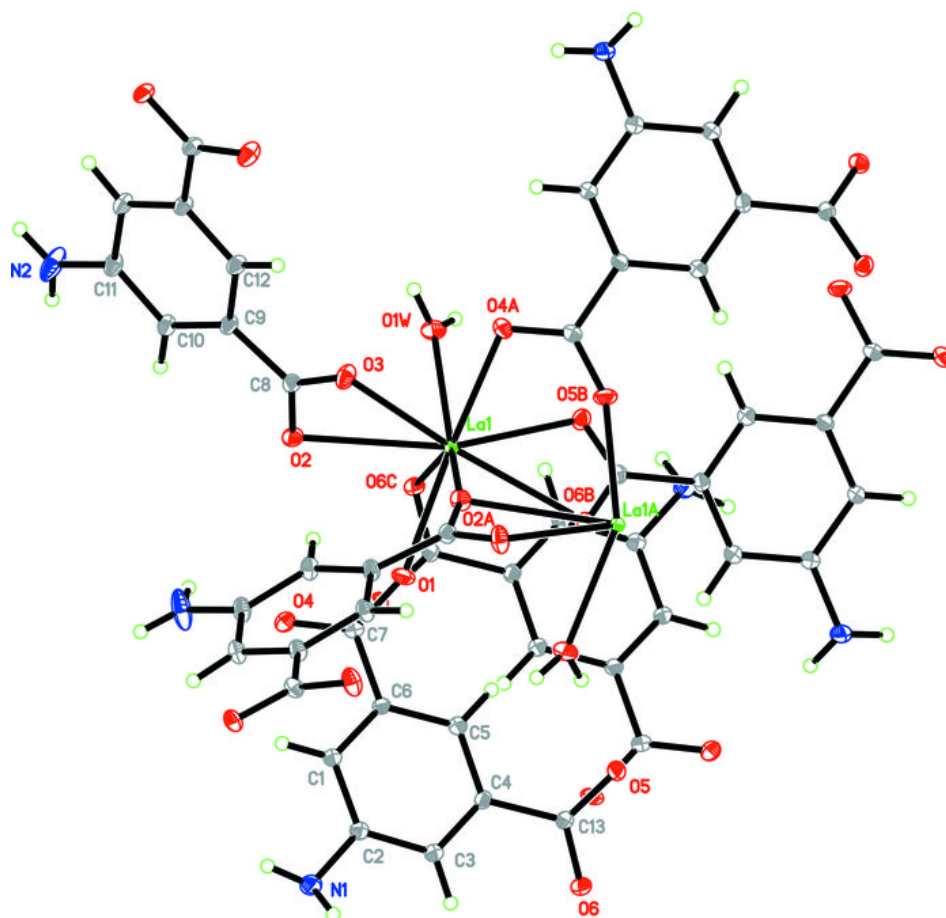


Fig. 2

