

catena-Poly[[bis(pyridine- κ N)nickel(II)]- μ -oxalato- κ^4 O¹,O²:O^{1'},O^{2'}]

Zhen-Yu Xuan,* Yong Che and Yong-Chun Huang

Department of Laboratory and Equipment Management, Yanbian University, Yanbian 133002, People's Republic of China

Correspondence e-mail: zyxuanchem@yahoo.com


Received 6 July 2008; accepted 12 July 2008

 Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.042; wR factor = 0.103; data-to-parameter ratio = 17.5.

The title compound, $[\text{Ni}(\text{C}_2\text{O}_4)(\text{C}_5\text{H}_5\text{N})_2]_n$, was synthesized under hydro(solvo)thermal conditions. The Ni^{II} atom, lying on a twofold rotation axis, has an octahedral coordination geometry involving two N atoms from two pyridine ligands and four O atoms from two oxalate ligands. The Ni atoms are connected by the tetradentate bridging oxalate ligands into a one-dimensional zigzag chain.

Related literature

For related literature, see: Lu *et al.* (1999); Vaidhyanathan *et al.* (2002); Wang *et al.* (2007); Yao *et al.* (2007).

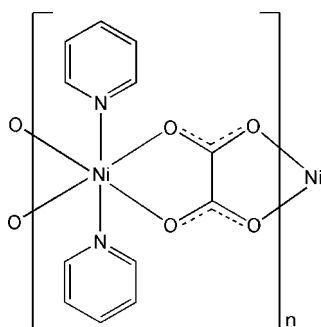

Experimental

Crystal data

$[\text{Ni}(\text{C}_2\text{O}_4)(\text{C}_5\text{H}_5\text{N})_2]$
 $M_r = 304.93$
 Monoclinic, $C2/c$
 $a = 14.357$ (3) Å
 $b = 10.801$ (2) Å
 $c = 8.6669$ (17) Å
 $\beta = 91.52$ (3)°

$V = 1343.5$ (5) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 1.45$ mm⁻¹
 $T = 293$ (2) K
 $0.26 \times 0.24 \times 0.22$ mm

Data collection

Rigaku R-AXIS RAPID diffractometer
 Absorption correction: multi-scan (*ABSCOR*; Higashi, 1995)
 $T_{\min} = 0.640$, $T_{\max} = 0.726$

6433 measured reflections
 1519 independent reflections
 1297 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.041$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.042$
 $wR(F^2) = 0.103$
 $S = 1.04$
 1519 reflections

87 parameters
 H-atom parameters constrained
 $\Delta\rho_{\max} = 0.73$ e Å⁻³
 $\Delta\rho_{\min} = -0.30$ e Å⁻³

Table 1

Selected geometric parameters (Å, °).

Ni1—O2 ⁱ	2.046 (2)	Ni1—N1	2.081 (2)
Ni1—O1	2.0716 (18)		
O2 ⁱ —Ni1—O2 ⁱⁱ	168.78 (10)	O2 ⁱⁱ —Ni1—N1	93.66 (9)
O2 ⁱ —Ni1—O1	89.88 (7)	O1—Ni1—N1	89.92 (9)
O2 ⁱⁱ —Ni1—O1	81.96 (7)	O1 ⁱⁱⁱ —Ni1—N1	174.81 (8)
O1—Ni1—O1 ⁱⁱⁱ	86.81 (11)	N1—Ni1—N1 ⁱⁱⁱ	93.61 (13)
O2 ⁱ —Ni1—N1	94.02 (8)		

Symmetry codes: (i) $x, -y + 1, z + \frac{1}{2}$; (ii) $-x + 1, -y + 1, -z$; (iii) $-x + 1, y, -z + \frac{1}{2}$.

Data collection: *PROCESS-AUTO* (Rigaku, 1998); cell refinement: *PROCESS-AUTO*; data reduction: *PROCESS-AUTO*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXTL*.

The authors thank Yanbian University for supporting this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2144).

References

- Higashi, T. (1995). *ABSCOR*. Rigaku Corporation, Tokyo, Japan.
 Lu, J.-Y., Lawandy, M.-A. & Li, J. (1999). *Inorg. Chem.* **38**, 2695–2704.
 Rigaku (1998). *PROCESS-AUTO*. Rigaku Corporation, Tokyo, Japan.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
 Vaidhyanathan, R., Natarajan, S. & Rao, C. N. R. (2002). *Inorg. Chem.* **41**, 4496–4501.
 Wang, G.-H., Li, Z.-G., Xu, J.-W. & Hu, N.-H. (2007). *Acta Cryst.* **E63**, m289–m291.
 Yao, H.-G., Ji, M., Ji, S.-H. & An, Y.-L. (2007). *Acta Cryst.* **E63**, m1349–m1350.

supplementary materials

Acta Cryst. (2008). E64, m1040 [doi:10.1107/S1600536808021703]

***catena*-Poly[[bis(pyridine- κ N)nickel(II)]- μ -oxalato- κ^4 O¹,O²:O^{1'},O^{2'}]**

Z.-Y. Xuan, Y. Che and Y.-C. Huang

Comment

Much research work has been done on metal–oxalate compounds, in the context of studies of molecular-based magnets and open framework structures (Lu *et al.*, 1999; Yao *et al.*, 2007). The geometrical coordination mode and strength of this ligand provide both rigidity and preferred coordination specificity for metal centers (Vaidhyanathan *et al.*, 2002; Wang *et al.*, 2007). In this paper, we report the hydro(solvo)thermal synthesis and structure of a new one-dimensional nickelous oxalate coordination polymer.

The title compound consists of one Ni^{II} atom lying on a twofold rotation axis, an oxalate ligand and two coordinated pyridine molecules (Fig. 1). The Ni^{II} atom exhibits a distorted octahedral geometry, defined by four O atoms of two oxalate ligands and two pyridine N atoms in a *cis* arrangement. The Ni—O distances are 2.046 (2) and 2.0716 (18) Å, while the O—Ni—O angles show distortions particularly as a result of chelation (Table 1). The tetradentate oxalate ligands link adjacent Ni atoms into a one-dimensional zigzag chain.

Experimental

A mixture of K₂C₂O₄·H₂O (0.037 g, 0.2 mmol), H₃BO₃ (0.013 g, 0.2 mmol), NiCl₂·2H₂O (0.033 g, 0.2 mmol), KOH (0.012 g, 0.2 mmol), pyridine (4 ml) and water (8 ml) in a 25 ml Teflon-lined stainless steel reactor was heated from 298 to 393 K in 2 h and maintained at 393 K for 72 h. After the mixture was cooled to 298 K, blue crystals of the title compound were obtained.

Refinement

H atoms were positioned geometrically and refined as riding atoms, with C—H = 0.93 Å and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$.

Figures

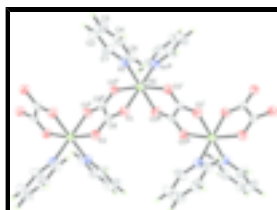


Fig. 1. Part of the polymeric structure of the title compound. Displacement ellipsoids are drawn at the 30% probability level. [Symmetry codes: (i) $x, 1-y, 1/2+z$; (ii) $1-x, 1-y, -z$; (iii) $1-x, y, 1/2-z$.]

catena-Poly[[bis(pyridine- κ N)nickel(II)]- μ -oxalato- κ^4 O¹,O²:O^{1'},O^{2'}]

Crystal data

[Ni(C₂O₄)(C₅H₅N)₂]

$M_r = 304.93$

Monoclinic, $C2/c$

Hall symbol: -C 2yc

$a = 14.357$ (3) Å

$b = 10.801$ (2) Å

$c = 8.6669$ (17) Å

$\beta = 91.52$ (3)°

$V = 1343.5$ (5) Å³

$Z = 4$

$F_{000} = 624$

$D_x = 1.508$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71073$ Å

Cell parameters from 1532 reflections

$\theta = 3.3$ – 27.5 °

$\mu = 1.45$ mm⁻¹

$T = 293$ (2) K

Block, blue

$0.26 \times 0.24 \times 0.22$ mm

Data collection

Rigaku R-Axis RAPID
diffractometer

Radiation source: rotating anode

Monochromator: graphite

Detector resolution: 10.0 pixels mm⁻¹

$T = 293$ (2) K

ω scans

Absorption correction: multi-scan
(ABSCOR; Higashi, 1995)

$T_{\min} = 0.640$, $T_{\max} = 0.726$

6433 measured reflections

1519 independent reflections

1297 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.041$

$\theta_{\max} = 27.5$ °

$\theta_{\min} = 3.3$ °

$h = -18 \rightarrow 18$

$k = -13 \rightarrow 13$

$l = -11 \rightarrow 10$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.042$

$wR(F^2) = 0.103$

$S = 1.04$

1519 reflections

87 parameters

Primary atom site location: structure-invariant direct
methods

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring
sites

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0487P)^2 + 1.5041P]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 0.73$ e Å⁻³

$\Delta\rho_{\min} = -0.30$ e Å⁻³

Extinction correction: none

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Ni1	0.5000	0.35667 (4)	0.2500	0.04167 (19)
O1	0.57949 (11)	0.49601 (17)	0.1553 (2)	0.0468 (4)
O2	0.57299 (12)	0.62481 (16)	-0.0453 (2)	0.0465 (4)
N1	0.59041 (14)	0.2248 (2)	0.1633 (3)	0.0491 (5)
C1	0.5679 (2)	0.1569 (3)	0.0391 (5)	0.0726 (10)
H1	0.5088	0.1664	-0.0059	0.090*
C2	0.6274 (3)	0.0743 (4)	-0.0251 (6)	0.0911 (13)
H2	0.6085	0.0290	-0.1116	0.090*
C3	0.7145 (3)	0.0584 (3)	0.0378 (5)	0.0790 (11)
H3	0.7558	0.0019	-0.0040	0.090*
C4	0.7395 (2)	0.1274 (4)	0.1630 (5)	0.0725 (10)
H4	0.7986	0.1190	0.2083	0.090*
C5	0.6764 (2)	0.2103 (3)	0.2231 (4)	0.0592 (8)
H5	0.6946	0.2577	0.3083	0.090*
C6	0.54390 (16)	0.5345 (2)	0.0324 (3)	0.0405 (5)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ni1	0.0290 (2)	0.0460 (3)	0.0499 (3)	0.000	-0.00167 (18)	0.000
O1	0.0341 (9)	0.0554 (11)	0.0503 (11)	-0.0087 (7)	-0.0082 (8)	0.0032 (8)
O2	0.0358 (9)	0.0508 (10)	0.0527 (11)	-0.0083 (7)	-0.0047 (8)	0.0002 (8)
N1	0.0351 (11)	0.0486 (12)	0.0637 (15)	0.0030 (9)	0.0034 (10)	0.0006 (10)
C1	0.0480 (17)	0.074 (2)	0.096 (3)	0.0063 (15)	-0.0007 (17)	-0.0296 (19)
C2	0.067 (2)	0.089 (3)	0.118 (3)	0.007 (2)	0.011 (2)	-0.043 (3)
C3	0.060 (2)	0.068 (2)	0.110 (3)	0.0157 (17)	0.025 (2)	-0.009 (2)
C4	0.0438 (16)	0.086 (2)	0.088 (3)	0.0185 (15)	0.0097 (16)	0.021 (2)
C5	0.0401 (14)	0.070 (2)	0.067 (2)	0.0114 (13)	0.0028 (13)	0.0074 (15)
C6	0.0293 (11)	0.0451 (13)	0.0470 (14)	-0.0015 (10)	0.0014 (10)	-0.0054 (11)

Geometric parameters (\AA , $^\circ$)

Ni1—O2 ⁱ	2.046 (2)	C1—C2	1.364 (5)
Ni1—O2 ⁱⁱ	2.046 (2)	C1—H1	0.9300
Ni1—O1	2.0716 (18)	C2—C3	1.362 (6)
Ni1—O1 ⁱⁱⁱ	2.0716 (18)	C2—H2	0.9300
Ni1—N1	2.081 (2)	C3—C4	1.357 (6)
Ni1—N1 ⁱⁱⁱ	2.081 (2)	C3—H3	0.9300
O1—C6	1.240 (3)	C4—C5	1.385 (5)
O2—C6	1.263 (3)	C4—H4	0.9300
O2—Ni1 ⁱⁱ	2.046 (2)	C5—H5	0.9300
N1—C1	1.335 (4)	C6—C6 ⁱⁱ	1.556 (4)
N1—C5	1.336 (3)		

supplementary materials

O2 ⁱ —Ni1—O2 ⁱⁱ	168.78 (10)	C5—N1—Ni1	121.3 (2)
O2 ⁱ —Ni1—O1	89.88 (7)	N1—C1—C2	123.1 (3)
O2 ⁱⁱ —Ni1—O1	81.96 (7)	N1—C1—H1	118.4
O2 ⁱ —Ni1—O1 ⁱⁱⁱ	81.96 (7)	C2—C1—H1	118.4
O2 ⁱⁱ —Ni1—O1 ⁱⁱⁱ	89.88 (7)	C3—C2—C1	119.9 (4)
O1—Ni1—O1 ⁱⁱⁱ	86.81 (11)	C3—C2—H2	120.1
O2 ⁱ —Ni1—N1	94.02 (8)	C1—C2—H2	120.1
O2 ⁱⁱ —Ni1—N1	93.66 (9)	C4—C3—C2	118.1 (3)
O1—Ni1—N1	89.92 (9)	C4—C3—H3	121.0
O1 ⁱⁱⁱ —Ni1—N1	174.81 (8)	C2—C3—H3	121.0
O2 ⁱ —Ni1—N1 ⁱⁱⁱ	93.66 (9)	C3—C4—C5	119.7 (3)
O2 ⁱⁱ —Ni1—N1 ⁱⁱⁱ	94.02 (8)	C3—C4—H4	120.2
O1—Ni1—N1 ⁱⁱⁱ	174.81 (8)	C5—C4—H4	120.2
O1 ⁱⁱⁱ —Ni1—N1 ⁱⁱⁱ	89.92 (9)	N1—C5—C4	122.4 (3)
N1—Ni1—N1 ⁱⁱⁱ	93.61 (13)	N1—C5—H5	118.8
C6—O1—Ni1	111.39 (15)	C4—C5—H5	118.8
C6—O2—Ni1 ⁱⁱ	111.64 (15)	O1—C6—O2	125.6 (2)
C1—N1—C5	116.8 (3)	O1—C6—C6 ⁱⁱ	117.5 (3)
C1—N1—Ni1	121.8 (2)	O2—C6—C6 ⁱⁱ	116.9 (3)

Symmetry codes: (i) $x, -y+1, z+1/2$; (ii) $-x+1, -y+1, -z$; (iii) $-x+1, y, -z+1/2$.

Fig. 1

