

## A second polymorph with composition $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$

Young Hoon Lee,<sup>a</sup> Jack K. Clegg,<sup>b</sup> Leonard F. Lindoy,<sup>b</sup>  
G. Q. Max Lu,<sup>c</sup> Yu-Chul Park<sup>a</sup> and Yang Kim<sup>d\*</sup>

<sup>a</sup>Department of Chemistry, Kyungpook National University, Daegu, 702-701, Republic of Korea, <sup>b</sup>Centre for Heavy Metals Research, School of Chemistry, F11, University of Sydney, New South Wales 2006, Australia, <sup>c</sup>ARC Centre of Excellence for Functional Nanomaterials, AIBN, University of Queensland, Brisbane, Queensland 4072, Australia, and <sup>d</sup>Department of Chemistry and Advanced Materials, Kosin University, 149-1 Dongsam-dong, Yeongdo-gu, Busan 606-701, Republic of Korea

Correspondence e-mail: ykim@kosin.ac.kr

Received 29 August 2008; accepted 4 September 2008

Key indicators: single-crystal X-ray study;  $T = 150$  K; mean  $\sigma(\text{P}=\text{O}) = 0.003$  Å;  $R$  factor = 0.033;  $wR$  factor = 0.095; data-to-parameter ratio = 12.8.

Single crystals of  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$ , tricobalt(II) bis[orthophosphate(V)] monohydrate, were obtained under hydrothermal conditions. The compound is the second polymorph of this composition and is isotypic with its zinc analogue,  $\text{Zn}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$ . Three independent  $\text{Co}^{2+}$  cations are bridged by two independent orthophosphate anions. Two of the metal cations exhibit a distorted tetrahedral coordination while the third exhibits a considerably distorted [5 + 1] octahedral coordination environment with one very long  $\text{Co}=\text{O}$  distance of 2.416 (3) Å. The former cations are bonded to four different phosphate anions, and the latter cation is bonded to four anions (one of which is bidentate) and one water molecule, leading to a framework structure. Additional hydrogen bonds of the type  $\text{O}-\text{H}\cdots\text{O}$  stabilize this arrangement.

### Related literature

Besides crystals of the title compound, crystals of the related phase  $\text{Co}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$  (Lee *et al.*, 2008) were also obtained under hydrothermal conditions. For a review of metal complexes of organophosphate esters and open-framework metal phosphates, see: Murugavel *et al.* (2008). For different cobalt(II) phosphates, see: Mellor (1935). The first polymorph of composition  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  was reported by Anderson *et al.* (1976), and the crystal structure of the isotypic Zn analogue  $\text{Zn}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  was described by Riou *et al.* (1986).

### Experimental

#### Crystal data

$\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$	$V = 704.1$ (2) Å <sup>3</sup>
$M_r = 384.75$	$Z = 4$
Monoclinic, $P2_1/c$	Mo $K\alpha$ radiation
$a = 8.7038$ (15) Å	$\mu = 7.47$ mm <sup>-1</sup>
$b = 4.8667$ (9) Å	$T = 150$ (2) K
$c = 16.705$ (3) Å	$0.46 \times 0.14 \times 0.08$ mm
$\beta = 95.670$ (3)°	

#### Data collection

Siemens SMART 1000 CCD diffractometer	6569 measured reflections
Absorption correction: multi-scan ( <i>SADABS</i> ; Sheldrick, 1999)	1697 independent reflections
$T_{\min} = 0.247$ , $T_{\max} = 0.554$	1603 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.026$

#### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.033$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.095$	$\Delta\rho_{\text{max}} = 0.73$ e Å <sup>-3</sup>
$S = 1.07$	$\Delta\rho_{\text{min}} = -1.39$ e Å <sup>-3</sup>
1697 reflections	
133 parameters	
2 restraints	

**Table 1**  
Selected bond lengths (Å).

Co1–O3	1.897 (3)	Co3–O8 <sup>ii</sup>	2.075 (3)
Co1–O4	1.941 (3)	Co3–O5 <sup>iii</sup>	2.108 (3)
Co1–O2	1.992 (3)	Co3–O3 <sup>iv</sup>	2.416 (3)
Co1–O1	2.002 (3)	P1–O6	1.513 (3)
Co2–O9	1.887 (3)	P1–O4 <sup>i</sup>	1.534 (3)
Co2–O5	1.949 (3)	P1–O2 <sup>v</sup>	1.560 (3)
Co2–O1	1.986 (3)	P1–O1	1.561 (3)
Co2–O2 <sup>i</sup>	2.054 (3)	P2–O9	1.511 (3)
Co3–O6	2.019 (3)	P2–O8 <sup>vi</sup>	1.544 (3)
Co3–O7	2.061 (3)	P2–O3 <sup>vii</sup>	1.549 (3)
Co3–O8	2.065 (3)	P2–O5 <sup>vi</sup>	1.565 (3)

Symmetry codes: (i)  $-x + 1, -y, -z + 2$ ; (ii)  $-x + 2, y + \frac{1}{2}, -z + \frac{3}{2}$ ; (iii)  $x, y + 1, z$ ; (iv)  $x + 1, y, z$ ; (v)  $-x + 1, -y + 1, -z + 2$ ; (vi)  $-x + 1, y - \frac{1}{2}, -z + \frac{3}{2}$ ; (vii)  $x, y - 1, z$ .

**Table 2**  
Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
O7–H2···O6 <sup>iii</sup>	0.90 (3)	1.86 (4)	2.753 (4)	170 (5)
O7–H1···O4 <sup>viii</sup>	0.903 (10)	1.864 (15)	2.758 (4)	171 (5)

Symmetry codes: (iii)  $x, y + 1, z$ ; (viii)  $x + 1, y + 1, z$ .

Data collection: *SMART* (Siemens, 1995); cell refinement: *SAINT* (Siemens, 1995); data reduction: *SAINT* and *XPREP* (Siemens, 1995); program(s) used to solve structure: *SIR97* (Altomare *et al.*, 1999); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP-3* (Farrugia, 1997), *WebLab ViewerPro* (Molecular Simulations, 2000) and *POV-RAY* (Cason, 2002); software used to prepare material for publication: *enCIFer* (Allen *et al.*, 2004).

We gratefully acknowledge the Brain Korea 21 programme and the Australian Research Council for support.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2194).

## References

- Allen, F. H., Johnson, O., Shields, G. P., Smith, B. R. & Towler, M. (2004). *J. Appl. Cryst.* **37**, 335–338.
- Altomare, A., Burla, M. C., Camalli, M., Cascarano, G. L., Giacovazzo, C., Guagliardi, A., Moliterni, A. G. G., Polidori, G. & Spagna, R. (1999). *J. Appl. Cryst.* **32**, 115–119.
- Anderson, J., Kostiner, E. & Ruszala, F. A. (1976). *Inorg. Chem.* **15**, 2744–2748.
- Cason, C. J. (2002). *POV-RAY*. Hallam Oaks Pty Ltd, Williamstown, Victoria, Australia.
- Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
- Lee, Y. H., Clegg, J. K., Lindoy, L. F., Lu, G. Q. M., Park, Y.-C. & Kim, Y. (2008). *Acta Cryst. E64*, i67–i68.
- Mellor, J. W. (1935). *Comprehensive Treatise on Inorganic Theoretical Chemistry*, Vol. XIV, p. 852. London: Longmans, Green Co.
- Molecular Simulations (2000). *WebLab ViewerPro*. Accelrys Software Inc., San Diego, California, USA.
- Murugavel, R., Choudhury, A., Walawalkar, M. G., Pothiraja, R. & Rao, C. N. R. (2008). *Chem. Rev.* **10**. doi: 10.1021/cr000119q.
- Riou, A., Cudennec, Y. & Gerault, Y. (1986). *Rev. Chim. Minéral.* **23**, 810–818.
- Sheldrick, G. M. (1999). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst. A64*, 112–122.
- Siemens (1995). *SMART*, *SAINT* and *XPREP*. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.

## **supplementary materials**

*Acta Cryst.* (2008). E64, i69–i70 [ doi:10.1107/S1600536808028365 ]

## A second polymorph with composition $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$

**Y. H. Lee, J. K. Clegg, L. F. Lindoy, G. Q. M. Lu, Y.-C. Park and Y. Kim**

### Comment

Synthesis and structural investigations of transition-metal phosphates under various conditions, including high temperature and high pressure, have been investigated for many years (Murugavel *et al.*, 2008). This is not only because of the multifarious structural chemistry, but also due to many potential applications. For a listing of reviews on these materials, see Lee *et al.* (2008). We are currently investigating the synthesis of a variety of similar functional materials through templation effects under hydrothermal conditions. The title compound,  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$ , (I), and the related compound  $\text{Co}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$  (Lee *et al.*, 2008) were synthesized as a part of these studies.

In the past, many different cobalt(II) orthophosphates have been described, ranging from the anhydrous form  $\text{Co}_3(\text{PO}_4)_2$  to its corresponding octahydrate (Mellor, 1935). In 1976 Anderson *et al.* reported a first polymorph of  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  formed under high pressure conditions. The second polymorph of  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  presented here has a different unit cell and a considerably different cell volume (638.3 (Anderson *et al.*, 1976) versus  $704.1 \text{ \AA}^3$  (this study)) and exhibits also a different assembly of the structural building units. The second polymorph (I) is isotypic with its Zn analogue  $\text{Zn}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  (Riou *et al.*, 1986).

The structure of (I) contains three different  $\text{Co}^{2+}$  centres bridged by orthophosphate anions (Fig 1). The coordination spheres of Co1 and Co2 are distorted tetrahedral while that of Co3 is distorted octahedral, with one considerably longer Co—O bond of 2.416 (3) Å (Table 1). Co1 and Co2 are bonded to the O atoms of four phosphate ligands, whereas Co3 is bonded to five O atoms of four phosphate ligands (one bidentate) and the sixth coordination site is occupied by a water molecule. This assembly leads to the formation of a three-dimensional framework (Fig. 2), which is stabilized by additional O—H···O hydrogen bonds (Table 2).

### Experimental

Conditions of the hydrothermal single crystal growth of the hydrous cobalt(II) orthophosphates  $\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  and  $\text{Co}_3(\text{PO}_4)_2 \cdot 4 \text{ H}_2\text{O}$  were described in detail in a preceding communication (Lee *et al.*, 2008).

### Refinement

Water H atoms were located in difference Fourier maps and were refined with  $U_{\text{iso}}(\text{H})$  values fixed at  $1.5U_{\text{eq}}$  of the parent O atoms. O—H bond length restraints of 0.89 (1) Å were also employed. The highest peak and the deepest hole in the final Fourier map are located 1.74 Å from O1 and 0.20 Å from P1, respectively.

# supplementary materials

---

## Figures

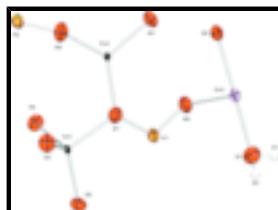


Fig. 1. The asymmetric unit of compound (I), drawn with displacement parameters at the 50% probability level. H atoms are given as spheres of arbitrary radius.

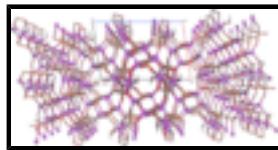


Fig. 2. A schematic representation of a section of the three-dimensional network of (I) in a projection along [010]. Hydrogen atoms are omitted for clarity.

## tricobalt(II) bis[orthophosphate(V)] monohydrate

### Crystal data

$\text{Co}_3(\text{PO}_4)_2 \cdot \text{H}_2\text{O}$	$F_{000} = 740$
$M_r = 384.75$	$D_x = 3.629 \text{ Mg m}^{-3}$
Monoclinic, $P2_1/c$	Mo $K\alpha$ radiation
Hall symbol: -P 2ybc	$\lambda = 0.71073 \text{ \AA}$
$a = 8.7038 (15) \text{ \AA}$	Cell parameters from 4684 reflections
$b = 4.8667 (9) \text{ \AA}$	$\theta = 2.5\text{--}28.4^\circ$
$c = 16.705 (3) \text{ \AA}$	$\mu = 7.47 \text{ mm}^{-1}$
$\beta = 95.670 (3)^\circ$	$T = 150 (2) \text{ K}$
$V = 704.1 (2) \text{ \AA}^3$	Plate, purple
$Z = 4$	$0.46 \times 0.14 \times 0.08 \text{ mm}$

### Data collection

Siemens SMART 1000 CCD diffractometer	1697 independent reflections
Radiation source: sealed tube	1603 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.026$
$T = 150(2) \text{ K}$	$\theta_{\text{max}} = 28.4^\circ$
$\omega$ scans	$\theta_{\text{min}} = 2.4^\circ$
Absorption correction: multi-scan (SADABS; Sheldrick, 1999)	$h = -11 \rightarrow 11$
$T_{\text{min}} = 0.247$ , $T_{\text{max}} = 0.554$	$k = -6 \rightarrow 6$
6569 measured reflections	$l = -21 \rightarrow 21$

### Refinement

Refinement on $F^2$	Secondary atom site location: difference Fourier map
Least-squares matrix: full	Hydrogen site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.033$	H atoms treated by a mixture of

	independent and constrained refinement
$wR(F^2) = 0.095$	$w = 1/[\sigma^2(F_o^2) + (0.0597P)^2 + 3.2629P]$
	where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.07$	$(\Delta/\sigma)_{\max} < 0.001$
1697 reflections	$\Delta\rho_{\max} = 0.74 \text{ e \AA}^{-3}$
133 parameters	$\Delta\rho_{\min} = -1.39 \text{ e \AA}^{-3}$
2 restraints	Extinction correction: none
Primary atom site location: structure-invariant direct methods	

### Special details

**Experimental.** The crystal was coated in Exxon Paratone N hydrocarbon oil and mounted on a thin mohair fibre attached to a copper pin. Upon mounting on the diffractometer, the crystal was quenched to 150(K) under a cold nitrogen gas stream supplied by an Oxford Cryosystems Cryostream.

**Geometry.** All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) etc. and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

### Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )

	$x$	$y$	$z$	$U_{\text{iso}}^*/U_{\text{eq}}$
Co1	0.32855 (5)	0.20270 (9)	0.94291 (3)	0.00253 (14)
Co2	0.56640 (5)	-0.20252 (9)	0.84576 (3)	0.00303 (15)
Co3	0.92910 (6)	0.49852 (10)	0.82254 (3)	0.00814 (16)
P1	0.68190 (11)	0.29320 (19)	0.94510 (6)	0.0086 (2)
P2	0.23599 (11)	-0.51187 (19)	0.78087 (6)	0.0087 (2)
O1	0.5357 (3)	0.1481 (6)	0.90286 (17)	0.0114 (5)
O2	0.3621 (3)	0.3976 (6)	1.04804 (16)	0.0106 (5)
O3	0.1907 (3)	0.3427 (6)	0.85760 (17)	0.0119 (5)
O4	0.2836 (3)	-0.1747 (6)	0.96996 (17)	0.0121 (6)
O5	0.7445 (3)	-0.2368 (6)	0.78428 (17)	0.0116 (5)
O6	0.8153 (3)	0.2545 (6)	0.89463 (17)	0.0120 (5)
O7	0.9749 (4)	0.7679 (6)	0.91711 (18)	0.0137 (6)
O8	0.9060 (3)	0.1703 (6)	0.74391 (17)	0.0108 (5)
O9	0.3852 (3)	-0.3512 (6)	0.79103 (18)	0.0148 (6)
H1	1.0769 (18)	0.797 (12)	0.929 (3)	0.022*
H2	0.933 (6)	0.936 (5)	0.909 (3)	0.022*

### Atomic displacement parameters ( $\text{\AA}^2$ )

$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$

## supplementary materials

---

Co1	0.0013 (2)	0.0038 (2)	0.0025 (2)	0.00007 (15)	-0.00013 (17)	0.00053 (15)
Co2	0.0006 (2)	0.0045 (3)	0.0040 (2)	-0.00041 (15)	0.00015 (17)	-0.00098 (15)
Co3	0.0077 (3)	0.0083 (3)	0.0088 (3)	-0.00123 (17)	0.00306 (19)	-0.00064 (17)
P1	0.0070 (5)	0.0090 (5)	0.0098 (5)	-0.0004 (3)	0.0014 (3)	-0.0002 (3)
P2	0.0067 (5)	0.0103 (4)	0.0091 (4)	0.0003 (3)	0.0008 (3)	0.0001 (3)
O1	0.0101 (13)	0.0112 (12)	0.0129 (13)	-0.0009 (10)	0.0004 (10)	-0.0005 (10)
O2	0.0114 (13)	0.0106 (13)	0.0099 (13)	0.0026 (10)	0.0011 (10)	-0.0003 (10)
O3	0.0121 (13)	0.0133 (13)	0.0102 (13)	-0.0003 (11)	0.0007 (11)	0.0014 (10)
O4	0.0135 (14)	0.0116 (13)	0.0110 (13)	-0.0005 (10)	-0.0004 (11)	0.0009 (10)
O5	0.0108 (14)	0.0131 (12)	0.0114 (13)	0.0007 (10)	0.0041 (10)	0.0008 (10)
O6	0.0106 (14)	0.0132 (12)	0.0127 (13)	-0.0009 (11)	0.0035 (11)	0.0007 (10)
O7	0.0110 (14)	0.0132 (13)	0.0164 (14)	0.0012 (11)	-0.0014 (11)	-0.0015 (11)
O8	0.0075 (13)	0.0122 (13)	0.0131 (13)	-0.0006 (10)	0.0026 (10)	-0.0022 (10)
O9	0.0109 (14)	0.0163 (13)	0.0171 (14)	-0.0033 (11)	0.0012 (11)	-0.0011 (11)

### Geometric parameters ( $\text{\AA}$ , $^\circ$ )

Co1—O3	1.897 (3)	Co3—O3 <sup>iv</sup>	2.416 (3)
Co1—O4	1.941 (3)	Co3—P2 <sup>v</sup>	2.8266 (12)
Co1—O2	1.992 (3)	P1—O6	1.513 (3)
Co1—O1	2.002 (3)	P1—O4 <sup>i</sup>	1.534 (3)
Co2—O9	1.887 (3)	P1—O2 <sup>vi</sup>	1.560 (3)
Co2—O5	1.949 (3)	P1—O1	1.561 (3)
Co2—O1	1.986 (3)	P2—O9	1.511 (3)
Co2—O2 <sup>i</sup>	2.054 (3)	P2—O8 <sup>vii</sup>	1.544 (3)
Co3—O6	2.019 (3)	P2—O3 <sup>viii</sup>	1.549 (3)
Co3—O7	2.061 (3)	P2—O5 <sup>vii</sup>	1.565 (3)
Co3—O8	2.065 (3)	P2—Co3 <sup>ix</sup>	2.8266 (12)
Co3—O8 <sup>ii</sup>	2.075 (3)	O7—H1	0.903 (10)
Co3—O5 <sup>iii</sup>	2.108 (3)	O7—H2	0.90 (3)
O3—Co1—O4	112.81 (13)	O4 <sup>i</sup> —P1—O2 <sup>vi</sup>	108.77 (15)
O3—Co1—O2	121.22 (12)	O6—P1—O1	109.15 (16)
O4—Co1—O2	105.11 (12)	O4 <sup>i</sup> —P1—O1	108.94 (16)
O3—Co1—O1	108.70 (12)	O2 <sup>vi</sup> —P1—O1	105.94 (16)
O4—Co1—O1	99.28 (12)	O9—P2—O8 <sup>vii</sup>	112.91 (17)
O2—Co1—O1	107.42 (12)	O9—P2—O3 <sup>viii</sup>	115.46 (17)
O9—Co2—O5	112.44 (13)	O8 <sup>vii</sup> —P2—O3 <sup>viii</sup>	102.81 (16)
O9—Co2—O1	114.62 (13)	O9—P2—O5 <sup>vii</sup>	106.80 (16)
O5—Co2—O1	118.58 (12)	O8 <sup>vii</sup> —P2—O5 <sup>vii</sup>	110.75 (16)
O9—Co2—O2 <sup>i</sup>	114.12 (12)	O3 <sup>viii</sup> —P2—O5 <sup>vii</sup>	108.04 (16)
O5—Co2—O2 <sup>i</sup>	103.10 (12)	O9—P2—Co3 <sup>ix</sup>	141.79 (13)
O1—Co2—O2 <sup>i</sup>	91.48 (11)	O8 <sup>vii</sup> —P2—Co3 <sup>ix</sup>	45.96 (10)
O6—Co3—O7	89.20 (12)	O3 <sup>viii</sup> —P2—Co3 <sup>ix</sup>	58.69 (11)
O6—Co3—O8	84.37 (11)	O5 <sup>vii</sup> —P2—Co3 <sup>ix</sup>	110.73 (12)

O7—Co3—O8	168.15 (12)	P1—O1—Co2	117.61 (16)
O6—Co3—O8 <sup>ii</sup>	164.15 (12)	P1—O1—Co1	120.63 (16)
O7—Co3—O8 <sup>ii</sup>	93.56 (12)	Co2—O1—Co1	116.29 (14)
O8—Co3—O8 <sup>ii</sup>	90.02 (7)	P1 <sup>vi</sup> —O2—Co1	120.56 (16)
O6—Co3—O5 <sup>iii</sup>	97.82 (11)	P1 <sup>vi</sup> —O2—Co2 <sup>i</sup>	115.98 (15)
O7—Co3—O5 <sup>iii</sup>	85.85 (12)	Co1—O2—Co2 <sup>i</sup>	123.17 (15)
O8—Co3—O5 <sup>iii</sup>	104.85 (11)	P2 <sup>iii</sup> —O3—Co1	126.29 (18)
O8 <sup>ii</sup> —Co3—O5 <sup>iii</sup>	97.95 (11)	P1 <sup>i</sup> —O4—Co1	123.07 (17)
O6—Co3—O3 <sup>iv</sup>	100.18 (11)	P2 <sup>x</sup> —O5—Co2	116.94 (17)
O7—Co3—O3 <sup>iv</sup>	84.70 (11)	P2 <sup>x</sup> —O5—Co3 <sup>viii</sup>	120.43 (16)
O8—Co3—O3 <sup>iv</sup>	86.65 (10)	Co2—O5—Co3 <sup>viii</sup>	120.96 (14)
O8 <sup>ii</sup> —Co3—O3 <sup>iv</sup>	64.61 (10)	P1—O6—Co3	135.08 (18)
O5 <sup>iii</sup> —Co3—O3 <sup>iv</sup>	159.51 (11)	Co3—O7—H1	113 (4)
O6—Co3—P2 <sup>v</sup>	131.88 (9)	Co3—O7—H2	115 (4)
O7—Co3—P2 <sup>v</sup>	94.83 (9)	H1—O7—H2	105 (5)
O8—Co3—P2 <sup>v</sup>	82.21 (8)	P2 <sup>x</sup> —O8—Co3	129.77 (16)
O8 <sup>ii</sup> —Co3—P2 <sup>v</sup>	32.34 (8)	P2 <sup>x</sup> —O8—Co3 <sup>xi</sup>	101.70 (14)
O5 <sup>iii</sup> —Co3—P2 <sup>v</sup>	130.28 (8)	Co3—O8—Co3 <sup>xi</sup>	128.53 (14)
O6—P1—O4 <sup>i</sup>	112.20 (17)	P2—O9—Co2	157.0 (2)
O6—P1—O2 <sup>vi</sup>	111.63 (16)		
O6—P1—O1—Co2	36.4 (2)	O1—Co2—O5—P2 <sup>x</sup>	-54.5 (2)
O4 <sup>i</sup> —P1—O1—Co2	-86.41 (19)	O2 <sup>i</sup> —Co2—O5—P2 <sup>x</sup>	-153.51 (18)
O2 <sup>vi</sup> —P1—O1—Co2	156.73 (16)	O9—Co2—O5—Co3 <sup>viii</sup>	-111.58 (17)
O6—P1—O1—Co1	-170.63 (17)	O1—Co2—O5—Co3 <sup>viii</sup>	110.83 (17)
O4 <sup>i</sup> —P1—O1—Co1	66.5 (2)	O2 <sup>i</sup> —Co2—O5—Co3 <sup>viii</sup>	11.79 (18)
O2 <sup>vi</sup> —P1—O1—Co1	-50.3 (2)	O4 <sup>i</sup> —P1—O6—Co3	-132.6 (2)
O9—Co2—O1—P1	-176.28 (16)	O2 <sup>vi</sup> —P1—O6—Co3	-10.2 (3)
O5—Co2—O1—P1	-39.6 (2)	O1—P1—O6—Co3	106.6 (3)
O2 <sup>i</sup> —Co2—O1—P1	66.23 (18)	O7—Co3—O6—P1	55.9 (3)
O9—Co2—O1—Co1	29.6 (2)	O8—Co3—O6—P1	-134.0 (3)
O5—Co2—O1—Co1	166.29 (13)	O8 <sup>ii</sup> —Co3—O6—P1	156.2 (3)
O2 <sup>i</sup> —Co2—O1—Co1	-87.91 (15)	O5 <sup>iii</sup> —Co3—O6—P1	-29.8 (3)
O3—Co1—O1—P1	122.72 (19)	P2 <sup>v</sup> —Co3—O6—P1	151.72 (19)
O4—Co1—O1—P1	-119.25 (19)	O6—Co3—O8—P2 <sup>x</sup>	44.9 (2)
O2—Co1—O1—P1	-10.1 (2)	O7—Co3—O8—P2 <sup>x</sup>	102.3 (6)
O3—Co1—O1—Co2	-83.97 (17)	O8 <sup>ii</sup> —Co3—O8—P2 <sup>x</sup>	-150.0 (2)
O4—Co1—O1—Co2	34.06 (16)	O5 <sup>iii</sup> —Co3—O8—P2 <sup>x</sup>	-51.7 (2)
O2—Co1—O1—Co2	143.21 (14)	P2 <sup>v</sup> —Co3—O8—P2 <sup>x</sup>	178.6 (2)
O3—Co1—O2—P1 <sup>vi</sup>	-18.9 (2)	O6—Co3—O8—Co3 <sup>xi</sup>	-134.86 (19)
O4—Co1—O2—P1 <sup>vi</sup>	-148.23 (18)	O7—Co3—O8—Co3 <sup>xi</sup>	-77.4 (6)
O1—Co1—O2—P1 <sup>vi</sup>	106.71 (19)	O8 <sup>ii</sup> —Co3—O8—Co3 <sup>xi</sup>	30.29 (16)

## supplementary materials

---

O3—Co1—O2—Co2 <sup>i</sup>	154.62 (15)	O5 <sup>iii</sup> —Co3—O8—Co3 <sup>xi</sup>	128.52 (17)
O4—Co1—O2—Co2 <sup>j</sup>	25.34 (19)	P2 <sup>v</sup> —Co3—O8—Co3 <sup>xi</sup>	-1.19 (16)
O1—Co1—O2—Co2 <sup>j</sup>	-79.72 (18)	O8 <sup>vii</sup> —P2—O9—Co2	116.3 (5)
O4—Co1—O3—P2 <sup>iii</sup>	-129.2 (2)	O3 <sup>viii</sup> —P2—O9—Co2	-1.5 (6)
O2—Co1—O3—P2 <sup>iii</sup>	105.0 (2)	O5 <sup>vii</sup> —P2—O9—Co2	-121.7 (5)
O1—Co1—O3—P2 <sup>iii</sup>	-20.1 (2)	Co3 <sup>ix</sup> —P2—O9—Co2	69.4 (6)
O3—Co1—O4—P1 <sup>i</sup>	-150.21 (19)	O5—Co2—O9—P2	137.1 (5)
O2—Co1—O4—P1 <sup>i</sup>	-16.1 (2)	O1—Co2—O9—P2	-83.5 (6)
O1—Co1—O4—P1 <sup>i</sup>	94.9 (2)	O2 <sup>i</sup> —Co2—O9—P2	20.1 (6)
O9—Co2—O5—P2 <sup>x</sup>	83.1 (2)		


Symmetry codes: (i)  $-x+1, -y, -z+2$ ; (ii)  $-x+2, y+1/2, -z+3/2$ ; (iii)  $x, y+1, z$ ; (iv)  $x+1, y, z$ ; (v)  $x+1, y+1, z$ ; (vi)  $-x+1, -y+1, -z+2$ ; (vii)  $-x+1, y-1/2, -z+3/2$ ; (viii)  $x, y-1, z$ ; (ix)  $x-1, y-1, z$ ; (x)  $-x+1, y+1/2, -z+3/2$ ; (xi)  $-x+2, y-1/2, -z+3/2$ .

### Hydrogen-bond geometry ( $\text{\AA}$ , $^\circ$ )

$D\text{—H}\cdots A$	$D\text{—H}$	$\text{H}\cdots A$	$D\cdots A$	$D\text{—H}\cdots A$
O7—H2 $\cdots$ O6 <sup>iii</sup>	0.90 (3)	1.86 (4)	2.753 (4)	170 (5)
O7—H1 $\cdots$ O4 <sup>v</sup>	0.903 (10)	1.864 (15)	2.758 (4)	171 (5)

Symmetry codes: (iii)  $x, y+1, z$ ; (v)  $x+1, y+1, z$ .

Fig. 1

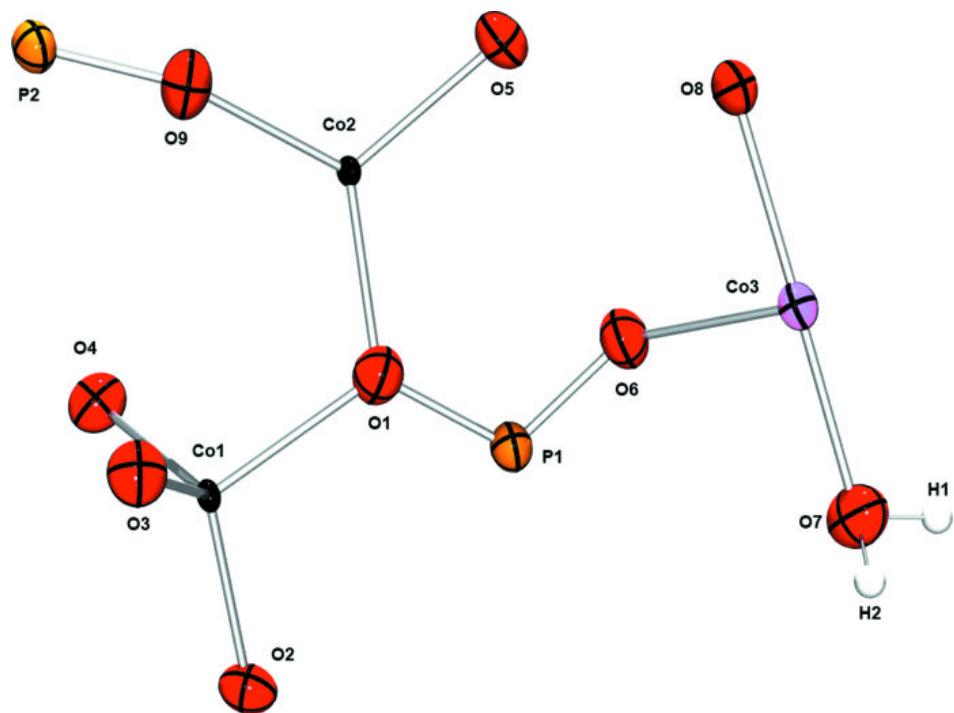

## **supplementary materials**

---

**Fig. 2**

