

Poly[$(\mu_6\text{-naphthalene-1,4-dicarboxylato-}\kappa^6\text{O}^1:\text{O}^1:\text{O}^4:\text{O}^4:\text{O}^4)$ iron(II)]

Jan Boeckmann, Inke Jess and Christian Näther*

Institut für Anorganische Chemie, Christian-Albrechts-Universität Kiel, Max-Eyth
Strasse 2, D-24098 Kiel, Germany

Correspondence e-mail: cnaether@ac.uni-kiel.de


Received 11 December 2008; accepted 15 December 2008

Key indicators: single-crystal X-ray study; $T = 170$ K; mean $\sigma(\text{C-C}) = 0.002$ Å;
 R factor = 0.030; wR factor = 0.087; data-to-parameter ratio = 14.6.

In the title compound, $[\text{Fe}(\text{C}_{12}\text{H}_6\text{O}_4)]_n$, the Fe^{II} atom is coordinated by six O atoms from six symmetrically equivalent naphthalene-1,4-dicarboxylate ligands in a strongly distorted octahedral geometry. These octahedra are connected *via* common edges into chains that elongate along the a axis, with $\text{Fe}\cdots\text{Fe}$ distances of 2.9712 (4) and 2.9724 (4) Å. The chains are linked *via* the naphthalene-1,4-dicarboxylate ligands into a three-dimensional coordination network.

Related literature

For isotypical structures with Mn^{II} and Co^{II} , see: Maji *et al.* (2005).

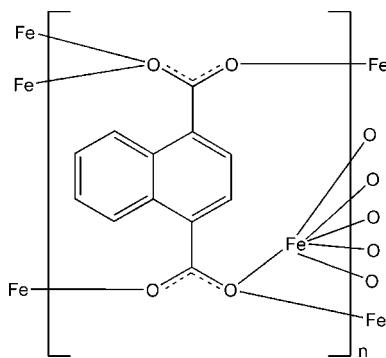

Experimental

Crystal data

$[\text{Fe}(\text{C}_{12}\text{H}_6\text{O}_4)]$	$V = 960.10 (12)$ Å ³
$M_r = 270.02$	$Z = 4$
Monoclinic, $P2_1/n$	Mo $K\alpha$ radiation
$a = 4.7863 (4)$ Å	$\mu = 1.57$ mm ⁻¹
$b = 14.8940 (9)$ Å	$T = 170 (2)$ K
$c = 13.4705 (10)$ Å	$0.30 \times 0.04 \times 0.04$ mm
$\beta = 91.098 (9)$ °	

Data collection

Stoe IPDS-1 diffractometer	2256 independent reflections
Absorption correction: none	1816 reflections with $I > 2\sigma(I)$
13722 measured reflections	$R_{\text{int}} = 0.026$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.030$	155 parameters
$wR(F^2) = 0.087$	H-atom parameters constrained
$S = 1.06$	$\Delta\rho_{\text{max}} = 0.40$ e Å ⁻³
2256 reflections	$\Delta\rho_{\text{min}} = -0.46$ e Å ⁻³

Table 1
Selected bond lengths (Å).

$\text{Fe1}-\text{O}3^i$	2.0557 (11)	$\text{Fe1}-\text{O}4^{\text{iv}}$	2.1867 (11)
$\text{Fe1}-\text{O}2^{\text{ii}}$	2.0604 (11)	$\text{Fe1}-\text{O}1^{\text{v}}$	2.1908 (11)
$\text{Fe1}-\text{O}1$	2.1533 (13)	$\text{Fe1}-\text{Fe}1^{\text{vi}}$	2.9712 (4)
$\text{Fe1}-\text{O}4^{\text{iii}}$	2.1550 (13)	$\text{Fe1}-\text{Fe}1^{\text{v}}$	2.9724 (4)

Symmetry codes: (i) $x + \frac{1}{2}, -y + \frac{1}{2}, z - \frac{1}{2}$; (ii) $x - 1, y, z$; (iii) $x - \frac{1}{2}, -y + \frac{1}{2}, z - \frac{1}{2}$; (iv) $-x + \frac{1}{2}, y + \frac{1}{2}, -z + \frac{3}{2}$; (v) $-x + 1, -y + 1, -z + 1$; (vi) $-x, -y + 1, -z + 1$.

Data collection: *IPDS* (Stoe & Cie, 1998); cell refinement: *IPDS*; data reduction: *IPDS*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008) and *DIAMOND* (Brandenburg, 1999); software used to prepare material for publication: *SHELXTL*.

This work was supported by the State of Schleswig-Holstein. We thank Professor Dr Wolfgang Bensch for the facility to use his equipment.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2174).

References

- Brandenburg, K. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
Maji, T. K., Kaneko, W., Ohba, M. & Kitagawa, S. (2005). *Chem. Commun.* pp. 4613–4615.
Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
Stoe & Cie (1998). *IPDS*. Stoe & Cie, Darmstadt, Germany.

supplementary materials

Acta Cryst. (2009). E65, m102 [doi:10.1107/S1600536808042669]

Poly[$(\mu_6\text{-naphthalene-1,4-dicarboxylato-\kappa}^6\text{O}^1:\text{O}^{1'}:\text{O}^1:\text{O}^4:\text{O}^{4'}:\text{O}^{4'})\text{iron(II)}$]

J. Boeckmann, I. Jess and C. Näther

Comment

The structure determination of the title compound was performed as a part of a project on the synthesis of new metal–organic frameworks. In this project we have reacted iron(II) sulfate with naphthalene-1,4-dicarboxylic acid in potassium hydroxide and water, which leads to the formation of a naphthalene-1,4-dicarboxylate iron(II) coordination polymer.

The title compound is isostructural to the manganese(II) and cobalt(II) complexes of naphthalene-1,4-dicarboxylate (Maji *et al.*, 2005). In the title compound, the Fe^{II} atom is surrounded by six O atoms from six crystallographically equivalent naphthalene-1,4-dicarboxylate ligands in a distorted octahedral coordination environment (Fig. 1 and Table 1). The Fe atoms are linked by O atoms of the carboxylate groups in a $\mu_3\text{-O}^1:\text{O}^{1'}:\text{O}^4$ mode into chains, which elongate along the *a* axis (Fig. 2). Within these chains the Fe coordination octahedra are connected *via* common edges. These chains are connected by the naphthalene-1,4-dicarboxylate ligands into a three-dimensional network.

Experimental

A mixture of FeSO₄·7H₂O (0.139 g, 0.5 mmol), naphthalene-1,4-dicarboxylic acid (0.108 g, 0.5 mmol), KOH (0.112 g, 1 mmol) and water (5 ml) was transferred into a glass tube and heated to 423 K for 4 d. On cooling, yellow needle crystals of the title compound were obtained.

Refinement

H atoms were positioned geometrically and refined as riding atoms, with C—H = 0.95 Å and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$.

Figures

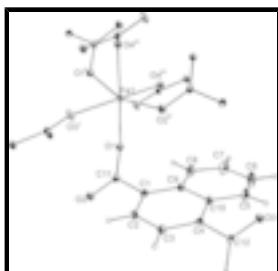


Fig. 1. The structure of the title compound, together with symmetry-related atoms to complete the Fe coordination. Displacement ellipsoids are drawn at the 50% probability level. [Symmetry codes: (i) $x+1/2, -y+1/2, z-1/2$; (ii) $x-1, y, z$; (iii) $x-1/2, -y+1/2, z-1/2$; (iv) $-x+1/2, y+1/2, -z+3/2$; (v) $-x+1, -y+1, -z+1$.]




Fig. 2. A view of the chains formed by the Fe coordination octahedra.

supplementary materials

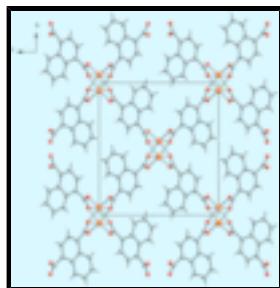


Fig. 3. Three-dimensional structure of the title compound viewed along the a axis.

Poly[$(\mu_6\text{-naphthalene-1,4-dicarboxylato-}\kappa^6\text{O}^1\text{:O}^1\text{:O}^4\text{:O}^4\text{:O}^4)$ iron(II)]

Crystal data

[Fe(C ₁₂ H ₆ O ₄)]	$F_{000} = 544$
$M_r = 270.02$	$D_x = 1.868 \text{ Mg m}^{-3}$
Monoclinic, $P2_1/n$	Mo $K\alpha$ radiation
Hall symbol: -P 2yn	$\lambda = 0.71073 \text{ \AA}$
$a = 4.7863 (4) \text{ \AA}$	Cell parameters from 8000 reflections
$b = 14.8940 (9) \text{ \AA}$	$\theta = 9\text{--}26^\circ$
$c = 13.4705 (10) \text{ \AA}$	$\mu = 1.57 \text{ mm}^{-1}$
$\beta = 91.098 (9)^\circ$	$T = 170 (2) \text{ K}$
$V = 960.10 (12) \text{ \AA}^3$	Needle, yellow
$Z = 4$	$0.30 \times 0.04 \times 0.04 \text{ mm}$

Data collection

Stoe IPDS-1 diffractometer	1816 reflections with $I > 2\sigma(I)$
Radiation source: fine-focus sealed tube	$R_{\text{int}} = 0.026$
Monochromator: graphite	$\theta_{\text{max}} = 28.0^\circ$
$T = 170(2) \text{ K}$	$\theta_{\text{min}} = 2.7^\circ$
φ scans	$h = -6 \rightarrow 6$
Absorption correction: none	$k = -19 \rightarrow 19$
13722 measured reflections	$l = -17 \rightarrow 17$
2256 independent reflections	

Refinement

Refinement on F^2	Hydrogen site location: inferred from neighbouring sites
Least-squares matrix: full	H-atom parameters constrained
$R[F^2 > 2\sigma(F^2)] = 0.030$	$w = 1/[\sigma^2(F_o^2) + (0.0535P)^2 + 0.4222P]$
$wR(F^2) = 0.087$	where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.06$	$(\Delta/\sigma)_{\text{max}} = 0.002$
	$\Delta\rho_{\text{max}} = 0.40 \text{ e \AA}^{-3}$

2256 reflections	$\Delta\rho_{\min} = -0.46 \text{ e \AA}^{-3}$
155 parameters	Extinction correction: SHELXL97 (Sheldrick, 2008), $F_c^* = k F_c [1 + 0.001 x F_c^2 \lambda^3 / \sin(2\theta)]^{1/4}$
Primary atom site location: structure-invariant direct methods	Extinction coefficient: 0.012 (3)
Secondary atom site location: difference Fourier map	

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Fe1	0.24998 (4)	0.440859 (14)	0.501167 (14)	0.00529 (13)
O1	0.6268 (3)	0.44515 (7)	0.59098 (9)	0.0071 (2)
O2	1.0178 (2)	0.36165 (8)	0.59405 (9)	0.0095 (2)
O3	-0.0120 (2)	0.13335 (8)	0.90581 (9)	0.0099 (2)
O4	0.3838 (3)	0.05263 (7)	0.90583 (9)	0.0067 (2)
C1	0.6451 (3)	0.31639 (10)	0.69582 (11)	0.0077 (3)
C2	0.6838 (4)	0.22537 (11)	0.68337 (12)	0.0097 (3)
H2	0.8026	0.2044	0.6326	0.012*
C3	0.5492 (4)	0.16326 (11)	0.74501 (12)	0.0097 (3)
H3	0.5782	0.1008	0.7353	0.012*
C4	0.3761 (3)	0.19163 (10)	0.81920 (11)	0.0074 (3)
C5	0.1863 (4)	0.31859 (12)	0.91907 (13)	0.0165 (4)
H5	0.0869	0.2776	0.9593	0.020*
C6	0.1788 (5)	0.40864 (12)	0.94029 (14)	0.0233 (5)
H6	0.0777	0.4292	0.9959	0.028*
C7	0.3198 (5)	0.47108 (12)	0.88038 (13)	0.0199 (4)
H7	0.3155	0.5332	0.8963	0.024*
C8	0.4628 (4)	0.44215 (10)	0.79915 (13)	0.0135 (4)
H8	0.5519	0.4848	0.7579	0.016*
C9	0.4798 (3)	0.34898 (10)	0.77570 (11)	0.0081 (3)
C10	0.3413 (3)	0.28589 (11)	0.83760 (11)	0.0084 (3)
C11	0.7751 (3)	0.37880 (10)	0.62232 (11)	0.0067 (3)
C12	0.2371 (3)	0.12168 (10)	0.88160 (11)	0.0067 (3)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Fe1	0.00470 (18)	0.00449 (16)	0.00679 (17)	0.00009 (8)	0.00311 (10)	0.00003 (7)
O1	0.0072 (6)	0.0065 (5)	0.0076 (5)	0.0000 (4)	0.0012 (4)	0.0020 (4)
O2	0.0071 (6)	0.0088 (5)	0.0129 (5)	0.0000 (4)	0.0048 (4)	0.0036 (4)
O3	0.0063 (6)	0.0095 (5)	0.0139 (5)	-0.0002 (4)	0.0036 (4)	0.0044 (4)
O4	0.0071 (6)	0.0056 (5)	0.0074 (5)	-0.0002 (4)	0.0009 (4)	0.0023 (4)
C1	0.0069 (7)	0.0085 (7)	0.0078 (7)	-0.0012 (6)	0.0011 (6)	0.0027 (5)
C2	0.0103 (8)	0.0096 (7)	0.0094 (7)	0.0010 (6)	0.0048 (6)	0.0017 (5)
C3	0.0116 (8)	0.0071 (7)	0.0104 (7)	0.0008 (5)	0.0032 (6)	0.0020 (6)
C4	0.0068 (8)	0.0071 (7)	0.0082 (6)	-0.0004 (5)	0.0009 (5)	0.0029 (5)
C5	0.0230 (10)	0.0120 (8)	0.0150 (8)	0.0004 (7)	0.0117 (7)	0.0020 (6)
C6	0.0367 (12)	0.0128 (9)	0.0210 (9)	0.0038 (8)	0.0183 (8)	-0.0011 (7)

supplementary materials

C7	0.0338 (11)	0.0089 (8)	0.0173 (8)	0.0011 (7)	0.0100 (8)	-0.0005 (6)
C8	0.0207 (10)	0.0077 (8)	0.0122 (7)	-0.0020 (6)	0.0050 (7)	0.0011 (6)
C9	0.0084 (8)	0.0075 (7)	0.0083 (7)	-0.0003 (5)	0.0017 (6)	0.0017 (5)
C10	0.0091 (8)	0.0081 (7)	0.0080 (7)	0.0004 (5)	0.0025 (6)	0.0016 (5)
C11	0.0074 (8)	0.0066 (7)	0.0061 (6)	-0.0018 (5)	0.0012 (5)	0.0000 (5)
C12	0.0076 (8)	0.0070 (7)	0.0056 (6)	-0.0011 (5)	0.0015 (5)	0.0004 (5)

Geometric parameters (\AA , $^\circ$)

Fe1—O3 ⁱ	2.0557 (11)	C2—H2	0.9500
Fe1—O2 ⁱⁱ	2.0604 (11)	C3—C4	1.377 (2)
Fe1—O1	2.1533 (13)	C3—H3	0.9500
Fe1—O4 ⁱⁱⁱ	2.1550 (13)	C4—C10	1.436 (2)
Fe1—O4 ^{iv}	2.1867 (11)	C4—C12	1.502 (2)
Fe1—O1 ^v	2.1908 (11)	C5—C6	1.372 (3)
Fe1—Fe1 ^{vi}	2.9712 (4)	C5—C10	1.422 (2)
Fe1—Fe1 ^v	2.9724 (4)	C5—H5	0.9500
O1—C11	1.2835 (19)	C6—C7	1.411 (3)
O2—C11	1.256 (2)	C6—H6	0.9500
O3—C12	1.254 (2)	C7—C8	1.371 (2)
O4—C12	1.2839 (19)	C7—H7	0.9500
C1—C2	1.379 (2)	C8—C9	1.426 (2)
C1—C9	1.433 (2)	C8—H8	0.9500
C1—C11	1.502 (2)	C9—C10	1.428 (2)
C2—C3	1.407 (2)		
O3 ⁱ —Fe1—O2 ⁱⁱ	112.54 (5)	C2—C1—C9	120.12 (14)
O3 ⁱ —Fe1—O1	84.19 (5)	C2—C1—C11	118.04 (13)
O2 ⁱⁱ —Fe1—O1	97.55 (5)	C9—C1—C11	121.82 (14)
O3 ⁱ —Fe1—O4 ⁱⁱⁱ	96.08 (5)	C1—C2—C3	120.69 (15)
O2 ⁱⁱ —Fe1—O4 ⁱⁱⁱ	86.89 (5)	C1—C2—H2	119.7
O1—Fe1—O4 ⁱⁱⁱ	175.08 (4)	C3—C2—H2	119.7
O3 ⁱ —Fe1—O4 ^{iv}	159.92 (5)	C4—C3—C2	121.01 (15)
O2 ⁱⁱ —Fe1—O4 ^{iv}	85.45 (4)	C4—C3—H3	119.5
O1—Fe1—O4 ^{iv}	84.65 (4)	C2—C3—H3	119.5
O4 ⁱⁱⁱ —Fe1—O4 ^{iv}	93.64 (4)	C3—C4—C10	119.93 (14)
O3 ⁱ —Fe1—O1 ^v	84.50 (4)	C3—C4—C12	118.20 (14)
O2 ⁱⁱ —Fe1—O1 ^v	160.39 (5)	C10—C4—C12	121.83 (13)
O1—Fe1—O1 ^v	93.65 (4)	C6—C5—C10	120.77 (16)
O4 ⁱⁱⁱ —Fe1—O1 ^v	81.50 (4)	C6—C5—H5	119.6
O4 ^{iv} —Fe1—O1 ^v	79.61 (5)	C10—C5—H5	119.6
O3 ⁱ —Fe1—Fe1 ^{vi}	140.19 (4)	C5—C6—C7	120.69 (16)
O2 ⁱⁱ —Fe1—Fe1 ^{vi}	84.39 (3)	C5—C6—H6	119.7
O1—Fe1—Fe1 ^{vi}	130.85 (3)	C7—C6—H6	119.7
O4 ⁱⁱⁱ —Fe1—Fe1 ^{vi}	47.26 (3)	C8—C7—C6	120.04 (16)

O4 ^{iv} —Fe1—Fe1 ^{vi}	46.37 (3)	C8—C7—H7	120.0
O1 ^v —Fe1—Fe1 ^{vi}	76.12 (3)	C6—C7—H7	120.0
O3 ⁱ —Fe1—Fe1 ^v	81.72 (3)	C7—C8—C9	120.93 (15)
O2 ⁱⁱ —Fe1—Fe1 ^v	142.14 (4)	C7—C8—H8	119.5
O1—Fe1—Fe1 ^v	47.35 (3)	C9—C8—H8	119.5
O4 ⁱⁱⁱ —Fe1—Fe1 ^v	127.79 (3)	C8—C9—C10	118.82 (14)
O4 ^{iv} —Fe1—Fe1 ^v	78.44 (3)	C8—C9—C1	122.06 (14)
O1 ^v —Fe1—Fe1 ^v	46.30 (3)	C10—C9—C1	119.01 (14)
Fe1 ^{vi} —Fe1—Fe1 ^v	107.275 (14)	C5—C10—C9	118.68 (14)
C11—O1—Fe1	127.88 (10)	C5—C10—C4	122.14 (14)
C11—O1—Fe1 ^v	129.03 (11)	C9—C10—C4	119.07 (13)
Fe1—O1—Fe1 ^v	86.35 (4)	O2—C11—O1	124.47 (14)
C11—O2—Fe1 ^{vii}	125.49 (10)	O2—C11—C1	118.13 (14)
C12—O3—Fe1 ^{viii}	128.98 (10)	O1—C11—C1	117.38 (14)
C12—O4—Fe1 ^{ix}	123.36 (10)	O3—C12—O4	124.25 (14)
C12—O4—Fe1 ^x	126.21 (10)	O3—C12—C4	118.88 (14)
Fe1 ^{ix} —O4—Fe1 ^x	86.36 (4)	O4—C12—C4	116.87 (14)

Symmetry codes: (i) $x+1/2, -y+1/2, z-1/2$; (ii) $x-1, y, z$; (iii) $x-1/2, -y+1/2, z-1/2$; (iv) $-x+1/2, y+1/2, -z+3/2$; (v) $-x+1, -y+1, -z+1$; (vi) $-x, -y+1, -z+1$; (vii) $x+1, y, z$; (viii) $x-1/2, -y+1/2, z+1/2$; (ix) $x+1/2, -y+1/2, z+1/2$; (x) $-x+1/2, y-1/2, -z+3/2$.

supplementary materials

Fig. 1


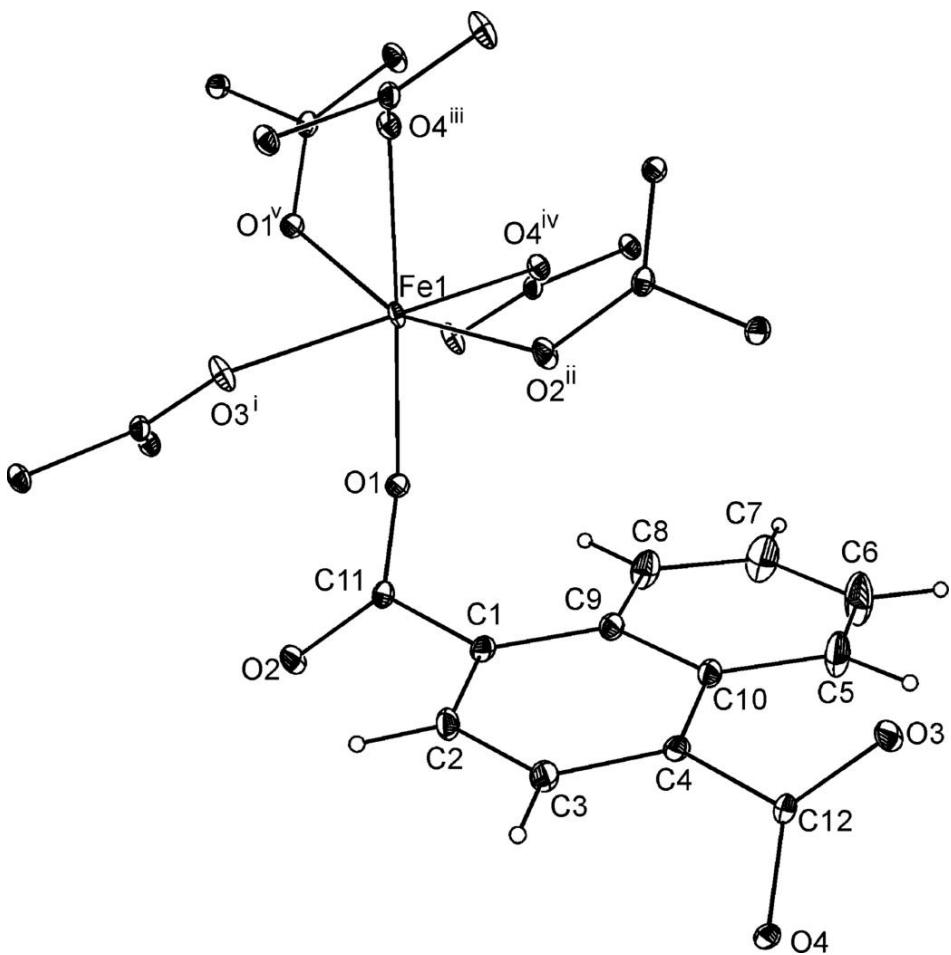


Fig. 2



supplementary materials

Fig. 3

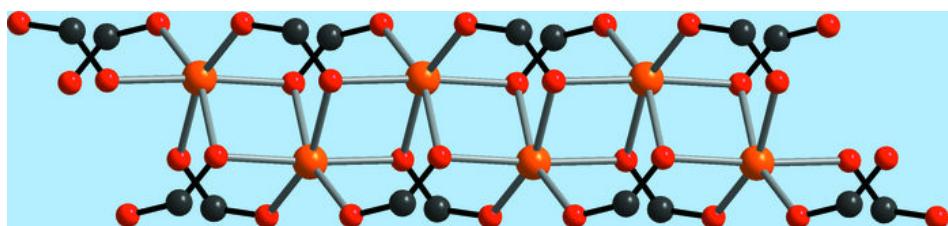