

A new polymorph of catena-poly[[tri-aquacadmium(II)]- μ_2 -pyrazine-2,3-dicarboxylato]

Hua Yin

Instrumental Measurement and Analysis Center, Fuzhou University, Fuzhou, Fujian 350002, People's Republic of China
Correspondence e-mail: yyh_shd@fzu.edu.cn


Received 13 July 2009; accepted 17 July 2009

Key indicators: single-crystal X-ray study; $T = 293\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.005\text{ \AA}$; R factor = 0.030; wR factor = 0.074; data-to-parameter ratio = 14.7.

The title complex, $[\text{Cd}(\text{C}_6\text{H}_2\text{N}_2\text{O}_4)(\text{H}_2\text{O})_3]_n$, is a new monoclinic polymorph. The orthorhombic form has previously been reported [Ma *et al.* (2006). *Acta Cryst. E62*, m2528–m2529]. The Cd–N and Cd–O bond lengths range from 2.265 (3) to 2.333 (3) Å; a weak Cd–O interaction is also present, the interatomic distance being 2.658 (4) Å. The Cd^{II} ions, which have a distorted pentagonal-bipyramidal geometry, are bridged by pyrazine-2,3-dicarboxylato ligands, forming a zigzag chain structure. The chains are connected by O–H···O hydrogen bonds into a three-dimensional framework.

Related literature

For the orthorhombic polymorph, see: Ma *et al.* (2006). For general background and related structures, see: Mao *et al.* (1996); Kitaura *et al.* (2002); Maji *et al.* (2004); Yin & Liu (2007, 2009).

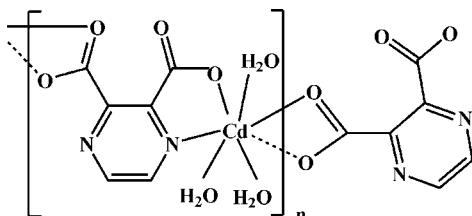

Experimental

Crystal data

 $[\text{Cd}(\text{C}_6\text{H}_2\text{N}_2\text{O}_4)(\text{H}_2\text{O})_3]$ $M_r = 332.54$ Monoclinic, $P2_1/n$ $a = 5.586$ (6) Å $b = 15.748$ (9) Å $c = 10.832$ (6) Å $\beta = 93.94$ (3)° $V = 950.5$ (12) \AA^3 $Z = 4$ Mo $K\alpha$ radiation $\mu = 2.32\text{ mm}^{-1}$ $T = 293\text{ K}$ $0.25 \times 0.23 \times 0.18\text{ mm}$

Data collection

Rigaku Weissenberg IP diffractometer

Absorption correction: multi-scan (*TEXRAY*; Molecular Structure Corporation, 1999) $T_{\min} = 0.668$, $T_{\max} = 1.000$
(expected range = 0.440–0.658)

5659 measured reflections

2129 independent reflections

1699 reflections with $I > 2\sigma(I)$ $R_{\text{int}} = 0.032$

Refinement

 $R[F^2 > 2\sigma(F^2)] = 0.030$ $wR(F^2) = 0.074$ $S = 1.03$

2129 reflections

145 parameters

9 restraints

H-atom parameters constrained

 $\Delta\rho_{\max} = 0.82\text{ e \AA}^{-3}$ $\Delta\rho_{\min} = -0.53\text{ e \AA}^{-3}$

Table 1
Selected geometric parameters (\AA , °).

Cd1–O3W	2.218 (3)	Cd1–N1	2.334 (3)
Cd1–O1	2.265 (3)	Cd1–O2W	2.397 (4)
Cd1–O3 ⁱ	2.294 (3)	Cd1–O1W	2.451 (3)

Symmetry code: (i) $-x + \frac{1}{2}, y + \frac{1}{2}, -z + \frac{1}{2}$.

Table 2
Hydrogen-bond geometry (\AA , °).

$D-\text{H} \cdots A$	$D-\text{H}$	$\text{H} \cdots A$	$D \cdots A$	$D-\text{H} \cdots A$
O1W–H1WA···O4 ⁱⁱ	0.82	2.56	3.328 (5)	156
O2W–H2WA···O1 ⁱⁱⁱ	0.84	2.02	2.834 (5)	164
O2W–H2WB···N2 ^{iv}	0.83	2.24	3.036 (4)	161
O3W–H3WA···O4 ^{iv}	0.85	1.82	2.656 (6)	169
O3W–H3WB···O4 ^v	0.83	2.25	2.865 (4)	132
O3W–H3WB···O2 ^v	0.83	2.22	2.935 (4)	144

Symmetry codes: (ii) $x + \frac{1}{2}, -y + \frac{1}{2}, z + \frac{1}{2}$; (iii) $x - 1, y, z$; (iv) $-x - \frac{1}{2}, y + \frac{1}{2}, -z + \frac{1}{2}$; (v) $x - \frac{1}{2}, -y + \frac{1}{2}, z + \frac{1}{2}$.

Data collection: *TEXRAY* (Molecular Structure Corporation, 1999); cell refinement: *TEXRAY*; data reduction: *TEXSAN* (Molecular Structure Corporation, 1999); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP* (McArdle, 1995); software used to prepare material for publication: *SHELXL97*.

The author is grateful for financial support from the Key Science and Technology Project of Fijian Province, China (grant Nos. 2008Y0051 and 2007Y0062).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BT5003).

References

- Kitaura, R., Fujimoto, K., Noro, S.-I., Kondo, M. & Kitagawa, S. (2002). *Angew. Chem. Int. Ed.* **41**, 133–135.
- Ma, Y., He, Y.-K. & Han, Z.-B. (2006). *Acta Cryst. E62*, m2528–m2529.
- Maji, T. K., Uemura, K., Chang, H. C., Matsuda, R. & Kitagawa, S. (2004). *Angew. Chem. Int. Ed.* **43**, 3269–3272.
- Mao, L., Rettig, S. J., Thompson, R. C., Trotter, J. & Xia, S. H. (1996). *Can. J. Chem.* **74**, 2413–2423.
- McArdle, P. (1995). *J. Appl. Cryst.* **28**, 65.
- Molecular Structure Corporation (1999). *TEXRAY* and *TEXSAN*. MSC, The Woodlands, Texas, USA.
- Sheldrick, G. M. (2008). *Acta Cryst. A64*, 112–122.
- Yin, H. & Liu, S. X. (2007). *Polyhedron*, **26**, 3103–3111.
- Yin, H. & Liu, S. X. (2009). *Chin. J. Inorg. Chem.* **25**, 893–899.

supplementary materials

Acta Cryst. (2009). E65, m971 [doi:10.1107/S1600536809028268]

A new polymorph of *catena*-poly[[triaquacadmium(II)]- μ_2 -pyrazine-2,3-dicarboxylato]

H. Yin

Comment

Pyrazine-2,3-dicarboxylic acid (pzdcH₂) as a multidentate bridging ligand has been widely applied to construct polymeric coordination compounds (Mao *et al.*, 1996; Kitaura *et al.*, 2002). Recently, some pzdc-Cd complexes that exhibit selective gas adsorption and photoluminescence were synthesized by self assembling (Maji *et al.*, 2004; Yin *et al.*, 2007; Yin *et al.*, 2009). In this work, a new polymorph of the title compound was obtained by introducing 1,2,4-triazol as the acidity modulating reagent in the reaction of pzdcH₂ and Cd(II) ion.

The title compound is a one-dimensional zigzag chain structure composed of Cd^{II} ions bridged by pzdc ligands. Cd1 is coordinated by N1, O1 and O3ⁱ atoms from two pzdc ligands [symmetry code (i), -x + 1/2, y + 1/2, -z + 1/2] and three coordinated water molecules (O1W, O2W and O3W) (see Fig. 1). The corresponding bond lengths range from 2.265 (3) to 2.333 (3) Å. The Cd1 atom has a weak interaction with O4ⁱ (Cd1···O4ⁱ = 2.658 (4) Å). Overall, the geometry of Cd may be considered as a distorted pentagonal bipyramid. The title compound crystallizes in the monoclinic space group P2₁/n whereas the already known polymorph crystallizes in the orthorhombic space group P2₁2₁2₁ (Ma *et al.*, 2006). O-H···O hydrogen bonds combine the chains into a three-dimensional framework (Table 2). The neighboring Cd···Cd distance is 8.25 (1) Å.

Experimental

By adding an aqueous solution of Cd(OAc)₂ (0.1 mmol) into an aqueous solution of pzdcH₂(0.1 mmol) and 1,2,4-triazol (0.1 mmol), the resulting mixture was stirred for 2 min and filtered immediately. The colorless crystals of the title compound I were isolated after slow evaporation for 3 days. Yield: *ca*43% based on Cd. Anal. Calcd for C₆H₈N₂O₇Cd: C, 21.65, H, 2.41, N, 8.42; found: C, 21.58, H, 2.36, N, 8.53.

Refinement

H atoms of water molecules were located in difference Fourier maps and were then constrained to ride on their parent atoms, with $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$. Other H atoms were positioned geometrically and constrained to ride on their parent atoms, with C—H = 0.93 Å and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The water H atoms were refined with distance restraints of O-H 0.86 (2) Å and H-H = 1.38 (2) Å.

Figures




Fig. 1. View of the title compound, showing 30% probability displacement ellipsoids. H atoms have been omitted for clarity. [Symmetry code: (i) -x + 1/2, y + 1/2, -z + 1/2.]

supplementary materials

catena-poly[[triaquacadmium(II)]- μ_2 -pyrazine-2,3-dicarboxylato]

Crystal data

[Cd(C ₆ H ₂ N ₂ O ₄)(H ₂ O) ₃]	$F_{000} = 648$
$M_r = 332.54$	$D_x = 2.324 \text{ Mg m}^{-3}$
Monoclinic, $P2_1/n$	Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$
Hall symbol: -P 2yn	Cell parameters from 4538 reflections
$a = 5.586 (6) \text{ \AA}$	$\theta = 3.2\text{--}27.5^\circ$
$b = 15.748 (9) \text{ \AA}$	$\mu = 2.32 \text{ mm}^{-1}$
$c = 10.832 (6) \text{ \AA}$	$T = 293 \text{ K}$
$\beta = 93.94 (3)^\circ$	Block, colourless
$V = 950.5 (12) \text{ \AA}^3$	$0.25 \times 0.23 \times 0.18 \text{ mm}$
$Z = 4$	

Data collection

Weissenberg IP diffractometer	2129 independent reflections
Radiation source: rotor target	1699 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.032$
$T = 293 \text{ K}$	$\theta_{\text{max}} = 27.5^\circ$
ω scans	$\theta_{\text{min}} = 3.2^\circ$
Absorption correction: multi-scan (TEXRAY; Molecular Structure Corporation, 1999)	$h = -7 \rightarrow 5$
$T_{\text{min}} = 0.668$, $T_{\text{max}} = 1.000$	$k = -19 \rightarrow 20$
5659 measured reflections	$l = -14 \rightarrow 14$

Refinement

Refinement on F^2	Secondary atom site location: difference Fourier map
Least-squares matrix: full	Hydrogen site location: inferred from neighbouring sites
$R[F^2 > 2\sigma(F^2)] = 0.030$	H-atom parameters constrained
$wR(F^2) = 0.074$	$w = 1/[\sigma^2(F_o^2) + (0.0366P)^2 + 0.562P]$
$S = 1.03$	where $P = (F_o^2 + 2F_c^2)/3$
2129 reflections	$(\Delta/\sigma)_{\text{max}} < 0.001$
145 parameters	$\Delta\rho_{\text{max}} = 0.82 \text{ e \AA}^{-3}$
9 restraints	$\Delta\rho_{\text{min}} = -0.53 \text{ e \AA}^{-3}$
Primary atom site location: structure-invariant direct methods	Extinction correction: none

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Cd1	0.07189 (6)	0.372955 (14)	0.31158 (2)	0.02540 (10)
O1	0.3289 (6)	0.28668 (14)	0.2181 (2)	0.0294 (6)
O2	0.4160 (6)	0.15343 (17)	0.1696 (2)	0.0319 (7)
O3	0.3399 (7)	-0.01740 (17)	0.3172 (3)	0.0434 (8)
O4	0.1098 (7)	-0.00334 (19)	0.1449 (3)	0.0475 (9)
O1W	0.2872 (7)	0.34613 (18)	0.5126 (2)	0.0374 (7)
H1WA	0.3989	0.3785	0.5318	0.056*
H1WB	0.1887	0.3401	0.5663	0.056*
O2W	-0.2530 (6)	0.37407 (15)	0.1551 (3)	0.0358 (7)
H2WA	-0.3683	0.3410	0.1640	0.054*
H2WB	-0.3071	0.4212	0.1323	0.054*
O3W	-0.1846 (8)	0.4335 (2)	0.4320 (3)	0.0583 (11)
H3WA	-0.3095	0.4581	0.4013	0.088*
H3WB	-0.1945	0.4277	0.5076	0.088*
N1	-0.0445 (7)	0.23327 (16)	0.3472 (3)	0.0218 (7)
N2	-0.1324 (7)	0.06150 (18)	0.3781 (3)	0.0253 (7)
C1	0.0905 (7)	0.17535 (19)	0.2954 (3)	0.0194 (7)
C2	0.0436 (7)	0.0893 (2)	0.3109 (3)	0.0195 (7)
C3	-0.2626 (8)	0.1201 (2)	0.4287 (3)	0.0269 (8)
H3A	-0.3866	0.1031	0.4763	0.032*
C4	-0.2215 (8)	0.2060 (2)	0.4137 (3)	0.0242 (8)
H4A	-0.3187	0.2453	0.4505	0.029*
C5	0.2939 (8)	0.2074 (2)	0.2211 (3)	0.0216 (7)
C6	0.1817 (9)	0.0189 (2)	0.2531 (4)	0.0279 (9)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cd1	0.02614 (19)	0.01735 (14)	0.03381 (15)	0.00158 (10)	0.00999 (10)	0.00080 (10)
O1	0.029 (2)	0.0203 (10)	0.0414 (13)	-0.0017 (11)	0.0180 (12)	-0.0012 (10)
O2	0.027 (2)	0.0258 (12)	0.0445 (15)	-0.0003 (11)	0.0184 (13)	-0.0045 (11)
O3	0.043 (3)	0.0278 (13)	0.0605 (19)	0.0147 (14)	0.0148 (16)	0.0078 (13)

supplementary materials

O4	0.044 (3)	0.0526 (17)	0.0482 (16)	-0.0186 (16)	0.0185 (15)	-0.0300 (14)
O1W	0.034 (2)	0.0431 (14)	0.0351 (14)	-0.0041 (13)	0.0042 (12)	0.0050 (12)
O2W	0.031 (2)	0.0274 (12)	0.0480 (15)	-0.0044 (12)	-0.0024 (13)	0.0038 (11)
O3W	0.053 (3)	0.089 (3)	0.0332 (14)	0.035 (2)	0.0059 (15)	-0.0104 (16)
N1	0.023 (2)	0.0185 (12)	0.0247 (13)	-0.0002 (11)	0.0056 (12)	-0.0004 (11)
N2	0.026 (2)	0.0217 (13)	0.0280 (14)	-0.0012 (12)	0.0035 (13)	0.0010 (11)
C1	0.022 (2)	0.0166 (14)	0.0198 (14)	0.0019 (13)	-0.0002 (13)	-0.0009 (12)
C2	0.017 (2)	0.0188 (14)	0.0233 (14)	0.0010 (13)	0.0038 (13)	0.0013 (12)
C3	0.024 (2)	0.0299 (17)	0.0273 (16)	-0.0027 (15)	0.0085 (14)	-0.0003 (14)
C4	0.022 (2)	0.0262 (16)	0.0253 (15)	0.0031 (14)	0.0095 (14)	-0.0030 (13)
C5	0.021 (2)	0.0202 (14)	0.0236 (14)	0.0020 (14)	0.0031 (14)	-0.0020 (13)
C6	0.025 (3)	0.0163 (14)	0.044 (2)	-0.0037 (15)	0.0156 (17)	-0.0055 (15)

Geometric parameters (\AA , $^\circ$)

Cd1—O3W	2.218 (3)	O2W—H2WB	0.8324
Cd1—O1	2.265 (3)	O3W—H3WA	0.8463
Cd1—O3 ⁱ	2.294 (3)	O3W—H3WB	0.8295
Cd1—N1	2.334 (3)	N1—C1	1.332 (4)
Cd1—O2W	2.397 (4)	N1—C4	1.334 (5)
Cd1—O1W	2.451 (3)	N2—C3	1.317 (5)
O1—C5	1.265 (4)	N2—C2	1.337 (5)
O2—C5	1.245 (4)	C1—C2	1.393 (5)
O3—C6	1.226 (6)	C1—C5	1.522 (5)
O3—Cd1 ⁱⁱ	2.294 (3)	C2—C6	1.510 (5)
O4—C6	1.262 (5)	C3—C4	1.384 (5)
O1W—H1WA	0.8214	C3—H3A	0.9300
O1W—H1WB	0.8327	C4—H4A	0.9300
O2W—H2WA	0.8385		
O3W—Cd1—O1	167.27 (11)	Cd1—O3W—H3WB	128.5
O3W—Cd1—O3 ⁱ	102.02 (13)	H3WA—O3W—H3WB	109.3
O1—Cd1—O3 ⁱ	90.61 (11)	C1—N1—C4	118.0 (3)
O3W—Cd1—N1	96.29 (14)	C1—N1—Cd1	113.8 (2)
O1—Cd1—N1	72.59 (11)	C4—N1—Cd1	128.2 (2)
O3 ⁱ —Cd1—N1	152.11 (10)	C3—N2—C2	116.5 (3)
O3W—Cd1—O2W	85.67 (14)	N1—C1—C2	119.9 (3)
O1—Cd1—O2W	99.25 (12)	N1—C1—C5	117.4 (3)
O3 ⁱ —Cd1—O2W	75.44 (12)	C2—C1—C5	122.6 (3)
N1—Cd1—O2W	85.28 (11)	N2—C2—C1	122.4 (3)
O3W—Cd1—O1W	81.30 (13)	N2—C2—C6	113.7 (3)
O1—Cd1—O1W	90.37 (12)	C1—C2—C6	124.0 (3)
O3 ⁱ —Cd1—O1W	123.85 (12)	N2—C3—C4	122.4 (4)
N1—Cd1—O1W	79.40 (11)	N2—C3—H3A	118.8
O2W—Cd1—O1W	158.60 (11)	C4—C3—H3A	118.8
C5—O1—Cd1	118.5 (2)	N1—C4—C3	120.9 (3)
C6—O3—Cd1 ⁱⁱ	100.6 (2)	N1—C4—H4A	119.6
Cd1—O1W—H1WA	115.8	C3—C4—H4A	119.6

Cd1—O1W—H1WB	109.4	O2—C5—O1	124.9 (3)
H1WA—O1W—H1WB	114.9	O2—C5—C1	117.5 (3)
Cd1—O2W—H2WA	117.7	O1—C5—C1	117.6 (3)
Cd1—O2W—H2WB	117.3	O3—C6—O4	124.5 (4)
H2WA—O2W—H2WB	108.8	O3—C6—C2	118.4 (3)
Cd1—O3W—H3WA	120.9	O4—C6—C2	116.7 (4)
O3W—Cd1—O1—C5	32.7 (8)	N1—C1—C2—N2	-0.9 (6)
O3 ⁱ —Cd1—O1—C5	-154.6 (3)	C5—C1—C2—N2	178.7 (3)
N1—Cd1—O1—C5	2.8 (3)	N1—C1—C2—C6	178.3 (3)
O2W—Cd1—O1—C5	-79.2 (3)	C5—C1—C2—C6	-2.1 (6)
O1W—Cd1—O1—C5	81.6 (3)	C2—N2—C3—C4	0.1 (6)
O3W—Cd1—N1—C1	-174.6 (3)	C1—N1—C4—C3	0.3 (6)
O1—Cd1—N1—C1	-0.9 (2)	Cd1—N1—C4—C3	-178.0 (3)
O3 ⁱ —Cd1—N1—C1	54.4 (4)	N2—C3—C4—N1	-0.5 (6)
O2W—Cd1—N1—C1	100.3 (3)	Cd1—O1—C5—O2	177.2 (3)
O1W—Cd1—N1—C1	-94.7 (3)	Cd1—O1—C5—C1	-4.1 (4)
O3W—Cd1—N1—C4	3.8 (4)	N1—C1—C5—O2	-178.0 (3)
O1—Cd1—N1—C4	177.4 (4)	C2—C1—C5—O2	2.4 (5)
O3 ⁱ —Cd1—N1—C4	-127.3 (3)	N1—C1—C5—O1	3.3 (5)
O2W—Cd1—N1—C4	-81.3 (3)	C2—C1—C5—O1	-176.4 (4)
O1W—Cd1—N1—C4	83.7 (3)	Cd1 ⁱⁱ —O3—C6—O4	-2.1 (5)
C4—N1—C1—C2	0.4 (5)	Cd1 ⁱⁱ —O3—C6—C2	171.1 (3)
Cd1—N1—C1—C2	178.9 (3)	N2—C2—C6—O3	-81.2 (5)
C4—N1—C1—C5	-179.2 (3)	C1—C2—C6—O3	99.6 (5)
Cd1—N1—C1—C5	-0.7 (4)	N2—C2—C6—O4	92.5 (4)
C3—N2—C2—C1	0.6 (6)	C1—C2—C6—O4	-86.7 (5)
C3—N2—C2—C6	-178.6 (3)		

Symmetry codes: (i) $-x+1/2, y+1/2, -z+1/2$; (ii) $-x+1/2, y-1/2, -z+1/2$.

Hydrogen-bond geometry (\AA , °)

$D—\text{H}\cdots A$	$D—\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D—\text{H}\cdots A$
O1W—H1WA···O4 ⁱⁱⁱ	0.82	2.56	3.328 (5)	156
O2W—H2WA···O1 ^{iv}	0.84	2.02	2.834 (5)	164
O2W—H2WB···N2 ^v	0.83	2.24	3.036 (4)	161
O3W—H3WA···O4 ^v	0.85	1.82	2.656 (6)	169
O3W—H3WB···O4 ^{vi}	0.83	2.25	2.865 (4)	132
O3W—H3WB···O2 ^{vi}	0.83	2.22	2.935 (4)	144

Symmetry codes: (iii) $x+1/2, -y+1/2, z+1/2$; (iv) $x-1, y, z$; (v) $-x-1/2, y+1/2, -z+1/2$; (vi) $x-1/2, -y+1/2, z+1/2$.

supplementary materials

Fig. 1

