

Poly[(dimethylformamide)(μ_4 -2,2'-sulfanediylbenzoato)nickel(II)]

Jiang-Bo Xie

College of Materials Science and Engineering, North University of China, Taiyuan, Shanxi, 030051, People's Republic of China
Correspondence e-mail: xjb209@126.com


Received 25 February 2010; accepted 1 March 2010

Key indicators: single-crystal X-ray study; $T = 298\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.005\text{ \AA}$; R factor = 0.036; wR factor = 0.079; data-to-parameter ratio = 14.7.

The title centrosymmetric dinuclear Ni^{II} complex, $[\text{Ni}(\text{C}_{14}\text{H}_8\text{O}_4\text{S})(\text{C}_3\text{H}_7\text{NO})]_n$, was prepared via reaction of $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and thiosalicylic acid, with H_2O and dimethyl-formamide (DMF) as the mixed solvent. The central Ni^{II} ion is five-coordinated by five O atoms from DMF and from the carboxylate groups of the organic ligand. The symmetry-related coordination polyhedra interlink into centrosymmetric dimeric units and these, in turn, are linked into infinite chains propagating parallel to [100].

Related literature

For high-dimensional coordination polymers, see: Li *et al.* (2009, 2010).

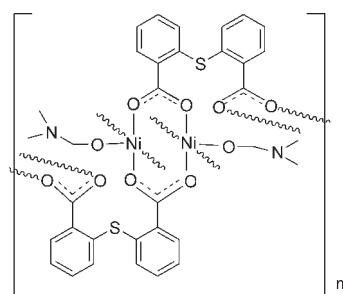

Experimental

Crystal data

$[\text{Ni}(\text{C}_{14}\text{H}_8\text{O}_4\text{S})(\text{C}_3\text{H}_7\text{NO})]$	$\gamma = 71.796 (1)^\circ$
$M_r = 808.12$	$V = 862.33 (3)\text{ \AA}^3$
Triclinic, $P\bar{1}$	$Z = 1$
$a = 8.5196 (2)\text{ \AA}$	Mo $K\alpha$ radiation
$b = 10.5240 (2)\text{ \AA}$	$\mu = 1.27\text{ mm}^{-1}$
$c = 11.0138 (3)\text{ \AA}$	$T = 298\text{ K}$
$\alpha = 67.241 (1)^\circ$	$0.30 \times 0.25 \times 0.19\text{ mm}$
$\beta = 79.0410 (11)^\circ$	

Data collection

Bruker APEXII area-detector diffractometer	11190 measured reflections
Absorption correction: multi-scan (<i>SADABS</i> ; Sheldrick, 2004)	3350 independent reflections
$R_{\text{int}} = 0.035$	2553 reflections with $I > 2\sigma(I)$
$T_{\min} = 0.701$, $T_{\max} = 0.794$	

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.036$	228 parameters
$wR(F^2) = 0.079$	H-atom parameters constrained
$S = 1.01$	$\Delta\rho_{\max} = 0.44\text{ e \AA}^{-3}$
3350 reflections	$\Delta\rho_{\min} = -0.35\text{ e \AA}^{-3}$

Data collection: *APEX2* (Bruker, 2004); cell refinement: *SAINT* (Bruker, 2004); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *XP* in *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXL97*.

The project was supported by the Science Foundation of North University of China.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BG2334).

References

- Bruker (2004). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
Li, Z.-Y., Dai, J.-W., Qiu, H.-H., Yue, S.-T. & Liu, Y.-L. (2010). *Inorg. Chem. Commun.* **13**, 452–455.
Li, Z., Dai, J. & Yue, S. (2009). *Acta Cryst. E65*, m775.
Sheldrick, G. M. (2004). *SADABS*. University of Göttingen, Germany.
Sheldrick, G. M. (2008). *Acta Cryst. A64*, 112–122.

supplementary materials

Acta Cryst. (2010). E66, m368 [doi:10.1107/S1600536810007749]

Poly[(dimethylformamide)(μ_4 -2,2'-sulfanediylbibenzoato)nickel(II)]

J.-B. Xie

Comment

Organic carboxylates as ligands attract much attention not only because of versatile coordination modes but also owing to their ability to facilitate the formation of high-dimensional coordination polymers (Li *et al.*, 2009; Li *et al.*, 2010). One such example, namely, thiosalicylic acid, is a semi-rigid, multidentate ligand that can provide up to four donor atoms with variable coordination modes. Unlike the imidazole-4,5-dicarboxylic acid and benzimidazole-5,6-dicarboxylic acid with nitrogen and oxygen coordinated dots, the thiosalicylic acid only has oxygen coordinated dot. So it can form low-dimensional compound. This is therefore considered as an excellent candidate for generating one-dimensional compound with chain structure.

In the title complex, the Ni^{II} atom is coordinated by one oxygen atom from one DMF ligand and four oxygen atoms from the thiosalicylic acid carboxylates, giving a centrosymmetric dimeric structure with a Ni··Ni distance of 2.6374 (7) Å (Fig. 1). A one-dimensional infinite chain is formed due to the bidentate bridging mode shown by all the thiosalicylic acid carboxylates (Fig. 2). The Ni—O bond distances vary from 1.947 (2) Å to 2.129 (2) Å. The O—Ni—O angles are in the range of 88.16 (9) to 168.24 (8) °. As far as we know, examples of dinuclear Ni^{II} complex bridged by thiosalicylic acid and DMF have not been characterized so far.

Experimental

A solution obtained by dissolving 0.145 g (0.5 mmol) Ni(NO₃)₂·6H₂O in 4 ml DMF and 10 ml H₂O was added. The mixture was stirred until complete dissolution. To the stirred solution was added equimolar quantities 0.136 g (0.5 mmol) thiosalicylic acid. The green solution was then under 160 °C for 72 h in a 23 ml Teflon-lined stainless-steel autoclave. After the reaction, the bomb was cooled to room temperature in a rate of 5 °C per hour. Green prismatic crystals were collected and dried in air. Yield: *ca.* 82 % on the basis of Ni.

Refinement

All H atoms were positioned in calculated positions, with C—H distances of 0.93 and 0.96 Å, and with Uiso~(H) = 1.2 or 1.5 Ueq~(C).

Figures

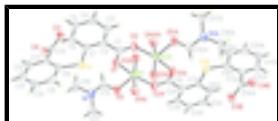


Fig. 1. Displacement ellipsoid plot (40% probability level) of the title compound(I), with atom numbering of structurally unique non-H.

supplementary materials

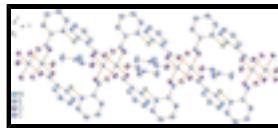


Fig. 2. The packing diagram of the title compound (I).

Poly[(dimethylformamide)(μ_4 -2,2'-sulfanediyldibenzoato)nickel(II)]

Crystal data

[Ni(C ₁₄ H ₈ O ₄ S)(C ₃ H ₇ NO)]	Z = 1
M _r = 808.12	F(000) = 416
Triclinic, P $\bar{1}$	D _x = 1.556 Mg m ⁻³
Hall symbol: -P 1	Mo K α radiation, λ = 0.71073 Å
a = 8.5196 (2) Å	Cell parameters from 2701 reflections
b = 10.5240 (2) Å	θ = 2.4–22.3°
c = 11.0138 (3) Å	μ = 1.27 mm ⁻¹
α = 67.241 (1)°	T = 298 K
β = 79.0410 (11)°	Block, green
γ = 71.796 (1)°	0.30 × 0.25 × 0.19 mm
V = 862.33 (3) Å ³	

Data collection

Bruker APEXII area-detector diffractometer	3350 independent reflections
Radiation source: fine-focus sealed tube graphite	2553 reflections with $I > 2\sigma(I)$
φ and ω scan	$R_{\text{int}} = 0.035$
Absorption correction: multi-scan (SADABS; Sheldrick, 2004)	$\theta_{\max} = 26.0^\circ$, $\theta_{\min} = 2.0^\circ$
$T_{\min} = 0.701$, $T_{\max} = 0.794$	$h = -9 \rightarrow 10$
11190 measured reflections	$k = -12 \rightarrow 12$
	$l = -13 \rightarrow 13$

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.036$	Hydrogen site location: inferred from neighbouring sites
$wR(F^2) = 0.079$	H-atom parameters constrained
$S = 1.01$	$w = 1/[\sigma^2(F_o^2) + (0.0295P)^2 + 0.4P]$
3350 reflections	where $P = (F_o^2 + 2F_c^2)/3$
228 parameters	$(\Delta/\sigma)_{\max} = 0.001$
0 restraints	$\Delta\rho_{\max} = 0.44 \text{ e \AA}^{-3}$
	$\Delta\rho_{\min} = -0.34 \text{ e \AA}^{-3}$

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Ni1	0.37381 (4)	0.57945 (3)	0.55076 (3)	0.03249 (12)
S1	-0.02998 (9)	0.75102 (9)	0.29878 (7)	0.0481 (2)
O1	0.2572 (2)	0.5904 (2)	0.40641 (19)	0.0499 (5)
O2	0.4743 (3)	0.4593 (2)	0.3200 (2)	0.0551 (6)
O3	-0.3145 (3)	0.5998 (2)	0.33626 (19)	0.0501 (5)
O4	-0.5286 (2)	0.7322 (2)	0.4242 (2)	0.0521 (5)
O5	0.1675 (3)	0.7125 (2)	0.6255 (2)	0.0547 (6)
N1	-0.1056 (3)	0.8241 (3)	0.6247 (3)	0.0535 (7)
C1	0.3275 (4)	0.5360 (3)	0.3199 (3)	0.0417 (7)
C2	0.2315 (3)	0.5674 (3)	0.2057 (3)	0.0381 (6)
C3	0.3089 (4)	0.5029 (3)	0.1132 (3)	0.0501 (8)
H3	0.4126	0.4380	0.1281	0.060*
C4	0.2369 (4)	0.5317 (4)	0.0004 (3)	0.0561 (8)
H4	0.2922	0.4894	-0.0614	0.067*
C5	0.0810 (4)	0.6248 (3)	-0.0189 (3)	0.0553 (8)
H5	0.0308	0.6456	-0.0948	0.066*
C6	-0.0010 (4)	0.6872 (3)	0.0722 (3)	0.0494 (8)
H6	-0.1072	0.7477	0.0582	0.059*
C7	0.0723 (3)	0.6616 (3)	0.1858 (3)	0.0411 (7)
C8	-0.2076 (4)	0.8749 (3)	0.2161 (3)	0.0429 (7)
C9	-0.1898 (4)	1.0066 (3)	0.1271 (3)	0.0571 (9)
H9	-0.0855	1.0235	0.1077	0.069*
C10	-0.3225 (5)	1.1122 (4)	0.0670 (3)	0.0665 (10)
H10	-0.3077	1.1993	0.0069	0.080*
C11	-0.4766 (4)	1.0887 (3)	0.0962 (3)	0.0620 (9)
H11	-0.5668	1.1595	0.0550	0.074*
C12	-0.4984 (4)	0.9601 (3)	0.1866 (3)	0.0529 (8)
H12	-0.6039	0.9455	0.2069	0.063*
C13	-0.3648 (3)	0.8520 (3)	0.2478 (3)	0.0388 (7)
C14	-0.4029 (4)	0.7160 (3)	0.3450 (3)	0.0399 (7)
C15	0.0244 (4)	0.7207 (3)	0.6097 (3)	0.0472 (7)
H15	0.0070	0.6507	0.5859	0.057*
C16	-0.2706 (4)	0.8325 (4)	0.5980 (4)	0.0821 (12)

supplementary materials

H16A	-0.2647	0.7545	0.5709	0.123*
H16B	-0.3115	0.9213	0.5289	0.123*
H16C	-0.3440	0.8271	0.6765	0.123*
C17	-0.0867 (4)	0.9353 (4)	0.6631 (4)	0.0730 (11)
H17A	0.0279	0.9356	0.6498	0.110*
H17B	-0.1239	0.9177	0.7546	0.110*
H17C	-0.1515	1.0264	0.6103	0.110*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ni1	0.0266 (2)	0.0328 (2)	0.0312 (2)	-0.00384 (15)	-0.00182 (14)	-0.00739 (15)
S1	0.0385 (5)	0.0590 (5)	0.0440 (4)	-0.0096 (4)	-0.0055 (3)	-0.0165 (4)
O1	0.0380 (12)	0.0645 (14)	0.0418 (12)	-0.0035 (11)	-0.0075 (9)	-0.0189 (11)
O2	0.0390 (13)	0.0620 (14)	0.0583 (14)	0.0012 (11)	-0.0136 (10)	-0.0217 (11)
O3	0.0488 (13)	0.0383 (12)	0.0507 (13)	-0.0109 (10)	0.0077 (10)	-0.0083 (10)
O4	0.0458 (13)	0.0440 (12)	0.0561 (13)	-0.0135 (10)	0.0116 (11)	-0.0125 (10)
O5	0.0396 (13)	0.0615 (14)	0.0619 (14)	-0.0011 (11)	-0.0042 (11)	-0.0302 (12)
N1	0.0392 (16)	0.0548 (17)	0.0596 (17)	-0.0016 (13)	-0.0001 (13)	-0.0230 (14)
C1	0.0382 (18)	0.0402 (17)	0.0422 (17)	-0.0145 (15)	-0.0034 (14)	-0.0062 (14)
C2	0.0373 (17)	0.0401 (16)	0.0344 (15)	-0.0146 (14)	-0.0054 (12)	-0.0058 (13)
C3	0.0479 (19)	0.0488 (19)	0.0492 (19)	-0.0120 (16)	-0.0056 (15)	-0.0124 (16)
C4	0.059 (2)	0.066 (2)	0.0479 (19)	-0.0171 (19)	-0.0054 (16)	-0.0247 (17)
C5	0.064 (2)	0.061 (2)	0.0452 (18)	-0.0191 (19)	-0.0137 (16)	-0.0157 (17)
C6	0.0444 (19)	0.056 (2)	0.0467 (18)	-0.0127 (16)	-0.0133 (15)	-0.0122 (16)
C7	0.0380 (17)	0.0432 (17)	0.0398 (16)	-0.0177 (14)	-0.0025 (13)	-0.0068 (13)
C8	0.0430 (18)	0.0410 (17)	0.0387 (16)	-0.0096 (14)	-0.0039 (13)	-0.0084 (14)
C9	0.056 (2)	0.055 (2)	0.055 (2)	-0.0266 (18)	0.0023 (17)	-0.0072 (17)
C10	0.075 (3)	0.044 (2)	0.060 (2)	-0.018 (2)	-0.001 (2)	0.0035 (17)
C11	0.059 (2)	0.0440 (19)	0.057 (2)	0.0006 (17)	-0.0058 (18)	-0.0013 (16)
C12	0.0407 (19)	0.0497 (19)	0.055 (2)	-0.0071 (16)	-0.0006 (15)	-0.0090 (16)
C13	0.0368 (17)	0.0370 (16)	0.0371 (16)	-0.0094 (14)	0.0002 (13)	-0.0088 (13)
C14	0.0338 (17)	0.0419 (18)	0.0397 (16)	-0.0105 (14)	-0.0036 (13)	-0.0090 (14)
C15	0.048 (2)	0.0482 (19)	0.0381 (17)	-0.0065 (16)	0.0032 (15)	-0.0155 (15)
C16	0.045 (2)	0.111 (3)	0.092 (3)	-0.013 (2)	-0.004 (2)	-0.044 (3)
C17	0.060 (2)	0.064 (2)	0.094 (3)	-0.0011 (19)	0.003 (2)	-0.042 (2)

Geometric parameters (\AA , $^\circ$)

Ni1—O2 ⁱ	1.947 (2)	C5—C6	1.373 (4)
Ni1—O4 ⁱⁱ	1.9695 (19)	C5—H5	0.9300
Ni1—O3 ⁱⁱⁱ	1.9751 (19)	C6—C7	1.400 (4)
Ni1—O1	1.9790 (19)	C6—H6	0.9300
Ni1—O5	2.129 (2)	C8—C9	1.389 (4)
Ni1—Ni1 ⁱ	2.6374 (6)	C8—C13	1.390 (4)
S1—C7	1.781 (3)	C9—C10	1.371 (4)
S1—C8	1.786 (3)	C9—H9	0.9300
O1—C1	1.259 (3)	C10—C11	1.368 (5)


O2—C1	1.258 (3)	C10—H10	0.9300
O3—C14	1.249 (3)	C11—C12	1.379 (4)
O4—C14	1.258 (3)	C11—H11	0.9300
O5—C15	1.236 (3)	C12—C13	1.391 (4)
N1—C15	1.325 (4)	C12—H12	0.9300
N1—C17	1.450 (4)	C13—C14	1.507 (4)
N1—C16	1.460 (4)	C15—H15	0.9300
C1—C2	1.504 (4)	C16—H16A	0.9600
C2—C3	1.391 (4)	C16—H16B	0.9600
C2—C7	1.405 (4)	C16—H16C	0.9600
C3—C4	1.375 (4)	C17—H17A	0.9600
C3—H3	0.9300	C17—H17B	0.9600
C4—C5	1.379 (4)	C17—H17C	0.9600
C4—H4	0.9300		
O2 ⁱ —Ni1—O4 ⁱⁱ	90.48 (9)	C7—C6—H6	119.4
O2 ⁱ —Ni1—O3 ⁱⁱⁱ	88.17 (9)	C6—C7—C2	118.1 (3)
O4 ⁱⁱ —Ni1—O3 ⁱⁱⁱ	168.24 (8)	C6—C7—S1	120.9 (2)
O2 ⁱ —Ni1—O1	168.07 (8)	C2—C7—S1	121.0 (2)
O4 ⁱⁱ —Ni1—O1	89.02 (9)	C9—C8—C13	118.9 (3)
O3 ⁱⁱⁱ —Ni1—O1	89.89 (8)	C9—C8—S1	117.6 (2)
O2 ⁱ —Ni1—O5	97.16 (8)	C13—C8—S1	123.1 (2)
O4 ⁱⁱ —Ni1—O5	97.19 (8)	C10—C9—C8	121.5 (3)
O3 ⁱⁱⁱ —Ni1—O5	94.56 (8)	C10—C9—H9	119.2
O1—Ni1—O5	94.73 (8)	C8—C9—H9	119.2
O2 ⁱ —Ni1—Ni1 ⁱ	84.58 (6)	C11—C10—C9	119.6 (3)
O4 ⁱⁱ —Ni1—Ni1 ⁱ	81.54 (6)	C11—C10—H10	120.2
O3 ⁱⁱⁱ —Ni1—Ni1 ⁱ	86.70 (6)	C9—C10—H10	120.2
O1—Ni1—Ni1 ⁱ	83.56 (6)	C10—C11—C12	120.1 (3)
O5—Ni1—Ni1 ⁱ	177.88 (6)	C10—C11—H11	120.0
C7—S1—C8	102.75 (13)	C12—C11—H11	120.0
C1—O1—Ni1	123.11 (19)	C11—C12—C13	120.9 (3)
C1—O2—Ni1 ⁱ	123.63 (19)	C11—C12—H12	119.6
C14—O3—Ni1 ⁱⁱⁱ	119.78 (18)	C13—C12—H12	119.6
C14—O4—Ni1 ^{iv}	125.92 (19)	C8—C13—C12	119.0 (3)
C15—O5—Ni1	120.6 (2)	C8—C13—C14	124.6 (3)
C15—N1—C17	120.9 (3)	C12—C13—C14	116.4 (2)
C15—N1—C16	120.9 (3)	O3—C14—O4	126.0 (3)
C17—N1—C16	118.2 (3)	O3—C14—C13	118.5 (2)
O2—C1—O1	124.9 (3)	O4—C14—C13	115.4 (3)
O2—C1—C2	117.1 (3)	O5—C15—N1	123.4 (3)
O1—C1—C2	118.0 (3)	O5—C15—H15	118.3
C3—C2—C7	119.1 (3)	N1—C15—H15	118.3
C3—C2—C1	117.4 (3)	N1—C16—H16A	109.5
C7—C2—C1	123.5 (3)	N1—C16—H16B	109.5
C4—C3—C2	122.1 (3)	H16A—C16—H16B	109.5

supplementary materials

C4—C3—H3	118.9	N1—C16—H16C	109.5
C2—C3—H3	118.9	H16A—C16—H16C	109.5
C3—C4—C5	118.5 (3)	H16B—C16—H16C	109.5
C3—C4—H4	120.7	N1—C17—H17A	109.5
C5—C4—H4	120.7	N1—C17—H17B	109.5
C6—C5—C4	120.9 (3)	H17A—C17—H17B	109.5
C6—C5—H5	119.6	N1—C17—H17C	109.5
C4—C5—H5	119.6	H17A—C17—H17C	109.5
C5—C6—C7	121.2 (3)	H17B—C17—H17C	109.5
C5—C6—H6	119.4		

Symmetry codes: (i) $-x+1, -y+1, -z+1$; (ii) $x+1, y, z$; (iii) $-x, -y+1, -z+1$; (iv) $x-1, y, z$.

Fig. 1

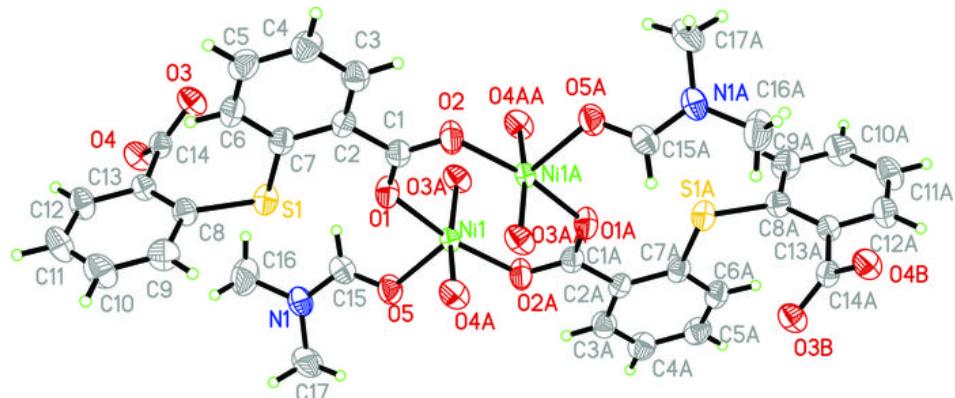

supplementary materials

Fig. 2

