

Poly[(μ - β -hexacosaoxidooctamolybdate)-tetrakis[3-(2-pyridyl)pyrazole]dizinc(II)]

Lujiang Hao* and Bo Liu

Shandong Provincial Key Laboratory of Microbial Engineering, Shandong Institute of Light Industry, Jinan 250353, People's Republic of China
Correspondence e-mail: lujianghao001@yahoo.com.cn


Received 19 June 2010; accepted 28 June 2010

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.019; wR factor = 0.058; data-to-parameter ratio = 12.1.

In the hydrothermally prepared title compound, $[\text{Mo}_8\text{Zn}_2\text{O}_{26}(\text{C}_8\text{H}_7\text{N}_3)_4]_n$ or $\{[\text{Zn}(\text{C}_8\text{H}_7\text{N}_3)_2]_2(\text{Mo}_8\text{O}_{26})\}_n$, the Zn^{II} atom is coordinated by two N,N' -bidentate 3-(2-pyridyl)pyrazole ligands and two O atoms from adjacent octamolybdate polyanions, generating a distorted $\text{cis-ZnO}_2\text{N}_4$ octahedral geometry for the divalent metal ion. The complete octamolybdate unit is generated by crystallographic inversion symmetry. The polyhedral connectivity leads to [100] chains in the crystal and $\text{N}-\text{H}\cdots\text{O}$ and $\text{N}-\text{H}\cdots(\text{O},\text{O})$ hydrogen bonds help to consolidate the packing.

Related literature

For background to polyoxido-molybdates, see: Pope & Müller (1991). For related structures, see: Artero & Proust (2000); Lee *et al.* (2002).

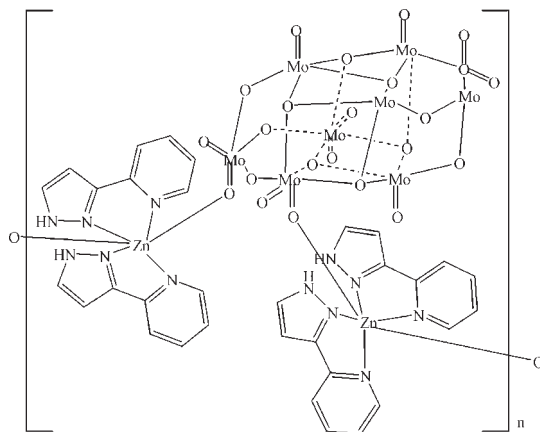

Experimental

Crystal data

 $[\text{Mo}_8\text{Zn}_2\text{O}_{26}(\text{C}_8\text{H}_7\text{N}_3)_4]$ $M_r = 947.46$

Triclinic, $P\bar{1}$
 $a = 10.0791$ (8) Å
 $b = 11.5339$ (10) Å
 $c = 11.6078$ (10) Å
 $\alpha = 89.007$ (1)°
 $\beta = 74.731$ (1)°
 $\gamma = 74.623$ (1)°

$V = 1253.19$ (18) Å³
 $Z = 2$
Mo $K\alpha$ radiation
 $\mu = 2.97$ mm⁻¹
 $T = 296$ K
 $0.12 \times 0.10 \times 0.08$ mm

Data collection

Bruker APEXII CCD diffractometer
Absorption correction: multi-scan (SADABS; Bruker, 2001)
 $T_{\text{min}} = 0.717$, $T_{\text{max}} = 0.797$

8795 measured reflections
4353 independent reflections
3927 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.015$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.019$
 $wR(F^2) = 0.058$
 $S = 1.00$
4353 reflections

361 parameters
H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 0.50$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.46$ e Å⁻³

Table 1

Selected bond lengths (Å).

Zn1—N1	2.081 (3)	Zn1—N6	2.181 (2)
Zn1—N3	2.196 (2)	Zn1—O5 ⁱ	2.104 (2)
Zn1—N5	2.065 (2)	Zn1—O13	2.252 (2)

Symmetry code: (i) $-x, -y + 1, -z + 1$.

Table 2

Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{N2}-\text{H2A}\cdots\text{O1}^{\text{i}}$	0.86	2.13	2.835 (3)	139
$\text{N4}-\text{H4}\cdots\text{O6}$	0.86	2.38	3.094 (4)	141
$\text{N4}-\text{H4}\cdots\text{O10}^{\text{ii}}$	0.86	2.53	3.097 (3)	124

Symmetry codes: (i) $-x, -y + 1, -z + 1$; (ii) $-x + 1, -y + 1, -z + 1$.

Data collection: APEX2 (Bruker, 2004); cell refinement: SAINT-Plus (Bruker, 2001); data reduction: SAINT-Plus; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: SHELXTL (Sheldrick, 2008); software used to prepare material for publication: SHELXTL.

Financial support from the International Cooperation Program for Excellent Lectures of 2008 by the Shandong Provincial Education Department is gratefully acknowledged.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HB5511).

References

- Artero, V. & Proust, A. (2000). *Eur. J. Inorg. Chem.* pp. 2393–2400.
Bruker (2001). SAINT-Plus and SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.
Bruker (2004). APEX2. Bruker AXS Inc., Madison, Wisconsin, USA.
Lee, U., Joo, H.-C. & Cho, M.-A. (2002). *Acta Cryst.* E58, m599–m601.
Pope, M. T. & Müller, A. (1991). *Angew. Chem. Int. Ed.* 30, 34–38.
Sheldrick, G. M. (2008). *Acta Cryst.* A64, 112–122.

supplementary materials

Acta Cryst. (2010). E66, m879 [doi:10.1107/S1600536810025286]

Poly[(μ - β -hexacosaoxidooctamolybdate)tetrakis[3-(2-pyridyl)pyrazole]dizinc(II)]

L. Hao and B. Liu

Comment

The design and synthesis of polyoxometalates has attracted continuous research interest not only because of their appealing structural and topological novelties, but also due to their interesting optical, electronic, magnetic, and catalytic properties, as well as their potential medical applications (Pope & Müller, 1991). Here, we describe the synthesis and structural characterization of the title compound.

As shown in Figure 1, As shown in Figure 1 and 2, the hexa-coordinated zinc cations act as a bridge to link two neighboring octamolybdate polyanions *via* terminal oxygen atoms, which are further chelated by two 3-(2-pyridyl)pyrazole ligands *via* four nitrogen atoms. The Zn—O and Zn—N distances are in the range of 2.104 (2)—2.252 (2) and 2.065 (2)—2.196 (2) Å, respectively.

The octamolybdate polyanion (Mo₈O₂₆)²⁻ shows a B configuration with a center of symmetry, which can be bisected into two [(/m5-O)(Mo₄O₁₂)]²⁻ planar subunits by Mo—O breaking bonds with the related lengths in the range of 2.26–2.39 Å, similar to previously reported isolated clusters (Lee *et al.*, 2002). The [(/m5-O)(Mo₄O₁₂)]²⁻ plane could be considered as one Mo atom protrudes outward from the other four Mo constituted planar. There are two types of Mo—O bonds in octamolybdate polyanion: terminal Mo—O, and bridging /m2-O—Mo, /m3-O—Mo, and /m5-O—Mo bonds. The related bond distances vary from the shortest, 1.690 (2) Å for one of the terminal Mo—O bonds, to the longest 2.389 (2) Å for one of the bonds to the unusual /m5-O atom that sits in the 4Mo plane near the center of each Mo—O moiety.

In addition, it is noteworthy that the multipoint hydrogen-bonding links also exist between the hydrogen atoms from organic amines and the cluster of the surface oxygen atoms from the wave-like chains; this may make a contribution to stabilizing the chain structures, shown in figure 3.

Experimental

The synthesis was performed in a 25-ml Teflon-lined stainless steel vessel. MoO₃ (1 mmol, 0.144 g), zinc(II) acetate dihydrate (0.2 mmol, 0.044 g), 3-(2-pyridyl)pyrazole (0.35 mmol, 0.05 g), and H₂O (14 ml) were mixed and heated to 423 K for three days. Upon cooling, colourless blocks of (I) were recovered by vacuum filtration.

Refinement

All hydrogen atoms bound to aromatic carbon atoms were refined in calculated positions using a riding model with a C—H distance of 0.93 Å and $U_{\text{iso}} = 1.2U_{\text{eq}}(\text{C})$. The hydrogen atoms bound to N atoms were refined in calculated positions using a riding model with a N—H distance of 0.86 Å and $U_{\text{iso}} = 1.2U_{\text{eq}}(\text{C})$.

Figures

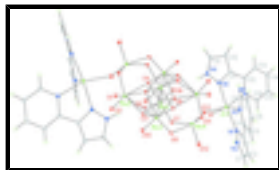


Fig. 1. The building blocks of (I) with displacement ellipsoids drawn at the 30% probability level; H atoms are given as spheres of arbitrary radius.




Fig. 2. The crystal packing of (I) displayed with N—H...O hydrogen bonds as dashed lines.

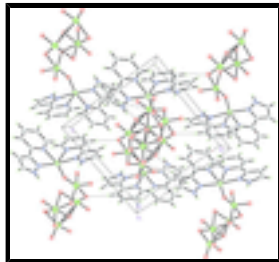


Fig. 3. The chain structure.

Poly[(μ - β -hexacosaoxidooctamolybdate)tetrakis[3-(2-pyridyl)pyrazole]dizinc(II)]

Crystal data

[Mo₈Zn₂O₂₆(C₈H₇N₃)₄]

$M_r = 947.46$

Triclinic, $P\bar{1}$

Hall symbol: -P 1

$a = 10.0791$ (8) Å

$b = 11.5339$ (10) Å

$c = 11.6078$ (10) Å

$\alpha = 89.007$ (1)°

$\beta = 74.731$ (1)°

$\gamma = 74.623$ (1)°

$V = 1253.19$ (18) Å³

$Z = 2$

$F(000) = 908$

$D_x = 2.511$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 6222 reflections

$\theta = 2.2$ – 27.4 °

$\mu = 2.97$ mm⁻¹

$T = 296$ K

Block, colorless

$0.12 \times 0.10 \times 0.08$ mm

Data collection

Bruker APEXII CCD
diffractometer

Radiation source: fine-focus sealed tube
graphite

phi and ω scans

Absorption correction: multi-scan
(*SADABS*; Bruker, 2001)

$T_{\min} = 0.717$, $T_{\max} = 0.797$

8795 measured reflections

4353 independent reflections

3927 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.015$

$\theta_{\max} = 25.0$ °, $\theta_{\min} = 2.2$ °

$h = -11 \rightarrow 11$

$k = -13 \rightarrow 13$

$l = -13 \rightarrow 13$

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.019$	Hydrogen site location: inferred from neighbouring sites
$wR(F^2) = 0.058$	H-atom parameters constrained
$S = 1.00$	$w = 1/[\sigma^2(F_o^2) + (0.038P)^2 + 0.1P]$
4353 reflections	where $P = (F_o^2 + 2F_c^2)/3$
361 parameters	$(\Delta/\sigma)_{\max} = 0.001$
0 restraints	$\Delta\rho_{\max} = 0.50 \text{ e } \text{\AA}^{-3}$
	$\Delta\rho_{\min} = -0.46 \text{ e } \text{\AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
C1	0.0264 (4)	-0.0590 (3)	0.3713 (3)	0.0412 (8)
H1	-0.0334	-0.1045	0.4112	0.049*
C2	0.1715 (4)	-0.0950 (3)	0.3361 (3)	0.0423 (8)
H2	0.2305	-0.1689	0.3471	0.051*
C3	0.2132 (3)	0.0033 (3)	0.2795 (3)	0.0308 (7)
C4	0.3522 (3)	0.0215 (3)	0.2193 (3)	0.0325 (7)
C5	0.4798 (4)	-0.0599 (3)	0.2184 (4)	0.0510 (10)
H5	0.4822	-0.1305	0.2587	0.061*
C6	0.6048 (4)	-0.0338 (4)	0.1556 (4)	0.0607 (11)
H6	0.6928	-0.0862	0.1550	0.073*
C7	0.5986 (4)	0.0683 (3)	0.0952 (4)	0.0529 (10)
H7	0.6820	0.0845	0.0499	0.063*
C8	0.4674 (4)	0.1478 (3)	0.1015 (3)	0.0404 (8)
H8	0.4636	0.2186	0.0613	0.048*
C9	0.2980 (4)	0.5417 (3)	0.0625 (3)	0.0411 (8)
H9	0.3472	0.6002	0.0569	0.049*
C10	0.2574 (4)	0.4981 (3)	-0.0278 (3)	0.0411 (8)
H10	0.2728	0.5205	-0.1065	0.049*

supplementary materials

C11	0.1880 (3)	0.4130 (3)	0.0236 (3)	0.0289 (7)
C12	0.1196 (3)	0.3344 (3)	-0.0244 (3)	0.0281 (7)
C13	0.1012 (4)	0.3425 (3)	-0.1379 (3)	0.0379 (8)
H13	0.1345	0.3977	-0.1891	0.045*
C14	0.0328 (4)	0.2675 (3)	-0.1741 (3)	0.0437 (9)
H14	0.0176	0.2720	-0.2499	0.052*
C15	-0.0133 (4)	0.1852 (3)	-0.0965 (3)	0.0445 (9)
H15	-0.0591	0.1331	-0.1197	0.053*
C16	0.0094 (3)	0.1815 (3)	0.0150 (3)	0.0382 (8)
H16	-0.0224	0.1264	0.0671	0.046*
Mo1	0.19711 (2)	0.56897 (2)	0.54612 (2)	0.02158 (8)
Mo2	0.39657 (2)	0.68604 (2)	0.68548 (2)	0.02263 (8)
Mo3	0.50488 (2)	0.40073 (2)	0.61961 (2)	0.01958 (8)
Mo4	0.30016 (3)	0.27733 (2)	0.48179 (2)	0.02400 (8)
N1	0.0993 (3)	0.0933 (2)	0.2815 (2)	0.0324 (6)
N2	-0.0148 (3)	0.0536 (2)	0.3381 (2)	0.0381 (7)
H2A	-0.1023	0.0953	0.3510	0.046*
N3	0.3455 (3)	0.1258 (2)	0.1639 (2)	0.0305 (6)
N4	0.2540 (3)	0.4845 (2)	0.1601 (2)	0.0366 (6)
H4	0.2672	0.4973	0.2285	0.044*
N5	0.1867 (3)	0.4047 (2)	0.1388 (2)	0.0305 (6)
N6	0.0758 (3)	0.2545 (2)	0.0517 (2)	0.0297 (6)
O1	0.2356 (2)	0.7884 (2)	0.7426 (2)	0.0368 (5)
O2	0.4653 (2)	0.64914 (19)	0.80341 (19)	0.0331 (5)
O3	0.33613 (19)	0.53414 (17)	0.67987 (16)	0.0213 (4)
O4	0.32825 (19)	0.67595 (16)	0.51042 (17)	0.0225 (4)
O5	0.0610 (2)	0.65481 (19)	0.65921 (19)	0.0317 (5)
O6	0.1412 (2)	0.5936 (2)	0.42044 (19)	0.0339 (5)
O7	0.17612 (19)	0.41424 (17)	0.58213 (17)	0.0254 (4)
O8	0.41746 (19)	0.44996 (16)	0.44765 (16)	0.0211 (4)
O9	0.4158 (2)	0.28943 (18)	0.62220 (17)	0.0266 (5)
O10	0.5745 (2)	0.37582 (19)	0.73826 (18)	0.0297 (5)
O11	0.4944 (2)	0.21251 (17)	0.39605 (18)	0.0273 (5)
O12	0.2475 (2)	0.1589 (2)	0.5449 (2)	0.0420 (6)
O13	0.2277 (2)	0.3041 (2)	0.36228 (19)	0.0341 (5)
Zn1	0.13422 (4)	0.25600 (3)	0.21960 (3)	0.02740 (10)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
C1	0.048 (2)	0.044 (2)	0.040 (2)	-0.0261 (17)	-0.0111 (17)	0.0084 (16)
C2	0.046 (2)	0.0324 (18)	0.048 (2)	-0.0101 (16)	-0.0131 (17)	0.0084 (16)
C3	0.0344 (17)	0.0280 (16)	0.0300 (17)	-0.0041 (13)	-0.0131 (14)	0.0023 (13)
C4	0.0336 (17)	0.0262 (16)	0.0331 (18)	-0.0012 (13)	-0.0078 (14)	-0.0032 (13)
C5	0.036 (2)	0.040 (2)	0.067 (3)	0.0012 (16)	-0.0104 (19)	0.0034 (18)
C6	0.032 (2)	0.059 (3)	0.083 (3)	-0.0005 (18)	-0.012 (2)	-0.009 (2)
C7	0.032 (2)	0.060 (3)	0.060 (3)	-0.0160 (19)	0.0035 (18)	-0.014 (2)
C8	0.043 (2)	0.0435 (19)	0.0363 (19)	-0.0196 (16)	-0.0052 (16)	-0.0066 (16)

C9	0.0412 (19)	0.046 (2)	0.042 (2)	-0.0223 (16)	-0.0122 (16)	0.0092 (17)
C10	0.046 (2)	0.047 (2)	0.0305 (18)	-0.0184 (17)	-0.0050 (16)	0.0082 (16)
C11	0.0260 (15)	0.0356 (17)	0.0223 (16)	-0.0061 (13)	-0.0043 (13)	0.0060 (13)
C12	0.0264 (15)	0.0320 (16)	0.0208 (15)	-0.0024 (13)	-0.0029 (12)	0.0010 (13)
C13	0.0412 (19)	0.047 (2)	0.0242 (17)	-0.0114 (16)	-0.0073 (15)	0.0019 (15)
C14	0.044 (2)	0.060 (2)	0.0270 (18)	-0.0108 (18)	-0.0121 (16)	-0.0042 (17)
C15	0.043 (2)	0.057 (2)	0.036 (2)	-0.0182 (17)	-0.0093 (16)	-0.0108 (17)
C16	0.0377 (19)	0.0397 (18)	0.0362 (19)	-0.0122 (15)	-0.0060 (15)	0.0000 (15)
Mo1	0.01351 (13)	0.02965 (14)	0.02125 (14)	-0.00523 (10)	-0.00454 (10)	-0.00102 (11)
Mo2	0.01700 (13)	0.02952 (14)	0.02131 (14)	-0.00717 (10)	-0.00387 (10)	-0.00267 (11)
Mo3	0.01706 (13)	0.02553 (14)	0.01692 (14)	-0.00626 (10)	-0.00557 (10)	0.00432 (10)
Mo4	0.02013 (14)	0.03132 (15)	0.02320 (15)	-0.01142 (11)	-0.00577 (11)	0.00101 (11)
N1	0.0256 (14)	0.0352 (14)	0.0321 (15)	-0.0045 (11)	-0.0044 (11)	0.0072 (12)
N2	0.0281 (14)	0.0484 (17)	0.0360 (16)	-0.0103 (13)	-0.0057 (12)	0.0060 (13)
N3	0.0287 (14)	0.0313 (14)	0.0297 (14)	-0.0063 (11)	-0.0065 (12)	-0.0038 (11)
N4	0.0402 (16)	0.0406 (16)	0.0350 (16)	-0.0123 (13)	-0.0190 (13)	0.0053 (13)
N5	0.0354 (15)	0.0327 (14)	0.0291 (14)	-0.0136 (12)	-0.0142 (12)	0.0077 (11)
N6	0.0308 (14)	0.0314 (13)	0.0254 (14)	-0.0067 (11)	-0.0068 (11)	-0.0008 (11)
O1	0.0228 (11)	0.0454 (13)	0.0374 (13)	-0.0042 (10)	-0.0043 (10)	-0.0099 (11)
O2	0.0352 (12)	0.0417 (13)	0.0285 (12)	-0.0151 (10)	-0.0138 (10)	-0.0011 (10)
O3	0.0159 (9)	0.0299 (10)	0.0185 (10)	-0.0075 (8)	-0.0037 (8)	-0.0001 (8)
O4	0.0180 (10)	0.0262 (10)	0.0225 (10)	-0.0049 (8)	-0.0055 (8)	0.0011 (8)
O5	0.0178 (10)	0.0401 (12)	0.0350 (13)	-0.0079 (9)	-0.0027 (9)	-0.0080 (10)
O6	0.0283 (12)	0.0461 (13)	0.0326 (12)	-0.0124 (10)	-0.0151 (10)	0.0049 (10)
O7	0.0188 (10)	0.0348 (11)	0.0227 (11)	-0.0119 (9)	-0.0010 (8)	-0.0010 (9)
O8	0.0180 (10)	0.0270 (10)	0.0184 (10)	-0.0067 (8)	-0.0045 (8)	0.0020 (8)
O9	0.0264 (11)	0.0325 (11)	0.0230 (11)	-0.0107 (9)	-0.0076 (9)	0.0069 (9)
O10	0.0295 (11)	0.0393 (12)	0.0229 (11)	-0.0090 (9)	-0.0120 (9)	0.0058 (9)
O11	0.0235 (11)	0.0266 (10)	0.0309 (12)	-0.0083 (8)	-0.0042 (9)	0.0008 (9)
O12	0.0392 (13)	0.0435 (14)	0.0482 (15)	-0.0243 (11)	-0.0070 (11)	0.0069 (11)
O13	0.0256 (11)	0.0489 (13)	0.0283 (12)	-0.0060 (10)	-0.0116 (10)	-0.0073 (10)
Zn1	0.02716 (19)	0.02776 (19)	0.02265 (19)	-0.00265 (14)	-0.00377 (15)	0.00391 (14)

Geometric parameters (\AA , $^\circ$)

C1—N2	1.337 (4)	Mo1—O7	1.8795 (19)
C1—C2	1.359 (5)	Mo1—O4	2.0000 (19)
C1—H1	0.9300	Mo1—O8	2.2855 (18)
C2—C3	1.406 (4)	Mo1—O3	2.3153 (18)
C2—H2	0.9300	Mo2—O2	1.690 (2)
C3—N1	1.324 (4)	Mo2—O1	1.706 (2)
C3—C4	1.459 (4)	Mo2—O11 ⁱ	1.8892 (19)
C4—N3	1.348 (4)	Mo2—O3	2.0089 (19)
C4—C5	1.375 (4)	Mo2—O8 ⁱ	2.3154 (18)
C5—C6	1.384 (5)	Mo2—O4	2.3248 (19)
C5—H5	0.9300	Mo3—O10	1.6910 (19)
C6—C7	1.356 (6)	Mo3—O9	1.747 (2)
C6—H6	0.9300	Mo3—O3	1.9424 (18)

supplementary materials

C7—C8	1.380 (5)	Mo3—O4 ⁱ	1.9517 (19)
C7—H7	0.9300	Mo3—O8 ⁱ	2.1294 (18)
C8—N3	1.337 (4)	Mo3—O8	2.3886 (18)
C8—H8	0.9300	Mo4—O12	1.682 (2)
C9—N4	1.334 (4)	Mo4—O13	1.718 (2)
C9—C10	1.369 (5)	Mo4—O11	1.8985 (19)
C9—H9	0.9300	Mo4—O7	1.9139 (19)
C10—C11	1.389 (4)	Mo4—O9	2.2644 (19)
C10—H10	0.9300	N1—N2	1.354 (3)
C11—N5	1.336 (4)	N2—H2A	0.8600
C11—C12	1.470 (4)	N4—N5	1.340 (3)
C12—N6	1.344 (4)	N4—H4	0.8600
C12—C13	1.377 (4)	O4—Mo3 ⁱ	1.9517 (19)
C13—C14	1.371 (5)	O5—Zn1 ⁱⁱ	2.104 (2)
C13—H13	0.9300	O8—Mo3 ⁱ	2.1294 (18)
C14—C15	1.382 (5)	O8—Mo2 ⁱ	2.3154 (18)
C14—H14	0.9300	O11—Mo2 ⁱ	1.8892 (19)
C15—C16	1.370 (5)	Zn1—N1	2.081 (3)
C15—H15	0.9300	Zn1—N3	2.196 (2)
C16—N6	1.342 (4)	Zn1—N5	2.065 (2)
C16—H16	0.9300	Zn1—N6	2.181 (2)
Mo1—O6	1.691 (2)	Zn1—O5 ⁱⁱ	2.104 (2)
Mo1—O5	1.721 (2)	Zn1—O13	2.252 (2)
N2—C1—C2	107.6 (3)	O8 ⁱ —Mo2—O4	72.75 (6)
N2—C1—H1	126.2	O10—Mo3—O9	104.53 (10)
C2—C1—H1	126.2	O10—Mo3—O3	102.49 (9)
C1—C2—C3	105.3 (3)	O9—Mo3—O3	96.90 (9)
C1—C2—H2	127.3	O10—Mo3—O4 ⁱ	100.83 (9)
C3—C2—H2	127.3	O9—Mo3—O4 ⁱ	96.38 (9)
N1—C3—C2	110.1 (3)	O3—Mo3—O4 ⁱ	149.23 (8)
N1—C3—C4	117.0 (3)	O10—Mo3—O8 ⁱ	99.20 (9)
C2—C3—C4	132.9 (3)	O9—Mo3—O8 ⁱ	156.24 (8)
N3—C4—C5	122.3 (3)	O3—Mo3—O8 ⁱ	78.72 (7)
N3—C4—C3	114.3 (3)	O4 ⁱ —Mo3—O8 ⁱ	77.97 (8)
C5—C4—C3	123.4 (3)	O10—Mo3—O8	174.80 (9)
C4—C5—C6	118.1 (4)	O9—Mo3—O8	80.66 (7)
C4—C5—H5	121.0	O3—Mo3—O8	76.97 (7)
C6—C5—H5	121.0	O4 ⁱ —Mo3—O8	77.98 (7)
C7—C6—C5	119.9 (4)	O8 ⁱ —Mo3—O8	75.60 (8)
C7—C6—H6	120.0	O12—Mo4—O13	104.85 (11)
C5—C6—H6	120.0	O12—Mo4—O11	104.88 (10)
C6—C7—C8	119.3 (4)	O13—Mo4—O11	98.55 (9)
C6—C7—H7	120.3	O12—Mo4—O7	104.77 (10)
C8—C7—H7	120.3	O13—Mo4—O7	97.38 (9)
N3—C8—C7	121.7 (3)	O11—Mo4—O7	141.25 (8)

N3—C8—H8	119.2	O12—Mo4—O9	91.45 (9)
C7—C8—H8	119.2	O13—Mo4—O9	163.67 (9)
N4—C9—C10	107.2 (3)	O11—Mo4—O9	77.82 (8)
N4—C9—H9	126.4	O7—Mo4—O9	77.04 (8)
C10—C9—H9	126.4	C3—N1—N2	105.8 (2)
C9—C10—C11	105.1 (3)	C3—N1—Zn1	117.2 (2)
C9—C10—H10	127.5	N2—N1—Zn1	136.5 (2)
C11—C10—H10	127.5	C1—N2—N1	111.2 (3)
N5—C11—C10	110.5 (3)	C1—N2—H2A	124.4
N5—C11—C12	116.9 (3)	N1—N2—H2A	124.4
C10—C11—C12	132.5 (3)	C8—N3—C4	118.6 (3)
N6—C12—C13	122.7 (3)	C8—N3—Zn1	126.8 (2)
N6—C12—C11	114.6 (3)	C4—N3—Zn1	113.3 (2)
C13—C12—C11	122.6 (3)	N5—N4—C9	111.9 (3)
C14—C13—C12	118.6 (3)	N5—N4—H4	124.1
C14—C13—H13	120.7	C9—N4—H4	124.1
C12—C13—H13	120.7	C11—N5—N4	105.3 (2)
C13—C14—C15	119.2 (3)	C11—N5—Zn1	116.1 (2)
C13—C14—H14	120.4	N4—N5—Zn1	136.35 (19)
C15—C14—H14	120.4	C12—N6—C16	118.0 (3)
C14—C15—C16	119.1 (3)	C12—N6—Zn1	113.7 (2)
C14—C15—H15	120.4	C16—N6—Zn1	128.2 (2)
C16—C15—H15	120.4	Mo3—O3—Mo2	108.99 (8)
N6—C16—C15	122.3 (3)	Mo3—O3—Mo1	110.34 (8)
N6—C16—H16	118.8	Mo2—O3—Mo1	104.40 (8)
C15—C16—H16	118.8	Mo3 ⁱ —O4—Mo1	108.87 (9)
O6—Mo1—O5	105.92 (10)	Mo3 ⁱ —O4—Mo2	109.70 (8)
O6—Mo1—O7	102.36 (9)	Mo1—O4—Mo2	104.35 (8)
O5—Mo1—O7	100.55 (9)	Mo1—O5—Zn1 ⁱⁱ	167.30 (12)
O6—Mo1—O4	96.01 (9)	Mo1—O7—Mo4	119.86 (10)
O5—Mo1—O4	100.20 (9)	Mo3 ⁱ —O8—Mo1	93.40 (7)
O7—Mo1—O4	147.19 (8)	Mo3 ⁱ —O8—Mo2 ⁱ	92.63 (7)
O6—Mo1—O8	93.81 (9)	Mo1—O8—Mo2 ⁱ	163.58 (9)
O5—Mo1—O8	159.90 (8)	Mo3 ⁱ —O8—Mo3	104.40 (8)
O7—Mo1—O8	78.43 (7)	Mo1—O8—Mo3	97.00 (7)
O4—Mo1—O8	73.40 (7)	Mo2 ⁱ —O8—Mo3	96.26 (6)
O6—Mo1—O3	163.48 (9)	Mo3—O9—Mo4	120.70 (9)
O5—Mo1—O3	87.50 (8)	Mo2 ⁱ —O11—Mo4	120.57 (10)
O7—Mo1—O3	84.12 (7)	Mo4—O13—Zn1	155.18 (13)
O4—Mo1—O3	71.70 (7)	N5—Zn1—N1	172.65 (10)
O8—Mo1—O3	72.41 (7)	N5—Zn1—O5 ⁱⁱ	98.46 (9)
O2—Mo2—O1	105.26 (11)	N1—Zn1—O5 ⁱⁱ	88.41 (9)
O2—Mo2—O11 ⁱ	102.35 (9)	N5—Zn1—N6	76.74 (10)
O1—Mo2—O11 ⁱ	100.69 (10)	N1—Zn1—N6	99.31 (10)
O2—Mo2—O3	94.91 (9)	O5 ⁱⁱ —Zn1—N6	102.52 (9)
O1—Mo2—O3	101.12 (10)	N5—Zn1—N3	98.82 (10)

supplementary materials

O11 ⁱ —Mo2—O3	147.40 (8)	N1—Zn1—N3	75.45 (10)
O2—Mo2—O8 ⁱ	94.13 (9)	O5 ⁱⁱ —Zn1—N3	155.52 (9)
O1—Mo2—O8 ⁱ	160.27 (9)	N6—Zn1—N3	98.23 (9)
O11 ⁱ —Mo2—O8 ⁱ	78.24 (7)	N5—Zn1—O13	84.54 (9)
O3—Mo2—O8 ⁱ	73.08 (7)	N1—Zn1—O13	98.92 (9)
O2—Mo2—O4	163.06 (9)	O5 ⁱⁱ —Zn1—O13	83.37 (8)
O1—Mo2—O4	87.52 (9)	N6—Zn1—O13	160.98 (9)
O11 ⁱ —Mo2—O4	85.74 (8)	N3—Zn1—O13	81.16 (8)
O3—Mo2—O4	71.34 (7)		

Symmetry codes: (i) $-x+1, -y+1, -z+1$; (ii) $-x, -y+1, -z+1$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
N2—H2A \cdots O1 ⁱⁱ	0.86	2.13	2.835 (3)	139
N4—H4 \cdots O6	0.86	2.38	3.094 (4)	141
N4—H4 \cdots O10 ⁱ	0.86	2.53	3.097 (3)	124

Symmetry codes: (ii) $-x, -y+1, -z+1$; (i) $-x+1, -y+1, -z+1$.

Fig. 1

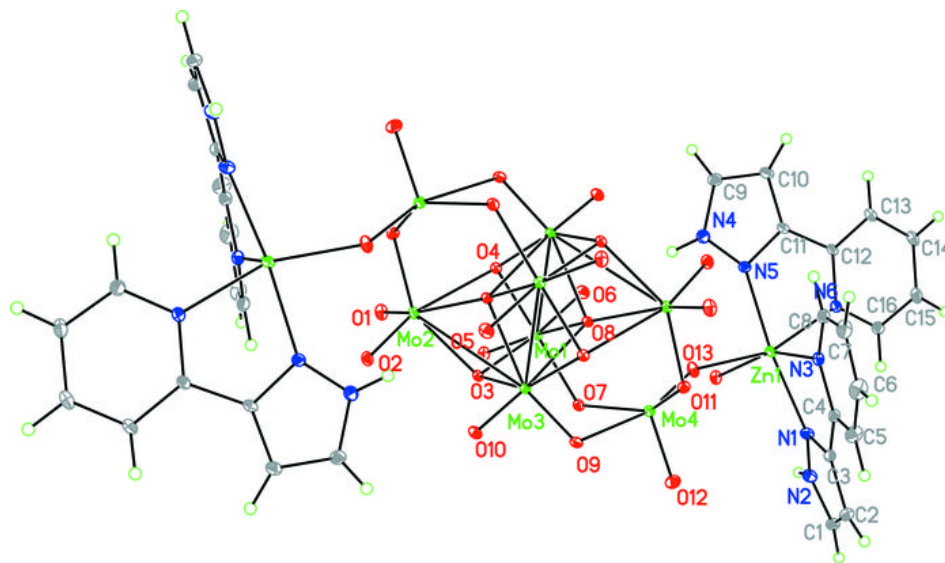


Fig. 2

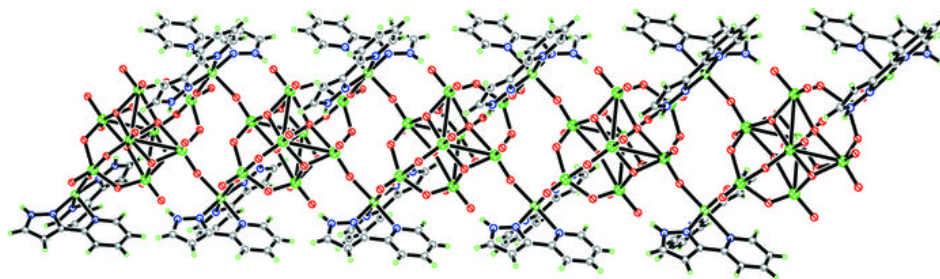


Fig. 3

