

Poly[hexaaqua hexakis(μ -pyridine-2,4-dicarboxylato)tricopper(II)-dieuropium(III)]

Shie Fu Lush^a and Fwu Ming Shen^{b*}

^aDepartment of General Education Center, Yuanpei University, HsinChu, 30015 Taiwan, and ^bDepartment of Biotechnology, Yuanpei University, No. 306, Yuanpei St, HsinChu, 30015 Taiwan

Correspondence e-mail: fmshen@mail.ypu.edu.tw


Received 26 October 2010; accepted 1 November 2010

Key indicators: single-crystal X-ray study; $T = 294\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.005\text{ \AA}$; R factor = 0.028; wR factor = 0.066; data-to-parameter ratio = 15.4.

The asymmetric unit of the title heterometallic coordination polymer, $[\text{Cu}_3\text{Eu}_2(\text{C}_7\text{H}_3\text{NO}_4)_6(\text{H}_2\text{O})_6]_n$, contains one Eu^{III} and two Cu^{II} atoms, three pyridine-2,4-dicarboxylate (pdc)²⁻ anions and three water molecules. One Cu^{II} atom is located on an inversion center and is N,O -chelated by two pdc²⁻ anions in the equatorial plane and further coordinated by two carboxylate O atoms from another two pdc anions in the axial positions, with an elongated octahedral geometry [$\text{Cu}-\text{O} = 2.409(3)\text{ \AA}$ in the axial direction]; the other Cu atom is N,O -chelated by two pdc anions in the coordination basal plane and coordinated by a carboxyl O atom at the apical position with a distorted square-pyramidal geometry [$\text{Cu}-\text{O} = 2.359(3)\text{ \AA}$ in the apical direction]. The Eu atom is eight-coordinated with a distorted square-antiprismatic geometry formed by five carboxylate O atoms from five pdc anions and three water molecules. The carboxylate anions bridge adjacent Eu and Cu atoms, forming the coordination polymer. Inter- and intramolecular O-H \cdots O hydrogen bonding occurs in the structure. $\pi-\pi$ stacking further consolidates the crystal structure, the centroid-centroid distance between parallel pyridine rings being 3.367(2) \AA .

Related literature

For structures and applications of related heterometallic lanthanide-transition metal coordination polymers, see: Huang *et al.* (2008a,b). For the coordination modes of the pyridine-2,6-dicarboxylate ligand, see: Ma *et al.* (2010); Zhao *et al.* (2007); Wang *et al.* (2007). For the coordination modes of the pyridine-2,5-dicarboxylate ligand, see: Song *et al.* (2006); Wang *et al.* (2009). For the coordination modes of the pyridine-2,3-dicarboxylate ligand, see: Wang *et al.* (2010).

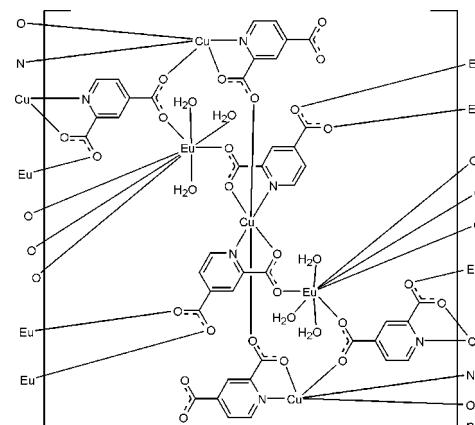

Experimental

Crystal data

$[\text{Cu}_3\text{Eu}_2(\text{C}_7\text{H}_3\text{NO}_4)_6(\text{H}_2\text{O})_6]$	$\gamma = 86.561(2)^\circ$
$M_r = 1593.29$	$V = 1222.0(2)\text{ \AA}^3$
Triclinic, $P\bar{1}$	$Z = 1$
$a = 9.4296(10)\text{ \AA}$	$\text{Mo K}\alpha$ radiation
$b = 10.7002(11)\text{ \AA}$	$\mu = 3.92\text{ mm}^{-1}$
$c = 12.2874(13)\text{ \AA}$	$T = 294\text{ K}$
$\alpha = 86.186(2)^\circ$	$0.24 \times 0.20 \times 0.20\text{ mm}$
$\beta = 81.556(2)^\circ$	

Data collection

Bruker SMART CCD area-detector diffractometer	12982 measured reflections
Absorption correction: multi-scan (<i>SADABS</i> ; Bruker, 2000)	5780 independent reflections
$T_{\min} = 0.659$, $T_{\max} = 0.977$	4828 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.044$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.028$	376 parameters
$wR(F^2) = 0.066$	H-atom parameters constrained
$S = 0.98$	$\Delta\rho_{\max} = 1.69\text{ e \AA}^{-3}$
5780 reflections	$\Delta\rho_{\min} = -0.94\text{ e \AA}^{-3}$

Table 1
Selected bond lengths (\AA).

$\text{Eu1}-\text{O}^{6\text{i}}$	2.485(2)	$\text{Cu1}-\text{O}1$	1.932(3)
$\text{Eu1}-\text{O}8$	2.386(3)	$\text{Cu1}-\text{O}5^{\text{iv}}$	1.944(2)
$\text{Eu1}-\text{O}10^{\text{ii}}$	2.404(2)	$\text{Cu1}-\text{O}7$	2.359(3)
$\text{Eu1}-\text{O}11^{\text{iii}}$	2.385(2)	$\text{Cu1}-\text{N}1$	1.975(3)
$\text{Eu1}-\text{O}12^{\text{i}}$	2.328(2)	$\text{Cu1}-\text{N}2^{\text{iv}}$	1.975(3)
$\text{Eu1}-\text{O}13$	2.454(3)	$\text{Cu2}-\text{O}2$	2.409(3)
$\text{Eu1}-\text{O}14$	2.442(3)	$\text{Cu2}-\text{O}9$	1.968(2)
$\text{Eu1}-\text{O}15$	2.510(3)	$\text{Cu2}-\text{N}3$	1.969(3)

Symmetry codes: (i) $-x + 1, -y + 1, -z$; (ii) $-x + 1, -y + 2, -z$; (iii) $x, y, z + 1$; (iv) $-x, -y + 1, -z$.

Table 2
Hydrogen-bond geometry (\AA , $^\circ$).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{O}13-\text{H}13\text{A}\cdots\text{O}5^{\text{i}}$	0.82	2.00	2.769(3)	155
$\text{O}13-\text{H}13\text{B}\cdots\text{O}15^{\text{v}}$	0.82	2.02	2.822(4)	164
$\text{O}14-\text{H}14\text{A}\cdots\text{O}7$	0.82	1.89	2.690(4)	164
$\text{O}14-\text{H}14\text{B}\cdots\text{O}4^{\text{vi}}$	0.82	1.88	2.667(4)	161
$\text{O}15-\text{H}15\text{A}\cdots\text{O}3^{\text{vii}}$	0.82	1.83	2.630(4)	164
$\text{O}15-\text{H}15\text{B}\cdots\text{O}4^{\text{vi}}$	0.82	2.06	2.814(4)	153

Symmetry codes: (i) $-x + 1, -y + 1, -z$; (v) $-x + 1, -y + 1, -z + 1$; (vi) $-x, -y + 2, -z + 1$; (vii) $x, y - 1, z$.

Data collection: *SMART* (Bruker, 2000); cell refinement: *SAINT* (Bruker, 1999); data reduction: *SAINT*; program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *PLATON* (Spek, 2009); software used to prepare material for publication: *PLATON*.

This work was financial supported by Yuanpei University, Taiwan.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: XU5066).

References

Bruker (1999). *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.

- Bruker (2000). *SMART*. Bruker AXS Inc., Madison, Wisconsin, USA.
Huang, Y.-G., Wu, M.-Y., Lian, F.-Y., Jiang, F.-L. & Hong, M.-C. (2008a). *Inorg. Chem. Commun.* **11**, 840–842.
Huang, Y.-G., Wu, M.-Y., Wei, W., Gao, Q., Yuan, D.-Q., Jiang, F.-L. & Hong, M.-C. (2008b). *J. Mol. Struct.* **885**, 23–27.
Ma, D.-Y., Wang, W.-X. & Li, Y.-W. (2010). *J. Coord. Chem.* **63**, 448–456.
Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
Song, Y.-S., Yan, B. & Weng, L.-H. (2006). *Inorg. Chem. Commun.* **9**, 567–570.
Spek, A. L. (2009). *Acta Cryst. D* **65**, 148–155.
Wang, N., Yue, S.-T., Liu, Y.-L., Yang, H.-Y. & Wu, H.-Y. (2009). *Cryst. Growth Des.* **9**, 368–371.
Wang, N., Yue, S.-T., Wu, H.-Y., Li, X.-X. & Liu, Y.-L. (2010). *Inorg. Chim. Acta*, **363**, 1008–1012.
Wang, F.-Q., Zheng, X.-J., Wan, Y.-H., Sun, C.-Y., Wang, Z.-M., Wang, K.-Z. & Jin, L.-P. (2007). *Inorg. Chem.* **46**, 2956–2958.
Zhao, X.-Q., Zhao, B., Ma, Y., Shi, W., Cheng, P., Jiang, Z.-H., Liao, D.-Z. & Yan, S.-P. (2007). *Inorg. Chem.* **46**, 5832–5834.

supplementary materials

Acta Cryst. (2010). E66, m1516-m1517 [doi:10.1107/S1600536810044594]

Poly[hexaaqua hexakis(μ -pyridine-2,4-dicarboxylato)tricopper(II)dieuropium(III)]

S. F. Lush and F. M. Shen

Comment

In recent years, many research groups have devoted their work to the design and synthesis of lanthanide–transition(3 d-4f) heterometallic coordination frameworks with bridging multifunctional organic ligands, such as pyridinedicarboxylic acid (Ma *et al.*, 2010; Song *et al.*, 2006; Wang *et al.*, 2007; Wang *et al.*, 2009; Wang *et al.*, 2010; Zhao *et al.*, 2007). Pyridine-2,4-dicarboxylic acid (pdaH₂) ligand is a good candidate due to its flexible and various coordination donors containing either N- or O-atom donors. Some examples of coordination with pdaH₂ have been reported (Huang *et al.*, 2008a; Huang *et al.*, 2008b.).

Herein we report a new 3 d-4f heterometallic coordination polymer based on pdaH₂ ligand, formulated as [Eu₂Cu₃(C₇H₃NO₄)₆(H₂O)₆]_n. The symmetric unit of the title compound contains one octa-coordinated Eu^{III} atom and two types of environments of Cu^{II} center, the penta-coordinate Cu^{II} atom is in a square- pyramidal geometry, the other Cu^{II} atom is in a slightly distorted octahedral geometry. The Eu^{III} ion presents a EuO₈ square antiprismatic coordination geometry, formed by five mono-dentate pda O atoms and three coordinate water molecules, the Cu^{II}1 ion presents a CuN₂O₃ square- pyramidal coordination geometry, formed by two bidentate pda (–NO–) ligand (2-carboxy) in the equatorial plane, and one O atom from monodentate pda (4-carboxy) ligand at the axial sites, the other Cu^{II}2 ion presents a slightly distorted (CuN₂O₄) octahedral coordination geometry, formed by two bidentate pda (–NO–) ligand (2-carboxy) in the equatorial plane, and two monodentate pda(2-carboxy) ligands at the axial sites (Table 1, Fig 1). The pda One carboxyl group bridges the neighboring Eu or Cu cations, forming the 3-D polymeric architecture.

In the title crystal structure, a three-dimensional network is formed *via* intra- intermolecular O—H···O hydrogen bonds (Table 2, Fig. 2). In addition, C—H···O hydrogen bonds (full details and symmetry codes are given in Table 2), C7—O3···Cg8 (N3/C15—C19) interactions are also present. The π ··· π , π ···Metal stacking interactions are also observed, the centroid-centroid distance between the pyridine rings being 3.367 (2) Å [Cg7^{iv}···Cg7 (N2/C8—C12)] [symmetry codes: -x, 1 - y, -z]. The Cg1 (Cu1/O1—N1—C1—C6)···Cu1 interaction is 3.905 Å [symmetry codes: -x, 2 - y, -z].

Experimental

A mixture of europium chloride hexahydrate (0.25 mmol, 0.0916 g), copper acetate hydrate (0.25 mmol, 0.050 g), pyridine-2,4-dicarboxylic acid (0.25 mmol, 0.0418 g) and 10 ml H₂O were put in a 23-ml Teflon liner reactor and heated at 418 K in oven for 48 h. The resulting solution was slowly cooled to room temperature. The blue transparent single crystals of the title complex were obtained in 43.21% yield (based on Eu).

supplementary materials

Refinement

Water H atoms were located in a difference Fourier map and refined with the distances constraints of O—H = 0.82 Å, $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$. Other H atoms were positioned geometrically with C—H = 0.93 Å (aromatic), and refined using a riding model with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$.

Figures

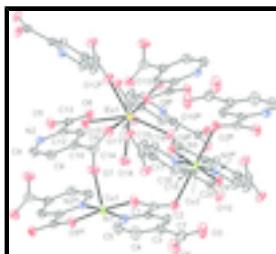


Fig. 1. View of the title compound with the atom numbering scheme. Displacement ellipsoids for non-H atoms are drawn at the 50% probability level. H atoms have been omitted for clarity. [Symmetry codes: (i) $x, y, z + 1$; (ii) $-x + 1, -y + 1, -z$; (iii) $-x + 1, -y + 2, -z$; (iv) $-x, -y + 1, -z$].

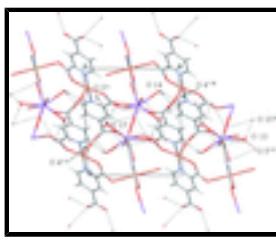


Fig. 2. The molecular packing for the title compound, viewed along the c axis. Hydrogen bonds are shown as dashed lines.

Poly[hexaaqua hexakis(μ -pyridine-2,4-dicarboxylato)tricopper(II)dieuropium(III)]

Crystal data

[Cu ₃ Eu ₂ (C ₇ H ₃ NO ₄) ₆ (H ₂ O) ₆]	$Z = 1$
$M_r = 1593.29$	$F(000) = 777$
Triclinic, $P\bar{1}$	$D_x = 2.165 \text{ Mg m}^{-3}$
Hall symbol: -P 1	Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$
$a = 9.4296 (10) \text{ \AA}$	Cell parameters from 6583 reflections
$b = 10.7002 (11) \text{ \AA}$	$\theta = 2.5\text{--}25.0^\circ$
$c = 12.2874 (13) \text{ \AA}$	$\mu = 3.92 \text{ mm}^{-1}$
$\alpha = 86.186 (2)^\circ$	$T = 294 \text{ K}$
$\beta = 81.556 (2)^\circ$	Equant, blue
$\gamma = 86.561 (2)^\circ$	$0.24 \times 0.20 \times 0.20 \text{ mm}$
$V = 1222.0 (2) \text{ \AA}^3$	

Data collection

Bruker SMART CCD area-detector diffractometer	5780 independent reflections
Radiation source: fine-focus sealed tube graphite	4828 reflections with $I > 2\sigma(I)$ $R_{\text{int}} = 0.044$

Detector resolution: 9 pixels mm ⁻¹	$\theta_{\max} = 28.3^\circ$, $\theta_{\min} = 1.7^\circ$
φ and ω scans	$h = -12 \rightarrow 12$
Absorption correction: multi-scan (SADABS; Bruker, 2000)	$k = -13 \rightarrow 13$
$T_{\min} = 0.659$, $T_{\max} = 0.977$	$l = -15 \rightarrow 16$
12982 measured reflections	

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.028$	Hydrogen site location: inferred from neighbouring sites
$wR(F^2) = 0.066$	H-atom parameters constrained
$S = 0.98$	$w = 1/[\sigma^2(F_o^2) + (0.0323P)^2]$ where $P = (F_o^2 + 2F_c^2)/3$
5780 reflections	$(\Delta/\sigma)_{\max} = 0.001$
376 parameters	$\Delta\rho_{\max} = 1.69 \text{ e \AA}^{-3}$
0 restraints	$\Delta\rho_{\min} = -0.94 \text{ e \AA}^{-3}$

Special details

Geometry. Bond distances, angles etc. have been calculated using the rounded fractional coordinates. All su's are estimated from the variances of the (full) variance-covariance matrix. The cell e.s.d.'s are taken into account in the estimation of distances, angles and torsion angles

Refinement. Refinement on F^2 for ALL reflections except those flagged by the user for potential systematic errors. Weighted R -factors wR and all goodnesses of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The observed criterion of $F^2 > \sigma(F^2)$ is used only for calculating - R -factor-obs etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Eu1	0.42924 (2)	0.65169 (1)	0.35169 (1)	0.0161 (1)
Cu1	-0.04296 (4)	0.81387 (4)	0.11987 (3)	0.0220 (1)
Cu2	0.50000	1.00000	0.00000	0.0188 (2)
O1	0.1188 (3)	0.8879 (2)	0.0288 (2)	0.0274 (8)
O2	0.2474 (3)	1.0583 (2)	0.0150 (2)	0.0272 (8)
O3	0.1716 (3)	1.3256 (3)	0.3467 (2)	0.0406 (10)
O4	-0.0222 (3)	1.2972 (3)	0.4696 (3)	0.0524 (11)
O5	0.2216 (2)	0.2480 (2)	-0.19845 (19)	0.0238 (7)
O6	0.3969 (2)	0.3742 (2)	-0.18098 (19)	0.0236 (8)
O7	0.0882 (3)	0.6635 (2)	0.2196 (2)	0.0313 (8)
O8	0.3149 (3)	0.5865 (2)	0.2057 (2)	0.0258 (8)
O9	0.5336 (3)	1.1177 (2)	-0.13010 (19)	0.0230 (7)

supplementary materials

O10	0.5037 (3)	1.1358 (2)	-0.30699 (19)	0.0235 (7)
O11	0.3895 (3)	0.7209 (2)	-0.46529 (19)	0.0254 (8)
O12	0.4790 (3)	0.5533 (2)	-0.3775 (2)	0.0269 (8)
O13	0.6647 (3)	0.6702 (3)	0.4101 (2)	0.0318 (9)
O14	0.2105 (3)	0.7873 (2)	0.3621 (2)	0.0285 (8)
O15	0.2311 (3)	0.5207 (2)	0.4481 (2)	0.0262 (8)
N1	-0.0265 (3)	0.9489 (3)	0.2186 (2)	0.0222 (9)
N2	0.0738 (3)	0.3055 (3)	-0.0108 (2)	0.0190 (8)
N3	0.4749 (3)	0.8802 (3)	-0.1097 (2)	0.0179 (8)
C1	0.0834 (3)	1.0218 (3)	0.1776 (3)	0.0193 (10)
C2	0.1182 (4)	1.1211 (3)	0.2322 (3)	0.0232 (10)
C3	0.0356 (4)	1.1510 (3)	0.3314 (3)	0.0260 (11)
C4	-0.0795 (4)	1.0771 (4)	0.3712 (3)	0.0344 (12)
C5	-0.1064 (4)	0.9764 (4)	0.3138 (3)	0.0314 (12)
C6	0.1590 (4)	0.9878 (3)	0.0650 (3)	0.0213 (10)
C7	0.0646 (4)	1.2678 (4)	0.3881 (3)	0.0282 (12)
C8	-0.0144 (4)	0.3380 (3)	0.0799 (3)	0.0214 (10)
C9	0.0190 (4)	0.4295 (3)	0.1443 (3)	0.0225 (10)
C10	0.1511 (4)	0.4835 (3)	0.1200 (3)	0.0200 (10)
C11	0.2450 (3)	0.4447 (3)	0.0287 (3)	0.0199 (10)
C12	0.2009 (3)	0.3591 (3)	-0.0364 (3)	0.0177 (9)
C13	0.2824 (3)	0.3236 (3)	-0.1467 (3)	0.0187 (10)
C14	0.1878 (4)	0.5861 (3)	0.1875 (3)	0.0209 (10)
C15	0.4789 (3)	0.9361 (3)	-0.2116 (3)	0.0177 (9)
C16	0.4629 (4)	0.8712 (3)	-0.3016 (3)	0.0195 (10)
C17	0.4471 (4)	0.7427 (3)	-0.2868 (3)	0.0193 (10)
C18	0.4458 (4)	0.6855 (3)	-0.1819 (3)	0.0248 (10)
C19	0.4564 (4)	0.7580 (3)	-0.0948 (3)	0.0233 (10)
C20	0.5063 (3)	1.0751 (3)	-0.2176 (3)	0.0178 (9)
C21	0.4380 (4)	0.6657 (3)	-0.3837 (3)	0.0195 (10)
H2A	0.19630	1.16800	0.20320	0.0280*
H4A	-0.13820	1.09550	0.43650	0.0410*
H5A	-0.18220	0.92660	0.34220	0.0380*
H8A	-0.10000	0.29790	0.09970	0.0260*
H9A	-0.04660	0.45500	0.20380	0.0270*
H11A	0.33600	0.47600	0.01220	0.0240*
H13A	0.71830	0.70010	0.35740	0.0480*
H13B	0.70360	0.60960	0.44030	0.0480*
H14A	0.16690	0.76300	0.31500	0.0430*
H14B	0.15520	0.77690	0.41960	0.0430*
H15A	0.19680	0.46590	0.41800	0.0390*
H15B	0.15630	0.55220	0.48000	0.0390*
H16A	0.46260	0.91230	-0.37070	0.0230*
H18A	0.43800	0.59920	-0.17040	0.0300*
H19A	0.45030	0.72020	-0.02400	0.0280*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Eu1	0.0202 (1)	0.0122 (1)	0.0166 (1)	-0.0010 (1)	-0.0040 (1)	-0.0033 (1)
Cu1	0.0214 (2)	0.0212 (2)	0.0238 (2)	-0.0061 (2)	0.0003 (2)	-0.0088 (2)
Cu2	0.0269 (3)	0.0140 (3)	0.0167 (3)	-0.0032 (2)	-0.0048 (2)	-0.0041 (2)
O1	0.0258 (13)	0.0283 (15)	0.0280 (14)	-0.0073 (11)	0.0036 (11)	-0.0125 (11)
O2	0.0224 (13)	0.0206 (14)	0.0364 (15)	-0.0039 (10)	0.0047 (11)	-0.0022 (11)
O3	0.0470 (18)	0.0376 (17)	0.0378 (16)	-0.0199 (14)	0.0054 (14)	-0.0160 (13)
O4	0.0512 (19)	0.046 (2)	0.057 (2)	-0.0178 (15)	0.0228 (16)	-0.0343 (16)
O5	0.0226 (12)	0.0271 (14)	0.0222 (12)	-0.0056 (10)	-0.0001 (10)	-0.0089 (10)
O6	0.0211 (12)	0.0235 (14)	0.0258 (13)	-0.0055 (10)	0.0027 (10)	-0.0073 (10)
O7	0.0308 (14)	0.0296 (15)	0.0369 (15)	0.0100 (12)	-0.0139 (12)	-0.0169 (12)
O8	0.0222 (13)	0.0320 (15)	0.0250 (13)	-0.0017 (11)	-0.0061 (11)	-0.0095 (11)
O9	0.0349 (14)	0.0140 (12)	0.0215 (12)	-0.0062 (10)	-0.0067 (11)	-0.0016 (10)
O10	0.0352 (14)	0.0145 (12)	0.0207 (12)	-0.0031 (10)	-0.0032 (11)	-0.0002 (10)
O11	0.0367 (14)	0.0211 (13)	0.0190 (12)	0.0028 (11)	-0.0064 (11)	-0.0042 (10)
O12	0.0392 (15)	0.0133 (13)	0.0285 (14)	0.0033 (11)	-0.0062 (12)	-0.0056 (10)
O13	0.0287 (14)	0.0401 (17)	0.0280 (14)	-0.0078 (12)	-0.0103 (11)	0.0068 (12)
O14	0.0282 (14)	0.0287 (15)	0.0301 (14)	0.0032 (11)	-0.0076 (11)	-0.0084 (11)
O15	0.0264 (13)	0.0219 (13)	0.0304 (14)	-0.0060 (10)	0.0002 (11)	-0.0076 (11)
N1	0.0215 (15)	0.0211 (16)	0.0239 (15)	-0.0018 (12)	0.0000 (12)	-0.0070 (12)
N2	0.0182 (14)	0.0165 (14)	0.0220 (15)	0.0014 (11)	-0.0025 (12)	-0.0018 (11)
N3	0.0223 (14)	0.0156 (14)	0.0159 (14)	-0.0019 (11)	-0.0018 (11)	-0.0034 (11)
C1	0.0178 (16)	0.0178 (17)	0.0229 (17)	0.0008 (13)	-0.0037 (14)	-0.0049 (13)
C2	0.0240 (18)	0.0167 (17)	0.0295 (19)	-0.0045 (14)	-0.0036 (15)	-0.0030 (14)
C3	0.0252 (19)	0.024 (2)	0.029 (2)	-0.0025 (15)	-0.0016 (16)	-0.0078 (16)
C4	0.037 (2)	0.034 (2)	0.031 (2)	-0.0092 (18)	0.0076 (17)	-0.0137 (17)
C5	0.029 (2)	0.032 (2)	0.032 (2)	-0.0102 (17)	0.0068 (17)	-0.0101 (17)
C6	0.0179 (17)	0.0220 (18)	0.0242 (18)	0.0047 (14)	-0.0054 (14)	-0.0030 (14)
C7	0.035 (2)	0.022 (2)	0.029 (2)	-0.0021 (16)	-0.0053 (17)	-0.0090 (16)
C8	0.0175 (16)	0.0229 (19)	0.0233 (17)	-0.0030 (13)	-0.0005 (14)	-0.0022 (14)
C9	0.0218 (17)	0.0253 (19)	0.0202 (17)	0.0024 (14)	-0.0017 (14)	-0.0061 (14)
C10	0.0215 (17)	0.0199 (18)	0.0197 (17)	0.0032 (14)	-0.0074 (14)	-0.0040 (13)
C11	0.0157 (16)	0.0218 (18)	0.0229 (17)	-0.0012 (13)	-0.0040 (14)	-0.0040 (14)
C12	0.0167 (16)	0.0178 (17)	0.0187 (16)	0.0004 (13)	-0.0027 (13)	-0.0021 (13)
C13	0.0188 (16)	0.0173 (17)	0.0207 (17)	0.0024 (13)	-0.0050 (14)	-0.0037 (13)
C14	0.0253 (18)	0.0232 (18)	0.0147 (16)	0.0010 (14)	-0.0046 (14)	-0.0036 (13)
C15	0.0205 (16)	0.0133 (16)	0.0195 (16)	-0.0003 (13)	-0.0030 (13)	-0.0026 (13)
C16	0.0272 (18)	0.0164 (17)	0.0154 (16)	0.0005 (13)	-0.0056 (14)	-0.0010 (13)
C17	0.0216 (17)	0.0158 (17)	0.0208 (17)	0.0016 (13)	-0.0033 (14)	-0.0048 (13)
C18	0.040 (2)	0.0151 (17)	0.0200 (17)	-0.0041 (15)	-0.0046 (16)	-0.0028 (13)
C19	0.036 (2)	0.0182 (18)	0.0160 (16)	-0.0015 (15)	-0.0051 (15)	0.0006 (13)
C20	0.0169 (16)	0.0136 (16)	0.0220 (17)	-0.0005 (12)	0.0009 (13)	-0.0031 (13)
C21	0.0209 (17)	0.0193 (18)	0.0184 (16)	-0.0049 (13)	-0.0001 (14)	-0.0043 (13)

supplementary materials

Geometric parameters (\AA , $^\circ$)

Eu1—O6 ⁱ	2.485 (2)	O15—H15B	0.8200
Eu1—O8	2.386 (3)	O15—H15A	0.8200
Eu1—O10 ⁱⁱ	2.404 (2)	N1—C5	1.335 (5)
Eu1—O11 ⁱⁱⁱ	2.385 (2)	N1—C1	1.352 (4)
Eu1—O12 ⁱ	2.328 (2)	N2—C8	1.341 (4)
Eu1—O13	2.454 (3)	N2—C12	1.346 (4)
Eu1—O14	2.442 (3)	N3—C15	1.348 (4)
Eu1—O15	2.510 (3)	N3—C19	1.327 (5)
Cu1—O1	1.932 (3)	C1—C6	1.517 (5)
Cu1—O5 ^{iv}	1.944 (2)	C1—C2	1.374 (5)
Cu1—O7	2.359 (3)	C2—C3	1.392 (5)
Cu1—N1	1.975 (3)	C3—C7	1.528 (5)
Cu1—N2 ^{iv}	1.975 (3)	C3—C4	1.392 (5)
Cu2—O2	2.409 (3)	C4—C5	1.382 (6)
Cu2—O9	1.968 (2)	C8—C9	1.377 (5)
Cu2—N3	1.969 (3)	C9—C10	1.389 (5)
Cu2—O2 ⁱⁱ	2.409 (3)	C10—C11	1.393 (5)
Cu2—O9 ⁱⁱ	1.968 (2)	C10—C14	1.505 (5)
Cu2—N3 ⁱⁱ	1.969 (3)	C11—C12	1.376 (5)
O1—C6	1.283 (4)	C12—C13	1.516 (5)
O2—C6	1.227 (4)	C15—C20	1.520 (5)
O3—C7	1.242 (5)	C15—C16	1.375 (5)
O4—C7	1.242 (5)	C16—C17	1.389 (5)
O5—C13	1.272 (4)	C17—C21	1.508 (5)
O6—C13	1.242 (4)	C17—C18	1.388 (5)
O7—C14	1.251 (4)	C18—C19	1.381 (5)
O8—C14	1.251 (5)	C2—H2A	0.9300
O9—C20	1.261 (4)	C4—H4A	0.9300
O10—C20	1.241 (4)	C5—H5A	0.9300
O11—C21	1.260 (4)	C8—H8A	0.9300
O12—C21	1.242 (4)	C9—H9A	0.9300
O13—H13B	0.8200	C11—H11A	0.9300
O13—H13A	0.8200	C16—H16A	0.9300
O14—H14A	0.8200	C18—H18A	0.9300
O14—H14B	0.8200	C19—H19A	0.9300
O8—Eu1—O13	143.07 (9)	H15A—O15—H15B	99.00
O8—Eu1—O14	76.92 (8)	Eu1—O15—H15A	123.00
O8—Eu1—O15	75.96 (8)	Eu1—O15—H15B	122.00
O8—Eu1—O11 ⁱⁱⁱ	144.45 (9)	C1—N1—C5	118.9 (3)
O6 ⁱ —Eu1—O8	68.55 (8)	Cu1—N1—C1	111.1 (2)
O8—Eu1—O12 ⁱ	88.94 (8)	Cu1—N1—C5	130.0 (3)
O8—Eu1—O10 ⁱⁱ	108.10 (8)	Cu1 ^{iv} —N2—C8	128.5 (2)
O13—Eu1—O14	133.64 (9)	C8—N2—C12	119.2 (3)

O13—Eu1—O15	126.29 (9)	Cu1 ^{iv} —N2—C12	112.3 (2)
O11 ⁱⁱⁱ —Eu1—O13	72.28 (9)	Cu2—N3—C19	128.7 (2)
O6 ⁱ —Eu1—O13	75.67 (8)	Cu2—N3—C15	111.9 (2)
O12 ⁱ —Eu1—O13	74.51 (10)	C15—N3—C19	119.4 (3)
O10 ⁱⁱ —Eu1—O13	72.65 (10)	N1—C1—C6	114.2 (3)
O14—Eu1—O15	73.99 (8)	C2—C1—C6	123.6 (3)
O11 ⁱⁱⁱ —Eu1—O14	74.60 (9)	N1—C1—C2	122.2 (3)
O6 ⁱ —Eu1—O14	124.22 (8)	C1—C2—C3	119.5 (3)
O12 ⁱ —Eu1—O14	144.83 (9)	C2—C3—C4	117.7 (3)
O10 ⁱⁱ —Eu1—O14	71.70 (9)	C2—C3—C7	120.2 (3)
O11 ⁱⁱⁱ —Eu1—O15	76.07 (8)	C4—C3—C7	122.0 (3)
O6 ⁱ —Eu1—O15	132.71 (7)	C3—C4—C5	120.0 (3)
O12 ⁱ —Eu1—O15	71.37 (9)	N1—C5—C4	121.7 (4)
O10 ⁱⁱ —Eu1—O15	143.28 (8)	O1—C6—C1	115.5 (3)
O6 ⁱ —Eu1—O11 ⁱⁱⁱ	146.55 (8)	O1—C6—O2	125.7 (3)
O11 ⁱⁱⁱ —Eu1—O12 ⁱ	102.40 (8)	O2—C6—C1	118.8 (3)
O10 ⁱⁱ —Eu1—O11 ⁱⁱⁱ	82.57 (8)	O3—C7—C3	116.6 (3)
O6 ⁱ —Eu1—O12 ⁱ	77.62 (8)	O3—C7—O4	126.3 (4)
O6 ⁱ —Eu1—O10 ⁱⁱ	79.02 (8)	O4—C7—C3	117.1 (3)
O10 ⁱⁱ —Eu1—O12 ⁱ	143.40 (10)	N2—C8—C9	121.5 (3)
O1—Cu1—O7	97.47 (10)	C8—C9—C10	119.7 (3)
O1—Cu1—N1	84.50 (11)	C9—C10—C11	118.4 (3)
O1—Cu1—O5 ^{iv}	172.30 (10)	C9—C10—C14	120.4 (3)
O1—Cu1—N2 ^{iv}	94.73 (11)	C11—C10—C14	121.1 (3)
O1—Cu1—O2 ^v	92.14 (9)	C10—C11—C12	118.9 (3)
O7—Cu1—N1	93.91 (10)	C11—C12—C13	124.3 (3)
O5 ^{iv} —Cu1—O7	90.08 (9)	N2—C12—C13	113.4 (3)
O7—Cu1—N2 ^{iv}	93.32 (10)	N2—C12—C11	122.1 (3)
O2 ^v —Cu1—O7	164.52 (8)	O5—C13—C12	115.7 (3)
O5 ^{iv} —Cu1—N1	96.55 (10)	O6—C13—C12	118.4 (3)
N1—Cu1—N2 ^{iv}	172.76 (12)	O5—C13—O6	125.9 (3)
O2 ^v —Cu1—N1	99.09 (10)	O8—C14—C10	117.1 (3)
O5 ^{iv} —Cu1—N2 ^{iv}	83.28 (10)	O7—C14—O8	126.2 (3)
O2 ^v —Cu1—O5 ^{iv}	80.16 (8)	O7—C14—C10	116.7 (3)
O2 ^v —Cu1—N2 ^{iv}	73.73 (10)	N3—C15—C20	113.9 (3)
O2—Cu2—O9	88.97 (10)	C16—C15—C20	123.7 (3)
O2—Cu2—N3	88.99 (10)	N3—C15—C16	122.4 (3)
O2—Cu2—O2 ⁱⁱ	180.00	C15—C16—C17	118.4 (3)
O2—Cu2—O9 ⁱⁱ	91.03 (10)	C16—C17—C21	120.6 (3)
O2—Cu2—N3 ⁱⁱ	91.01 (10)	C18—C17—C21	120.5 (3)
O9—Cu2—N3	83.49 (11)	C16—C17—C18	118.9 (3)
O2 ⁱⁱ —Cu2—O9	91.03 (10)	C17—C18—C19	119.3 (3)

supplementary materials

O9—Cu2—O9 ⁱⁱ	180.00	N3—C19—C18	121.6 (3)
O9—Cu2—N3 ⁱⁱ	96.51 (10)	O9—C20—C15	115.9 (3)
O2 ⁱⁱ —Cu2—N3	91.01 (10)	O10—C20—C15	118.3 (3)
O9 ⁱⁱ —Cu2—N3	96.51 (11)	O9—C20—O10	125.7 (3)
N3—Cu2—N3 ⁱⁱ	180.00	O12—C21—C17	117.9 (3)
O2 ⁱⁱ —Cu2—O9 ⁱⁱ	88.97 (10)	O11—C21—O12	124.9 (3)
O2 ⁱⁱ —Cu2—N3 ⁱⁱ	88.99 (10)	O11—C21—C17	117.2 (3)
O9 ⁱⁱ —Cu2—N3 ⁱⁱ	83.49 (10)	C1—C2—H2A	120.00
Cu1—O1—C6	114.4 (2)	C3—C2—H2A	120.00
Cu2—O2—C6	120.1 (2)	C3—C4—H4A	120.00
Cu1 ^v —O2—Cu2	138.98 (10)	C5—C4—H4A	120.00
Cu1 ^v —O2—C6	94.1 (2)	N1—C5—H5A	119.00
Cu1 ^{iv} —O5—C13	115.0 (2)	C4—C5—H5A	119.00
Eu1 ⁱ —O6—C13	131.3 (2)	N2—C8—H8A	119.00
Cu1—O7—C14	130.9 (2)	C9—C8—H8A	119.00
Eu1—O8—C14	134.9 (2)	C8—C9—H9A	120.00
Cu2—O9—C20	113.9 (2)	C10—C9—H9A	120.00
Eu1 ⁱⁱ —O10—C20	127.0 (2)	C10—C11—H11A	121.00
Eu1 ^{vi} —O11—C21	125.3 (2)	C12—C11—H11A	121.00
Eu1 ⁱ —O12—C21	173.8 (3)	C15—C16—H16A	121.00
H13A—O13—H13B	112.00	C17—C16—H16A	121.00
Eu1—O13—H13A	108.00	C17—C18—H18A	120.00
Eu1—O13—H13B	120.00	C19—C18—H18A	120.00
H14A—O14—H14B	104.00	N3—C19—H19A	119.00
Eu1—O14—H14A	105.00	C18—C19—H19A	119.00
Eu1—O14—H14B	114.00		
O13—Eu1—O8—C14	−178.0 (3)	Cu1—O7—C14—C10	−65.8 (4)
O14—Eu1—O8—C14	−27.5 (3)	Eu1—O8—C14—O7	31.0 (5)
O15—Eu1—O8—C14	49.0 (3)	Eu1—O8—C14—C10	−149.5 (2)
O11 ⁱⁱⁱ —Eu1—O8—C14	9.9 (4)	Cu2—O9—C20—O10	171.5 (3)
O6 ⁱ —Eu1—O8—C14	−162.9 (3)	Cu2—O9—C20—C15	−10.4 (3)
O12 ⁱ —Eu1—O8—C14	120.0 (3)	Eu1 ⁱⁱ —O10—C20—O9	6.3 (5)
O10 ⁱⁱ —Eu1—O8—C14	−93.0 (3)	Eu1 ⁱⁱ —O10—C20—C15	−171.72 (19)
O8—Eu1—O11 ⁱⁱⁱ —C21 ⁱⁱⁱ	119.5 (3)	Eu1 ^{vi} —O11—C21—O12	−20.8 (5)
O13—Eu1—O11 ⁱⁱⁱ —C21 ⁱⁱⁱ	−55.5 (3)	Eu1 ^{vi} —O11—C21—C17	159.0 (2)
O14—Eu1—O11 ⁱⁱⁱ —C21 ⁱⁱⁱ	157.4 (3)	Cu1—N1—C1—C2	−179.0 (3)
O15—Eu1—O11 ⁱⁱⁱ —C21 ⁱⁱⁱ	80.5 (3)	Cu1—N1—C1—C6	3.7 (3)
O8—Eu1—O6 ⁱ —C13 ⁱ	152.9 (3)	C5—N1—C1—C2	1.9 (5)
O13—Eu1—O6 ⁱ —C13 ⁱ	−36.4 (3)	C5—N1—C1—C6	−175.5 (3)
O14—Eu1—O6 ⁱ —C13 ⁱ	97.0 (3)	Cu1—N1—C5—C4	−179.0 (3)
O15—Eu1—O6 ⁱ —C13 ⁱ	−163.0 (3)	C1—N1—C5—C4	0.0 (5)
O8—Eu1—O10 ⁱⁱ —C20 ⁱⁱ	−10.3 (3)	C12—N2—C8—C9	3.3 (5)
O13—Eu1—O10 ⁱⁱ —C20 ⁱⁱ	130.9 (3)	Cu1 ^{iv} —N2—C8—C9	−175.7 (3)

O14—Eu1—O10 ⁱⁱ —C20 ⁱⁱ	−79.3 (3)	C8—N2—C12—C11	1.3 (5)
O15—Eu1—O10 ⁱⁱ —C20 ⁱⁱ	−100.9 (3)	C8—N2—C12—C13	−174.1 (3)
O7—Cu1—O1—C6	−96.6 (2)	Cu1 ^{iv} —N2—C12—C11	−179.6 (3)
N1—Cu1—O1—C6	−3.3 (2)	Cu1 ^{iv} —N2—C12—C13	5.0 (3)
N2 ^{iv} —Cu1—O1—C6	169.5 (3)	Cu2—N3—C15—C16	−179.6 (3)
O2 ^v —Cu1—O1—C6	95.6 (2)	Cu2—N3—C15—C20	1.9 (3)
O1—Cu1—O7—C14	−48.9 (3)	C19—N3—C15—C16	0.7 (5)
N1—Cu1—O7—C14	−133.9 (3)	C19—N3—C15—C20	−177.8 (3)
O5 ^{iv} —Cu1—O7—C14	129.6 (3)	Cu2—N3—C19—C18	−177.5 (3)
N2 ^{iv} —Cu1—O7—C14	46.3 (3)	C15—N3—C19—C18	2.2 (5)
O1—Cu1—N1—C1	−0.5 (2)	N1—C1—C2—C3	−2.1 (5)
O1—Cu1—N1—C5	178.5 (3)	C6—C1—C2—C3	175.1 (3)
O7—Cu1—N1—C1	96.6 (2)	N1—C1—C6—O1	−6.7 (4)
O7—Cu1—N1—C5	−84.4 (3)	N1—C1—C6—O2	170.7 (3)
O5 ^{iv} —Cu1—N1—C1	−172.9 (2)	C2—C1—C6—O1	176.0 (3)
O5 ^{iv} —Cu1—N1—C5	6.2 (3)	C2—C1—C6—O2	−6.7 (5)
O2 ^v —Cu1—N1—C1	−91.8 (2)	C1—C2—C3—C4	0.4 (5)
O2 ^v —Cu1—N1—C5	87.2 (3)	C1—C2—C3—C7	−174.7 (3)
O7—Cu1—O5 ^{iv} —C13 ^{iv}	−98.6 (2)	C2—C3—C4—C5	1.4 (6)
N1—Cu1—O5 ^{iv} —C13 ^{iv}	167.5 (2)	C7—C3—C4—C5	176.3 (4)
O1—Cu1—N2 ^{iv} —C8 ^{iv}	14.0 (3)	C2—C3—C7—O3	−6.4 (5)
O1—Cu1—N2 ^{iv} —C12 ^{iv}	−166.9 (2)	C2—C3—C7—O4	172.3 (4)
O7—Cu1—N2 ^{iv} —C8 ^{iv}	−83.8 (3)	C4—C3—C7—O3	178.8 (4)
O7—Cu1—N2 ^{iv} —C12 ^{iv}	95.3 (2)	C4—C3—C7—O4	−2.5 (6)
O1—Cu1—O2 ^v —C6 ^v	−12.3 (2)	C3—C4—C5—N1	−1.6 (6)
N1—Cu1—O2 ^v —C6 ^v	72.5 (2)	N2—C8—C9—C10	−4.7 (5)
O9—Cu2—O2—C6	158.3 (3)	C8—C9—C10—C11	1.4 (5)
O9—Cu2—O2—Cu1 ^v	15.88 (14)	C8—C9—C10—C14	178.3 (3)
N3—Cu2—O2—C6	74.8 (3)	C9—C10—C11—C12	2.9 (5)
N3—Cu2—O2—Cu1 ^v	−67.63 (15)	C14—C10—C11—C12	−173.9 (3)
O9 ⁱⁱ —Cu2—O2—C6	−21.7 (3)	C9—C10—C14—O7	−37.3 (5)
N3 ⁱⁱ —Cu2—O2—C6	−105.2 (3)	C9—C10—C14—O8	143.1 (3)
O2—Cu2—O9—C20	−80.0 (2)	C11—C10—C14—O7	139.4 (3)
N3—Cu2—O9—C20	9.1 (2)	C11—C10—C14—O8	−40.2 (5)
O2 ⁱⁱ —Cu2—O9—C20	100.0 (2)	C10—C11—C12—N2	−4.4 (5)
N3 ⁱⁱ —Cu2—O9—C20	−170.9 (2)	C10—C11—C12—C13	170.5 (3)
O2—Cu2—N3—C15	83.5 (2)	N2—C12—C13—O5	−0.9 (4)
O2—Cu2—N3—C19	−96.9 (3)	N2—C12—C13—O6	175.6 (3)
O9—Cu2—N3—C15	−5.6 (2)	C11—C12—C13—O5	−176.2 (3)
O9—Cu2—N3—C19	174.1 (3)	C11—C12—C13—O6	0.3 (5)
O2 ⁱⁱ —Cu2—N3—C15	−96.5 (2)	N3—C15—C16—C17	−2.3 (5)
O2 ⁱⁱ —Cu2—N3—C19	83.1 (3)	C20—C15—C16—C17	176.1 (3)
O9 ⁱⁱ —Cu2—N3—C15	174.4 (2)	N3—C15—C20—O9	5.8 (4)

supplementary materials

O9 ⁱⁱ —Cu2—N3—C19	−6.0 (3)	N3—C15—C20—O10	−176.0 (3)
Cu1—O1—C6—O2	−171.0 (3)	C16—C15—C20—O9	−172.7 (3)
Cu1—O1—C6—C1	6.1 (4)	C16—C15—C20—O10	5.5 (5)
Cu2—O2—C6—O1	−76.7 (4)	C15—C16—C17—C18	1.0 (5)
Cu2—O2—C6—C1	106.3 (3)	C15—C16—C17—C21	−176.4 (3)
Cu1 ^v —O2—C6—O1	79.6 (4)	C16—C17—C18—C19	1.7 (6)
Cu1 ^v —O2—C6—C1	−97.4 (3)	C21—C17—C18—C19	179.1 (3)
Cu1 ^{iv} —O5—C13—O6	179.9 (3)	C16—C17—C21—O11	−27.2 (5)
Cu1 ^{iv} —O5—C13—C12	−3.9 (3)	C16—C17—C21—O12	152.6 (4)
Eu1 ⁱ —O6—C13—O5	−4.7 (5)	C18—C17—C21—O11	155.5 (4)
Eu1 ⁱ —O6—C13—C12	179.13 (19)	C18—C17—C21—O12	−24.7 (5)
Cu1—O7—C14—O8	113.8 (4)	C17—C18—C19—N3	−3.4 (6)


Symmetry codes: (i) $-x+1, -y+1, -z$; (ii) $-x+1, -y+2, -z$; (iii) $x, y, z+1$; (iv) $-x, -y+1, -z$; (v) $-x, -y+2, -z$; (vi) $x, y, z-1$.

Hydrogen-bond geometry (\AA , °)

$D\cdots H$	$H\cdots A$	$D\cdots A$	$D\cdots H\cdots A$
O13—H13A···O5 ⁱ	0.82	2.00	2.769 (3)
O13—H13B···O15 ^{vii}	0.82	2.02	2.822 (4)
O14—H14A···O7	0.82	1.89	2.690 (4)
O14—H14B···O4 ^{viii}	0.82	1.88	2.667 (4)
O15—H15A···O3 ^{ix}	0.82	1.83	2.630 (4)
O15—H15B···O4 ^{viii}	0.82	2.06	2.814 (4)
C18—H18A···O6	0.93	2.48	3.389 (4)

Symmetry codes: (i) $-x+1, -y+1, -z$; (vii) $-x+1, -y+1, -z+1$; (viii) $-x, -y+2, -z+1$; (ix) $x, y-1, z$.

Fig. 1

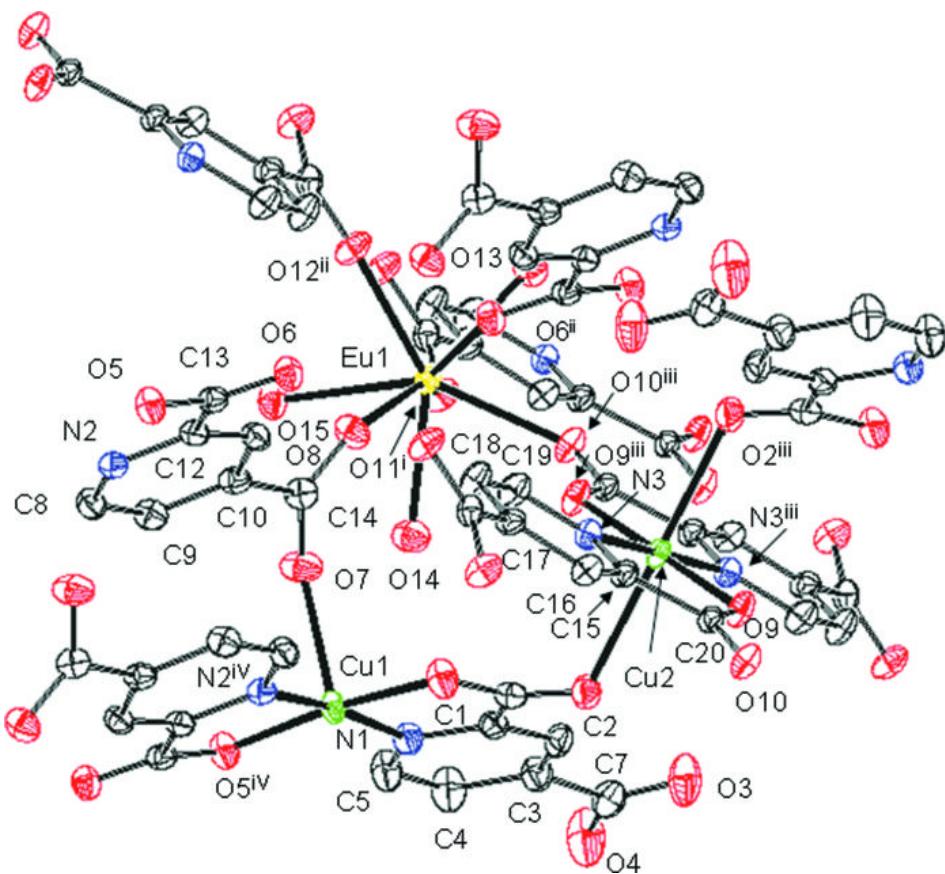

supplementary materials

Fig. 2

