

Li₂Ca_{1.5}Nb₃O₁₀ from X-ray powder dataBai-Chuan Zhu^a and Kai-Bin Tang^{a,b*}

^aDepartment of Chemistry, University of Science and Technology of China, Hefei, Anhui 230026, People's Republic of China, and ^bDepartment of Nanomaterial and Nanochemistry, Hefei National Laboratory for Physical Sciences at Microscale, University of Science and Technology of China, Hefei, Anhui 230026, People's Republic of China

Correspondence e-mail: kbtang@ustc.edu.cn

Received 7 January 2011; accepted 23 February 2011

Key indicators: powder X-ray study; $T = 298$ K; mean $\sigma(\text{Nb}-\text{O}) = 0.004$ Å; disorder in main residue; R factor = 0.050; wR factor = 0.076; data-to-parameter ratio = 138.4.

Lithium calcium niobium oxide (2/1.5/3/10), Li₂Ca_{1.5}Nb₃O₁₀, has been synthesized by conventional solid-state reaction. Its structure consists of triple-layer perovskite slabs of corner-sharing NbO₆ octahedra interleaved with lithium ions; Ca cations partially occupy the perovskite *A* sites at 75% occupancy probability. All eight atoms in the asymmetric unit are on special positions: one Nb atom has site symmetry $4/mmm$; the second Nb, both K, the Sr and two O atoms have site symmetry $4mm$; the remaining two O atoms have site symmetries $2mm$. and mmm ., respectively.

Related literature

For background to Ruddlesden–Popper layered perovskites, see: Schaak & Mallouk (2002). Structures of related crystal *A*-site deficient three-layer Ruddlesden–Popper phases have been reported for K₂Sr_{1.5}Ta₃O₁₀ (Le Berre *et al.*, 2002), Li₄Sr₃Nb₆O₂₀ (Bhuvanesh *et al.*, 1999a), Li₂La_{1.78}Nb_{0.66}Ti_{2.34}O₁₀ (Bhuvanesh *et al.*, 1999b) and Li₂CaTa₂O₇ (Liang *et al.*, 2008). For crystallographic background, see: Howard (1982); Thompson *et al.* (1987).

Experimental

Crystal data

Li₂Ca_{1.5}Nb₃O₁₀ $M_r = 512.71$ Tetragonal, $I4/mmm$ $a = 3.87880$ (6) Å $c = 26.2669$ (4) Å $V = 395.19$ (1) Å³ $Z = 2$ Cu $K\alpha$ radiation, $\lambda = 1.54060$,

1.54443 Å

 $T = 298$ Kflat sheet, 20×20 mm

Data collection

PANalytical X'pert PRO diffractometer

Specimen mounting: packed powder pellet

Data collection mode: reflection
Scan method: continuous
 $2\theta_{\min} = 10.004^\circ$, $2\theta_{\max} = 129.939^\circ$,
 $2\theta_{\text{step}} = 0.017^\circ$

Refinement

 $R_p = 0.050$ $R_{wp} = 0.076$ $R_{\text{exp}} = 0.009$ $R(F^2) = 0.068$ $\chi^2 = 0.706$

7056 data points

51 parameters

Table 1

Selected bond lengths (Å).

Nb1–O1 ⁱ	1.9394 (1)	Ca1–O1 ⁱⁱ	2.805 (4)
Nb1–O4	2.027 (11)	Ca1–O3 ⁱⁱⁱ	2.567 (4)
Nb2–O2	1.689 (8)	Ca1–O4 ⁱⁱⁱ	2.7427 (1)
Nb2–O3 ⁱ	1.9704 (11)	Li1–O2	1.599 (4)
Nb2–O4	2.029 (11)		

Symmetry codes: (i) $x, y - 1, z$; (ii) $x - \frac{1}{2}, y - \frac{1}{2}, z + \frac{1}{2}$; (iii) $x + \frac{1}{2}, y + \frac{1}{2}, z + \frac{1}{2}$.

Data collection: *X'pert Data Collector* (PANalytical, 2003); cell refinement: *GSAS* (Larson & Von Dreele, 2004) and *EXPGUI* (Toby, 2001); data reduction: *X'pert Highscore* (PANalytical, 2003); method used to solve structure: coordinates taken from an isotopic compound (Bhuvanesh *et al.*, 1999a; Liang *et al.*, 2008); program(s) used to refine structure: *GSAS* and *EXPGUI*; molecular graphics: *DIAMOND* (Brandenburg, 1999); software used to prepare material for publication: *publCIF* (Westrip, 2010).

The authors are grateful for financial support by the National Natural Science Foundation of China, the 973 Projects of China and the Program for New Century Excellent Talents in Universities (NCET).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: VN2001).

References

- Bhuvanesh, N. S. P., Crosnier-Lopez, M. P., Bohnke, O., Emery, J. & Fourquet, J. L. (1999a). *Chem. Mater.* **11**, 634–641.
- Bhuvanesh, N. S. P., Crosnier-Lopez, M. P., Duroy, H. & Fourquet, J. L. (1999b). *J. Mater. Chem.* **9**, 3093–3100.
- Brandenburg, K. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Howard, C. J. (1982). *J. Appl. Cryst.* **15**, 615–620.
- Larson, A. C. & Von Dreele, R. B. (2004). *General Structure Analysis System (GSAS)*. Report LAUR 86-748. Los Alamos National Laboratory, New Mexico, USA.
- Le Berre, F., Crosnier-Lopez, M. P., Lalignant, Y. & Fourquet, J. L. (2002). *J. Mater. Chem.* **12**, 258–263.
- Liang, Z., Tang, K., Shao, Q., Lia, G., Zenga, S. & Zheng, H. (2008). *J. Solid State Chem.* **181**, 964–970.
- PANalytical (2003). *X'pert Data Collector* and *X'pert Highscore*. PANalytical BV, Almelo, The Netherlands.
- Schaak, R. E. & Mallouk, T. E. (2002). *Chem. Mater.* **14**, 1455–1471.
- Thompson, P., Cox, D. E. & Hastings, J. B. (1987). *J. Appl. Cryst.* **20**, 79–83.
- Toby, B. H. (2001). *J. Appl. Cryst.* **34**, 210–213.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.

supplementary materials

Acta Cryst. (2011). E67, i25 [doi:10.1107/S160053681100688X]

Li₂Ca_{1.5}Nb₃O₁₀ from X-ray powder data

B.-C. Zhu and K.-B. Tang

Comment

Layered perovskites that belong to the Ruddlesden-Popper family have a general formula $A'_2[A_{n-1}B_nO_{3n+1}]$ (Schaak *et al.*, 2002), where B is a small transition metal cation, A is a larger s -, d -, or f -block cation and A' is always an alkali cation. The Ruddlesden-Popper phases which are intergrowths of the perovskite and rocksalt structures possess a wide variety of interesting properties including superconductivity, colossal magnetoresistance, ferroelectricity, and catalytic activity. Related crystal structures of A sites deficiency three-layer Ruddlesden-Popper phases have been reported for $K_2Sr_{1.5}Ta_3O_{10}$ (Le Berre *et al.*, 2002), $Li_2La_{1.78}Nb_{0.66}Ti_{2.34}O_{10}$ (Bhuvanesh *et al.*, 1999b), and $Li_4Sr_3Nb_6O_{20}$ (Bhuvanesh *et al.*, 1999a).

Fig. 1 shows the observed, calculated and difference plots of the Rietveld refinement. We applied the March-Dollase formalism for a correction of the $00l$ preferential orientation which is frequently observed in Rietveld refinement of layered perovskites.

The structure of the compound is illustrated in Fig. 2. It is formed from two differently stacked NbO_6 octahedra thick slabs cut along the c direction. Two successive layers are shifted by $(a+b)/2$ with Ca cations partially occupying the 12-coordinated sites. The Li cations occupy the interlayer spacing at Wyckoff site $8f$ and not the $4e$ site since the distance between two adjacent layers is short. Ca cations partially occupy the perovskite A sites at 75% occupancy probability. The Nb cations are coordinated by six oxygen atoms to form NbO_6 octahedra with Nb—O distances ranging from 1.689 (8) to 2.029 (11) Å. The octahedra forming the outer layer of the slabs are characterized by off-centering of the Nb atoms, leading to four equal equatorial Nb—O distances within the perovskite layers [1.9704 (11) Å], a short Nb—O bond toward the interlayer spacing [1.689 (8) Å], and a long opposite Nb—O bond [2.029 (11) Å]. The octahedra forming the inner layer are less distorted with four equal equatorial Nb—O distances [1.9394 (1) Å] and other two equal Nb—O distances [2.027 (11) Å] parallel to the c axis. These type of distortions are well known in triple-layer perovskites.

Experimental

The sample was prepared by conventional solid-state reaction. Stoichiometric amounts of Li_2CO_3 , $CaCO_3$ and Nb_2O_5 were mixed, ground, and calcined at 1423 K for 6 h with one intermediate grind. An excess amount of Li_2CO_3 (20 mol%) was added to compensate for the loss due to the volatilization of alkali metal carbonate.

Refinement

The crystal structures of $Li_4Sr_3Nb_6O_{20}$ (Bhuvanesh *et al.*, 1999a) and $Li_2CaTa_2O_7$ (Liang *et al.*, 2008) were used as a starting model for the Rietveld refinement. The X-ray powder diffraction patterns of $Li_2Ca_{1.5}Nb_3O_{10}$ were indexed in a body-centered tetragonal space group $I4/mmm$. Structure refinement was carried out by the Rietveld method using the *GSAS* profile refinement program (Larson & Von Dreele, 2004). The site occupancy factors of Ca and Li were set at 0.75 and 0.50, respectively in view of the close resemblance of the cell parameters with those of the related structures and they were

supplementary materials

not further refined. The corresponding isotropic atomic displacement parameters of all oxygen atoms and niobium atoms were constrained to be equal, respectively. The March-Dollase option in the EXPGUI program (Toby, 2001) was applied to correct 00 l preferential orientation.

Figures

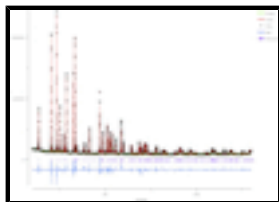


Fig. 1. Experimental and calculated X-ray diffraction pattern of $\text{Li}_2\text{Ca}_{1.5}\text{Nb}_3\text{O}_{10}$. The difference profile is given at the bottom. The Bragg positions are indicated by the vertical markers below the observed pattern.

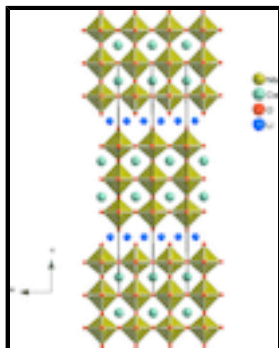


Fig. 2. The crystal structure of $\text{Li}_2\text{Ca}_{1.5}\text{Nb}_3\text{O}_{10}$ in a projection along [010].

Lithium calcium niobium oxide (2/1.5/3/10)

Crystal data

$\text{Li}_2\text{Ca}_{1.5}\text{Nb}_3\text{O}_{10}$

$M_r = 512.71$

Tetragonal, $I4/mmm$

Hall symbol: $-I\ 4\ 2$

$a = 3.87880$ (6) Å

$c = 26.2669$ (4) Å

$V = 395.19$ (1) Å³

$Z = 2$

$D_x = 4.309$ Mg m⁻³

Cu $K\alpha$ radiation, $\lambda = 1.540600, 1.544430$ Å

$T = 298$ K

white

flat sheet, 20×20 mm

Specimen preparation: Prepared at 1423 K

Data collection

PANalytical X'pert PRO
diffractometer

Radiation source: sealed tube
graphite

Specimen mounting: packed powder pellet

Data collection mode: reflection

Scan method: continuous

$2\theta_{\min} = 10.004^\circ$, $2\theta_{\max} = 129.939^\circ$, $2\theta_{\text{step}} = 0.017^\circ$

Refinement

Refinement on F^2

Profile function: CW Profile function number 2 with
18 terms Profile coefficients for Simpson's rule integ-
ration of pseudovoigt function C.J. Howard (1982).
J. Appl. Cryst., 15, 615-620. P. Thompson, D.E. Cox

& J.B. Hastings (1987). J. Appl. Cryst.,20,79-83.
 #1(GU) = 149.621 #2(GV) = -120.364 #3(GW) =
 31.573 #4(LX) = 1.000 #5(LY) = 17.840 #6(trns) =
 0.000 #7(asym) = 0.0000 #8(shft) = 0.0000 #9(GP)
 = 0.000 #10(stec)= 0.00 #11(pte) = 0.00 #12(sfec)=
 0.00 #13(L11) = 0.000 #14(L22) = 0.000 #15(L33) =
 0.000 #16(L12) = 0.000 #17(L13) = 0.000 #18(L23)
 = 0.000 Peak tails are ignored where the intensity is
 below 0.0010 times the peak Aniso. broadening axis
 0.0 0.0 1.0

Least-squares matrix: full

$R_p = 0.050$

$R_{wp} = 0.076$

$R_{exp} = 0.009$

$R(F^2) = 0.06796$

$\chi^2 = 0.706$

7056 data points

Excluded region(s): none

51 parameters

0 restraints

4 constraints

$w = 1/[\sigma^2(F_o^2) + (0.0677P)^2]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{max} = 0.01$

Background function: GSAS Background function
 number 1 with 36 terms. Shifted Chebyshev func-
 tion of 1st kind 1: 10229.8 2: -3178.07 3: 2423.18
 4: -808.112 5: 540.944 6: -198.924 7: 271.065 8:
 94.4177 9: 234.644 10: 188.507 11: 146.243 12:
 265.504 13: -11.6147 14: 51.8836 15: 137.742 16:
 26.3316 17: -53.6065 18: 3.80136 19: 279.859 20:
 -56.8162 21: -60.3405 22: 50.5886 23: 41.8504 24:
 9.38150 25: -48.8258 26: -20.5686 27: -49.8098 28:
 74.7145 29: -37.5745 30: 90.5252 31: -21.2918 32: -
 56.1545 33: 0.932266 34: -17.8446 35: -27.9120 36:
 -2.66006

Preferred orientation correction: March-Dollase AX-
 IS 1 Ratio= 0.89341 h= 0.000 k= 0.000 l= 1.000
 Preferred orientation correction range: Min= 0.84444,
 Max= 1.40236

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	U_{iso}^*/U_{eq}	Occ. (<1)
Nb1	0.0	0.0	0.0	0.0112 (3)*	
Nb2	0.0	0.0	0.15442 (5)	0.0112 (3)*	
Ca1	0.0	0.0	0.5771 (2)	0.0157 (3)*	0.75
O1	0.0	0.5	0.0	0.0132 (3)*	
O2	0.0	0.0	0.2187 (3)	0.0132 (3)*	
O3	0.0	0.5	0.1412 (2)	0.0132 (3)*	
O4	0.0	0.0	0.0772 (4)	0.0132 (3)*	
Li1	0.25	0.25	0.25	0.0182 (3)*	0.5

Geometric parameters (\AA , $^\circ$)

Nb1—O1 ⁱ	1.939400 (30)	Ca1—O1 ⁱⁱ	2.805 (4)
Nb1—O4	2.027 (11)	Ca1—O3 ⁱⁱ	2.567 (4)
Nb2—O2	1.689 (8)	Ca1—O4 ⁱⁱⁱ	2.74272 (4)
Nb2—O3 ⁱ	1.9704 (11)	Li1—O2	1.599 (4)

supplementary materials

Nb2—O4	2.029 (11)		
O1 ⁱ —Nb1—O1	180.0	O1 ⁱⁱ —Ca1—O3 ^{vi}	118.25 (6)
O1 ⁱ —Nb1—O1 ^{iv}	90.0	O1 ⁱⁱ —Ca1—O4 ⁱⁱ	60.74 (21)
O1 ⁱ —Nb1—O4	90.0	O1 ⁱⁱ —Ca1—O4 ^v	119.28 (27)
O2—Nb2—O3 ⁱ	100.17 (18)	O1 ^v —Ca1—O3 ^v	87.19 (9)
O2—Nb2—O4	180.0	O3 ⁱⁱ —Ca1—O3 ^v	98.14 (22)
O3 ⁱ —Nb2—O3	159.7 (4)	O3 ⁱⁱ —Ca1—O3 ^{vi}	64.58 (12)
O3 ⁱ —Nb2—O3 ^{iv}	88.21 (6)	O3 ⁱⁱ —Ca1—O4 ^{vii}	57.70 (19)
O3 ⁱ —Nb2—O4	79.83 (18)	O3 ⁱⁱ —Ca1—O4 ^v	122.28 (26)
O1 ⁱⁱ —Ca1—O1 ^v	87.49 (16)	O4 ⁱⁱ —Ca1—O4 ^{vii}	90.00000 (20)
O1 ⁱⁱ —Ca1—O1 ^{vi}	58.54 (9)	O4 ⁱⁱ —Ca1—O4 ⁱⁱⁱ	180.00000 (30)
O1 ⁱⁱ —Ca1—O3 ^v	174.68 (17)	O2—Li1—O2 ^{viii}	180.0

Symmetry codes: (i) $x, y-1, z$; (ii) $x-1/2, y-1/2, z+1/2$; (iii) $x+1/2, y+1/2, z+1/2$; (iv) $-y, x, z$; (v) $x+1/2, y-1/2, z+1/2$; (vi) $-y+1/2, x-1/2, z+1/2$; (vii) $x-1/2, y+1/2, z+1/2$; (viii) $-x-1/2, -y-1/2, -z-1/2$.

Fig. 1

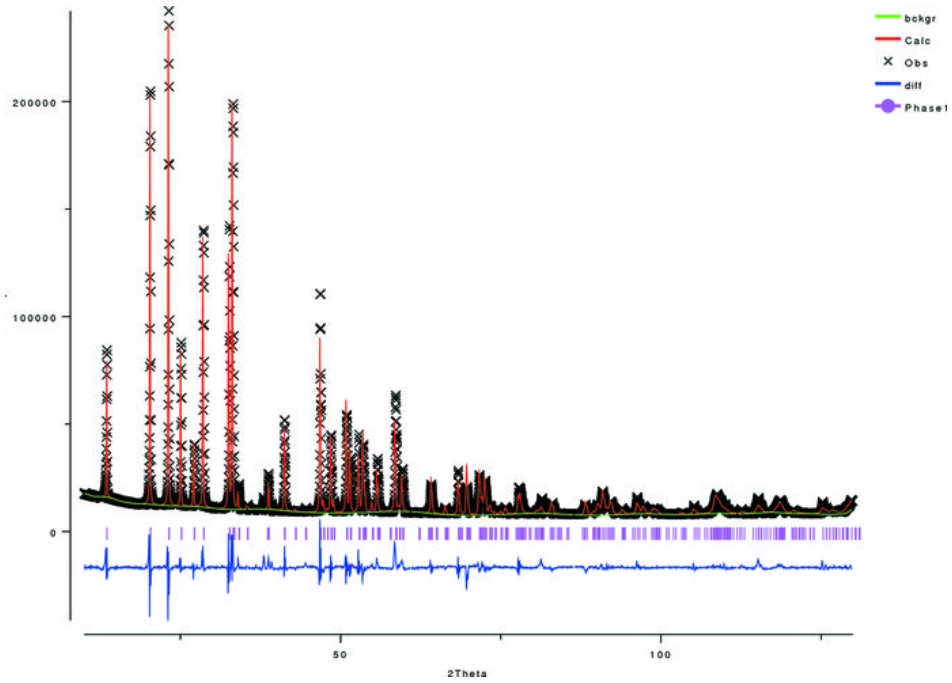


Fig. 2

