

catena-[[$(\text{nitrato}-\kappa\text{O})\text{silver(I)}-\mu$ -1,10-phenanthroline-5,6-dione- $\kappa^4\text{O},\text{O}':\text{N},\text{N}']$

Xiao Jing,^a Yu-Lan Zhu,^{b*} Kui-Rong Ma,^b Li Cao^b and Shuai Shao^a

^aDepartment of Chemistry, Northeast Normal University, Changchun 130021, People's Republic of China, and ^bJiangsu Key Laboratory for the Chemistry of Low-Dimensional Materials, Huaiyin Normal University, Huaian 223300, People's Republic of China
Correspondence e-mail: yulanzhu2008@126.com


Received 13 April 2011; accepted 31 May 2011

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(\text{C}-\text{C}) = 0.010$ Å; R factor = 0.052; wR factor = 0.124; data-to-parameter ratio = 12.1.

In the title one-dimensional coordination polymer, $[\text{Ag}(\text{NO}_3)(\text{C}_{12}\text{H}_6\text{N}_2\text{O}_2)]_n$, the Ag^{I} atom is pentacoordinated by two N atoms from a 1,10-phenanthroline-5,6-dione (phen-dione) ligand, one O atom from the nitrate anion and two O atoms from another phen-dione ligand. The coordination environment around silver is slightly distorted square-pyramidal. Interestingly, the $\text{Ag}-\text{O}$ distances to the phen-dione ligand are different [$\text{Ag}-\text{O} = 2.612$ (6) and 2.470 (5) Å]. The one-dimensional chains run parallel to [101] and are further interconnected by weak hydrogen bonds ($\text{C}-\text{H}\cdots\text{O}$) and $\pi-\pi$ stacking interactions [centroid–centroid distances 3.950 (4) and 3.792 (4) Å], forming a three-dimensional supramolecular network.

Related literature

For the use of 1,10-phenanthroline-5,6-dione (phen-dione) as an efficient chelating ligand establishing coordination polymers, see: Calderazzo *et al.* (2002); Wu *et al.* (1996); Liu & Xu (2006); Li *et al.* (2005). For examples of complexes with N,O -coordination of phen-dione, see: Paw & Eisenberg (1997); Ruiz *et al.* (1999); Shavaleev *et al.* (2003). For the synthesis of phen-dione, see: Paw & Eisenberg (1997). For the structure of a related phen-dione complex of Ag^{I} , see: Onuegbu *et al.* (2009). For a comparison of $\text{Ag}-\text{O}$ bond lengths, see: Young & Hanton (2008); Sun *et al.* (2010); Wang *et al.* (2011).

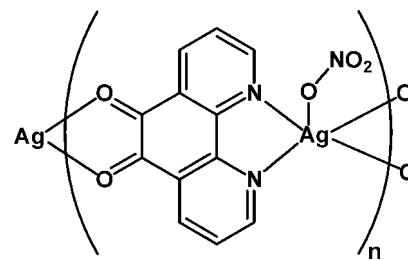

Experimental

Crystal data

$[\text{Ag}(\text{NO}_3)(\text{C}_{12}\text{H}_6\text{N}_2\text{O}_2)]$	$V = 1192.2$ (3) Å ³
$M_r = 380.07$	$Z = 4$
Monoclinic, $P2_1/n$	Mo $K\alpha$ radiation
$a = 9.5058$ (14) Å	$\mu = 1.72$ mm ⁻¹
$b = 10.4647$ (15) Å	$T = 296$ K
$c = 12.1615$ (17) Å	$0.3 \times 0.2 \times 0.1$ mm
$\beta = 99.766$ (2)°	

Data collection

Bruker APEXII CCD area-detector diffractometer	6626 measured reflections
Absorption correction: multi-scan (<i>SADABS</i> ; Bruker, 2000)	2307 independent reflections
$R_{\text{int}} = 0.041$	1374 reflections with $I > 2\sigma(I)$
$T_{\min} = 0.66$, $T_{\max} = 0.84$	

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.052$	32 restraints
$wR(F^2) = 0.124$	H-atom parameters constrained
$S = 1.00$	$\Delta\rho_{\max} = 0.84$ e Å ⁻³
2307 reflections	$\Delta\rho_{\min} = -1.05$ e Å ⁻³
190 parameters	

Table 1
Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots\text{A}$	$D-\text{H}$	$\text{H}\cdots\text{A}$	$D\cdots\text{A}$	$D-\text{H}\cdots\text{A}$
C1—H1 \cdots O4 ⁱ	0.93	2.37	3.21 (1)	149

Symmetry code: (i) $-x$, $-y$, $-z + 1$.

Data collection: *APEX2* (Bruker, 2004); cell refinement: *SAINT* (Bruker, 2004); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP-3 for Windows* (Farrugia, 1997); software used to prepare material for publication: *SHELXL97* and *PLATON* (Spek, 2009).

This work was supported by the National Natural Science Foundation of China (grant Nos. 20671038 and 20975043) and Jiangsu Key Laboratory for the Chemistry of Low-Dimensional Materials (grant No. JSKC09061).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: IM2282).

References

- Bruker (2000). *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
Bruker (2004). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.

metal-organic compounds

- Calderazzo, F., Pampaloni, G. & Passarelli, V. (2002). *Inorg. Chim. Acta*, **330**, 136–142.
- Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
- Li, X., Cao, R., Bi, W. H., Yuan, D. Q. & Sun, D. F. (2005). *Eur. J. Inorg. Chem.* pp. 3156–3166.
- Liu, Q. Y. & Xu, L. (2006). *Eur. J. Inorg. Chem.* pp. 1620–1628.
- Onuegbu, J., Butcher, R. J., Hosten, C., Udeochu, U. C. & Bakare, O. (2009). *Acta Cryst. E65*, m1119–m1120.
- Paw, W. & Eisenberg, R. (1997). *Inorg. Chem.* **36**, 2287–2293.
- Ruiz, R., Caneschi, A., Gatteschi, D., Gaspar, A. B., Real, J. A., Fernandez, I. & Munoz, M. C. (1999). *Inorg. Chem. Commun.* **2**, 521–523.
- Shavaleev, N. M., Moorcraft, L. P., Pope, S. J. A., Bell, Z. R., Faulkner, S. & Ward, M. D. (2003). *Chem. Commun.* pp. 1134–1135.
- Sheldrick, G. M. (2008). *Acta Cryst. A64*, 112–122.
- Spek, A. L. (2009). *Acta Cryst. D65*, 148–155.
- Sun, D., Zhang, N., Huang, R. B. & Zheng, L. S. (2010). *Cryst. Growth Des.* **10**, 3699–3709.
- Wang, H., Yuan, G., Sun, C. & Yang, G. C. (2011). *Inorg. Chem. Commun.* **14**, 347–350.
- Wu, Q., Maskus, M., Pariente, F., Tobalina, F. & Fernandez, V. M. (1996). *Anal. Chem.* **68**, 3688–3696.
- Young, A. G. & Hanton, L. R. (2008). *Coord. Chem. Rev.* **252**, 1346–1386.

supplementary materials

Acta Cryst. (2011). E67, m957-m958 [doi:10.1107/S1600536811020939]

catena-[[(nitrato- κO)silver(I)]- μ -1,10-phenanthroline-5,6-dione- $\kappa^4 O,O':N,N'$]

X. Jing, Y.-L. Zhu, K.-R. Ma, L. Cao and S. Shao

Comment

1, 10-phenanthroline-5,6-dione (phen-dione) is an efficient chelating ligand exhibiting two types of coordinating atoms (N and O) that are electronically coupled due to conjugation throughout the ligand. While phen-dione usually binds to metals through N atoms, in some cases both the N and O atoms are used simultaneously (Paw & Eisenberg, 1997; Ruiz *et al.*, 1999; Shavaleev *et al.*, 2003).

In this paper we report the synthesis and characterization of the title compound, $[\text{Ag}(\text{phen-dione})(\text{NO}_3)]_n$ (**1**). Single-crystal X-ray diffraction study of **1** reveals the asymmetric unit to consist of one Ag (I) ion, one phen-dione ligand and one nitrate anion (Fig. 1). The silver atom is coordinated to two N atoms of a 1,10-phenanthroline-5,6-dione (phen-dione), one O atom from the nitrate anion and two O atoms from another phen-dione ligand giving rise to a slightly distorted square-pyramidal coordination sphere. The corresponding Ag–N bond distances are 2.445 (6) Å for Ag–N(1), 2.287 (6) Å for Ag–N(2) and Ag–O bond distances are observed to 2.474 (6) Å for Ag–O(1 A), 2.438 (7) Å for Ag–O(3) and 2.612 (6) Å for Ag–O(2 A). The latter bond length is longer than Ag–O(1 A) and Ag–O(3), but is well-matched to other examples reported in the literature (Young & Hanton, 2008; Wang *et al.*, 2011; Sun *et al.*, 2010).

In compound **1**, the basic building units with a $[\text{AgN}_2\text{O}_3]$ center are firstly interconnected to each other to produce a one-dimensional chain by additional Ag—O(1 A) and Ag—O(2 A) bonds (Fig. 2). Then the adjacent one-dimensional chains are further linked to each other to form three-dimensional network structure by the weak hydrogen bond C (1)–H(1)···O(4) (3.184 Å) between a CH function of a pyridine and an oxygen atom of the nitrate anion and π – π stacking interactions (Fig. 3). Two types of aromatic stacking interactions in **1** are observed between pyridine ring I (N (1), C (10), C (9), C (8), C (7), C (11)) and pyridine ring II (N (1), C (10), C (9), C (8), C (7), C (11)). There is one close distance between the centroids of pyridine I and II and another between two neighboring pyridine I moieties. The respective centroid-to-centroid distances are 3.950 (4) Å and 3.792 (4) Å.

The combination of coordinative bonds, hydrogen bonds, and π – π stacking interactions assemble the one-dimensional chain into a complicated three-dimensional supramolecular network.

Experimental

The title compound was synthesized according to the following steps: a solution of silver (I) nitrate (0.068 g, 0.4 mmol) and phen-dione (0.0212 g, 0.1 mmol) in methanol (8 ml) was stirred for 2 h. After filtering, the filtrate was left at room temperature for about two weeks. Yellow block shaped crystals of **1** were collected by vacuum filtration, washed thoroughly with methanol dried in air (yield 23% based on silver).

supplementary materials

Refinement

All non-hydrogen atoms were located from the difference Fourier maps, and were refined anisotropically. All H atoms were positioned geometrically, and were allowed to ride on their corresponding parent atoms with $U_{\text{iso}} = 1.2 U_{\text{eq}}$.

Figures

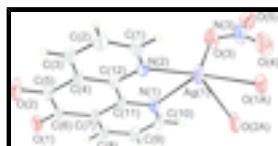


Fig. 1. Molecular structure of the title compound, displacement ellipsoids are drawn at the 30% probability level.

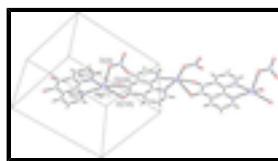


Fig. 2. One-dimensional polymeric structure of the title compound.




Fig. 3. Crystal packing of the title compound, $\pi-\pi$ stacking interactions are shown as green dashed lines and hydrogen bonds are shown as black dashed lines.

catena-[[(nitrato- κO)silver(I)]- μ -1,10-phenanthroline- 5,6-dione- $\kappa^4 O,O':N,N'$]

Crystal data

[Ag(NO₃)(C₁₂H₆N₂O₂)]

$F(000) = 744$

$M_r = 380.07$

$D_x = 2.117 \text{ Mg m}^{-3}$

Monoclinic, $P2_1/n$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Hall symbol: -P 2yn

Cell parameters from 1252 reflections

$a = 9.5058 (14) \text{ \AA}$

$\theta = 2.6\text{--}22.6^\circ$

$b = 10.4647 (15) \text{ \AA}$

$\mu = 1.72 \text{ mm}^{-1}$

$c = 12.1615 (17) \text{ \AA}$

$T = 296 \text{ K}$

$\beta = 99.766 (2)^\circ$

Block, yellow

$V = 1192.2 (3) \text{ \AA}^3$

$0.3 \times 0.2 \times 0.1 \text{ mm}$

$Z = 4$

Data collection

Bruker APEXII CCD area-detector diffractometer

2307 independent reflections

Radiation source: fine-focus sealed tube graphite

1374 reflections with $I > 2\sigma(I)$

Detector resolution: 0 pixels mm^{-1}

$\theta_{\text{max}} = 26.0^\circ$, $\theta_{\text{min}} = 2.6^\circ$

φ and ω scans

$h = -11 \rightarrow 11$

Absorption correction: multi-scan (SADABS; Bruker 2000)

$k = -12 \rightarrow 12$

$T_{\min} = 0.66$, $T_{\max} = 0.84$
6626 measured reflections

$l = -14 \rightarrow 7$

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.052$	Hydrogen site location: inferred from neighbouring sites
$wR(F^2) = 0.124$	H-atom parameters constrained
$S = 1.00$	$w = 1/[\sigma^2(F_o^2) + (0.0445P)^2 + 3.5057P]$ where $P = (F_o^2 + 2F_c^2)/3$
2307 reflections	$(\Delta/\sigma)_{\max} < 0.001$
190 parameters	$\Delta\rho_{\max} = 0.84 \text{ e \AA}^{-3}$
32 restraints	$\Delta\rho_{\min} = -1.05 \text{ e \AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Ag1	0.20025 (7)	0.15378 (7)	0.49084 (6)	0.0703 (3)
C1	0.3824 (8)	-0.0492 (8)	0.3745 (6)	0.055 (2)
H1	0.3348	-0.1065	0.4136	0.066*
C2	0.4710 (9)	-0.0969 (8)	0.3058 (7)	0.060 (2)
H2	0.4815	-0.1846	0.2981	0.072*
C3	0.5436 (8)	-0.0134 (7)	0.2488 (6)	0.0489 (19)
H3	0.6034	-0.0437	0.2015	0.059*
C4	0.5264 (7)	0.1159 (6)	0.2628 (6)	0.0399 (17)
C5	0.6048 (7)	0.2087 (6)	0.2031 (6)	0.0449 (18)
C6	0.5831 (7)	0.3489 (6)	0.2189 (5)	0.0416 (16)
C7	0.4826 (7)	0.3887 (7)	0.2938 (5)	0.0391 (17)
C8	0.4591 (7)	0.5165 (7)	0.3107 (6)	0.0485 (19)
H8	0.5058	0.5787	0.2758	0.058*
C9	0.3654 (8)	0.5503 (8)	0.3800 (6)	0.053 (2)
H9	0.3460	0.6358	0.3918	0.064*
C10	0.3008 (8)	0.4552 (8)	0.4318 (6)	0.056 (2)

supplementary materials

H10	0.2393	0.4790	0.4801	0.067*
C11	0.4114 (7)	0.2975 (6)	0.3479 (5)	0.0356 (16)
C12	0.4337 (7)	0.1596 (7)	0.3331 (5)	0.0380 (15)
N1	0.3214 (6)	0.3316 (6)	0.4165 (5)	0.0439 (14)
N2	0.3618 (6)	0.0775 (6)	0.3874 (5)	0.0424 (14)
N3	-0.1319 (8)	0.2293 (8)	0.4504 (7)	0.0784 (15)
O1	0.6449 (5)	0.4259 (5)	0.1699 (4)	0.0567 (14)
O2	0.6867 (6)	0.1721 (5)	0.1428 (5)	0.0708 (17)
O3	-0.0348 (6)	0.2265 (7)	0.3995 (6)	0.0846 (15)
O4	-0.1158 (8)	0.1860 (9)	0.5450 (7)	0.126 (2)
O5	-0.2488 (6)	0.2729 (7)	0.4152 (5)	0.0896 (18)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ag1	0.0779 (5)	0.0783 (5)	0.0691 (5)	0.0005 (4)	0.0539 (4)	-0.0004 (4)
C1	0.062 (5)	0.052 (5)	0.057 (5)	-0.006 (4)	0.027 (4)	0.012 (4)
C2	0.066 (5)	0.047 (5)	0.071 (6)	0.003 (4)	0.023 (5)	0.004 (4)
C3	0.048 (4)	0.052 (5)	0.051 (5)	0.008 (4)	0.017 (4)	-0.006 (4)
C4	0.040 (4)	0.042 (4)	0.040 (4)	0.007 (3)	0.016 (3)	-0.004 (3)
C5	0.047 (4)	0.052 (5)	0.041 (4)	0.001 (3)	0.022 (4)	0.001 (3)
C6	0.040 (4)	0.053 (4)	0.035 (4)	-0.006 (4)	0.015 (3)	0.002 (4)
C7	0.040 (4)	0.047 (4)	0.034 (4)	-0.003 (3)	0.016 (3)	0.001 (3)
C8	0.053 (4)	0.046 (5)	0.051 (5)	-0.002 (4)	0.020 (4)	0.004 (4)
C9	0.069 (5)	0.042 (4)	0.053 (5)	0.009 (4)	0.019 (4)	-0.004 (4)
C10	0.062 (5)	0.064 (6)	0.048 (5)	0.012 (4)	0.027 (4)	-0.002 (4)
C11	0.038 (4)	0.042 (4)	0.029 (4)	0.005 (3)	0.013 (3)	-0.004 (3)
C12	0.036 (3)	0.045 (4)	0.035 (4)	-0.003 (3)	0.011 (3)	-0.003 (3)
N1	0.045 (3)	0.045 (4)	0.047 (4)	0.003 (3)	0.024 (3)	-0.002 (3)
N2	0.044 (3)	0.042 (4)	0.045 (3)	0.001 (3)	0.019 (3)	0.003 (3)
N3	0.054 (3)	0.111 (4)	0.077 (3)	0.003 (3)	0.029 (3)	0.021 (3)
O1	0.059 (3)	0.058 (3)	0.062 (3)	-0.008 (3)	0.034 (3)	0.002 (3)
O2	0.088 (4)	0.066 (4)	0.075 (4)	0.012 (3)	0.062 (3)	0.003 (3)
O3	0.061 (3)	0.108 (4)	0.092 (3)	0.006 (3)	0.036 (3)	0.009 (3)
O4	0.095 (4)	0.188 (5)	0.092 (4)	-0.022 (4)	0.012 (3)	0.058 (4)
O5	0.059 (3)	0.131 (5)	0.078 (4)	0.022 (3)	0.010 (3)	-0.017 (3)

Geometric parameters (\AA , $^\circ$)

Ag1—N2	2.287 (5)	C6—C7	1.487 (8)
Ag1—O3	2.442 (6)	C7—C8	1.377 (10)
Ag1—N1	2.442 (6)	C7—C11	1.397 (9)
Ag1—O1 ⁱ	2.470 (5)	C8—C9	1.372 (10)
C1—N2	1.354 (10)	C8—H8	0.9300
C1—C2	1.376 (10)	C9—C10	1.376 (10)
C1—H1	0.9300	C9—H9	0.9300
C2—C3	1.372 (10)	C10—N1	1.326 (9)
C2—H2	0.9300	C10—H10	0.9300

C3—C4	1.377 (9)	C11—N1	1.341 (7)
C3—H3	0.9300	C11—C12	1.474 (10)
C4—C12	1.405 (8)	C12—N2	1.340 (8)
C4—C5	1.486 (9)	N3—O3	1.195 (8)
C5—O2	1.218 (7)	N3—O5	1.210 (9)
C5—C6	1.499 (7)	N3—O4	1.222 (9)
C6—O1	1.211 (7)	O1—Ag1 ⁱⁱ	2.470 (5)
N2—Ag1—O3	120.4 (2)	C9—C8—C7	118.7 (7)
N2—Ag1—N1	70.10 (19)	C9—C8—H8	120.6
O3—Ag1—N1	92.7 (2)	C7—C8—H8	120.6
N2—Ag1—O1 ⁱ	129.06 (19)	C8—C9—C10	118.8 (7)
O3—Ag1—O1 ⁱ	101.00 (18)	C8—C9—H9	120.6
N1—Ag1—O1 ⁱ	140.18 (19)	C10—C9—H9	120.6
N2—C1—C2	122.8 (7)	N1—C10—C9	123.5 (6)
N2—C1—H1	118.6	N1—C10—H10	118.2
C2—C1—H1	118.6	C9—C10—H10	118.2
C1—C2—C3	119.2 (7)	N1—C11—C7	121.5 (6)
C1—C2—H2	120.4	N1—C11—C12	117.2 (6)
C3—C2—H2	120.4	C7—C11—C12	121.3 (6)
C2—C3—C4	118.9 (7)	N2—C12—C4	121.1 (6)
C2—C3—H3	120.6	N2—C12—C11	118.1 (5)
C4—C3—H3	120.6	C4—C12—C11	120.8 (6)
C3—C4—C12	119.7 (7)	C10—N1—C11	118.2 (6)
C3—C4—C5	120.1 (6)	C10—N1—Ag1	127.0 (4)
C12—C4—C5	120.2 (6)	C11—N1—Ag1	114.7 (4)
O2—C5—C4	120.9 (6)	C12—N2—C1	118.3 (6)
O2—C5—C6	120.0 (6)	C12—N2—Ag1	119.6 (4)
C4—C5—C6	119.1 (5)	C1—N2—Ag1	122.0 (4)
O1—C6—C7	122.1 (6)	O3—N3—O5	124.7 (9)
O1—C6—C5	119.9 (6)	O3—N3—O4	119.6 (9)
C7—C6—C5	118.0 (6)	O5—N3—O4	115.7 (8)
C8—C7—C11	119.3 (6)	C6—O1—Ag1 ⁱⁱ	113.8 (4)
C8—C7—C6	120.0 (6)	N3—O3—Ag1	120.0 (6)
C11—C7—C6	120.7 (6)		

Symmetry codes: (i) $x-1/2, -y+1/2, z+1/2$; (ii) $x+1/2, -y+1/2, z-1/2$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D\text{—H}\cdots A$	$D\text{—H}$	$H\cdots A$	$D\cdots A$	$D\text{—H}\cdots A$
C1—H1 ⁱⁱⁱ —O4 ⁱⁱⁱ	0.93	2.37	3.21 (1)	149

Symmetry codes: (iii) $-x, -y, -z+1$.

supplementary materials

Fig. 1


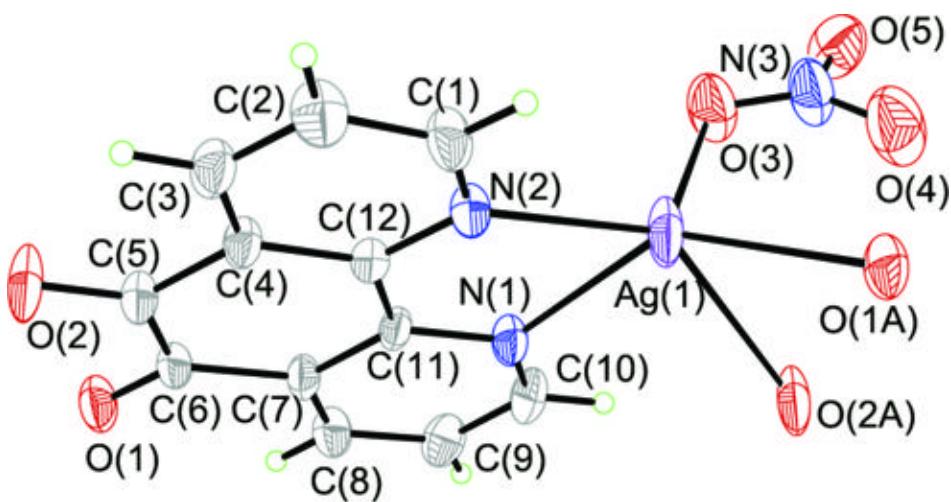


Fig. 2



supplementary materials

Fig. 3

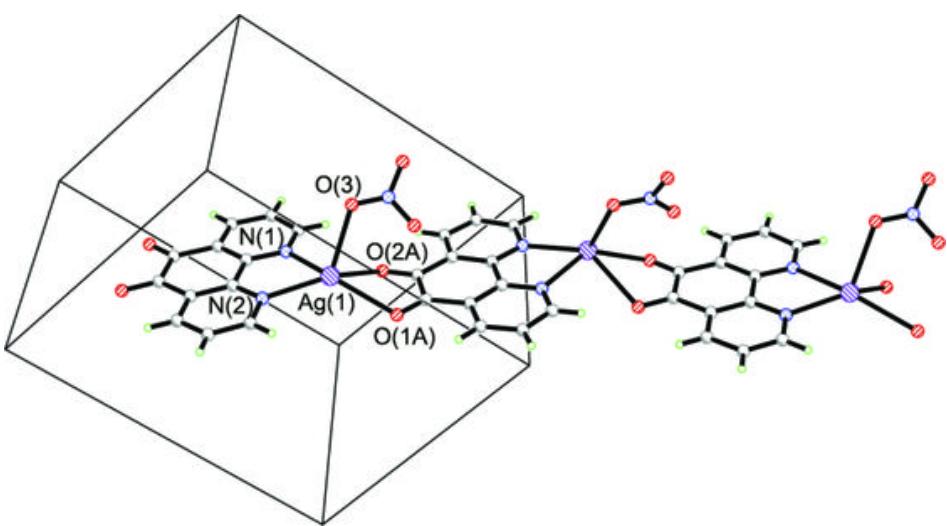