

A one-dimensional triaqueaeuropium(III)- 1*H,3H*-benzimidazol-3-ium-5,6-dicarboxylate-sulfate polymeric structure

Xia Cai,^a Jing-Jun Lin,^a Hao-Zhao Chen,^a Lai-Chen Chen^a and Rong-Hua Zeng^{a,b*}

^aSchool of Chemistry and Environment, South China Normal University, Guangzhou 510006, People's Republic of China, and ^bKey Laboratory of Technology of Electrochemical Energy Storage and Power Generation in Guangdong Universities, South China Normal University, Guangzhou 510006, People's Republic of China
Correspondence e-mail: zrh321@yahoo.com.cn


Received 5 August 2011; accepted 21 August 2011

Key indicators: single-crystal X-ray study; $T = 298\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.008\text{ \AA}$; R factor = 0.036; wR factor = 0.097; data-to-parameter ratio = 11.5.

In the title coordination polymer, *catena-poly*[[[triaquaeuropium(III)]-bis(μ -1*H,3H*-benzimidazol-3-ium-5,6-dicarboxylato- $\kappa^3O^5,O^{5'}:O^6$)-[triaquaeuropium(III)]-di- μ -sulfato- $\kappa^3O:O,O';\kappa^3O,O':O'$] hexahydrate], $[\text{Eu}_2(\text{C}_9\text{H}_5\text{N}_2\text{O}_4)_2(\text{SO}_4)_2(\text{H}_2\text{O})_6] \cdot 6\text{H}_2\text{O}]_n$, the 1*H,3H*-benzimidazol-3-ium-5,6-dicarboxylate ligand is protonated at the imidazole group (H_2bdc). The Eu^{III} ion is coordinated by nine O atoms from two H_2bdc ligands, two sulfate anions and three water molecules, displaying a bicapped trigonal prismatic geometry. The carboxylate groups of the H_2bdc ligands and the sulfate anions link the Eu^{III} ions, forming a chain along [010]. These chains are further connected by N–H···O and O–H···O hydrogen bonds and π – π interactions between the imidazole and benzene rings [centroid–centroid distances = 3.997 (4), 3.829 (4) and 3.573 (4) \AA] into a three-dimensional supramolecular network.

Related literature

For background to 1*H*-benzimidazole-5,6-dicarboxylate complexes, see: Wang *et al.* (2010); Wei *et al.* (2008); Xie *et al.* (2010); Yao *et al.* (2008).

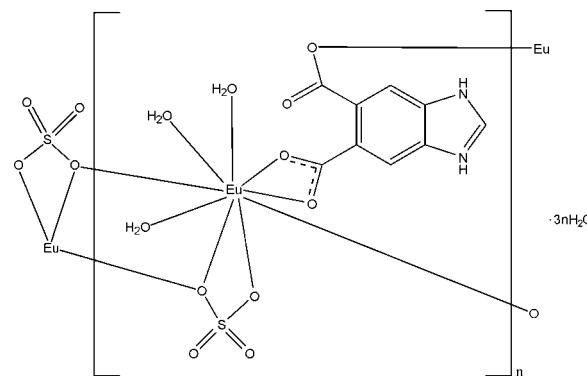

Experimental

Crystal data

| | |
|--|--|
| $[\text{Eu}_2(\text{C}_9\text{H}_5\text{N}_2\text{O}_4)_2(\text{SO}_4)_2(\text{H}_2\text{O})_6] \cdot 6\text{H}_2\text{O}$ | $\beta = 98.060 (3)^\circ$ |
| $M_r = 1122.58$ | $\gamma = 94.979 (3)^\circ$ |
| Triclinic, $P\bar{1}$ | $V = 820.3 (3)\text{ \AA}^3$ |
| $a = 7.1261 (16)\text{ \AA}$ | $Z = 1$ |
| $b = 9.581 (2)\text{ \AA}$ | Mo $K\alpha$ radiation |
| $c = 12.424 (3)\text{ \AA}$ | $\mu = 4.03\text{ mm}^{-1}$ |
| $\alpha = 100.496 (3)^\circ$ | $T = 298\text{ K}$ |
| | $0.30 \times 0.26 \times 0.20\text{ mm}$ |

Data collection

| | |
|---|--|
| Bruker APEXII CCD diffractometer | 4076 measured reflections |
| Absorption correction: multi-scan (<i>SADABS</i> ; Bruker, 2001) | 2841 independent reflections |
| $T_{\min} = 0.310$, $T_{\max} = 0.446$ | 2669 reflections with $I > 2\sigma(I)$ |
| | $R_{\text{int}} = 0.024$ |

Refinement

| | |
|---------------------------------|--|
| $R[F^2 > 2\sigma(F^2)] = 0.036$ | H atoms treated by a mixture of independent and constrained refinement |
| $wR(F^2) = 0.097$ | $\Delta\rho_{\max} = 1.82\text{ e \AA}^{-3}$ |
| $S = 1.02$ | $\Delta\rho_{\min} = -2.51\text{ e \AA}^{-3}$ |
| 2841 reflections | |
| 248 parameters | |

Table 1
Hydrogen-bond geometry (\AA , $^\circ$).

| $D-\text{H}\cdots A$ | $D-\text{H}$ | $\text{H}\cdots A$ | $D\cdots A$ | $D-\text{H}\cdots A$ |
|------------------------------|--------------|--------------------|-------------|----------------------|
| O1W–H1W···O4 ⁱ | 0.84 | 1.90 | 2.717 (6) | 165 |
| O1W–H2W···O7 ⁱⁱ | 0.84 | 2.24 | 3.049 (6) | 163 |
| O2W–H3W···O5 ⁱⁱ | 0.84 | 1.96 | 2.775 (6) | 162 |
| O2W–H4W···O3 ⁱⁱⁱ | 0.85 | 1.85 | 2.659 (6) | 159 |
| O3W–H5W···O4W ⁱⁱⁱ | 0.84 | 2.07 | 2.810 (6) | 146 |
| O3W–H6W···O2 ^{iv} | 0.85 | 2.10 | 2.864 (6) | 149 |
| O4W–H7W···O5 ⁱⁱ | 0.86 | 2.34 | 3.045 (6) | 139 |
| O4W–H8W···O1 | 0.84 | 2.04 | 2.869 (6) | 168 |
| O5W–H9W···O6W | 0.84 | 2.03 | 2.864 (8) | 171 |
| O5W–H10W···O6 ^v | 0.84 | 2.01 | 2.790 (7) | 154 |
| O6W–H11W···O6 ^{vi} | 0.84 | 2.37 | 3.165 (8) | 158 |
| O6W–H12W···O5 ⁱⁱ | 0.85 | 2.20 | 2.895 (7) | 139 |
| O6W–H12W···O1W | 0.85 | 2.46 | 3.060 (7) | 129 |
| N1–H1A···O5W ^{vii} | 0.86 (8) | 1.96 (8) | 2.752 (8) | 153 (7) |
| N1–H1A···O4W ^{vii} | 0.86 (8) | 2.48 (8) | 2.989 (7) | 119 (6) |
| N2–H2···O6W ^{viii} | 0.86 | 1.91 | 2.734 (7) | 161 |

Symmetry codes: (i) $x, y + 1, z$; (ii) $-x + 1, -y + 1, -z$; (iii) $-x + 1, -y, -z$; (iv) $-x + 2, -y, -z$; (v) $x, y, z + 1$; (vi) $-x + 2, -y + 1, -z$; (vii) $-x + 2, -y, -z + 1$; (viii) $-x + 2, -y + 1, -z + 1$.

Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINT* (Bruker, 2007); data reduction: *SAINT*; program(s) used to solve

structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEPIII* (Burnett & Johnson, 1996) and *PLATON* (Spek, 2009); software used to prepare material for publication: *SHELXL97*.

The authors acknowledge the Undergraduates' Innovating Experimentation Project of Guangdong Province, the Undergraduates' Innovating Experimentation Project of South China Normal University and the Students' Extracurricular Scientific Research Project of South China Normal University for supporting this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2456).

References

- Bruker (2001). *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
Bruker (2007). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
Burnett, M. N. & Johnson, C. K. (1996). *ORTEPIII*. Report ORNL-6895. Oak Ridge National Laboratory, Tennessee, USA.
Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
Spek, A. L. (2009). *Acta Cryst. D* **65**, 148–155.
Wang, Z.-X., Wu, X.-F., Liu, H.-J., Shao, M., Xiao, H.-P. & Li, M.-X. (2010). *CrystEngComm*, **12**, 1139–1146.
Wei, Y.-Q., Yu, Y.-F. & Wu, K.-C. (2008). *Cryst. Growth Des.* **8**, 2087–2089.
Xie, Y., Xing, Y.-H., Wang, Z., Zhao, H.-Y., Zeng, X.-Q., Ge, M.-F. & Niu, S.-Y. (2010). *Inorg. Chim. Acta*, **363**, 918–924.
Yao, Y.-L., Che, Y.-X. & Zheng, J.-M. (2008). *Cryst. Growth Des.* **8**, 2299–2306.

supplementary materials

Acta Cryst. (2011). E67, m1310-m1311 [doi:10.1107/S1600536811034337]

A one-dimensional triaqueeuropium(III)-1*H*,3*H*-benzimidazol-3-i um-5,6-dicarboxylate-sulfate polymeric structure

X. Cai, J.-J. Lin, H.-Z. Chen, L.-C. Chen and R.-H. Zeng

Comment

In recent years, research on coordination polymers has made considerable progress in the fields of supramolecular chemistry and crystal engineering, because of their intriguing structural motifs and functional properties, such as molecular adsorption, magnetism and luminescence. Ligands play a key role in the construction of coordination polymers with fascinating topology, intriguing architectures and useful physical-chemical properties. Benzimidazole-5,6-dicarboxylic acid (H_3bdc) is a potential bifunctional ligand with carboxylate and N-donor functional groups and has been used to prepare such metal-organic complexes in possession of multidimensional networks and interesting properties (Wang *et al.*, 2010; Wei *et al.*, 2008; Xie *et al.*, 2010; Yao *et al.*, 2008). Recently, we obtained the title coordination polymer, which was synthesized by the hydrothermal reaction of Eu_2O_3 with H_3bdc in an aqueous solution.

The title compound has a polymeric chain architecture. As shown in Fig. 1, the Eu^{III} ion is in a bicapped trigonal-prismatic geometry, defined by nine O atoms from two 1*H*,3*H*-benzimidazol-3-i um-5,6-dicarboxylate ligands (H_2bdc), which are protonated at the imidazole groups, two sulfate anions and three water molecules. The H_2bdc ligands and sulfate anions link the Eu^{III} ions into a chain along [0 1 0] (Fig. 2). The adjacent Eu···Eu separations are 4.272 (4) and 6.663 (5) Å. The Eu—O bond lengths range from 2.376 (4) to 2.610 (4) Å and O—Eu—O bond angles vary from 52.01 (1) to 143.68 (1) °. The chains are further connected by N—H···O and O—H···O hydrogen bonds (Table 1) and π — π interactions between the imidazole and benzene rings [centroid–centroid distances = 3.997 (4), 3.829 (4) and 3.573 (4) Å] into a three-dimensional supramolecular network.

Experimental

A mixture of Eu_2O_3 (0.352 g, 1 mmol), H_3bdc (0.206 g, 1 mmol), water (10 ml) in the presence of H_2SO_4 (0.038 g, 0.385 mmol) was stirred vigorously for 30 min and then sealed in a 20 ml Teflon-lined stainless-steel autoclave. The autoclave was heated and maintained at 443 K for 3 days, and then cooled to room temperature at 5 K h⁻¹. Colorless block crystals of the title compound were obtained.

Refinement

Water H atoms were tentatively located in difference Fourier maps and were refined with distance restraints of O—H = 0.84 and H···H = 1.35 Å, and with $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$. H atoms bound to C and N atoms were positioned geometrically and refined as riding atoms, with C—H = 0.93 and N—H = 0.86 Å and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C}, \text{N})$. H1A atom attached to N1 was refined with $U_{\text{iso}}(\text{H}) = 0.035$ Å². The highest residual electron density was found at 1.00 Å from Eu1 atom and the deepest hole at 0.97 Å from Eu1 atom.

supplementary materials

Figures

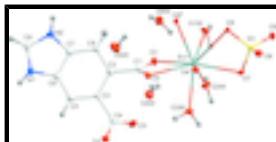


Fig. 1. The asymmetric unit of the title compound. Displacement ellipsoids are drawn at the 30% probability level. [Symmetry codes: (i) 2-x, -y, -z; (ii) 2-x, 1-y, -z.]

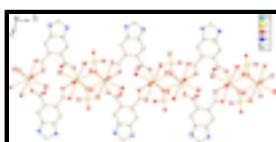


Fig. 2. A view of the chain structure along [0 1 0].

catena-poly[[[triaquaeuropium(III)]-bis(μ -1H,3H- \backslash benzimidazol-3-i u m-5,6-dicarboxylato- \backslash $\kappa^3O^5,O^{5\prime}:O^6$)- \backslash [triaquaeuropium(III)]-di- μ -sulfato- \backslash $\kappa^3O:O,O^{\prime};\kappa^3O,O^{\prime}:O^{\prime}$] hexahydrate]

Crystal data

| | |
|---|--|
| [Eu ₂ (C ₉ H ₅ N ₂ O ₄) ₂ (SO ₄) ₂ (H ₂ O) ₆] _· 6H ₂ O | Z = 1 |
| M _r = 1122.58 | F(000) = 552 |
| Triclinic, P $\bar{1}$ | D _x = 2.273 Mg m ⁻³ |
| Hall symbol: -P 1 | Mo K α radiation, λ = 0.71073 Å |
| a = 7.1261 (16) Å | Cell parameters from 3240 reflections |
| b = 9.581 (2) Å | θ = 2.5–25.2° |
| c = 12.424 (3) Å | μ = 4.03 mm ⁻¹ |
| α = 100.496 (3)° | T = 298 K |
| β = 98.060 (3)° | Block, colorless |
| γ = 94.979 (3)° | 0.30 × 0.26 × 0.20 mm |
| V = 820.3 (3) Å ³ | |

Data collection

| | |
|--|--|
| Bruker APEXII CCD diffractometer | 2841 independent reflections |
| Radiation source: fine-focus sealed tube graphite | 2669 reflections with $I > 2\sigma(I)$ |
| φ and ω scans | $R_{\text{int}} = 0.024$ |
| Absorption correction: multi-scan (SADABS; Bruker, 2001) | $\theta_{\max} = 25.2^\circ$, $\theta_{\min} = 1.7^\circ$ |
| $T_{\min} = 0.310$, $T_{\max} = 0.446$ | $h = -8 \rightarrow 8$ |
| 4076 measured reflections | $k = -10 \rightarrow 11$ |
| | $l = -14 \rightarrow 14$ |

Refinement

| | |
|---------------------------------|--|
| Refinement on F^2 | Primary atom site location: structure-invariant direct methods |
| Least-squares matrix: full | Secondary atom site location: difference Fourier map |
| $R[F^2 > 2\sigma(F^2)] = 0.036$ | Hydrogen site location: inferred from neighbouring sites |

| | |
|-------------------|--|
| $wR(F^2) = 0.097$ | H atoms treated by a mixture of independent and constrained refinement |
| $S = 1.02$ | $w = 1/[\sigma^2(F_o^2) + (0.0656P)^2 + 2.2735P]$ |
| 2841 reflections | where $P = (F_o^2 + 2F_c^2)/3$ |
| 248 parameters | $(\Delta/\sigma)_{\max} < 0.001$ |
| 0 restraints | $\Delta\rho_{\max} = 1.82 \text{ e \AA}^{-3}$ |
| | $\Delta\rho_{\min} = -2.51 \text{ e \AA}^{-3}$ |

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

| | <i>x</i> | <i>y</i> | <i>z</i> | $U_{\text{iso}}^*/U_{\text{eq}}$ |
|------|-------------|--------------|---------------|----------------------------------|
| Eu1 | 0.82011 (3) | 0.30949 (3) | -0.00038 (2) | 0.01547 (13) |
| S3 | 0.7557 (2) | 0.48078 (15) | -0.19659 (11) | 0.0178 (3) |
| O1 | 0.8381 (6) | 0.2686 (5) | 0.1916 (3) | 0.0245 (9) |
| O2 | 1.0266 (6) | 0.1509 (4) | 0.0920 (3) | 0.0235 (9) |
| O7 | 0.6411 (6) | 0.3533 (5) | -0.1756 (3) | 0.0255 (9) |
| O8 | 0.9029 (5) | 0.5245 (4) | -0.0939 (3) | 0.0197 (8) |
| O5 | 0.6331 (6) | 0.5948 (5) | -0.2072 (3) | 0.0274 (9) |
| O6 | 0.8483 (7) | 0.4467 (5) | -0.2935 (3) | 0.0286 (10) |
| N1 | 1.3014 (7) | -0.0260 (6) | 0.5455 (4) | 0.0249 (11) |
| N2 | 1.2981 (7) | 0.2039 (6) | 0.5675 (4) | 0.0251 (11) |
| H2 | 1.3174 | 0.2932 | 0.5979 | 0.030* |
| C1 | 0.9614 (8) | 0.1832 (6) | 0.1807 (5) | 0.0190 (12) |
| C2 | 1.0383 (8) | 0.1201 (6) | 0.2791 (5) | 0.0194 (12) |
| C3 | 1.0338 (8) | -0.0312 (6) | 0.2662 (4) | 0.0164 (11) |
| C5 | 1.1219 (8) | -0.0927 (6) | 0.3485 (5) | 0.0198 (12) |
| H5 | 1.1239 | -0.1911 | 0.3393 | 0.024* |
| C6 | 1.2079 (8) | -0.0005 (6) | 0.4462 (5) | 0.0218 (12) |
| C7 | 1.2050 (8) | 0.1468 (6) | 0.4603 (5) | 0.0213 (12) |
| C8 | 1.3518 (9) | 0.0977 (7) | 0.6146 (5) | 0.0274 (14) |
| H8 | 1.4162 | 0.1086 | 0.6866 | 0.033* |
| C9 | 1.1232 (8) | 0.2109 (6) | 0.3771 (4) | 0.0189 (11) |
| H9 | 1.1250 | 0.3095 | 0.3864 | 0.023* |
| O4W | 0.5121 (7) | 0.1310 (5) | 0.2584 (4) | 0.0352 (11) |
| H8W | 0.6008 | 0.1653 | 0.2294 | 0.053* |
| H7W | 0.4457 | 0.2009 | 0.2736 | 0.053* |
| O6W | 0.7298 (9) | 0.5166 (6) | 0.3452 (4) | 0.0439 (13) |
| H11W | 0.8442 | 0.5054 | 0.3395 | 0.066* |
| H12W | 0.6655 | 0.4779 | 0.2826 | 0.09 (4)* |
| O5W | 0.6913 (11) | 0.3173 (6) | 0.4890 (5) | 0.0644 (19) |
| H9W | 0.6934 | 0.3808 | 0.4506 | 0.097* |
| H10W | 0.7710 | 0.3559 | 0.5453 | 0.097* |
| O3W | 0.7114 (6) | 0.0596 (4) | -0.0781 (4) | 0.0283 (10) |
| H5W | 0.6097 | 0.0179 | -0.1180 | 0.042* |
| H6W | 0.7713 | -0.0084 | -0.0605 | 0.042* |
| O1W | 0.7080 (6) | 0.5224 (4) | 0.0984 (4) | 0.0266 (9) |
| H2W | 0.6011 | 0.5504 | 0.1051 | 0.040* |
| H1W | 0.7804 | 0.5996 | 0.1181 | 0.040* |

supplementary materials

| | | | | |
|-----|------------|-------------|------------|-------------|
| O2W | 0.4946 (6) | 0.2615 (5) | 0.0214 (4) | 0.0308 (10) |
| H4W | 0.4110 | 0.1952 | -0.0161 | 0.046* |
| H3W | 0.4346 | 0.3063 | 0.0678 | 0.046* |
| C4 | 0.9079 (8) | -0.1258 (6) | 0.1673 (4) | 0.0179 (11) |
| O4 | 0.9655 (6) | -0.2426 (4) | 0.1255 (3) | 0.0226 (9) |
| O3 | 0.7505 (6) | -0.0878 (5) | 0.1382 (4) | 0.0290 (10) |
| H1A | 1.323 (11) | -0.109 (9) | 0.557 (6) | 0.035* |

Atomic displacement parameters (\AA^2)

| | U^{11} | U^{22} | U^{33} | U^{12} | U^{13} | U^{23} |
|-----|--------------|--------------|--------------|--------------|--------------|--------------|
| Eu1 | 0.01833 (18) | 0.01343 (19) | 0.01383 (18) | 0.00052 (11) | 0.00124 (11) | 0.00220 (12) |
| S3 | 0.0222 (7) | 0.0163 (7) | 0.0138 (6) | -0.0006 (5) | 0.0006 (5) | 0.0030 (5) |
| O1 | 0.031 (2) | 0.026 (2) | 0.018 (2) | 0.0101 (18) | 0.0039 (17) | 0.0053 (17) |
| O2 | 0.032 (2) | 0.022 (2) | 0.018 (2) | 0.0070 (18) | 0.0074 (17) | 0.0046 (17) |
| O7 | 0.027 (2) | 0.021 (2) | 0.024 (2) | -0.0095 (17) | -0.0053 (17) | 0.0065 (17) |
| O8 | 0.021 (2) | 0.020 (2) | 0.0140 (19) | -0.0041 (16) | -0.0042 (15) | 0.0017 (16) |
| O5 | 0.034 (2) | 0.023 (2) | 0.024 (2) | 0.0087 (18) | -0.0010 (18) | 0.0051 (18) |
| O6 | 0.042 (3) | 0.025 (2) | 0.018 (2) | 0.0020 (19) | 0.0083 (18) | 0.0016 (17) |
| N1 | 0.029 (3) | 0.027 (3) | 0.021 (3) | 0.005 (2) | 0.004 (2) | 0.011 (2) |
| N2 | 0.033 (3) | 0.022 (3) | 0.016 (2) | -0.003 (2) | 0.002 (2) | -0.001 (2) |
| C1 | 0.026 (3) | 0.013 (3) | 0.018 (3) | 0.001 (2) | 0.001 (2) | 0.004 (2) |
| C2 | 0.018 (3) | 0.020 (3) | 0.020 (3) | 0.000 (2) | 0.004 (2) | 0.004 (2) |
| C3 | 0.019 (3) | 0.013 (3) | 0.017 (3) | -0.001 (2) | 0.003 (2) | 0.002 (2) |
| C5 | 0.024 (3) | 0.013 (3) | 0.024 (3) | 0.002 (2) | 0.007 (2) | 0.002 (2) |
| C6 | 0.024 (3) | 0.022 (3) | 0.020 (3) | 0.000 (2) | 0.005 (2) | 0.007 (2) |
| C7 | 0.025 (3) | 0.022 (3) | 0.015 (3) | -0.002 (2) | 0.005 (2) | 0.002 (2) |
| C8 | 0.028 (3) | 0.039 (4) | 0.013 (3) | 0.001 (3) | -0.002 (2) | 0.007 (3) |
| C9 | 0.025 (3) | 0.015 (3) | 0.016 (3) | -0.001 (2) | 0.005 (2) | 0.002 (2) |
| O4W | 0.035 (2) | 0.037 (3) | 0.039 (3) | 0.003 (2) | 0.012 (2) | 0.014 (2) |
| O6W | 0.067 (4) | 0.036 (3) | 0.024 (3) | 0.016 (3) | -0.003 (2) | -0.002 (2) |
| O5W | 0.123 (6) | 0.031 (3) | 0.033 (3) | 0.003 (3) | -0.006 (3) | 0.007 (2) |
| O3W | 0.030 (2) | 0.019 (2) | 0.032 (2) | -0.0014 (18) | -0.0022 (18) | 0.0008 (18) |
| O1W | 0.024 (2) | 0.014 (2) | 0.043 (3) | 0.0046 (16) | 0.0111 (19) | 0.0037 (18) |
| O2W | 0.023 (2) | 0.035 (3) | 0.028 (2) | -0.0041 (18) | 0.0029 (18) | -0.0072 (19) |
| C4 | 0.024 (3) | 0.015 (3) | 0.015 (3) | -0.003 (2) | 0.007 (2) | 0.002 (2) |
| O4 | 0.030 (2) | 0.019 (2) | 0.019 (2) | 0.0003 (17) | 0.0081 (17) | -0.0012 (16) |
| O3 | 0.024 (2) | 0.025 (2) | 0.032 (2) | 0.0055 (18) | -0.0039 (18) | -0.0061 (19) |

Geometric parameters (\AA , $^\circ$)

| | | | |
|----------------------|-----------|-------|-----------|
| Eu1—O4 ⁱ | 2.374 (4) | C3—C5 | 1.375 (8) |
| Eu1—O2W | 2.387 (4) | C3—C4 | 1.510 (8) |
| Eu1—O3W | 2.427 (4) | C5—C6 | 1.392 (8) |
| Eu1—O8 ⁱⁱ | 2.434 (4) | C5—H5 | 0.9300 |
| Eu1—O1W | 2.439 (4) | C6—C7 | 1.392 (9) |
| Eu1—O1 | 2.474 (4) | C7—C9 | 1.381 (8) |
| Eu1—O2 | 2.518 (4) | C8—H8 | 0.9300 |

| | | | |
|--|-------------|-----------|-----------|
| Eu1—O8 | 2.607 (4) | C9—H9 | 0.9300 |
| S3—O6 | 1.451 (4) | O4W—H8W | 0.8415 |
| S3—O5 | 1.470 (4) | O4W—H7W | 0.8612 |
| S3—O7 | 1.493 (4) | O6W—H11W | 0.8423 |
| S3—O8 | 1.502 (4) | O6W—H12W | 0.8471 |
| O1—C1 | 1.256 (7) | O5W—H9W | 0.8390 |
| O2—C1 | 1.252 (7) | O5W—H10W | 0.8403 |
| N1—C8 | 1.319 (8) | O3W—H5W | 0.8408 |
| N1—C6 | 1.390 (8) | O3W—H6W | 0.8534 |
| N1—H1A | 0.86 (8) | O1W—H2W | 0.8393 |
| N2—C8 | 1.322 (8) | O1W—H1W | 0.8396 |
| N2—C7 | 1.392 (7) | O2W—H4W | 0.8507 |
| N2—H2 | 0.8600 | O2W—H3W | 0.8434 |
| C1—C2 | 1.517 (8) | C4—O3 | 1.235 (7) |
| C2—C9 | 1.387 (8) | C4—O4 | 1.272 (7) |
| C2—C3 | 1.426 (8) | | |
| O4 ⁱ —Eu1—O2W | 140.91 (14) | C8—N1—C6 | 108.3 (5) |
| O4 ⁱ —Eu1—O3W | 76.22 (15) | C8—N1—H1A | 127 (5) |
| O2W—Eu1—O3W | 71.09 (15) | C6—N1—H1A | 124 (5) |
| O4 ⁱ —Eu1—O8 ⁱⁱ | 81.63 (13) | C8—N2—C7 | 108.3 (5) |
| O2W—Eu1—O8 ⁱⁱ | 137.26 (14) | C8—N2—H2 | 125.8 |
| O3W—Eu1—O8 ⁱⁱ | 143.77 (14) | C7—N2—H2 | 125.8 |
| O4 ⁱ —Eu1—O1W | 140.46 (14) | O2—C1—O1 | 122.2 (5) |
| O2W—Eu1—O1W | 69.33 (15) | O2—C1—C2 | 118.8 (5) |
| O3W—Eu1—O1W | 140.36 (14) | O1—C1—C2 | 119.0 (5) |
| O8 ⁱⁱ —Eu1—O1W | 71.68 (14) | C9—C2—C3 | 121.4 (5) |
| O4 ⁱ —Eu1—O1 | 126.79 (14) | C9—C2—C1 | 119.3 (5) |
| O2W—Eu1—O1 | 75.86 (15) | C3—C2—C1 | 119.1 (5) |
| O3W—Eu1—O1 | 92.05 (14) | C5—C3—C2 | 121.3 (5) |
| O8 ⁱⁱ —Eu1—O1 | 78.65 (13) | C5—C3—C4 | 119.1 (5) |
| O1W—Eu1—O1 | 76.39 (14) | C2—C3—C4 | 119.1 (5) |
| O4 ⁱ —Eu1—O2 | 75.47 (14) | C3—C5—C6 | 116.7 (5) |
| O2W—Eu1—O2 | 111.08 (15) | C3—C5—H5 | 121.6 |
| O3W—Eu1—O2 | 69.40 (14) | C6—C5—H5 | 121.6 |
| O8 ⁱⁱ —Eu1—O2 | 77.54 (13) | N1—C6—C5 | 131.7 (6) |
| O1W—Eu1—O2 | 124.10 (14) | N1—C6—C7 | 106.4 (5) |
| O1—Eu1—O2 | 52.20 (13) | C5—C6—C7 | 121.8 (5) |
| O4 ⁱ —Eu1—O8 | 71.41 (13) | C9—C7—N2 | 131.6 (6) |
| O2W—Eu1—O8 | 116.64 (14) | C9—C7—C6 | 122.3 (5) |
| O3W—Eu1—O8 | 131.57 (13) | N2—C7—C6 | 106.2 (5) |
| O8 ⁱⁱ —Eu1—O8 | 64.15 (14) | N1—C8—N2 | 110.7 (5) |
| O1W—Eu1—O8 | 70.87 (13) | N1—C8—H8 | 124.6 |
| O1—Eu1—O8 | 136.26 (13) | N2—C8—H8 | 124.6 |
| O2—Eu1—O8 | 131.95 (13) | C7—C9—C2 | 116.4 (5) |
| O4 ⁱ —Eu1—Eu1 ⁱⁱ | 73.90 (10) | C7—C9—H9 | 121.8 |
| O2W—Eu1—Eu1 ⁱⁱ | 133.79 (11) | C2—C9—H9 | 121.8 |

supplementary materials

| | | | |
|---|-------------|------------------------|-----------|
| O3W—Eu1—Eu1 ⁱⁱ | 149.81 (11) | H8W—O4W—H7W | 104.3 |
| O8 ⁱⁱ —Eu1—Eu1 ⁱⁱ | 33.30 (9) | H11W—O6W—H12W | 105.6 |
| O1W—Eu1—Eu1 ⁱⁱ | 67.72 (10) | H9W—O5W—H10W | 101.4 |
| O1—Eu1—Eu1 ⁱⁱ | 109.19 (10) | Eu1—O3W—H5W | 132.6 |
| O2—Eu1—Eu1 ⁱⁱ | 106.55 (10) | Eu1—O3W—H6W | 122.9 |
| O8—Eu1—Eu1 ⁱⁱ | 30.84 (8) | H5W—O3W—H6W | 104.1 |
| O6—S3—O5 | 111.0 (3) | Eu1—O1W—H2W | 135.5 |
| O6—S3—O7 | 112.3 (3) | Eu1—O1W—H1W | 120.5 |
| O5—S3—O7 | 109.6 (3) | H2W—O1W—H1W | 101.5 |
| O6—S3—O8 | 110.1 (3) | Eu1—O2W—H4W | 128.4 |
| O5—S3—O8 | 110.2 (2) | Eu1—O2W—H3W | 128.4 |
| O7—S3—O8 | 103.5 (2) | H4W—O2W—H3W | 103.2 |
| C1—O1—Eu1 | 93.8 (3) | O3—C4—O4 | 125.0 (5) |
| C1—O2—Eu1 | 91.8 (3) | O3—C4—C3 | 116.9 (5) |
| S3—O8—Eu1 ⁱⁱ | 146.0 (2) | O4—C4—C3 | 117.9 (5) |
| S3—O8—Eu1 | 97.84 (18) | C4—O4—Eu1 ⁱ | 135.3 (4) |
| Eu1 ⁱⁱ —O8—Eu1 | 115.85 (14) | | |


Symmetry codes: (i) $-x+2, -y, -z$; (ii) $-x+2, -y+1, -z$.

Hydrogen-bond geometry (\AA , $^\circ$)

| $D—\text{H}\cdots A$ | $D—\text{H}$ | $\text{H}\cdots A$ | $D\cdots A$ | $D—\text{H}\cdots A$ |
|-----------------------------|--------------|--------------------|-------------|----------------------|
| O1W—H1W···O4 ⁱⁱⁱ | 0.84 | 1.90 | 2.717 (6) | 165 |
| O1W—H2W···O7 ^{iv} | 0.84 | 2.24 | 3.049 (6) | 163 |
| O2W—H3W···O5 ^{iv} | 0.84 | 1.96 | 2.775 (6) | 162 |
| O2W—H4W···O3 ^v | 0.85 | 1.85 | 2.659 (6) | 159 |
| O3W—H5W···O4W ^v | 0.84 | 2.07 | 2.810 (6) | 146 |
| O3W—H6W···O2 ⁱ | 0.85 | 2.10 | 2.864 (6) | 149 |
| O4W—H7W···O5 ^{iv} | 0.86 | 2.34 | 3.045 (6) | 139 |
| O4W—H8W···O1 | 0.84 | 2.04 | 2.869 (6) | 168 |
| O5W—H9W···O6W | 0.84 | 2.03 | 2.864 (8) | 171 |
| O5W—H10W···O6 ^{vi} | 0.84 | 2.01 | 2.790 (7) | 154 |
| O6W—H11W···O6 ⁱⁱ | 0.84 | 2.37 | 3.165 (8) | 158 |
| O6W—H12W···O5 ^{iv} | 0.85 | 2.20 | 2.895 (7) | 139 |
| O6W—H12W···O1W | 0.85 | 2.46 | 3.060 (7) | 129 |
| N1—H1A···O5W ^{vii} | 0.86 (8) | 1.96 (8) | 2.752 (8) | 153 (7) |
| N1—H1A···O4W ^{vii} | 0.86 (8) | 2.48 (8) | 2.989 (7) | 119 (6) |
| N2—H2···O6W ^{viii} | 0.86 | 1.91 | 2.734 (7) | 161 |

Symmetry codes: (iii) $x, y+1, z$; (iv) $-x+1, -y+1, -z$; (v) $-x+1, -y, -z$; (i) $-x+2, -y, -z$; (vi) $x, y, z+1$; (ii) $-x+2, -y+1, -z$; (vii) $-x+2, -y, -z+1$; (viii) $-x+2, -y+1, -z+1$.

Fig. 1

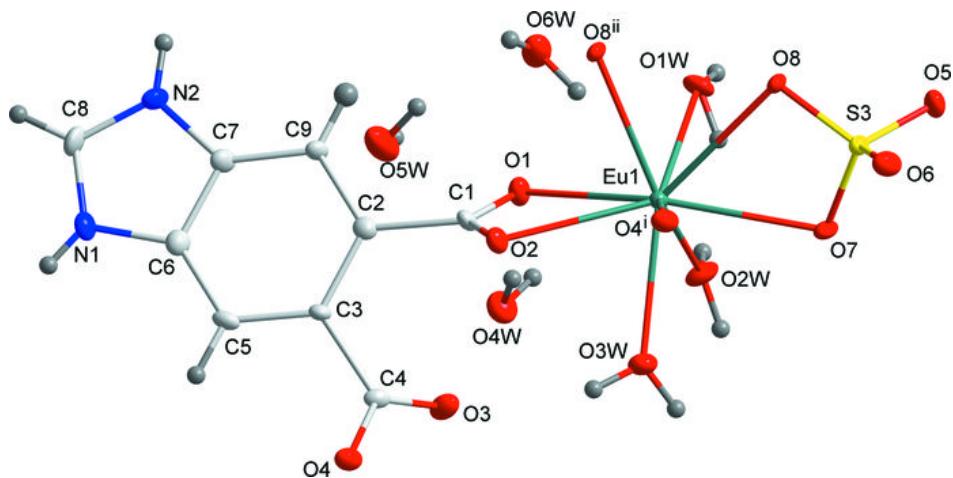

supplementary materials

Fig. 2

