

Poly[aqua(μ_1 -4,6-dihydroxybenzene-1,3-disulfonato)dipotassium]

Zhu-Lin Xie,^{a*} Wu-Leng Lai,^b Rui-Qing Yang^b and Yong-Rong Xie^b

^aSchool of Chemistry and Chemical Engineering, University of Jinan, Jinan 250022, People's Republic of China, and ^bKey Laboratory of Jiangxi University for Functional Materials Chemistry, College of Chemistry and Chemical Engineering, Gannan Normal University, Ganzhou 341000, People's Republic of China
Correspondence e-mail: yongrongxie@yahoo.com.cn


Received 10 October 2011; accepted 8 November 2011

Key indicators: single-crystal X-ray study; $T = 292\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.002\text{ \AA}$; R factor = 0.024; wR factor = 0.071; data-to-parameter ratio = 13.7.

In the title salt, $[\text{K}_2(\text{C}_6\text{H}_4\text{O}_8\text{S}_2)(\text{H}_2\text{O})]_n$, both K^+ ions exhibit a seven-coordination with $\text{K}-\text{O}$ bond lengths in the range 2.6600 (14) to 3.0522 (16) \AA . One K^+ ion is coordinated by seven O atoms from the sulfonate and phenolic hydroxy groups of six 4,6-dihydroxybenzene-1,3-disulfonate (L^{2-}) anions while the other K^+ ion is coordinated by six O atoms from the sulfonate and phenolic hydroxy groups of five L^{2-} anions and one water O atom. The L^{2-} anion exhibits chelating-bridging multidentate coordination to potassium, resulting in the formation of a cross-linked three-dimensional network.

Related literature

For $\text{K}-\text{O}$ bond lengths of potassium complexes, see: Hatano *et al.* (2008); Xie *et al.* (2006); Zhang *et al.* (2006). For other complexes with seven-coordinate potassium atoms, see: Deacon *et al.* (1999).

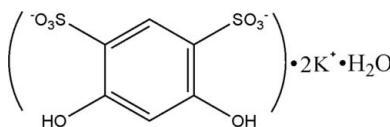

Experimental

Crystal data

$[\text{K}_2(\text{C}_6\text{H}_4\text{O}_8\text{S}_2)(\text{H}_2\text{O})]$
 $M_r = 364.43$

Monoclinic, $P2_1/c$
 $a = 7.3427(3)\text{ \AA}$

$b = 11.5194(5)\text{ \AA}$
 $c = 14.6331(6)\text{ \AA}$
 $\beta = 100.495(1)^{\circ}$
 $V = 1217.01(9)\text{ \AA}^3$
 $Z = 4$

Mo $K\alpha$ radiation
 $\mu = 1.16\text{ mm}^{-1}$
 $T = 292\text{ K}$
 $0.33 \times 0.20 \times 0.17\text{ mm}$

Data collection

Bruker SMART APEXII CCD area-detector diffractometer
Absorption correction: multi-scan (*SADABS*; Sheldrick, 1996)
 $T_{\min} = 0.753$, $T_{\max} = 0.816$

6519 measured reflections
2365 independent reflections
2164 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.013$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.024$
 $wR(F^2) = 0.071$
 $S = 1.08$
2365 reflections

173 parameters
H-atom parameters constrained
 $\Delta\rho_{\max} = 0.38\text{ e \AA}^{-3}$
 $\Delta\rho_{\min} = -0.33\text{ e \AA}^{-3}$

Table 1
Hydrogen-bond geometry (\AA , $^{\circ}$).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
O8—H8A \cdots O4	0.82	1.88	2.625 (2)	151
O7—H7A \cdots O1	0.82	1.86	2.613 (2)	152
O9—H9A \cdots O6 ⁱ	0.85	2.29	2.916 (2)	130
O9—H9B \cdots O2 ⁱⁱ	0.85	2.26	2.913 (3)	134

Symmetry codes: (i) $-x + 1, y + \frac{1}{2}, -z + \frac{1}{2}$; (ii) $x + 1, y, z$.

Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINT* (Bruker, 2007); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXTL*.

This work was supported financially by the National Natural Science Foundation of China (grant No. 20861001) and the Natural Science Foundation of Jiangxi Provincial Education Department (grant Nos. GJJ11587 and GJJ08505).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: VM2127).

References

- Bruker (2007). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Deacon, G. B., Gitlits, A., Zelesny, G., Stellfeldt, D. & Meyer, G. (1999). *Z. Anorg. Allg. Chem.* **625**, 764–772.
- Hatano, M., Maki, T., Moriyama, K., Arinobe, M. & Ishihara, K. (2008). *J. Am. Chem. Soc.* **130**, 16858–16860.
- Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
- Xie, Y.-R., Lui, G.-R. & Yuan, X.-Y. (2006). *Acta Cryst. E* **62**, m1016–m1017.
- Zhang, T. L., Chen, H. Y., Zhang, J. G., Yang, L. & Guo, J. Y. (2006). *Struct. Chem.* **17**, 445–450.

supplementary materials

Acta Cryst. (2011). E67, m1745 [doi:10.1107/S1600536811047210]

Poly[aqua(μ_{11} -4,6-dihydroxybenzene-1,3-disulfonato)dipotassium]

Z.-L. Xie, W.-L. Lai, R.-Q. Yang and Y.-R. Xie

Comment

The title compound, (I), consists of a three dimensional framework of K^+ ions coordinated to 4, 6-dihydroxybenzene-1, 3-disulfonate anions. The K^+ ion is typically seven-coordinated (Deacon *et al.*, 1999), in which the coordination environment around the K^+ center in (I) is a distorted pentangular dipyramid. As shown in Fig. 1, the K1 ion is coordinated by seven O atoms from six 4, 6-dihydroxybenzene-1, 3-disulfonate anions, in which the K—O bond distances range from 2.7160 (14) to 3.0206 (16) Å, with an average bond distance of 2.8460 Å, and the K2 ion is also coordinated by five 4, 6-dihydroxybenzene-1, 3-disulfonate anions and one water molecule, in which the K—O bond distances range from 2.6606 (14) to 3.0518 (16) Å, with an average bond distance of 2.791 Å. The K—O bond distances are similar to the values in other potassium complexes (Hatano *et al.*, 2008; Xie *et al.*, 2006; Zhang *et al.*, 2006). The two sulfonate groups of the 4, 6-dihydroxybenzene-1, 3-disulfonate anions in (I) exhibit a chelating-bridging pentadentate or tetradeятate coordination. The O1/O2 atoms and O5/O6 atoms bridge two different K^+ ions, the other O atoms including those of the hydroxide groups chelate to one type of K^+ ion (Fig. 2) giving a three dimensional structure (Fig. 3).

Experimental

KOH (0.14 g, 2.5 mmol) and 4, 6-dihydroxybenzene-1, 3-disulfonate acid (0.91 g, 2.5 mmol) were dissolved in 10 ml of distilled water by vigorous stirring. Filtering solution was evaporated slowly at room temperature. Colorless block crystals of the tilted compound suitable for X-ray analysis were collected in 55% yield (based on potassium) after one week.

Refinement

H atoms bound to C atoms were placed in calculated positions and treated as riding on their parent atoms, with C—H = 0.93 Å, and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. Water H atoms were initially located in a difference Fourier map, but they were treated as riding on their parent atoms with O—H = 0.85 Å, and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{O})$. Hydroxy H atoms were placed in calculated positions and treated as riding on their parent atoms, with O—H = 0.82 Å, and with $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$.

Figures

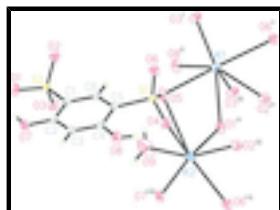


Fig. 1. The coordination environment of the K^+ ions showing displacement ellipsoids drawn at the 30% probability level. [Symmetry codes: (i) $x, -y + 1/2, z + 1/2$; (ii) $-x + 1, y + 1/2, -z + 1/2$; (iii) $-x + 1, y - 1/2, -z + 1/2$; (iv) $x + 1, -y + 1/2, z + 1/2$; (v) $-x + 1, -y, -z + 1$; (vii) $x + 1, y, z$; (viii) $-x + 1, -y, -z$].

supplementary materials

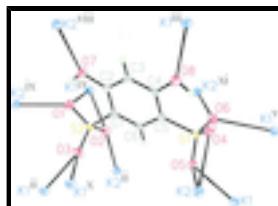


Fig. 2. View of chelating/bridging to K^+ ions by the sulfonic and phenolic hydroxy groups in the L^{2-} -anion, displacement ellipsoids are drawn at 30% probability level. [Symmetry codes: (ii) $-x + 1, y + 1/2, -z + 1/2$; (iii) $-x + 1, y - 1/2, -z + 1/2$; (v) $-x + 1, -y, -z + 1$; (viii) $-x + 1, -y, -z$; (ix) $x - 1, -y + 1/2, z - 1/2$; (x) $x, -y + 1/2, z - 1/2$; (xi) $x - 1, y, z$].

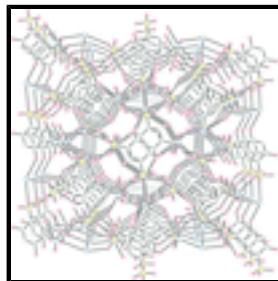


Fig. 3. Perspective view of crystal packing along the a axis. Hydrogen atoms are omitted for clarity.

Poly[aqua(μ_{11} -4,6-dihydroxybenzene-1,3-disulfonato)dipotassium]

Crystal data

$[\text{K}_2(\text{C}_6\text{H}_4\text{O}_8\text{S}_2)(\text{H}_2\text{O})]$

$F(000) = 736$

$M_r = 364.43$

$D_x = 1.989 \text{ Mg m}^{-3}$

Monoclinic, $P2_1/c$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Hall symbol: -P 2ybc

Cell parameters from 2637 reflections

$a = 7.3427 (3) \text{ \AA}$

$\theta = 2.3\text{--}27.4^\circ$

$b = 11.5194 (5) \text{ \AA}$

$\mu = 1.16 \text{ mm}^{-1}$

$c = 14.6331 (6) \text{ \AA}$

$T = 292 \text{ K}$

$\beta = 100.495 (1)^\circ$

Block, colorless

$V = 1217.01 (9) \text{ \AA}^3$

$0.33 \times 0.20 \times 0.17 \text{ mm}$

$Z = 4$

Data collection

Bruker SMART APEXII CCD area-detector diffractometer

2365 independent reflections

Radiation source: fine-focus sealed tube

2164 reflections with $I > 2\sigma(I)$

graphite

$R_{\text{int}} = 0.013$

φ and ω scans

$\theta_{\max} = 26.0^\circ, \theta_{\min} = 2.3^\circ$

Absorption correction: multi-scan (*SADABS*; Sheldrick, 1996)

$h = -9 \rightarrow 8$

$T_{\min} = 0.753, T_{\max} = 0.816$

$k = -14 \rightarrow 14$

6519 measured reflections

$l = -13 \rightarrow 18$

Refinement

Refinement on F^2

Secondary atom site location: difference Fourier map

Least-squares matrix: full

Hydrogen site location: inferred from neighbouring sites

$R[F^2 > 2\sigma(F^2)] = 0.024$	H-atom parameters constrained
$wR(F^2) = 0.071$	$w = 1/[\sigma^2(F_o^2) + (0.0436P)^2 + 0.4024P]$ where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.08$	$(\Delta/\sigma)_{\text{max}} < 0.001$
2365 reflections	$\Delta\rho_{\text{max}} = 0.38 \text{ e \AA}^{-3}$
173 parameters	$\Delta\rho_{\text{min}} = -0.33 \text{ e \AA}^{-3}$
0 restraints	Extinction correction: <i>SHELXL97</i> (Sheldrick, 2008), $F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$
Primary atom site location: structure-invariant direct methods	Extinction coefficient: 0.0022 (7)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
K1	0.65409 (5)	0.13314 (3)	0.49915 (3)	0.03113 (13)
K2	0.92404 (6)	0.02144 (4)	0.28049 (3)	0.03374 (13)
S1	0.44515 (6)	0.00084 (4)	0.26286 (3)	0.02489 (13)
S2	0.13059 (5)	0.32694 (3)	0.01439 (3)	0.02338 (13)
O1	0.0057 (2)	0.32564 (11)	-0.07575 (9)	0.0390 (3)
O2	0.03127 (18)	0.35943 (11)	0.08772 (10)	0.0349 (3)
O3	0.29405 (18)	0.39641 (11)	0.01473 (10)	0.0372 (3)
O4	0.5722 (2)	-0.09468 (13)	0.25379 (10)	0.0431 (4)
O5	0.5404 (2)	0.10174 (12)	0.30606 (9)	0.0401 (3)
O6	0.29385 (19)	-0.03620 (13)	0.30678 (9)	0.0410 (3)
O7	0.0959 (2)	0.11766 (12)	-0.12326 (9)	0.0381 (3)
H7A	0.0522	0.1834	-0.1271	0.046*
O8	0.3915 (2)	-0.15510 (11)	0.08903 (10)	0.0383 (3)
H8A	0.4576	-0.1604	0.1404	0.046*
O9	0.8087 (4)	0.21939 (16)	0.19154 (15)	0.0948 (8)
H9A	0.7450	0.2678	0.2163	0.114*
H9B	0.8358	0.2336	0.1386	0.114*
C1	0.2023 (2)	0.18131 (14)	0.03585 (11)	0.0225 (3)
C2	0.1799 (2)	0.09683 (15)	-0.03415 (11)	0.0254 (4)
C3	0.2454 (2)	-0.01451 (15)	-0.01379 (12)	0.0292 (4)
H3A	0.2321	-0.0700	-0.0607	0.035*
C4	0.3303 (2)	-0.04435 (14)	0.07530 (12)	0.0258 (3)

supplementary materials

C5	0.3490 (2)	0.03891 (14)	0.14670 (11)	0.0233 (3)
C6	0.2866 (2)	0.15100 (14)	0.12554 (12)	0.0241 (3)
H6A	0.3015	0.2069	0.1722	0.029*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
K1	0.0284 (2)	0.0278 (2)	0.0368 (2)	-0.00127 (15)	0.00475 (16)	0.00329 (15)
K2	0.0373 (2)	0.0326 (2)	0.0297 (2)	0.00037 (16)	0.00155 (17)	-0.00276 (16)
S1	0.0255 (2)	0.0254 (2)	0.0225 (2)	0.00017 (16)	0.00132 (16)	0.00241 (15)
S2	0.0237 (2)	0.0199 (2)	0.0257 (2)	0.00147 (15)	0.00221 (16)	0.00099 (15)
O1	0.0470 (8)	0.0309 (7)	0.0329 (7)	0.0074 (6)	-0.0093 (6)	0.0026 (6)
O2	0.0364 (7)	0.0305 (7)	0.0402 (8)	0.0088 (5)	0.0131 (6)	-0.0009 (5)
O3	0.0319 (7)	0.0263 (7)	0.0538 (9)	-0.0039 (5)	0.0092 (6)	0.0049 (6)
O4	0.0458 (8)	0.0437 (8)	0.0363 (7)	0.0193 (7)	-0.0020 (6)	0.0016 (6)
O5	0.0492 (8)	0.0366 (7)	0.0291 (7)	-0.0113 (6)	-0.0071 (6)	0.0010 (6)
O6	0.0364 (7)	0.0531 (9)	0.0349 (7)	-0.0057 (6)	0.0100 (6)	0.0096 (6)
O7	0.0549 (9)	0.0336 (7)	0.0219 (6)	0.0099 (6)	-0.0029 (6)	-0.0033 (5)
O8	0.0521 (8)	0.0218 (6)	0.0366 (7)	0.0081 (6)	-0.0033 (6)	-0.0020 (5)
O9	0.178 (3)	0.0389 (10)	0.0766 (14)	0.0139 (13)	0.0474 (15)	0.0119 (9)
C1	0.0222 (8)	0.0205 (8)	0.0249 (8)	0.0014 (6)	0.0041 (6)	0.0008 (6)
C2	0.0259 (8)	0.0279 (9)	0.0220 (8)	0.0002 (7)	0.0029 (6)	-0.0012 (7)
C3	0.0343 (10)	0.0250 (9)	0.0269 (9)	0.0011 (7)	0.0023 (7)	-0.0073 (7)
C4	0.0270 (8)	0.0202 (8)	0.0300 (9)	0.0001 (7)	0.0046 (7)	-0.0015 (7)
C5	0.0233 (8)	0.0236 (8)	0.0223 (8)	0.0002 (6)	0.0019 (6)	0.0007 (6)
C6	0.0256 (8)	0.0224 (8)	0.0234 (8)	-0.0004 (6)	0.0019 (6)	-0.0036 (6)

Geometric parameters (\AA , $^\circ$)

K1—O3 ⁱ	2.7160 (14)	O1—K2 ^{viii}	2.7256 (13)
K1—O8 ⁱⁱ	2.7514 (13)	O1—K1 ^{viii}	3.0207 (16)
K1—O3 ⁱⁱⁱ	2.7660 (14)	O2—K2 ⁱⁱ	2.6607 (14)
K1—O5	2.8200 (14)	O2—K1 ^{viii}	2.8372 (14)
K1—O2 ^{iv}	2.8372 (14)	O3—K1 ^{ix}	2.7160 (14)
K1—O6 ^v	3.0104 (14)	O3—K1 ⁱⁱ	2.7660 (14)
K1—O1 ^{iv}	3.0207 (16)	O6—K2 ^x	2.7535 (15)
K1—O9 ⁱ	3.307 (2)	O6—K1 ^v	3.0104 (14)
K1—S2 ^{iv}	3.4954 (6)	O7—C2	1.359 (2)
K2—O2 ⁱⁱⁱ	2.6607 (14)	O7—K2 ^{vii}	2.7856 (13)
K2—O9	2.6851 (19)	O7—H7A	0.8204
K2—O1 ^{iv}	2.7256 (13)	O8—C4	1.356 (2)
K2—O6 ^{vi}	2.7535 (15)	O8—K1 ⁱⁱⁱ	2.7514 (13)
K2—O7 ^{vii}	2.7856 (13)	O8—H8A	0.8194
K2—O4	2.8720 (16)	O9—K1 ^{ix}	3.307 (2)
K2—O5	3.0521 (16)	O9—H9A	0.8500
K2—S1	3.4867 (6)	O9—H9B	0.8502

S1—O5	1.4417 (13)	C1—C6	1.390 (2)
S1—O6	1.4455 (14)	C1—C2	1.401 (2)
S1—O4	1.4641 (14)	C2—C3	1.383 (2)
S1—C5	1.7729 (16)	C3—C4	1.382 (2)
S2—O3	1.4418 (13)	C3—H3A	0.9300
S2—O2	1.4519 (13)	C4—C5	1.406 (2)
S2—O1	1.4628 (13)	C5—C6	1.386 (2)
S2—C1	1.7691 (16)	C6—H6A	0.9300
S2—K1 ^{viii}	3.4954 (6)		
O3 ⁱ —K1—O8 ⁱⁱ	96.50 (4)	O1 ^{iv} —K2—S1	100.27 (3)
O3 ⁱ —K1—O3 ⁱⁱⁱ	91.82 (4)	O6 ^{vi} —K2—S1	161.72 (4)
O8 ⁱⁱ —K1—O3 ⁱⁱⁱ	147.81 (5)	O7 ^{vii} —K2—S1	89.95 (3)
O3 ⁱ —K1—O5	87.31 (5)	O4—K2—S1	24.24 (3)
O8 ⁱⁱ —K1—O5	69.84 (4)	O5—K2—S1	24.33 (3)
O3 ⁱⁱⁱ —K1—O5	79.60 (4)	O2 ⁱⁱⁱ —K2—K1	71.35 (3)
O3 ⁱ —K1—O2 ^{iv}	148.16 (4)	O9—K2—K1	87.63 (5)
O8 ⁱⁱ —K1—O2 ^{iv}	102.29 (4)	O1 ^{iv} —K2—K1	44.92 (3)
O3 ⁱⁱⁱ —K1—O2 ^{iv}	85.83 (4)	O6 ^{vi} —K2—K1	123.37 (3)
O5—K1—O2 ^{iv}	123.22 (4)	O7 ^{vii} —K2—K1	146.39 (3)
O3 ⁱ —K1—O6 ^v	80.36 (4)	O4—K2—K1	73.30 (3)
O8 ⁱⁱ —K1—O6 ^v	139.02 (4)	O5—K2—K1	41.41 (3)
O3 ⁱⁱⁱ —K1—O6 ^v	73.03 (4)	S1—K2—K1	58.329 (11)
O5—K1—O6 ^v	149.45 (4)	O2 ⁱⁱⁱ —K2—K1 ^{xi}	37.90 (3)
O2 ^{iv} —K1—O6 ^v	68.57 (4)	O9—K2—K1 ^{xi}	144.42 (6)
O3 ⁱ —K1—O1 ^{iv}	163.66 (4)	O1 ^{iv} —K2—K1 ^{xi}	70.77 (3)
O8 ⁱⁱ —K1—O1 ^{iv}	74.31 (4)	O6 ^{vi} —K2—K1 ^{xi}	42.14 (3)
O3 ⁱⁱⁱ —K1—O1 ^{iv}	89.44 (4)	O7 ^{vii} —K2—K1 ^{xi}	107.18 (3)
O5—K1—O1 ^{iv}	76.90 (4)	O4—K2—K1 ^{xi}	113.91 (3)
O2 ^{iv} —K1—O1 ^{iv}	48.18 (4)	O5—K2—K1 ^{xi}	124.94 (3)
O6 ^v —K1—O1 ^{iv}	115.50 (4)	S1—K2—K1 ^{xi}	126.161 (14)
O3 ⁱ —K1—O9 ⁱ	100.44 (5)	K1—K2—K1 ^{xi}	86.205 (11)
O8 ⁱⁱ —K1—O9 ⁱ	86.41 (5)	O5—S1—O6	113.19 (9)
O3 ⁱⁱⁱ —K1—O9 ⁱ	122.58 (5)	O5—S1—O4	112.30 (9)
O5—K1—O9 ⁱ	155.78 (5)	O6—S1—O4	111.87 (9)
O2 ^{iv} —K1—O9 ⁱ	55.98 (6)	O5—S1—C5	107.31 (8)
O6 ^v —K1—O9 ⁱ	54.73 (5)	O6—S1—C5	107.16 (8)
O1 ^{iv} —K1—O9 ⁱ	92.56 (5)	O4—S1—C5	104.37 (8)
O3 ⁱ —K1—S2 ^{iv}	171.66 (4)	O5—S1—K2	60.70 (6)
O8 ⁱⁱ —K1—S2 ^{iv}	87.03 (3)	O6—S1—K2	146.47 (6)
O3 ⁱⁱⁱ —K1—S2 ^{iv}	89.13 (3)	O4—S1—K2	53.65 (6)
O5—K1—S2 ^{iv}	101.01 (3)	C5—S1—K2	105.92 (6)
O2 ^{iv} —K1—S2 ^{iv}	23.71 (3)	O3—S2—O2	112.60 (8)

supplementary materials

O6 ^v —K1—S2 ^{iv}	92.00 (3)	O3—S2—O1	113.16 (9)
O1 ^{iv} —K1—S2 ^{iv}	24.59 (2)	O2—S2—O1	110.63 (8)
O9 ⁱ —K1—S2 ^{iv}	72.17 (5)	O3—S2—C1	107.76 (8)
O3 ⁱ —K1—K1 ^v	46.45 (3)	O2—S2—C1	106.66 (8)
O8 ⁱⁱ —K1—K1 ^v	133.97 (3)	O1—S2—C1	105.53 (8)
O3 ⁱⁱⁱ —K1—K1 ^v	45.37 (3)	O3—S2—K1 ^{viii}	138.60 (6)
O5—K1—K1 ^v	80.54 (3)	O2—S2—K1 ^{viii}	51.80 (6)
O2 ^{iv} —K1—K1 ^v	123.52 (3)	O1—S2—K1 ^{viii}	59.22 (6)
O6 ^v —K1—K1 ^v	70.68 (3)	C1—S2—K1 ^{viii}	113.46 (6)
O1 ^{iv} —K1—K1 ^v	132.54 (3)	S2—O1—K2 ^{viii}	134.67 (8)
O9 ⁱ —K1—K1 ^v	121.30 (4)	S2—O1—K1 ^{viii}	96.20 (7)
S2 ^{iv} —K1—K1 ^v	133.906 (18)	K2 ^{viii} —O1—K1 ^{viii}	95.50 (4)
O3 ⁱ —K1—K2	128.22 (3)	S2—O2—K2 ⁱⁱ	134.76 (8)
O8 ⁱⁱ —K1—K2	87.08 (3)	S2—O2—K1 ^{viii}	104.48 (7)
O3 ⁱⁱⁱ —K1—K2	63.75 (3)	K2 ⁱⁱ —O2—K1 ^{viii}	106.93 (4)
O5—K1—K2	45.71 (3)	S2—O3—K1 ^{ix}	138.81 (8)
O2 ^{iv} —K1—K2	78.64 (3)	S2—O3—K1 ⁱⁱ	132.27 (8)
O6 ^v —K1—K2	126.89 (3)	K1 ^{ix} —O3—K1 ⁱⁱ	88.18 (4)
O1 ^{iv} —K1—K2	39.58 (2)	S1—O4—K2	102.11 (8)
O9 ⁱ —K1—K2	131.33 (5)	S1—O5—K1	125.04 (8)
S2 ^{iv} —K1—K2	59.350 (11)	S1—O5—K2	94.98 (7)
K1 ^v —K1—K2	96.882 (15)	K1—O5—K2	92.88 (4)
O3 ⁱ —K1—K2 ^{xi}	116.87 (3)	S1—O6—K2 ^x	133.23 (8)
O8 ⁱⁱ —K1—K2 ^{xi}	135.14 (3)	S1—O6—K1 ^v	123.58 (7)
O3 ⁱⁱⁱ —K1—K2 ^{xi}	64.45 (3)	K2 ^x —O6—K1 ^v	100.01 (4)
O5—K1—K2 ^{xi}	136.03 (3)	C2—O7—K2 ^{vii}	129.60 (11)
O2 ^{iv} —K1—K2 ^{xi}	35.17 (3)	C2—O7—H7A	109.4
O6 ^v —K1—K2 ^{xi}	37.85 (3)	K2 ^{vii} —O7—H7A	120.9
O1 ^{iv} —K1—K2 ^{xi}	78.24 (3)	C4—O8—K1 ⁱⁱⁱ	139.13 (11)
O9 ⁱ —K1—K2 ^{xi}	59.97 (4)	C4—O8—H8A	109.4
S2 ^{iv} —K1—K2 ^{xi}	56.355 (10)	K1 ⁱⁱⁱ —O8—H8A	111.4
K1 ^v —K1—K2 ^{xi}	90.518 (14)	K2—O9—K1 ^{ix}	151.40 (8)
K2—K1—K2 ^{xi}	93.795 (11)	K2—O9—H9A	120.0
O2 ⁱⁱⁱ —K2—O9	158.97 (6)	K1 ^{ix} —O9—H9A	84.0
O2 ⁱⁱⁱ —K2—O1 ^{iv}	85.02 (4)	K2—O9—H9B	120.0
O9—K2—O1 ^{iv}	80.27 (6)	K1 ^{ix} —O9—H9B	39.3
O2 ⁱⁱⁱ —K2—O6 ^{vi}	75.01 (4)	H9A—O9—H9B	120.0
O9—K2—O6 ^{vi}	119.25 (7)	C6—C1—C2	119.26 (15)
O1 ^{iv} —K2—O6 ^{vi}	88.58 (5)	C6—C1—S2	118.21 (12)
O2 ⁱⁱⁱ —K2—O7 ^{vii}	100.15 (4)	C2—C1—S2	122.52 (13)
O9—K2—O7 ^{vii}	97.10 (5)	O7—C2—C3	116.73 (15)

O1 ^{iv} —K2—O7 ^{vii}	168.61 (5)	O7—C2—C1	123.46 (15)
O6 ^{vi} —K2—O7 ^{vii}	83.04 (4)	C3—C2—C1	119.80 (15)
O2 ⁱⁱⁱ —K2—O4	76.18 (4)	C4—C3—C2	120.87 (16)
O9—K2—O4	97.64 (7)	C4—C3—H3A	119.6
O1 ^{iv} —K2—O4	118.17 (5)	C2—C3—H3A	119.6
O6 ^{vi} —K2—O4	138.28 (4)	O8—C4—C3	117.02 (15)
O7 ^{vii} —K2—O4	73.09 (4)	O8—C4—C5	123.15 (15)
O2 ⁱⁱⁱ —K2—O5	96.80 (4)	C3—C4—C5	119.83 (15)
O9—K2—O5	65.50 (6)	C6—C5—C4	119.06 (15)
O1 ^{iv} —K2—O5	77.75 (4)	C6—C5—S1	120.16 (13)
O6 ^{vi} —K2—O5	164.73 (4)	C4—C5—S1	120.76 (13)
O7 ^{vii} —K2—O5	111.39 (4)	C5—C6—C1	121.14 (15)
O4—K2—O5	47.96 (4)	C5—C6—H6A	119.4
O2 ⁱⁱⁱ —K2—S1	89.74 (3)	C1—C6—H6A	119.4
O9—K2—S1	78.29 (6)		

Symmetry codes: (i) $x, -y+1/2, z+1/2$; (ii) $-x+1, y+1/2, -z+1/2$; (iii) $-x+1, y-1/2, -z+1/2$; (iv) $x+1, -y+1/2, z+1/2$; (v) $-x+1, -y, -z+1$; (vi) $x+1, y, z$; (vii) $-x+1, -y, -z$; (viii) $x-1, -y+1/2, z-1/2$; (ix) $x, -y+1/2, z-1/2$; (x) $x-1, y, z$; (xi) $-x+2, -y, -z+1$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D—\text{H}\cdots A$	$D—\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D—\text{H}\cdots A$
O8—H8A \cdots O4	0.82	1.88	2.625 (2)	151
O7—H7A \cdots O1	0.82	1.86	2.613 (2)	152
O9—H9A \cdots O6 ⁱⁱ	0.85	2.29	2.916 (2)	130
O9—H9B \cdots O2 ^{vi}	0.85	2.26	2.913 (3)	134

Symmetry codes: (ii) $-x+1, y+1/2, -z+1/2$; (vi) $x+1, y, z$.

supplementary materials

Fig. 1


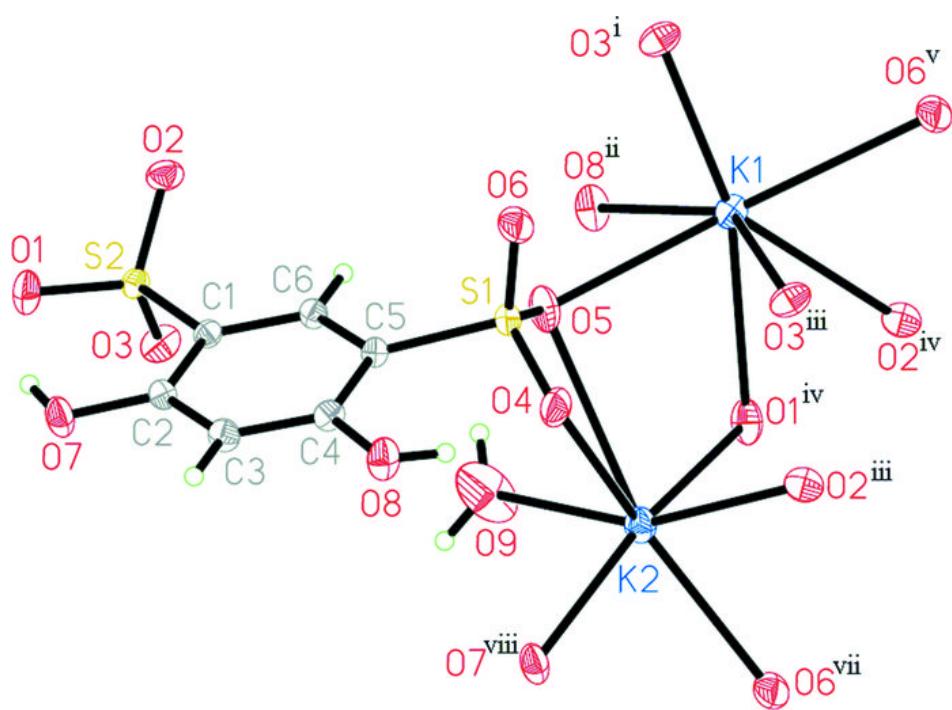


Fig. 2



supplementary materials

Fig. 3

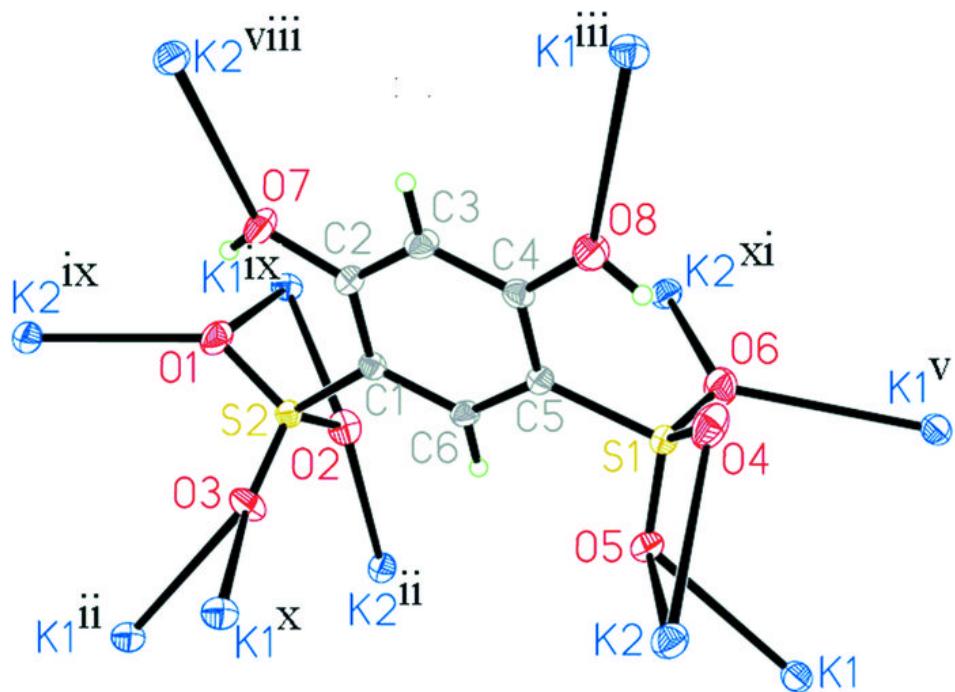