

5,5'-Bis(naphthalen-2-yl)-2,2'-bi(1,3,4-oxadiazole)

Haitao Wang,^a Xiaoshi Jia,^a Songnan Qu,^b Binglian Bai^c and Min Li^{a*}

^aKey Laboratory of Automobile Materials (MOE), College of Materials Science and Engineering, Jilin University, Changchun 130012, People's Republic of China, ^bKey Laboratory of Excited State Processes, Changchun Institute of Optics, Fine Mechanics and Physics, Chinese Academy of Sciences, Changchun 130033, People's Republic of China, and ^cCollege of Physics, Jilin University, Changchun 130012, People's Republic of China

Correspondence e-mail: minli@jlu.edu.cn


Received 10 November 2011; accepted 15 November 2011

Key indicators: single-crystal X-ray study; $T = 293\text{ K}$; mean $\sigma(\text{C}-\text{C}) = 0.002\text{ \AA}$; R factor = 0.039; wR factor = 0.106; data-to-parameter ratio = 15.4.

The title molecule, $\text{C}_{24}\text{H}_{14}\text{N}_4\text{O}_2$, lies on an inversion centre and the asymmetric unit contains one half-molecule. The naphthalene ring systems are twisted slightly with respect to the oxadiazole rings, making a dihedral angle of $1.36(6)^\circ$. These molecules are π -stacked along the crystallographic a axis, with an interplanar distance of $3.337(1)\text{ \AA}$. Adjacent molecules are slipped from the 'ideal' cofacial π -stack in both the long and short molecular axis (the long molecular axis is defined as the line through the naphthalene C atom in the 6-position and the molecular center, the short molecular axis is in the molecular plane perpendicular to it). The slip distance along the long molecular axis (S_1) is $7.064(1)\text{ \AA}$, nearly a two-ring-length displacement. The side slip (S_2 , along the short molecular axis) is $1.159(8)\text{ \AA}$.

Related literature

For the synthesis of 1,3,4-oxadiazole derivatives: see Schulz *et al.* (1997). For related structures: see Schulz *et al.* (2005); Qu *et al.* (2008); Landis *et al.* (2008).

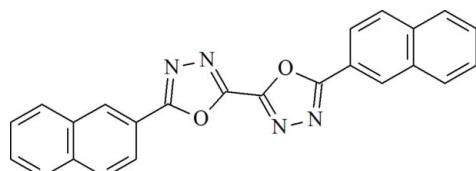

Experimental

Crystal data

$\text{C}_{24}\text{H}_{14}\text{N}_4\text{O}_2$
 $M_r = 390.39$
Monoclinic, $P2_1/c$
 $a = 7.8982(16)\text{ \AA}$
 $b = 5.7107(11)\text{ \AA}$
 $c = 21.503(5)\text{ \AA}$
 $\beta = 109.82(3)^\circ$

$V = 912.4(3)\text{ \AA}^3$
 $Z = 2$
Mo $K\alpha$ radiation
 $\mu = 0.09\text{ mm}^{-1}$
 $T = 293\text{ K}$
 $0.18 \times 0.14 \times 0.12\text{ mm}$

Data collection

Rigaku R-AXIS RAPID
diffractometer
Absorption correction: multi-scan
(ABSCOR; Higashi, 1995)
 $T_{\min} = 0.983$, $T_{\max} = 0.989$

8518 measured reflections
2091 independent reflections
1468 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.030$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.039$
 $wR(F^2) = 0.106$
 $S = 1.07$
2091 reflections

136 parameters
H-atom parameters constrained
 $\Delta\rho_{\max} = 0.16\text{ e \AA}^{-3}$
 $\Delta\rho_{\min} = -0.18\text{ e \AA}^{-3}$

Data collection: RAPID-AUTO (Rigaku, 1998); cell refinement: RAPID-AUTO; data reduction: RAPID-AUTO; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: PLATON (Spek, 2009) and CrystalStructure (Rigaku/MSC, 2002); software used to prepare material for publication: SHELXL97.

We would like to thank Mrs Ye Ling and Dr Li Bao of Jilin University for the crystal structure analysis. This work was supported by the National Science Foundation of China (50873044, 51073071, 51103057, and 21072076) and Jilin University (200903014).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: VM2137).

References

- Higashi, T. (1995). ABSCOR. Rigaku Corporation, Tokyo, Japan.
Landis, C. A., Dhar, B., Lee, T., Sarjeant, A. & Katz, E. (2008). *J. Phys. Chem. B*, **112**, 7939–7945.
Qu, S., Chen, X., Shao, X., Li, F., Zhang, H., Wang, H., Zhang, P., Yu, Z., Wu, K., Wang, Y. & Li, M. (2008). *J. Mater. Chem.* **18**, 3954–3964.
Rigaku (1998). RAPID-AUTO. Rigaku Corporation, Tokyo, Japan.
Rigaku/MSC (2002). CrystalStructure. Rigaku/MSC Inc., The Woodlands, Texas, USA.
Schulz, B., Bruma, M. & Brehmer, L. (1997). *Adv. Mater.* **9**, 601–613.
Schulz, B., Orgzall, I., Freydank, A. & Xu, C. (2005). *Adv. Colloid Interface Sci.* **116**, 143–164.
Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
Spek, A. L. (2009). *Acta Cryst. D* **65**, 148–155.

supplementary materials

Acta Cryst. (2011). E67, o3360 [doi:10.1107/S1600536811048513]

5,5'-Bis(naphthalen-2-yl)-2,2'-bi(1,3,4-oxadiazole)

H. Wang, X. Jia, S. Qu, B. Bai and M. Li

Comment

Aromatic heterocycles, such as 1,3,4-oxadiazole and thiophene rings, which are conjugatable to phenyl rings, are often directly connected to the phenyl ring to obtain a large π -conjugated system or to tune the electronic structure. These compounds are of interest as charge transport materials or emitting layers in electroluminescent diodes (Schulz *et al.*, 1997, Schulz *et al.*, 2005). Comparing to thiophene derivatives, 1,3,4-oxadiazole derivatives are more likely to form π -stacked molecular packing (Schulz *et al.*, 2005, Qu *et al.*, 2008, Landis *et al.*, 2008).

As shown in Fig. 1, both 1,3,4-oxadiazole rings are in a *trans*-conformation, which yields a linear molecular shape. These molecules are π -stacked along the crystallographic *a*-axis (Fig. 2). The molecules in the stacks are canted relative to the stacking axis by 26.57 (1) $^{\circ}$. Adjacent molecules are slipped off each other in both long and short molecular axis to avoid unfavorable electrostatic interactions in the "ideal" cofacial stacks (Fig. 3).

Experimental

The title compound was synthesized through a two-step reaction. Firstly, naphthylacetyl hydrazide was reacted with oxalyl chloride in THF at room temperature for 8 h, yielding the product, oxalyl acid *N,N'*-di-naphthylacetyl hydrazide. Secondly, the title compound was derived by intramolecular cyclization of this dihydrazide derivative with POCl_3 under reflux conditions, and the coarse product was further purified by washing with DMSO for the ${}^1\text{H}$ NMR FT—IR spectroscopic characterization and elemental analysis. Yield >70%. Crystals of the title compound suitable for X-ray diffraction were obtained by a slow diffusion method (diethyl ether was diffused into chloroform solution).

Refinement

Carbon-bound H-atoms were placed in calculated positions with C—H = 0.93 Å and were included in the refinement in the riding model with $U_{\text{iso}}(\text{H}) = 1.2 U_{\text{eq}}(\text{C})$.

Figures




Fig. 1. The molecular structure of the title compound with displacement ellipsoids drawn at the 50% probability level. The asymmetric unit only contains a half molecule, the second half is generated by symmetry code $-x, -y+1, -z+2$. The line through C8 and the molecular center is defined as the long molecular axis.




Fig. 2. Molecular packing as viewed down the crystallographic *a* axis.

supplementary materials




Fig. 3. Two adjacent molecules in the molecular stacks as viewed perpendicular to the molecular plane. The slip distances along the long molecular axis (S_1) and short axis (S_2) are 7.064 (1) Å and 1.159 (8) Å, respectively.

5,5'-Bis(naphthalen-2-yl)-2,2'-bi(1,3,4-oxadiazole)

Crystal data

$C_{24}H_{14}N_4O_2$	$Z = 2$
$M_r = 390.39$	$F(000) = 404$
Monoclinic, $P2_1/c$	$D_x = 1.421 \text{ Mg m}^{-3}$
Hall symbol: -P 2ybc	Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$
$a = 7.8982 (16) \text{ \AA}$	$\mu = 0.09 \text{ mm}^{-1}$
$b = 5.7107 (11) \text{ \AA}$	$T = 293 \text{ K}$
$c = 21.503 (5) \text{ \AA}$	Block, colourless
$\beta = 109.82 (3)^\circ$	$0.18 \times 0.14 \times 0.12 \text{ mm}$
$V = 912.4 (3) \text{ \AA}^3$	

Data collection

Rigaku R-AXIS RAPID diffractometer	2091 independent reflections
Radiation source: fine-focus sealed tube graphite	1468 reflections with $I > 2\sigma(I)$
ω scans	$R_{\text{int}} = 0.030$
Absorption correction: multi-scan (ABSCOR; Higashi, 1995)	$\theta_{\max} = 27.5^\circ, \theta_{\min} = 3.7^\circ$
$T_{\min} = 0.983, T_{\max} = 0.989$	$h = -10 \rightarrow 10$
8518 measured reflections	$k = -7 \rightarrow 7$
	$l = -27 \rightarrow 27$

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.039$	Hydrogen site location: inferred from neighbouring sites
$wR(F^2) = 0.106$	H-atom parameters constrained
$S = 1.07$	$w = 1/[\sigma^2(F_o^2) + (0.0577P)^2]$ where $P = (F_o^2 + 2F_c^2)/3$
2091 reflections	$(\Delta/\sigma)_{\max} = 0.001$
136 parameters	$\Delta\rho_{\max} = 0.16 \text{ e \AA}^{-3}$
0 restraints	$\Delta\rho_{\min} = -0.18 \text{ e \AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
O1	0.18040 (11)	0.40921 (16)	0.97102 (4)	0.0412 (2)
N1	0.01904 (14)	0.7350 (2)	0.94532 (6)	0.0482 (3)
N2	0.14392 (14)	0.7347 (2)	0.91193 (6)	0.0479 (3)
C1	0.04644 (15)	0.5425 (2)	0.97855 (6)	0.0407 (3)
C2	0.23461 (16)	0.5413 (2)	0.92839 (6)	0.0388 (3)
C3	0.38061 (15)	0.4564 (2)	0.90721 (6)	0.0373 (3)
C4	0.46713 (17)	0.2407 (2)	0.93102 (6)	0.0448 (3)
H4	0.4287	0.1499	0.9596	0.054*
C5	0.60641 (17)	0.1660 (2)	0.91221 (7)	0.0453 (3)
H5	0.6637	0.0256	0.9288	0.054*
C6	0.66520 (15)	0.2993 (2)	0.86777 (6)	0.0389 (3)
C7	0.80712 (17)	0.2254 (3)	0.84590 (7)	0.0506 (4)
H7	0.8681	0.0868	0.8621	0.061*
C8	0.85466 (18)	0.3556 (3)	0.80150 (8)	0.0586 (4)
H8	0.9466	0.3037	0.7870	0.070*
C9	0.76681 (19)	0.5674 (3)	0.77722 (8)	0.0565 (4)
H9	0.8008	0.6543	0.7468	0.068*
C10	0.63230 (17)	0.6463 (3)	0.79789 (6)	0.0459 (3)
H10	0.5763	0.7881	0.7821	0.055*
C11	0.57699 (15)	0.5144 (2)	0.84322 (6)	0.0364 (3)
C12	0.43475 (15)	0.5888 (2)	0.86414 (6)	0.0379 (3)
H12	0.3768	0.7297	0.8485	0.045*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
O1	0.0390 (4)	0.0454 (6)	0.0423 (5)	0.0017 (4)	0.0180 (4)	0.0038 (4)
N1	0.0447 (6)	0.0538 (7)	0.0506 (6)	0.0060 (5)	0.0222 (5)	0.0051 (6)
N2	0.0464 (6)	0.0498 (7)	0.0518 (6)	0.0059 (5)	0.0225 (5)	0.0066 (5)
C1	0.0343 (6)	0.0481 (8)	0.0402 (6)	0.0009 (5)	0.0133 (5)	-0.0021 (6)
C2	0.0392 (6)	0.0417 (7)	0.0358 (6)	-0.0030 (5)	0.0131 (5)	0.0017 (5)
C3	0.0363 (6)	0.0379 (7)	0.0371 (6)	-0.0013 (5)	0.0115 (5)	-0.0009 (5)

supplementary materials

C4	0.0512 (7)	0.0399 (7)	0.0453 (7)	0.0005 (6)	0.0190 (6)	0.0083 (6)
C5	0.0481 (7)	0.0357 (7)	0.0495 (7)	0.0050 (5)	0.0130 (6)	0.0036 (6)
C6	0.0366 (6)	0.0377 (7)	0.0403 (6)	0.0001 (5)	0.0103 (5)	-0.0054 (5)
C7	0.0433 (7)	0.0485 (9)	0.0588 (8)	0.0042 (6)	0.0156 (6)	-0.0084 (7)
C8	0.0438 (7)	0.0718 (11)	0.0680 (9)	-0.0010 (7)	0.0290 (7)	-0.0128 (8)
C9	0.0522 (8)	0.0680 (11)	0.0569 (8)	-0.0083 (7)	0.0285 (7)	0.0018 (8)
C10	0.0450 (7)	0.0465 (8)	0.0472 (7)	-0.0033 (6)	0.0168 (6)	0.0036 (6)
C11	0.0363 (6)	0.0366 (7)	0.0355 (6)	-0.0036 (5)	0.0110 (5)	-0.0029 (5)
C12	0.0395 (6)	0.0340 (7)	0.0391 (6)	0.0019 (5)	0.0118 (5)	0.0026 (5)

Geometric parameters (\AA , $^\circ$)

O1—C1	1.3568 (15)	C6—C7	1.4190 (17)
O1—C2	1.3636 (15)	C6—C11	1.4228 (18)
N1—C1	1.2889 (18)	C7—C8	1.360 (2)
N1—N2	1.4031 (16)	C7—H7	0.9300
N2—C2	1.2986 (17)	C8—C9	1.404 (2)
C1—C1 ⁱ	1.443 (3)	C8—H8	0.9300
C2—C3	1.4588 (17)	C9—C10	1.3600 (19)
C3—C12	1.3714 (17)	C9—H9	0.9300
C3—C4	1.4175 (18)	C10—C11	1.4130 (18)
C4—C5	1.3629 (19)	C10—H10	0.9300
C4—H4	0.9300	C11—C12	1.4098 (17)
C5—C6	1.4173 (19)	C12—H12	0.9300
C5—H5	0.9300		
C1—O1—C2	101.84 (10)	C7—C6—C11	118.45 (12)
C1—N1—N2	105.54 (11)	C8—C7—C6	120.48 (14)
C2—N2—N1	106.25 (11)	C8—C7—H7	119.8
N1—C1—O1	113.78 (11)	C6—C7—H7	119.8
N1—C1—C1 ⁱ	127.93 (15)	C7—C8—C9	120.87 (14)
O1—C1—C1 ⁱ	118.28 (15)	C7—C8—H8	119.6
N2—C2—O1	112.58 (11)	C9—C8—H8	119.6
N2—C2—C3	128.24 (12)	C10—C9—C8	120.39 (14)
O1—C2—C3	119.18 (12)	C10—C9—H9	119.8
C12—C3—C4	120.03 (11)	C8—C9—H9	119.8
C12—C3—C2	119.22 (12)	C9—C10—C11	120.50 (14)
C4—C3—C2	120.75 (12)	C9—C10—H10	119.8
C5—C4—C3	120.24 (12)	C11—C10—H10	119.8
C5—C4—H4	119.9	C12—C11—C10	121.71 (12)
C3—C4—H4	119.9	C12—C11—C6	119.00 (11)
C4—C5—C6	120.93 (13)	C10—C11—C6	119.29 (11)
C4—C5—H5	119.5	C3—C12—C11	120.93 (12)
C6—C5—H5	119.5	C3—C12—H12	119.5
C5—C6—C7	122.68 (13)	C11—C12—H12	119.5
C5—C6—C11	118.86 (11)		
C1—N1—N2—C2	0.01 (14)	C4—C5—C6—C11	0.41 (19)
N2—N1—C1—O1	0.15 (15)	C5—C6—C7—C8	177.78 (13)
N2—N1—C1—C1 ⁱ	179.92 (16)	C11—C6—C7—C8	-1.28 (19)

C2—O1—C1—N1	−0.23 (14)	C6—C7—C8—C9	1.1 (2)
C2—O1—C1—C1 ⁱ	179.97 (14)	C7—C8—C9—C10	0.1 (2)
N1—N2—C2—O1	−0.16 (14)	C8—C9—C10—C11	−1.1 (2)
N1—N2—C2—C3	−179.98 (12)	C9—C10—C11—C12	−178.28 (12)
C1—O1—C2—N2	0.24 (13)	C9—C10—C11—C6	0.84 (19)
C1—O1—C2—C3	−179.92 (11)	C5—C6—C11—C12	0.36 (17)
N2—C2—C3—C12	−0.4 (2)	C7—C6—C11—C12	179.46 (11)
O1—C2—C3—C12	179.76 (10)	C5—C6—C11—C10	−178.78 (11)
N2—C2—C3—C4	179.09 (12)	C7—C6—C11—C10	0.33 (17)
O1—C2—C3—C4	−0.72 (18)	C4—C3—C12—C11	−0.42 (18)
C12—C3—C4—C5	1.19 (19)	C2—C3—C12—C11	179.11 (11)
C2—C3—C4—C5	−178.33 (12)	C10—C11—C12—C3	178.77 (11)
C3—C4—C5—C6	−1.2 (2)	C6—C11—C12—C3	−0.35 (18)
C4—C5—C6—C7	−178.66 (12)		

Symmetry codes: (i) $-x, -y+1, -z+2$.

supplementary materials

Fig. 1


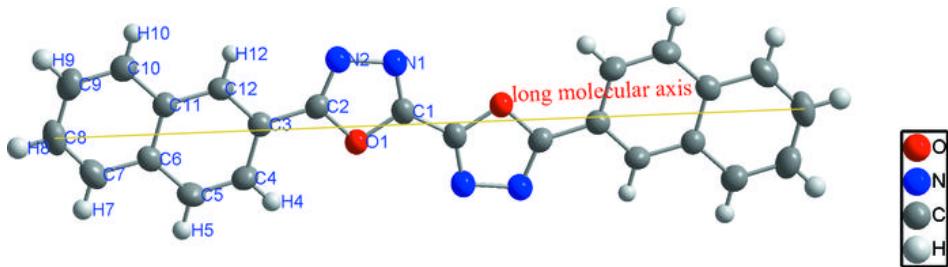


Fig. 2



supplementary materials

Fig. 3

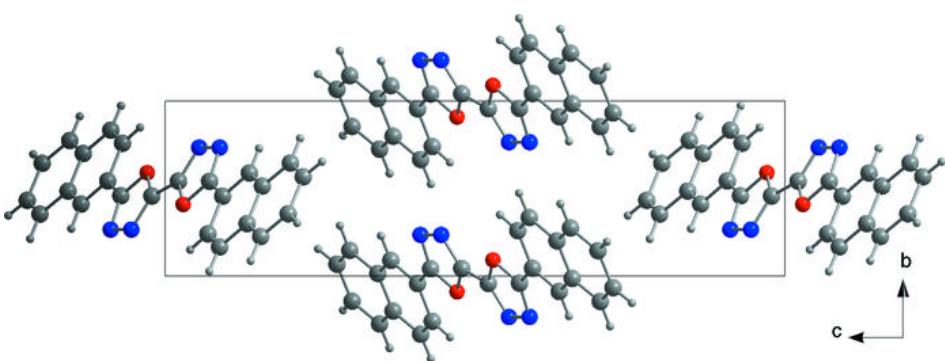