

Poly[diaquadi- μ -hydroxido- κ^4 O:O-dinitrato- κ^4 O:O'-bis[3-(pyridin-4-yl- κ N)-5-(pyridin-3-yl)-1,2,4-oxadiazole]-dicopper(II)]

Longfei Wu, Linxia Huang and Mouhai Shu*

School of Chemistry and Chemical Engineering, State Key Laboratory of Metal Matrix Composites, Shanghai Jiao Tong University, Shanghai 200240, People's Republic of China

Correspondence e-mail: mhshu@sjtu.edu.cn


Received 27 February 2012; accepted 8 March 2012

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(C-C) = 0.004$ Å; R factor = 0.048; wR factor = 0.139; data-to-parameter ratio = 13.0.

The title compound, $[Cu_2(NO_3)_2(OH)_2(C_{12}H_8N_4O)_2(H_2O)_2]_n$, consists of a neutral polymeric Cu^{II} complex in which each Cu^{II} atom has a distorted octahedral geometry defined by a pyridyl N atom from a 3-(pyridin-3-yl)-5-(pyridin-4-yl)-1,2,4-oxadiazole ligand and five O atoms from a water molecule, two nitrates and two hydroxides. Two Cu^{II} ions are bridged by two hydroxide anions resulting in a Cu₂O₂ loop, located across an inversion center and connected by the nitrate anions into a broad two-dimensional polymeric structure parallel to (100). In the crystal, there are O—H···O hydrogen bonds between the coordinated water molecule and the nitrate and hydroxide, and between the hydroxide and the nitrate. Intermolecular π — π interactions are present between pyridine rings in adjacent two-dimensional structures, with a centroid–centroid distance of 3.582 (2) Å.

Related literature

For the preparation of the ligand, see: Chiou & Shine (1989). For a related structure, see: Sarkar *et al.* (2008).

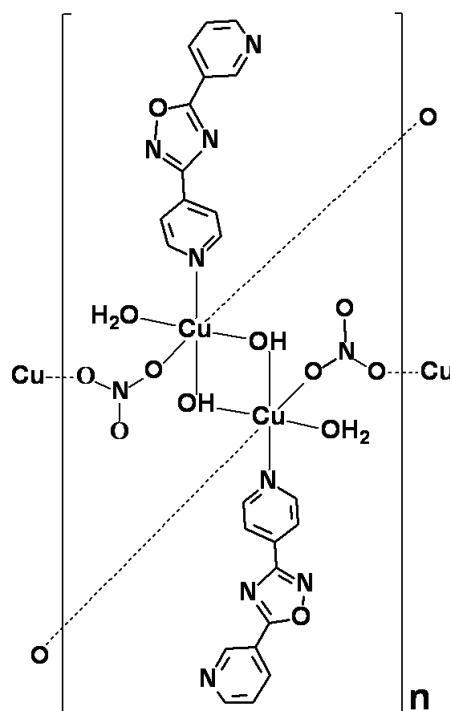

Experimental

Crystal data

$[Cu_2(NO_3)_2(OH)_2(C_{12}H_8N_4O)_2(H_2O)_2]$	$\beta = 105.572 (1)$ °
$M_r = 384.81$	$V = 1378.43 (15)$ Å ³
Monoclinic, $P2_1/c$	$Z = 4$
$a = 17.7718 (11)$ Å	Mo $K\alpha$ radiation
$b = 5.9088 (4)$ Å	$\mu = 1.63$ mm ⁻¹
$c = 13.6268 (8)$ Å	$T = 293$ K
	$0.51 \times 0.31 \times 0.08$ mm

Data collection

Bruker APEX CCD area-detector diffractometer	7672 measured reflections
Absorption correction: multi-scan (<i>SADABS</i> ; Bruker, 2000)	2976 independent reflections
$T_{\min} = 0.594$, $T_{\max} = 1.000$	2768 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.119$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.048$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.139$	$\Delta\rho_{\max} = 1.14$ e Å ⁻³
$S = 1.05$	$\Delta\rho_{\min} = -1.05$ e Å ⁻³
2976 reflections	
229 parameters	
3 restraints	

Table 1
Hydrogen-bond geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
O2—H6···O3 ⁱ	0.86 (2)	1.84 (2)	2.680 (2)	166 (2)
O2—H7···O5 ⁱⁱ	0.86 (3)	2.00 (3)	2.857 (3)	178 (5)
O2—H7···O6 ⁱⁱ	0.86 (3)	2.58 (3)	3.137 (3)	124 (2)
O3—H8···O5 ⁱⁱⁱ	0.86 (2)	2.22 (3)	2.987 (3)	150 (3)

Symmetry codes: (i) x , $y + 1$, z ; (ii) $-x + 1$, $y + \frac{1}{2}$, $-z + \frac{1}{2}$; (iii) $-x + 1$, $-y$, $-z$.

Data collection: *SMART* (Bruker, 2000); cell refinement: *SAINT* (Bruker, 2000); data reduction: *SAINT*; program(s) used to solve

structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *SHELXTL*; software used to prepare material for publication: *SHELXTL, publCIF* (Westrip, 2010) and *PLATON* (Spek, 2009).

The authors thank Professor D.-J. Xu, Zhejiang University, China, for his helpful suggestions.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BG2449).

References

- Bruker (2000). *SMART, SAINT* and *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
Chiou, S. & Shine, H. J. (1989). *J. Heterocycl. Chem.* **26**, 125–128.
Sarkar, B., Drew, M. G. B., Estrader, M., Diaz, C. & Ghosh, A. (2008). *Polyhedron*, **27**, 2625–2633.
Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.
Spek, A. L. (2009). *Acta Cryst. D* **65**, 148–155.
Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.

supplementary materials

Acta Cryst. (2012). E68, m422–m423 [doi:10.1107/S1600536812010355]

Poly[diaquadi- μ -hydroxido- κ^4 O:O-dinitrato- κ^4 O:O'-bis[3-(pyridin-4-yl)- κ N)-5-(pyridin-3-yl)-1,2,4-oxadiazole]dicopper(II)]

Longfei Wu, Linxia Huang and Mouhai Shu

Comment

The title compound, $[Cu_2(C_{12}H_8N_4O)_2(H_2O)_2(OH)_2(NO_3)_2]_n$, was obtained unintentionally during an attempted synthesis of infinite network complex of copper(II) with a rod-like nitrogen containing ligand, 3-(pyridin-3-yl)-5-(pyridin-4-yl)-1,2,4-oxadiazole (Chiou and Shine, 1989).

In the structure, each Cu^{II} ion has a distorted octahedral geometry defined by a pyridyl N atom from a 3-(pyridin-3-yl)-5-(pyridin-4-yl)-1,2,4-oxadiazole ligand and five O atoms from a water molecule, two nitrates, and two hydroxides (Fig. 1). For each Cu^{II} center, the equatorial sites are occupied by a water molecule, a pyridyl N atom, and two hydroxides, the apical sites being occupied by two oxygen atoms of nitrate anions. The equatorial bond distances are in the range 1.945 (2)–1.999 (2) Å while the axial bond distances are 2.431 (2) and 2.716 (2) Å. Neighbouring Cu^{II} ions are connected by two hydroxide anions into Cu₂O₂ loops with a Cu···Cu distance of 2.956 (1) Å. Similar Cu₂O₂ structure can be constructed by acetates (Sarkar *et al.* 2008). The result is the formation of centrosymmetric dimeric units, further connected by the nitrate anions to form broad two-dimensional structures parallel to (100).

In the crystal, there are O—H···O hydrogen bonds between the coordinated water molecule and the nitrate or hydroxide, and between the hydroxide and the nitrate. The details are listed in Table 1. There are also intermolecular π—π interactions between pyridine rings in neighboring two-dimensional structures, with a centroid—centroid distance of 3.582 (2) Å (Fig. 2).

Experimental


A solution of 3-(pyridin-3-yl)-5-(pyridin-4-yl)-1,2,4-oxadiazole (0.2 mmol) in methanol (10 ml) was layered carefully on the solution of Cu(NO₃)₂·3H₂O (0.2 mmol) in water (5 ml) in a straight test tube. The test tube was covered and kept in the refrigerator. Green crystals suitable for X-ray diffraction analysis were obtained after 2 weeks.

Refinement


H atoms bonded to O atoms were located in a difference map and refined with distance restraints of O—H = 0.86 (2) Å. Other H atoms were positioned geometrically and refined using a riding model with C—H = 0.93 (aromatic) and C—H = 0.96 (CH₃) Å. All H atoms were refined with $U_{\text{iso}}(\text{H}) = 1.2$ (1.5 for methyl groups) times $U_{\text{eq}}(\text{C})$.

Computing details

Data collection: SMART (Bruker, 2000); cell refinement: SAINT (Bruker, 2000); data reduction: SAINT (Bruker, 2000); program(s) used to solve structure: SHELXTL (Sheldrick, 2008); program(s) used to refine structure: SHELXTL (Sheldrick, 2008); molecular graphics: SHELXTL (Sheldrick, 2008); software used to prepare material for publication: SHELXTL (Sheldrick, 2008), publCIF (Westrip, 2010) and PLATON (Spek, 2009).

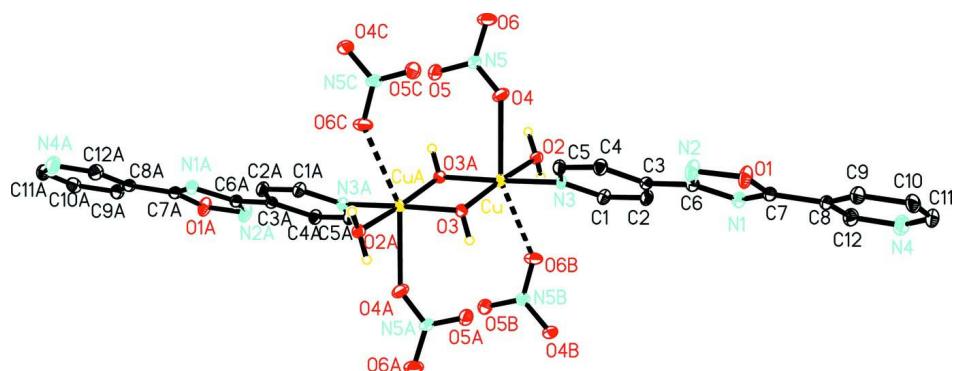**Figure 1**


The molecular structure of the title complex with atom labels and 30% probability displacement ellipsoids for non-H atoms. Hydrogen atoms bound to the carbon atoms were omitted for clarity. Symmetry codes A: 1-x,-y,-z; B: x,1/2-y,-1/2+z; C: 1-x,-1/2+y,1/2-z.

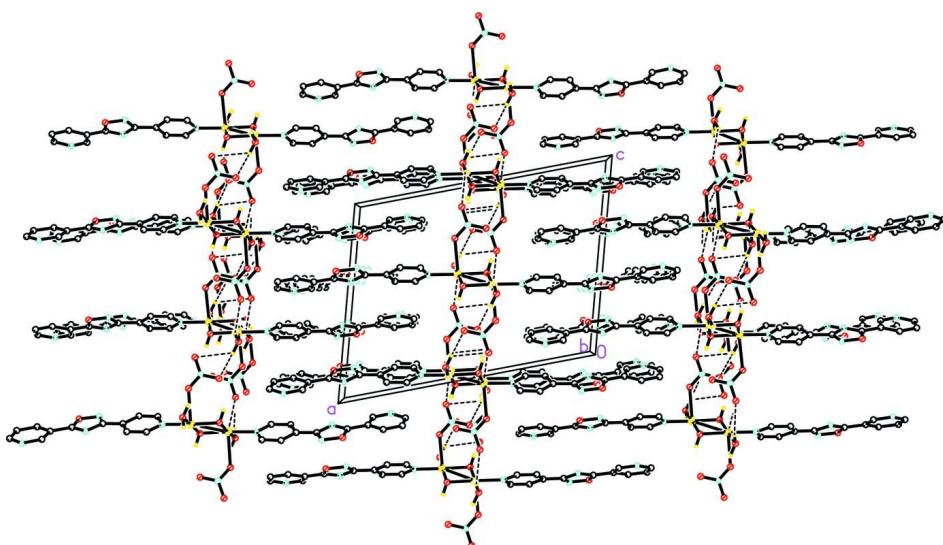**Figure 2**

Packing view of the complex down the a axis, showing the two-dimensional structures in projection. O—H···O hydrogen bonds are shown in dashed lines. Note interdigitation of the aromatic groups in neighbouring two-dimensional structures, leading to π — π interactions.

Poly[diaquadi- μ -hydroxido- κ^4 O:O-dinitrato- κ^4 O:O'-bis[3-(pyridin-4-yl- κ N)-5-(pyridin-3-yl)-1,2,4-oxadiazole]dicopper(II)]

Crystal data



$$M_r = 384.81$$

Monoclinic, $P2_1/c$

Hall symbol: -P 2ybc

$$a = 17.7718 (11) \text{ \AA}$$

$$b = 5.9088 (4) \text{ \AA}$$

$$c = 13.6268 (8) \text{ \AA}$$

$$\beta = 105.572 (1)^\circ$$

$$V = 1378.43 (15) \text{ \AA}^3$$

$$Z = 4$$

$$F(000) = 780$$

$$D_x = 1.854 \text{ Mg m}^{-3}$$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 5190 reflections

$$\theta = 4.8\text{--}56.4^\circ$$

$$\mu = 1.63 \text{ mm}^{-1}$$

$T = 293\text{ K}$

Block, blue

*Data collection*Bruker APEX CCD area-detector
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

phi and ω scansAbsorption correction: multi-scan
(*SADABS*; Bruker, 2000) $T_{\min} = 0.594$, $T_{\max} = 1.000$ $0.51 \times 0.31 \times 0.08\text{ mm}$

7672 measured reflections

2976 independent reflections

2768 reflections with $I > 2\sigma(I)$ $R_{\text{int}} = 0.119$ $\theta_{\max} = 27.0^\circ$, $\theta_{\min} = 1.2^\circ$ $h = -17 \rightarrow 22$ $k = -7 \rightarrow 7$ $l = -17 \rightarrow 17$ *Refinement*Refinement on F^2

Least-squares matrix: full

 $R[F^2 > 2\sigma(F^2)] = 0.048$ $wR(F^2) = 0.139$ $S = 1.05$

2976 reflections

229 parameters

3 restraints

Primary atom site location: structure-invariant
direct methodsSecondary atom site location: difference Fourier
mapHydrogen site location: inferred from
neighbouring sitesH atoms treated by a mixture of independent
and constrained refinement $w = 1/[\sigma^2(F_o^2) + (0.089P)^2]$ where $P = (F_o^2 + 2F_c^2)/3$ $(\Delta/\sigma)_{\max} = 0.001$ $\Delta\rho_{\max} = 1.14\text{ e \AA}^{-3}$ $\Delta\rho_{\min} = -1.05\text{ e \AA}^{-3}$ Extinction correction: *SHELXTL* (Sheldrick,
2008), $F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$

Extinction coefficient: 0.0143 (18)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Cu	0.568231 (15)	0.14812 (5)	0.04093 (2)	0.02002 (18)
O1	1.03390 (11)	-0.2157 (4)	0.16936 (16)	0.0378 (5)
O2	0.58494 (10)	0.4687 (3)	0.08870 (12)	0.0228 (4)
O3	0.54446 (11)	-0.1523 (3)	-0.02081 (14)	0.0211 (4)
O4	0.59173 (11)	0.0905 (4)	0.22324 (14)	0.0351 (4)
O5	0.47452 (11)	0.0938 (4)	0.24387 (14)	0.0327 (4)
O6	0.57569 (13)	0.1084 (4)	0.37477 (14)	0.0433 (5)
N1	0.98046 (13)	0.1098 (4)	0.10703 (16)	0.0270 (5)
N2	0.95355 (13)	-0.2348 (5)	0.1616 (2)	0.0391 (6)
N3	0.68350 (13)	0.1057 (4)	0.06699 (16)	0.0219 (4)
N4	1.20685 (16)	0.3615 (4)	0.1113 (2)	0.0412 (6)
N5	0.54702 (13)	0.0982 (4)	0.28059 (16)	0.0268 (5)
C1	0.73297 (14)	0.2588 (4)	0.04712 (19)	0.0262 (5)
H1B	0.7129	0.3968	0.0190	0.031*
C2	0.81232 (15)	0.2217 (5)	0.06637 (19)	0.0274 (5)
H2C	0.8449	0.3335	0.0528	0.033*
C3	0.84262 (14)	0.0141 (4)	0.10637 (17)	0.0229 (5)

C4	0.79131 (16)	-0.1452 (4)	0.1275 (2)	0.0278 (6)
H4B	0.8097	-0.2849	0.1551	0.033*
C5	0.71365 (14)	-0.0937 (5)	0.10707 (19)	0.0260 (5)
H5A	0.6800	-0.2015	0.1215	0.031*
C6	0.92614 (14)	-0.0393 (4)	0.12543 (18)	0.0246 (5)
C7	1.04446 (14)	-0.0069 (4)	0.13676 (18)	0.0255 (5)
C8	1.12382 (14)	0.0631 (5)	0.13945 (18)	0.0252 (5)
C9	1.18772 (15)	-0.0806 (5)	0.1720 (2)	0.0304 (5)
H9A	1.1814	-0.2285	0.1918	0.036*
C10	1.26094 (16)	0.0024 (5)	0.1741 (2)	0.0355 (6)
H10A	1.3049	-0.0888	0.1957	0.043*
C11	1.26778 (16)	0.2211 (6)	0.1440 (2)	0.0377 (7)
H11A	1.3174	0.2750	0.1464	0.045*
C12	1.13696 (16)	0.2822 (5)	0.1103 (2)	0.0334 (6)
H12A	1.0942	0.3783	0.0889	0.040*
H7	0.5678 (18)	0.504 (6)	0.1398 (16)	0.045 (9)*
H8	0.5559 (17)	-0.160 (4)	-0.0774 (13)	0.024 (5)*
H6	0.5725 (15)	0.576 (4)	0.0449 (17)	0.024 (5)*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cu	0.0140 (2)	0.0237 (3)	0.0225 (2)	-0.00041 (9)	0.00511 (15)	-0.00202 (9)
O1	0.0176 (9)	0.0423 (11)	0.0543 (12)	0.0047 (8)	0.0112 (8)	0.0142 (10)
O2	0.0233 (8)	0.0238 (9)	0.0227 (8)	-0.0004 (7)	0.0087 (7)	-0.0011 (7)
O3	0.0163 (9)	0.0265 (10)	0.0214 (8)	0.0014 (6)	0.0066 (7)	-0.0020 (6)
O4	0.0307 (10)	0.0526 (11)	0.0257 (9)	0.0025 (9)	0.0141 (8)	0.0074 (9)
O5	0.0248 (10)	0.0409 (11)	0.0336 (10)	-0.0020 (8)	0.0098 (7)	0.0022 (8)
O6	0.0442 (12)	0.0669 (14)	0.0187 (9)	0.0024 (10)	0.0083 (8)	0.0033 (9)
N1	0.0185 (10)	0.0351 (11)	0.0282 (11)	0.0013 (9)	0.0077 (8)	0.0006 (9)
N2	0.0186 (11)	0.0451 (15)	0.0544 (15)	0.0036 (11)	0.0114 (10)	0.0152 (12)
N3	0.0151 (10)	0.0285 (10)	0.0223 (10)	0.0001 (8)	0.0051 (8)	-0.0007 (8)
N4	0.0341 (15)	0.0455 (16)	0.0456 (15)	-0.0060 (10)	0.0133 (11)	0.0039 (11)
N5	0.0292 (12)	0.0311 (10)	0.0223 (10)	-0.0024 (10)	0.0106 (8)	0.0038 (9)
C1	0.0225 (13)	0.0269 (12)	0.0309 (12)	0.0006 (10)	0.0102 (9)	0.0037 (10)
C2	0.0212 (12)	0.0317 (13)	0.0309 (12)	-0.0018 (11)	0.0098 (10)	0.0028 (11)
C3	0.0185 (11)	0.0316 (12)	0.0190 (10)	-0.0007 (9)	0.0057 (8)	-0.0005 (9)
C4	0.0216 (14)	0.0303 (14)	0.0307 (13)	0.0007 (9)	0.0053 (10)	0.0072 (9)
C5	0.0197 (12)	0.0289 (12)	0.0287 (12)	-0.0025 (10)	0.0053 (9)	0.0048 (10)
C6	0.0185 (11)	0.0340 (14)	0.0218 (11)	0.0004 (10)	0.0062 (9)	-0.0002 (9)
C7	0.0189 (11)	0.0360 (13)	0.0217 (10)	0.0028 (10)	0.0058 (9)	-0.0004 (10)
C8	0.0174 (11)	0.0363 (14)	0.0226 (11)	0.0019 (10)	0.0065 (8)	-0.0019 (10)
C9	0.0231 (13)	0.0359 (14)	0.0328 (13)	0.0025 (11)	0.0086 (10)	-0.0006 (11)
C10	0.0186 (12)	0.0509 (17)	0.0354 (13)	0.0047 (12)	0.0046 (10)	-0.0072 (13)
C11	0.0220 (13)	0.0542 (18)	0.0387 (15)	-0.0071 (13)	0.0110 (11)	-0.0059 (14)
C12	0.0247 (13)	0.0404 (15)	0.0351 (13)	0.0035 (12)	0.0082 (10)	0.0034 (12)

Geometric parameters (\AA , ^\circ)

Cu—O3 ⁱ	1.9474 (19)	N4—C11	1.342 (4)
Cu—O3	1.9613 (16)	C1—C2	1.381 (3)
Cu—N3	1.999 (2)	C1—H1B	0.9300
Cu—O2	1.9992 (17)	C2—C3	1.390 (4)
Cu—O4	2.4301 (18)	C2—H2C	0.9300
Cu—Cu ⁱ	2.9559 (5)	C3—C4	1.393 (4)
O1—C7	1.341 (3)	C3—C6	1.471 (3)
O1—N2	1.408 (3)	C4—C5	1.367 (4)
O2—H7	0.856 (10)	C4—H4B	0.9300
O2—H6	0.859 (10)	C5—H5A	0.9300
O3—H8	0.849 (10)	C7—C8	1.461 (3)
O4—N5	1.256 (3)	C8—C12	1.392 (4)
O5—N5	1.251 (3)	C8—C9	1.392 (4)
O6—N5	1.249 (3)	C9—C10	1.384 (4)
N1—C7	1.299 (3)	C9—H9A	0.9300
N1—C6	1.379 (3)	C10—C11	1.371 (4)
N2—C6	1.298 (4)	C10—H10A	0.9300
N3—C1	1.339 (3)	C11—H11A	0.9300
N3—C5	1.348 (3)	C12—H12A	0.9300
N4—C12	1.324 (4)		
O3 ⁱ —Cu—O3	81.73 (7)	C2—C1—H1B	118.4
O3 ⁱ —Cu—N3	173.18 (8)	C1—C2—C3	118.9 (2)
O3—Cu—N3	93.16 (8)	C1—C2—H2C	120.6
O3 ⁱ —Cu—O2	95.23 (7)	C3—C2—H2C	120.6
O3—Cu—O2	173.40 (7)	C2—C3—C4	118.1 (2)
N3—Cu—O2	90.31 (8)	C2—C3—C6	121.7 (2)
O3 ⁱ —Cu—O4	91.93 (7)	C4—C3—C6	120.3 (2)
O3—Cu—O4	105.65 (8)	C5—C4—C3	119.3 (2)
N3—Cu—O4	85.07 (7)	C5—C4—H4B	120.4
O2—Cu—O4	80.23 (7)	C3—C4—H4B	120.4
O3 ⁱ —Cu—Cu ⁱ	41.04 (5)	N3—C5—C4	123.1 (2)
O3—Cu—Cu ⁱ	40.69 (6)	N3—C5—H5A	118.4
N3—Cu—Cu ⁱ	133.69 (6)	C4—C5—H5A	118.4
O2—Cu—Cu ⁱ	135.98 (5)	N2—C6—N1	115.3 (2)
O4—Cu—Cu ⁱ	101.61 (5)	N2—C6—C3	121.1 (2)
C7—O1—N2	106.1 (2)	N1—C6—C3	123.6 (2)
Cu—O2—H7	116 (2)	N1—C7—O1	113.8 (2)
Cu—O2—H6	119 (2)	N1—C7—C8	128.0 (2)
H7—O2—H6	108 (3)	O1—C7—C8	118.2 (2)
Cu ⁱ —O3—Cu	98.27 (7)	C12—C8—C9	118.3 (2)
Cu ⁱ —O3—H8	111 (2)	C12—C8—C7	119.4 (2)
Cu—O3—H8	111.2 (17)	C9—C8—C7	122.3 (2)
N5—O4—Cu	131.85 (16)	C10—C9—C8	118.2 (3)
C7—N1—C6	101.6 (2)	C10—C9—H9A	120.9
C6—N2—O1	103.1 (2)	C8—C9—H9A	120.9
C1—N3—C5	117.5 (2)	C11—C10—C9	119.1 (3)
C1—N3—Cu	125.22 (18)	C11—C10—H10A	120.4

C5—N3—Cu	117.30 (17)	C9—C10—H10A	120.4
C12—N4—C11	117.1 (3)	N4—C11—C10	123.6 (3)
O6—N5—O5	120.3 (2)	N4—C11—H11A	118.2
O6—N5—O4	119.3 (2)	C10—C11—H11A	118.2
O5—N5—O4	120.4 (2)	N4—C12—C8	123.7 (3)
N3—C1—C2	123.1 (2)	N4—C12—H12A	118.1
N3—C1—H1B	118.4	C8—C12—H12A	118.1
O3 ⁱ —Cu—O3—Cu ⁱ	0.0	Cu—N3—C5—C4	179.3 (2)
N3—Cu—O3—Cu ⁱ	175.46 (7)	C3—C4—C5—N3	0.0 (4)
O4—Cu—O3—Cu ⁱ	89.69 (8)	O1—N2—C6—N1	0.6 (3)
O3 ⁱ —Cu—O4—N5	−9.7 (2)	O1—N2—C6—C3	−179.3 (2)
O3—Cu—O4—N5	−91.7 (3)	C7—N1—C6—N2	−1.3 (3)
N3—Cu—O4—N5	176.4 (3)	C7—N1—C6—C3	178.6 (2)
O2—Cu—O4—N5	85.3 (2)	C2—C3—C6—N2	−179.1 (3)
Cu ⁱ —Cu—O4—N5	−49.9 (2)	C4—C3—C6—N2	0.3 (4)
C7—O1—N2—C6	0.3 (3)	C2—C3—C6—N1	1.0 (4)
O2—Cu—N3—C1	−40.0 (2)	C4—C3—C6—N1	−179.6 (2)
O4—Cu—N3—C1	−120.2 (2)	C6—N1—C7—O1	1.5 (3)
Cu ⁱ —Cu—N3—C1	138.47 (18)	C6—N1—C7—C8	−177.8 (2)
O3—Cu—N3—C5	−45.1 (2)	N2—O1—C7—N1	−1.2 (3)
O2—Cu—N3—C5	140.52 (18)	N2—O1—C7—C8	178.1 (2)
O4—Cu—N3—C5	60.36 (18)	N1—C7—C8—C12	2.0 (4)
Cu ⁱ —Cu—N3—C5	−41.0 (2)	O1—C7—C8—C12	−177.2 (2)
Cu—O4—N5—O6	−165.23 (19)	N1—C7—C8—C9	−179.1 (3)
Cu—O4—N5—O5	15.4 (4)	O1—C7—C8—C9	1.7 (4)
C5—N3—C1—C2	−0.4 (4)	C12—C8—C9—C10	0.3 (4)
Cu—N3—C1—C2	−179.92 (19)	C7—C8—C9—C10	−178.5 (2)
N3—C1—C2—C3	1.4 (4)	C8—C9—C10—C11	−0.2 (4)
C1—C2—C3—C4	−1.5 (4)	C12—N4—C11—C10	1.2 (4)
C1—C2—C3—C6	177.9 (2)	C9—C10—C11—N4	−0.5 (4)
C2—C3—C4—C5	0.9 (4)	C11—N4—C12—C8	−1.1 (4)
C6—C3—C4—C5	−178.6 (2)	C9—C8—C12—N4	0.3 (4)
C1—N3—C5—C4	−0.3 (4)	C7—C8—C12—N4	179.2 (3)

Symmetry code: (i) $-x+1, -y, -z$.

Hydrogen-bond geometry (\AA , $^\circ$)

D—H···A	D—H	H···A	D···A	D—H···A
O2—H6···O3 ⁱⁱ	0.86 (2)	1.84 (2)	2.680 (2)	166 (2)
O2—H7···O5 ⁱⁱⁱ	0.86 (3)	2.00 (3)	2.857 (3)	178 (5)
O2—H7···O6 ⁱⁱⁱ	0.86 (3)	2.58 (3)	3.137 (3)	124 (2)
O3—H8···O5 ⁱ	0.86 (2)	2.22 (3)	2.987 (3)	150 (3)

Symmetry codes: (i) $-x+1, -y, -z$; (ii) $x, y+1, z$; (iii) $-x+1, y+1/2, -z+1/2$.