High Turnover Numbers for the Catalytic Selective Epoxidation of Alkenes with 1 atm of Molecular Oxygen**

Yoshiyuki Nishiyama, Yoshinao Nakagawa, and Noritaka Mizuno*

Catalytic epoxidation of alkenes has attracted much attention both in industrial processes and in organic syntheses, because epoxides are among the most useful synthetic intermediates. Epoxidation of alkenes can be carried out by various techniques with various oxidants. However, stoichiometric (noncatalytic) epoxidation is still widely used, and large amounts of byproducts, particularly salts, are formed. For example, propylene oxide has been produced commercially by alkaline dehydrochlorination of propylene chlorohydrin with formation of large amounts of metal salts.^[1–3] The utilization of molecular oxygen for a catalytic epoxidation without reducing reagents or radical initiators is a rewarding goal, because molecular oxygen has the highest content of active oxygen, and no byproducts are formed from it, in contrast to various other oxidants.[4-13] However, only a few ideal homogeneous epoxidations of alkenes with molecular oxygen at 1 atm without reducing reagents or radical initiators have been achieved, because organic ligands of the catalysts are degraded or the catalysts act as stoichiometric oxidants.

Therefore, a high catalyst turnover number (TON) is a key. The catalytic activity of polyoxometalates has attracted much attention, because their acidic and redox properties can be controlled at the atomic or molecular level. The strong acidity and oxidizing power of polyoxometalates have led to many studies on homogeneous and heterogeneous catalysis. [13–16] The additional attractive and technologically significant



Figure 1. Polyhedral representation of γ -SiW₁₀{Fe³⁺(OH₂)}₂O₃₈⁶⁻ (1). The two iron atoms are represented by shaded octahedra. The WO₆ moieties occupy the white octahedra, and an SiO₄ group is shown as the internal black tetrahedron.

aspect of polyoxometalates in catalysis is their inherent stability towards oxygen donors.[17-19] We used the Keggin-type diironsubstituted silicotungstate 1 (Figure 1) as a catalyst precursor for the selective epoxidation of alkenes with molecular oxygen at 1 atm and found that this epoxidation can be catalyzed with high TONs. The catalyst is thus able to use molecular oxygen as an oxidant, and raises the prospect of using this type of inorganic catalyst for industrial epoxidation processes.

[*] Prof. Dr. N. Mizuno, Y. Nishiyama, Y. Nakagawa Department of Applied Chemistry, School of Engineering The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656 (Japan)

Fax: (+81) 3-5841-7220

E-mail: tmizuno@mail.ecc.u-tokyo.ac.jp

[**] We acknowledge T. Hayashi (The University of Tokyo), M. Wada (Nippon Shokubai Co., Ltd.), and Y. Sumita (Nippon Shokubai Co., Ltd.) for their help with experiments. This work was supported in part by a Grant-in-Aid for Scientific Research from the Ministry of Education, Science, Sports and Culture of Japan. Figure 2 shows the time course of the oxygenation of cyclooctene with 1 atm of molecular oxygen catalyzed by **1** at 356 K. The average carbon balance for six runs was (100 ± 8)%. Cyclooctene oxide was selectively produced together

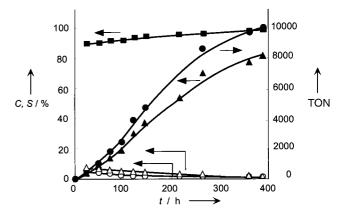


Figure 2. Oxygenation of cyclooctene with molecular oxygen catalyzed by 1 at 356 K. \triangle , conversion of cyclooctene; \bullet , TON; \blacksquare , selectivity for cyclooctene oxide; \bigcirc , selectivity for 2-cycloocten-1-one. Catalyst, 1.5 μ mol; solvent, 1,2-dichloroethane/acetonitrile 1.5/0.1 mL; substrate, 18.5 mmol; $p_{O_2} = 1$ atm. C = conversion, S = selectivity.

with small amounts of 2-cycloocten-1-ol and 2-cycloocten-1-one. After 385 h, the conversion and selectivity for cyclooctene oxide reached 82 and 98 %, respectively, and the TON was 10 000. The value is more than 100 times higher than those so far reported for the epoxidation of cyclooctene with 1 atm of molecular oxygen alone. $^{[20]}$

Oxygenation of various alkenes with 1 atm of molecular oxygen was carried out in the presence of 1 at 356 K. Similarly to the oxygenation of cyclooctene, longer reaction periods increased the TON for each alkene. The results are summarized in Table 1. The main products were the corresponding

Table 1. Oxygenation of various alkenes with molecular oxygen catalyzed by ${\bf 1}$ at 356 K.[a]

Substrate	TON	C[%]	Products	S [%]
cyclododecene	9600	74	cyclododecene oxide	64 ^[b]
			2-cyclododecen-1-ol	31
			2-cyclododecen-1-one	5
cyclooctene	10000	82	cyclooctene oxide	98
			2-cycloocten-1-ol	1
			2-cycloocten-1-one	1
1-octene	2200	17	1,2-octene oxide	93
			1-octen-3-ol	5
			1-octen-3-one	2
2-octene ($cis/trans = 8/2$)	2500	20	2,3-octene oxide	94
			2-octen-4-ol	5
			2-octen-4-one	1
2-heptene (cis/trans = 8/2)	2900	24	2,3-heptene oxide	91
			2-hepten-4-ol	8
			2-hepten-4-one	1
2-hexene ($cis/trans = 4/6$)	1300	11	2,3-hexene oxide	79
			2-hexen-4-ol	19
			2-hexen-4-one	2

[a] Reaction conditions: catalyst, 1.5 μ mol; solvent, 1,2-dichloroethane/acetonitrile, 1.5/0.1 mL; substrate, 18.5 mmol; $p_{O_2}=1$ atm; reaction time, 385 h. The substrate/O₂ ratio in the gas phase may lie within the explosion limit. [b] Includes the selectivity for 1,2-cyclododecanediol (6%).

epoxides in all oxygenation reactions. This fact and the obtained TONs show that 1 can efficiently catalyze the epoxidation of various kinds of alkenes.

Keggin-type polyoxometalates show characteristic UV/Vis bands, and therefore their structures have often been characterized by UV/Vis spectroscopy. The UV/Vis spectrum of asprepared **1** showed bands at 275 ($\varepsilon = 22600$), 334 (10000), and 470 nm (68 m⁻¹ cm⁻¹), and after being used for the oxygenation of cyclooctene 1 showed the original absorption bands with almost the same intensities. The IR bands of the original skeletal vibration of 1 changed only slightly (see below). Magnetic susceptibility measurements and recording of Mössbauer and $^{183}\mbox{W}$ NMR spectra on the reaction solution to investigate the structure of 1 were thwarted by insufficient sensitivity at the low concentration (0.38 mm). After 1 (0.15 m) was treated with 1 atm of molecular oxygen in [D₃]acetonitrile for 96 h at 356 K, the ¹⁸³W NMR spectrum showed two broad signals at $\delta = -1330$ and -1840 with an integral ratio of 2:1, characteristic of the C_{2v} symmetry of the original γ -Keggin structure. This indicates that the two iron atoms occupy the same positions as shown in Figure 1 under the reaction conditions and that the structure of 1 is retained during the reaction. In addition, the fact that 1 is even stable in the presence of hydrogen peroxide, [21] as demonstrated by 183W NMR spectrocopy, supports this conclusion.

The oxygenation of cyclooctene was not inhibited by the presence of 1-3 equiv (relative to 1) of alkyl-radical scavengers such as p-tert-butylcatechol. For example, the conversion and selectivity for cyclooctene oxide after 96 h in the presence of 1 equiv of *p-tert*-butylcatechol were 20 and 92%, respectively. These values are in good agreement with those of 18 and 92%, respectively, in the absence of the radical scavenger. For epoxidation of trans- and cis-2-octenes, the trans/cis-oxide ratios were 10 and 0.2, respectively, that is, the reaction was rather stereospecific. Similarly, epoxidation of cis-2-hexene proceeded rather stereospecifically. In contrast, epoxidation via a radical intermediate proceeds nonstereospecifically. In fact, addition of a radical initiator, N-hydroxyphthalimide, mainly produced trans-2-octene oxide (trans/ cis = 4) in the epoxidation of cis-2-octene. In addition, epoxidations of cis-2-octene and cis-2-hexene were faster than those of the corresponding trans-2-alkenes, as has been observed for epoxidation catalyzed by oxo iron porphyrins, which proceeds differently from epoxidation via a radical pathway.[22]

The kinetic studies showed zero-order dependence of reaction rates on the concentration of cyclooctene ([cyclooctene]), and first-order dependence on the concentration of 1 ([1]) and the partial pressure of molecular oxygen (p_{O_2}) . These results indicate that the rate of decrease in [cyclooctene] is expressed by $-d[cyclooctene]/dt = k[1]p_{O_2}[cyclooctene]^0$. Moreover, a maximum rate was obtained for $p_{O_2} = 1 - 2$ atm. The oxygenation of adamantane showed that the ratio of tertiary/secondary C-H bond selectivity on a per bond basis was 11. Under free-radical conditions, the value is normally three, that is, different from that in the present system. All these results demonstrate that nonradical processes prevail to a major degree in the present system, $[2^{4}]$ although some contribution of free radicals is still a possibility.

Figure 3 shows IR spectra of **1** after oxygenation of cyclooctene with ${}^{16}O_2$ and ${}^{18}O_2$ at 356 K. As-prepared **1** shows bands at 960 [v(W=O_{terminal})], 902, 884 [v(SiO)], 800 (v(W-O-W) for corner-sharing octahedra), and 753 cm⁻¹ (v(W-O-W)




Figure 3. IR spectra of **1** after oxygenation of cyclooctene with $^{16}O_2$ (a) and $^{18}O_2$ (b and dotted line in a) for 96 h at 356 K. The spectra were measured by quickly evaporating the reaction solution, washing the resulting solid with diethyl ether, drying and then pressing it into a KBr pellet. A = absorbance.

for edge-sharing octahedra). After 1 being used for the oxygenation of cyclooctene with 16O2, a new band was observed at 832 cm⁻¹ (Figure 3a). It is reported that Fe=O bands appear in the range of 810-860 cm^{-1,[22]} After oxygenation with ¹⁸O₂ a new band was observed at 776 cm⁻¹ (Figure 3b). The shift of 56 cm⁻¹ is in fair agreement with the expected shift of 48 cm⁻¹. The band disappeared after the reaction with cyclooctene under Ar, and cyclooctene oxide (1.9 equiv) was formed; this shows that the iron-oxygen species is reactive. The amount of $H_2^{18}O$ produced was $2 \times$ 10⁻⁴ mol, close to that of 2-cycloocten-1-one, and much less than that of cyclooctene oxide. In addition, the amount of cyclooctene oxide produced was about two times larger than the amount of O2 consumed.[25] The above results show that the epoxidation proceeds without co-formation of water, and an intermediate iron – oxygen species is formed.

In conclusion, we have demonstrated that 1 efficiently catalyzes the epoxidation of alkenes with molecular oxygen alone, a green route to epoxides. Detailed investigations on the reaction mechanism are in progress.

Experimental Section

The catalyst precursor 1 was synthesized as its tetrabutylammonium salt by the reported procedure: [26] A solution of $K_8[\gamma-SiW_{10}O_{36}]\cdot 12H_2O$ (3.0 g, 1.0 mmol) in deionized water (30 mL) was quickly adjusted to pH 3.90 with concentrated nitric acid. Then, an aqueous solution of Fe(NO₃)₃·9H₂O (0.82 g, 2.0 mmol) in water (5 mL) was added. The color of the solution turned to pale yellow. After the solution had been stirred for 5 min, the addition of an excess of tetra-n-butylammonium nitrate (3.1 g, 10 mmol) resulted in a yellow-white precipitate. The precipitate was collected by filtration and purified by twice dissolving it in acetonitrile (15 mL) and adding water (300 mL) to reprecipitate the product. The yield of the purified compound was about 1.5 g (50%). The polyoxometalate γ -SiW₁₀{Fe³⁺(OH₂)}₂O₃₈⁶⁻ (1) has a γ -Keggin structure with C_{2v} symmetry, and the two iron centers occupy adjacent, edge-shared octahedra, as shown in Figure 1. UV/Vis, Mössbauer, EPR, and magnetic susceptibility data show that two high-spin Fe³⁺ centers are equivalent and antiferromagnetically coupled.[26]

Alkenes were distilled and treated with activated alumina to remove impurities and alkyl hydroperoxide. The reaction was carried out in a glass vial or a round-bottomed flask containing a magnetic stir bar under 1 atm of molecular oxygen as described previously. [21] 2-Cyclohexen-1-one was usually used as an internal standard. The homogeneous reaction solution was periodically sampled and analyzed by gas chromatography on a TC-WAX capillary column and by NMR spectroscopy. The amounts of oxygen consumed were measured with a gas burette. It was confirmed for the oxygenation of cyclooctene that no reaction proceeded without catalysts. Turnover numbers were calculated as moles of products per mole of 1.

Received: May 17, 2001 [Z17132]

- R. A. Sheldon, J. K. Kochi, Metal-Catalyzed Oxidations of Organic Compounds, Academic Press, New York, 1981.
- [2] Chlorohydrins: W. F. Richey, Kirk Othmer Encyclopedia of Chemical Technology, Vol. 6, Wiley, New York, 1993, pp. 140.
- [3] The Activation of Dioxygen and Homogeneous Catalytic Oxidation (Eds.: D. H. R. Barton, A. E. Martell, D. T. Sawyer), Plenum, New York, 1993.
- [4] B. J. Wallar, J. D. Lipscomb, Chem. Rev. 1996, 96, 2625.
- [5] B. Meunier, Chem. Rev. 1992, 92, 1411.
- [6] J. T. Groves, R. Quinn, J. Am. Chem. Soc. 1985, 107, 5790.
- [7] A. S. Goldstein, R. H. Beer, R. S. Drago, J. Am. Chem. Soc. 1994, 116, 2424
- [8] R. Neumann, M. A. Dahan, Nature 1997, 388, 353.
- [9] C. L. Hill, I. A. Weinstock, Nature 1997, 388, 332.
- [10] J. M. Thomas, R. Raja, G. Sanker, R. G. Bell, Nature 1999, 398, 227.
- [11] R. G. Finke, H. Weiner, J. Am. Chem. Soc. 1999, 121, 9831.
- [12] R. A. Sheldon, Top. Curr. Chem. 1993, 164, 22.
- [13] C. L. Hill, C. M. Prosser-McCartha, Coord. Chem. Rev. 1995, 143, 407.
- [14] T. Okuhara, N. Mizuno, M. Misono, Adv. Catal. 1996, 41, 113.
- [15] I. V. Kozhevnikov, Chem. Rev. 1998, 98, 171.
- [16] N. Mizuno, M. Misono, Chem. Rev. 1998, 98, 199.
- [17] C. L. Hill, Activation and Functionalization of Alkanes, Wiley, New York, 1989, p. 243.
- [18] M. T. Pope, A. Müller, Angew. Chem. 1991, 103, 56; Angew. Chem. Int. Ed. Engl. 1991, 30, 34.
- [19] R. Neumann, Prog. Inorg. Chem. 1998, 47, 317.
- [20] The TON of 26 reported in ref. [6] is still one of the highest for the epoxidation of *cis*-cyclooctene with 1 atm of molecular oxygen alone.
- [21] N. Mizuno, C. Nozaki, I. Kiyoto, M. Misono, J. Am. Chem. Soc. 1998, 120, 9267.
- [22] B. Meunier, A. Robert, G. Pratviel, J. Bernadou, *The Porphyrin Handbook*, Academic Press, New York, 2000, p. 119.
- [23] The oxygenation of adamantane was carried out under the following conditions: 1, 11 μ mol; solvent, 1,2-dichloroethane/benzene = 8 mL/2 mL; adamantane, 12.4 mmol; p_{O_2} , 1 atm; reaction temperature, 356 K; reaction time, 118 h. The conversion was 4% and the selectivities for 1-adamantanol, 2-adamantanol, and 2-adamantanone were 79, 11, and 10%, respectively.
- [24] R. A. Sheldon, J. K. Kochi, Oxidation and Combustion Reviews, Vol. 5, 1973, p. 135; R. Neumann, M. Dahan, J. Am. Chem. Soc. 1998, 120, 11969.
- [25] The amount of oxygen consumed was 1.5 mmol when the amount of cyclooctene oxide produced was 2.9 mmol. The corresponding conversion was 16%.
- [26] C. Nozaki, I. Kiyoto, Y. Minai, M. Misono, N. Mizuno, *Inorg. Chem.* 1999, 38, 5724.

Cleavage of the C_{alkyl}-C_{aryl} Bond of [Pd-CH₂CMe₂Ph] Complexes**

Juan Cámpora,* Enrique Gutiérrez-Puebla, Jorge A. López, Angeles Monge, Pilar Palma,* Diego del Río, and Ernesto Carmona*

The cleavage and functionalization of strong C–C single bonds^[1] by transition metal compounds is an important transformation, ^[2-6] which is relevant to Ziegler–Natta catalysis^[7] and to other organometallic processes.^[8, 9] Aryl elimination by activation of a β -C_{alkyl}–C_{aryl} bond^[5] is the microscopic reverse of the migratory insertion of an alkene into a M–C_{aryl} bond, a relevant step of the Heck reaction^[8] and of the SHOP process.^[9] Herein we report on the conversion of a [Pd–CH₂CMe₂Ph]⁺ moiety into the corresponding phenyl derivative, [Pd–Ph]⁺, and the subsequent functionalization of the latter by conventional C₂H₄ migratory insertion chemistry to produce C₆H₅CH=CH₂.

The cationic complex $[Pd(CH_2CMe_2Ph)(dmpe)(PMe_3)]^+$ (1) $(dmpe = Me_2PCH_2CH_2PMe_2)$ can be generated by reacting the palladacycle $[PdCH_2CMe_2-o-C_6H_4)(dmpe)]$ (2) $^{[10]}$ with $[HPMe_3]^+$ $BAr_4^ (Ar = 3,5-C_6H_3(CF_3)_2)$. At 60° C it under-

[*] Dr. J. Cámpora, Dr. P. Palma, Prof. Dr. E. Carmona, Dr. J. A. López, D. del Río

Departamento de Química Inorgánica-Instituto

de Investigaciones Químicas

Universidad de Sevilla-Consejo Superior de Investigaciones Científicas

C/Americo Vespucio s/n, Isla de la Cartuja

41092 Sevilla (Spain)

Fax: (+34) 95-4460565

E-mail: campora@cica.es

ppalma@cica.es

guzman@cica.es

Dr. E. Gutiérrez-Puebla, Dr. A. Monge

Instituto de Ciencia de Materiales

Consejo Superior de Investigaciones Científicas Campus de Cantoblanco, 28049 Madrid (Spain)

- [**] This work was supported by the Dirección General de Enseñanza Superior e Investigación Científica (Project 1FD97-0919), the Ministerio de Educación y Ciencia (PFPI grant to D. del Rio), and the Junta de Andalucia. J. A. L. thanks the CONACYT and the University of Guanajuato (Mexico) for a fellowship.
- Supporting information (kinetic data and reaction rates for the transformation 1→3 calyzed by 4) for this article is available on the WWW under http://www.angewandte.com or from the author.