


[2+1] Cycloaddition of Nitrene onto C₆₀ Revisited: Interconversion between an Aziridinofullerene and an Azafulleroid**

Tsukasa Nakahodo, Mitsunori Okada, Hiroyuki Morita, Toshiaki Yoshimura, Midori O. Ishitsuka, Takahiro Tsuchiya, Yutaka Maeda, Hisashi Fujihara, Takeshi Akasaka,* Xingfa Gao, and Shigeru Nagase*

It is known that organic azides react with a [6,6] bond of C₆₀ through a 1,3-dipolar [3+2] cycloaddition to afford triazolines.^[1] Thermolysis of a triazoline, followed by concomitant loss of nitrogen, gives rise to a [1,6]azafulleroid **1** and a [1,2]aziridinofullerene **2** (Scheme 1).^[2] Both **1** and **2** can also be obtained directly from the reaction of C₆₀ and azides at higher temperatures, but the ratio of **1**:**2** depends on the

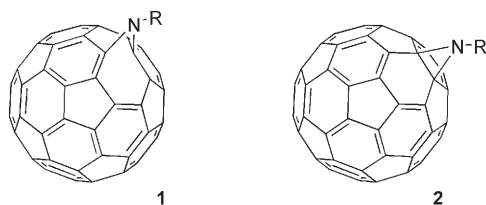


Scheme 1. Structures of **1** and **2**.

nature of the substituent.^[3] Furthermore, azides have major associated problems in regards to toxicity and explosibility.^[4] Thus, new useful methods for the preparation of azafulleroids and aziridinofullerenes are expected.

Sulfilimines^[5] are known to generate an *N*-substituted nitrene in thermal and photochemical reactions. Recently, it has been reported that *N*-sulfonylsulfilimine generates a sulfonylnitrene under mild conditions. Nitrenes readily react with alkenes to afford the corresponding three-membered aziridines.^[6] In this context, a nitrene is expected to be a key intermediate, instead of an azide, in the aziridination of fullerene.

In the course of our study on the development of synthetic methodology for the preparation of [1,2]aziridinofullerene,^[2] we carried out the photoreaction of C₆₀ with an *N*-*p*-toluenesulfonylsulfilimine^[7] having a dibenzothiophene structure (**3**; Scheme 2) to accomplish the regioselective

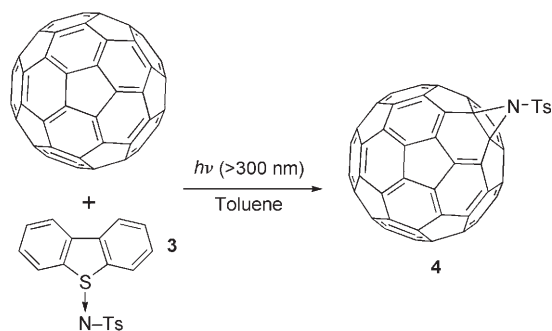

Scheme 2. Photoreaction of C₆₀ with *N*-tosylsulfilimine **3**. Ts = tosyl = *p*-toluenesulfonyl.

synthesis of *N*-tosyl[1,2]aziridinofullerene ([6,6]-closed C₆₀NTs, **4**). It is well known that 1,6-azafulleroids **1** readily cyclize thermally and photochemically to afford [1,2]aziridinofullerenes **2**, while the reverse reaction hardly occurs.^[8] This finding may indicate that **2** is more thermally stable than **1**. We examined the stability of the newly synthesized **4** and found that it thermally rearranges to a [1,6]azafulleroid ([5,6]-open C₆₀NTs, **5**) and that the photochemical reversible reaction also takes place.^[9] Here we report for the first time the reversible interconversion between **1** and **2**. The structures of both adducts were successfully determined by single-crystal X-ray analyses.

[*] M. Okada, Dr. M. O. Ishitsuka, Dr. T. Tsuchiya, Prof. Dr. T. Akasaka
Center for Tsukuba Advanced Research Alliance
University of Tsukuba, Tsukuba, Ibaraki 305-8577 (Japan)
Fax: (+81) 29-853-6409
E-mail: akasaka@tara.tsukuba.ac.jp
Homepage: <http://www.tara.tsukuba.ac.jp/~akasaka-lab/>

Dr. X. Gao, Prof. Dr. S. Nagase
Department of Theoretical Molecular Science
Institute for Molecular Science, Okazaki, Aichi 444-8585 (Japan)
Fax: (+81) 56-453-4660
E-mail: nagase@ims.ac.jp

Dr. T. Nakahodo, Prof. Dr. H. Fujihara
Department of Applied Chemistry
Kinki University, Kowakae, Higashi-Osaka, Osaka 577-8502 (Japan)

Dr. Y. Maeda
Department of Chemistry
Tokyo Gakugei University, Koganei, Tokyo 184-8501 (Japan)

Prof. Dr. H. Morita, Prof. Dr. T. Yoshimura
Department of Applied Chemistry
Graduate School of Science and Engineering
University of Toyama, Gofuku, Toyama 930-8555 (Japan)

[**] We thank Dr. H. Sawa for his experimental help at the Photon Factory. We also thank T. Wakahara for interesting discussions. This work was supported in part by a Grant-in-Aid and the 21st Century COE Program, Nanotechnology Support Project, The Next Generation Super Computing Project (Nanoscience Project), and Scientific Research on Priority Area from the Ministry of Education, Culture, Sports, Science, and Technology of Japan.

Supporting information for this article is available on the WWW under <http://www.angewandte.org> or from the author.

The photoreaction of C_{60} with one equivalent of sulfilimine **3** afforded the corresponding monoadduct (C_{60} NTs, **4**) as a major product with 80% conversion. The absorption band at 430 nm in the UV/Vis spectrum of **4** is indicative of the formation of a 1,2-addition product of C_{60} (Figure 1).^[10]


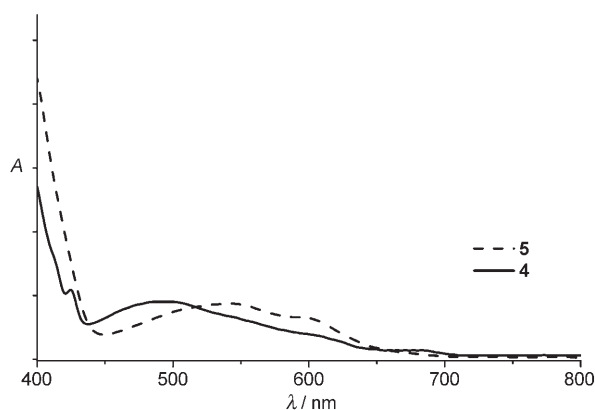


Figure 1. UV/Vis spectra of aziridinofullerene **4** and azafulleroid **5**.

To examine the thermal stability of the monoadduct, a solution of **4** in *o*-dichlorobenzene (ODCB) was heated at 180 °C for 10 hours (Scheme 3). HPLC analysis of the reaction

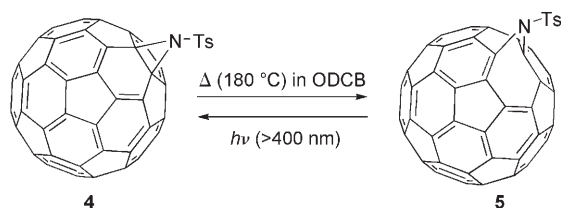

Scheme 3. Interconversion between **4** and **5**.

mixture showed that the peak intensity of **4** decreased while that of a new peak increased in size. The MALDI-TOF mass spectrum of the product exhibited a molecular ion signal at m/z 889. A band at 430 nm, which is characteristic of a 1,2-addition product,^[10] did not appear in its UV/Vis spectrum. These data reveal that **5** may be a regioisomer of **4** which has an open structure.^[3] It was found that the isomerization of **4** occurs in good yield upon heating. A reverse isomerization of **5** to **4** was also observed photochemically (see the Supporting Information).

Although a [5,6]-open azafulleroid **1** has been shown to isomerize readily to a [6,6]-closed type aziridinofullerene **2**,^[11] the single-crystal X-ray analysis of **1** had not been reported. We have succeeded in the structural determination of both [6,6]-closed aziridinofullerene **4** and [5,6]-open azafulleroid **5** by single-crystal X-ray analysis (Figure 2).^[12,13] The dihedral angles of the *N*-tosyl ligand on C_{60} ($\phi(N-S-C_{ipso} = C_{ortho})$) in **4** and **5** are 95.6° and 104.0°, respectively, for the aryl sulfonamide conformations.^[14]

To clarify the reversible rearrangement, the relative stabilities and HOMO/LUMO energies of **4** and **5** were

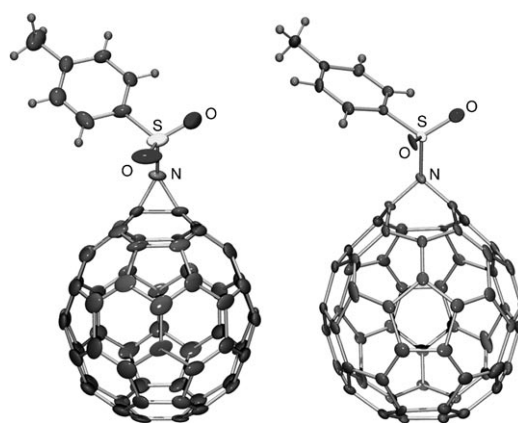


Figure 2. X-ray crystal structures of **4** (left) and **5** (right) with thermal ellipsoids at the 50% probability level; only one orientation is shown and CS_2 is omitted for clarity.

calculated at the B3LYP/6-31G(d,p) level.^[15] Azafulleroid **5** has two geometric isomers (**5a** and **5b**) with different conformations of the *N*-tosyl group (see the Supporting Information for the optimized structures of **5a** and **5b**). Both **5a** and **5b** are slightly more stable than **4** (Table 1). These

Table 1: Relative energies ($kcal\ mol^{-1}$) and HOMO/LUMO energies (eV) of **4** and **5**.

Isomers	Relative energies	HOMO	LUMO	HOMO/LUMO gap
[6,6]-closed 4	0.00	−5.82	−3.21	2.61
[5,6]-open 5a	−0.04	−6.01	−3.32	2.69
[5,6]-open 5b	−0.75	−5.93	−3.21	2.72

results are consistent with the fact that **4** thermally rearranges to **5**. This situation is different from the known thermal isomerization of **1** to **2**. This unusual phenomenon may originate from the introduction of a tosylated amine bridge.

In conclusion, it has been shown that the addition of a nitrene generated by the photochemical reaction of sulfilimine **3** occurs at the [6,6] junction of C_{60} to afford the [1,2]aziridinofullerene **4**. It is found that **4** thermally rearranges to the [1,6]azafulleroid **5**, and is the first example for a monosubstituted fullerene.^[16] Moreover, photochemical ring-closure of **5** also takes place to afford **4**. The structures of **4** and **5** have been characterized by NMR spectroscopy and X-ray crystallographic analyses.^[17]

Experimental Section

General: Toluene was distilled over benzophenone sodium ketyl under argon prior to use in the reactions. ODCB was distilled over P_2O_5 under vacuum prior to use. CS_2 was distilled over P_2O_5 under argon prior to use. HPLC isolation was performed on a LC-908 system (Japan Analytical Industry Co., Ltd.). Toluene was used as the eluent. Mass spectrometric analysis was performed on a Bruker BIFLEX III spectrometer in the negative mode with 1,1,4,4-tetraphenylbutadiene used as the matrix. The UV/Vis spectra were measured between 400 and 800 nm in toluene solution on a

SHIMADZU UV-3150 spectrophotometer. NMR spectra were obtained on a Bruker AVANCE 500 spectrometer. The ^1H and ^{13}C shifts were calibrated with tetramethylsilane (TMS) as an internal reference ($\delta = 0.0$).

3: A solution of dibenzothiophene (2.0 g, 10.73 mol), chloramine-T (4.53 g, 16.10 mol), and MgSO_4 (1.93 g, 16.10 mol) in acetonitrile (20 mL) was stirred at 50°C for 18 h. The reaction mixture was then cooled to room temperature and the MgSO_4 removed by filtration. The filtrate was extracted with CHCl_3 (20 mL $\times$ 3), and the organic layer then dried over MgSO_4 and evaporated under reduced pressure. The resulting solid was recrystallized from MeOH to give **3** (1.42 g, 38%) as a colorless solid. ^1H NMR (300 MHz, CDCl_3 , 293 K): $\delta = 2.44$ (s, 3H), 7.26 (d, $J = 8.3$ Hz, 2H), 7.44–7.47 (m, 2H), 7.63–7.67 (m, 4H), 7.83 (d, $J = 8.4$ Hz, 2H), 7.87 ppm (d, $J = 8.3$ Hz, 2H); ^{13}C NMR (75 MHz; CDCl_3 , 293 K): $\delta = 21.7$, 122.7, 126.9, 127.8, 129.6, 130.3, 133.2, 137.5, 137.7, 141.5, 142.2 ppm; m.p. 171.5–173.0 $^\circ\text{C}$; MALDI-TOF MS: m/z 353 $[M]^+$; UV/Vis: λ_{max} (ϵ) 320 (1313) nm.

Photoreaction of C_{60} with **3** (Scheme 2): A solution of C_{60} (15.0 mg, 2.8×10^{-3} M) and sulfilimine **3** (7.4 mg, 2.8×10^{-3} M) in toluene was placed in a pyrex tube and degassed by freeze-thaw cycles under reduced pressure before irradiating with a high-pressure mercury lamp (> 300 nm) at 20°C for 30 min. The reaction mixture was analyzed by HPLC as follows: column, Buckyprep $\phi 4.6 \times 250$ mm; eluent, toluene; flow rate, 1.0 mL min^{-1} ; temperature, 40°C ; detector, UV 320 nm. **4:** ^1H NMR (300 MHz, $[\text{D}_6]$ acetone in a capillary/ CS_2 , 293 K): $\delta = 1.95$ (s, 3H), 6.81 (d, $J = 8.3$, 2H), 7.44 ppm (d, $J = 8.3$, 2H); ^{13}C NMR (125 MHz; $[\text{D}_6]$ acetone in a capillary/ CS_2 , 293 K): $\delta = 22.47$, 80.10, 128.98, 130.35, 136.43, 141.18, 141.61, 142.14, 142.47, 143.05, 143.36, 143.42, 143.69, 144.18, 144.28, 144.46, 144.76, 145.21, 145.29, 145.37, 145.39, 145.54 ppm; MALDI-TOF MS: m/z 889 $[M]^+$, 734 $[M-(\text{tosyl})]^+$, 720 $[M-(N\text{-tosyl})]^+$.

Interconversion between **4** and **5**: Thermal rearrangement: A solution of **4** (4.2×10^{-4} M) in $[\text{D}_4]$ ODCB was degassed by freeze-thaw cycles under reduced pressure and then heated at 180°C in the dark for 10 h. Photochemical rearrangement: The solution was heated for 5 h and then photoirradiated with a halogen lamp fitted with a filter (cut-off < 400 nm) at 20°C for 15 min. These reactions were monitored by ^1H NMR spectroscopy (500 MHz, $[\text{D}_4]$ ODCB, 293 K) and HPLC as follows: column, Buckyprep $\phi 4.6 \times 250$ mm; eluent, toluene; flow rate, 1.0 mL min^{-1} ; temperature, 25°C ; detector, UV 400 nm. **5:** ^1H NMR (300 MHz, $[\text{D}_6]$ acetone in a capillary/ CS_2 , 293 K): $\delta = 1.82$ (s, 3H), 6.65 (d, $J = 8.3$, 2H), 7.24 ppm (d, $J = 8.3$, 2H); ^{13}C NMR (125 MHz; $[\text{D}_6]$ acetone in a capillary/ CS_2 , 293 K): $\delta = 22.35$, 129.27, 130.08, 134.54, 135.12, 136.06, 136.52, 138.15, 138.23, 138.62, 138.87, 139.97, 140.31, 141.98, 143.01, 143.04, 143.29, 143.51, 143.72, 143.92, 143.97, 144.08, 144.23, 144.27, 144.36, 144.44, 144.53, 144.65, 144.98, 147.69, 148.54 ppm; MALDI-TOF MS: m/z 889 $[M]^+$.

Recrystallization of **4** and **5**: Black crystals of **4** and **5** were obtained by slow evaporation of CS_2 at 0°C .

Received: September 25, 2007

Published online: January 8, 2008

Keywords: azafulleroids · fullerenes · photochemistry · rearrangement · structural determination

- [1] a) T. Grösser, M. Prato, V. Lucchini, A. Hirsch, F. Wudl, *Angew. Chem.* **1995**, 107, 1462–1464; *Angew. Chem. Int. Ed. Engl.* **1995**, 34, 1343–1345; b) B. Nuber, F. Hampel, A. Hirsch, *Chem. Commun.* **1996**, 1799–1800; c) J. Zhou, A. Rieker, T. Groesser, A. Skiebe, A. Hirsch, *J. Chem. Soc. Perkin Trans. 2* **1997**, 1–5; d) A. Yashiro, Y. Nishida, M. Ohno, S. Eguchi, K. Kobayashi, *Tetrahedron Lett.* **1998**, 39, 9031–9034; e) G. Schick, T. Jarrosson, Y. Rubin, *Angew. Chem.* **1999**, 111, 2508–2512; *Angew. Chem. Int. Ed.* **1999**, 38, 2360–2363.

- [2] J. Averdung, J. Mattay, *Tetrahedron* **1996**, 52, 5407–5420.
 [3] L. Ulmer, J. Mattay, *Eur. J. Org. Chem.* **2003**, 2933–2940.
 [4] M. Prato, Q. C. Li, F. Wudl, V. Lucchini, *J. Am. Chem. Soc.* **1993**, 115, 1148–1150.
 [5] a) N. Furukawa, M. Fukumura, T. Nishio, S. Oae, *J. Chem. Soc. Perkin Trans. 1* **1977**, 96–98; b) Y. Hayashi, D. Swern, *J. Am. Chem. Soc.* **1973**, 95, 5205–5210.
 [6] T. Yoshimura, T. Fujie, T. Fujii, *Tetrahedron Lett.* **2007**, 48, 427–430.
 [7] Y. Shiraishi, T. Naito, T. Hirai, I. Komasa, *Chem. Commun.* **2001**, 1256–1257.
 [8] P. P. Kanakamma, S.-L. Huang, C.-G. Juo, G.-R. Her, T.-Y. Luh, *Chem. Eur. J.* **1998**, 4, 2037–2042.
 [9] A. Ouchi, R. Hatsuda, B. Z. S. Awen, M. Sakuragi, R. Ogura, T. Ishii, Y. Araki, O. Ito, *J. Am. Chem. Soc.* **2002**, 124, 13364–13365.
 [10] A. Hirsch, T. Groesser, A. Skiebe, A. Soi, *Chem. Ber.* **1993**, 126, 1061–1067.
 [11] J. Averdung, J. Mattay, *Tetrahedron* **1996**, 52, 5407–5420.
 [12] The X-ray diffraction data collection of [5,6]-open azafulleroid **5** was performed on beamline BL-1B at the Photon Factory, KEK, Japan.
 [13] a) Crystal data for **4**· CS_2 : $\text{C}_{136.53}\text{H}_{14}\text{N}_2\text{O}_4\text{S}_{7.06}$, $M_r = 1972.33$, black needles, $0.50 \times 0.14 \times 0.06$ mm, triclinic, space group $P\bar{1}$ (no. 2), $a = 18.572(2)$, $b = 21.376(2)$, $c = 10.0431(13)$ Å, $\alpha = 92.632(3)$, $\beta = 105.614(3)$, $\gamma = 94.808(2)^\circ$, $V = 3816.7(8)$ Å 3 , $Z = 2$; $\rho_{\text{calcd}} = 1.716$ g cm^{-3} , $\mu(\text{MoK}\alpha) = 2.88$ cm $^{-1}$, $\theta_{\text{max}} = 20.82^\circ$, $T = 120$ K, 12 109 measured reflections, 5858 independent reflections, 1367 refined parameters, GOF = 1.128, $R_1 = 0.0906$ and $wR_2 = 0.2020$ for all data; $R_1 = 0.0905$ for 5850 independent reflections ($I > 2.0\sigma(I)$), min./max. electron density 0.89/−0.63 e Å $^{-3}$; b) crystal data for **5**· CS_2 : $\text{C}_{68}\text{H}_7\text{NO}_2\text{S}_3$, $M_r = 965.99$, black plates, $0.20 \times 0.15 \times 0.10$ mm, orthorhombic, space group $Pnma$ (no. 62), $a = 18.2815(6)$, $b = 13.6431(5)$, $c = 14.5987(5)$ Å, $V = 3641.2(2)$ Å 3 , $Z = 4$; $\rho_{\text{calcd}} = 1.762$ g cm^{-3} , wavelength = 0.68880 Å, $\mu = 2.71$ cm $^{-1}$, $\theta_{\text{max}} = 35.71^\circ$, $T = 123$ K, 30 606 measured reflections, 6656 independent reflections, 641 refined parameters, GOF = 1.186, $R_1 = 0.0954$ and $wR_2 = 0.1700$ for all data; $R_1 = 0.0791$ for 5738 independent reflections ($I > 2.0\sigma(I)$), min./max. electron density 1.05/−0.86 e Å $^{-3}$; c) CCDC 665365 (**4**) and 665366 (**5**) contain the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif
 [14] a) V. Petrov, V. Petrova, G. V. Girichev, H. Oberhammer, N. I. Giricheva, S. Ivanov, *J. Org. Chem.* **2006**, 71, 2952–2956; b) F. Hof, A. Schütz, C. Fähr, S. Meyer, D. Bur, J. Liu, D. E. Goldberg, F. Diederich, *Angew. Chem.* **2006**, 118, 2193–2196; *Angew. Chem. Int. Ed. Engl.* **2006**, 45, 2138–2141.
 [15] Geometries were optimized with hybrid density functional theory at the B3LYP/6-31G(d,p) level using the Gaussian 03 program. For B3LYP, see a) A. D. Becke, *Phys. Rev. A* **1988**, 38, 3098–3100; b) A. D. Becke, *J. Chem. Phys.* **1993**, 98, 5648–5652; c) C. Lee, W. Yang, R. G. Parr, *Phys. Rev. B* **1988**, 37, 785–789; for 6-31G(d,p), see d) W. J. Hehre, R. Ditchfield, J. A. Pople, *J. Chem. Phys.* **1972**, 56, 2257–2261; e) P. C. Hariharan, J. A. Pople, *Theoret. Chim. Acta* **1973**, 28, 213–222.
 [16] I. P. Romanova, G. G. Yusupova, O. A. Larionova, A. A. Balandina, Sh. K. Latypov, V. V. Zverev, D. G. Yakhvarov, G. L. Rusinov, O. G. Sinyashin, *Russ. Chem. Bull. Int. Ed.* **2006**, 55, 502–506.
 [17] When this study was presented at the annual meeting of the Japan Chemical Society, in April, 2007, H. Hachiya and Y. Kabe informed us that they were also able for the first time to characterize a [5,6]-monoazafulleroid by X-ray crystallographic analysis.