

Supported Catalysts

International Edition: DOI: 10.1002/anie.201510678
German Edition: DOI: 10.1002/ange.201510678

Cationic Silica-Supported N-Heterocyclic Carbene Tungsten Oxo Alkylidene Sites: Highly Active and Stable Catalysts for Olefin Metathesis

Margherita Pucino, Victor Mougél, Roman Schowner, Alexey Fedorov, Michael R. Buchmeiser,* and Christophe Copéret*

Abstract: Designing supported alkene metathesis catalysts with high activity and stability is still a challenge, despite significant advances in the last years. Described herein is the combination of strong σ -donating N-heterocyclic carbene ligands with weak σ -donating surface silanulates and cationic tungsten sites leading to highly active and stable alkene metathesis catalysts. These well-defined silica-supported catalysts, $[(\equiv\text{SiO})\text{W}(=\text{O})(=\text{CHCMe}_2\text{Ph})(\text{IMes})(\text{OTf})]$ and $[(\equiv\text{SiO})\text{W}(=\text{O})(=\text{CHCMe}_2\text{Ph})(\text{IMes})^+][\text{B}(\text{Ar}^F)_4^-]$ [$\text{IMes} = 1,3\text{-bis}(2,4,6\text{-trimethylphenyl})\text{-imidazol-2-ylidene}$, $\text{B}(\text{Ar}^F)_4 = \text{B}(3,5\text{-(CF}_3)_2\text{C}_6\text{H}_3)_4$] catalyze alkene metathesis, and the cationic species display unprecedented activity for a broad range of substrates, especially for terminal olefins with turnover numbers above 1.2 million for propene.

In recent years, tremendous advances in the design of alkene and alkyne metathesis catalysts have been made for both homogeneous and heterogeneous systems.^[1–3] In particular, the development of highly active tungsten oxo alkylidene molecular catalysts^[4] and the adaption of N-heterocyclic carbene (NHC) ligands, widely used in ruthenium-based alkene metathesis catalysts,^[5] to molybdenum and tungsten systems^[6] have significantly widened the range of applications of d^0 -metal-based olefin metathesis catalysts.

For heterogeneous catalysts, major advances have been possible through surface organometallic chemistry,^[3,7] which enables the generation of well-defined active sites at the surface of oxide supports.^[8] This approach identified the electronic dissymmetry at the metal center as a key factor for greatly improved activity of silica-supported Schrock alkylidene complexes.^[9] DFT calculations^[10] have revealed that this increase in activity is due to the easier coordination of the olefin substrate to the metal-alkylidene sites and the destabilization of metallacyclobutane intermediates because of the presence of both weak and strong σ -donor ligands, that is, one

surface siloxy and either one alkyl or amide ligand, respectively. This conclusion has inspired the synthesis of catalysts with enhanced dissymmetry at the metal site.^[1c,11] One of the most recent and compelling examples is the use of poor σ -donor surface silanulates^[12] with strong σ -donating thiolate ligands in silica-supported tungsten oxo alkylidene catalysts,^[4e,15] which display substantially enhanced activity towards terminal olefins.

The recent report of highly active and stable tungsten oxo alkylidenes supported by an NHC^[6c] as a strong σ -donor ligand thus opens new avenues to significantly improve the activity of silica-supported metathesis catalysts by combining cationic intermediates and a strong σ -donating NHC ligand with a weak σ -donating surface silanolate. Herein we report the synthesis and characterization of silica-supported neutral and cationic tungsten oxo alkylidene complexes bearing an NHC ligand and show the unprecedented activity and stability of the supported cationic olefin metathesis catalyst.


Grafting $\text{W}(=\text{O})(=\text{CHCMe}_2\text{Ph})(\text{IMes})(\text{OTf})(\text{OtBu}_{\text{F}_6})$ ^[13] (**1**) and the related cationic species $[\text{W}(=\text{O})(=\text{CHCMe}_2\text{Ph})(\text{IMes})(\text{OtBu}_{\text{F}_6})^+][\text{B}(\text{Ar}^F)_4^-]$ (**2**) onto SiO_{2-700} afforded the corresponding materials **1**@ SiO_2 and **2**@ SiO_2 , respectively (Scheme 1). Quantification by solution NMR spectroscopy of $t\text{Bu}_{\text{F}_6}\text{OH}$ released upon grafting indicates that about 47 and 51 % of the surface silanols (0.26 mmol g^{-1}) reacted with **1** and **2**, respectively. This data is in agreement with the tungsten loading of 2.51 % (**1**@ SiO_2 , 0.13 mmol g^{-1}) and 2.67 % (**2**@ SiO_2 , 0.14 mmol g^{-1}) as determined by elemental analysis and the presence of residual silanols interacting with nearby aromatic residues according to infrared (IR) spectroscopy (a broad band at 3647 cm^{-1} ; Figure S25 in the Supporting Information).^[9c]

The ^1H magic angle spinning (MAS) NMR spectrum of **1**@ SiO_2 showed resonances at $\delta = 11.2$, 7.1, and 2.1 ppm, which were assigned to the alkylidene, the aromatic, and methyl proton signals, respectively (Figure S19). A similar ^1H MAS spectrum was observed for **2**@ SiO_2 (Figure S21), with peaks at $\delta = 10.4$, 7.4 and 1.9 ppm, accounting for the alkylidene, aromatic, and methyl moieties, respectively. As generally observed for supported tungsten alkylidene complexes, the carbene signals were not detected at natural abundance in the ^{13}C cross-polarization (CP) MAS spectra, but all the other signals corresponding to the ligands were observed (Figures S20–S22). The ^{11}B NMR spectrum of **2**@ SiO_2 shows only one signal at $\delta = -6.3$ ppm and it is consistent with the presence of isolated $\text{B}(\text{Ar}^F)_4^-$ anions as observed for the molecular precursor **2** (Figure S23).

[*] M. Pucino, Dr. V. Mougél, Dr. A. Fedorov, Prof. Dr. C. Copéret
Department of Chemistry and Applied Biosciences, ETH Zürich
Vladimir-Prelog-Weg 2, 8093 Zurich (Switzerland)
E-mail: ccoperet@ethz.ch

R. Schowner, Prof. Dr. M. R. Buchmeiser
Institute of Polymer Chemistry, University of Stuttgart
Pfaffenwaldring 55, 70569 Stuttgart (Germany)
E-mail: michael.buchmeiser@ipoc.uni-stuttgart.de

Supporting information and ORCID(s) from the author(s) for this article are available on the WWW under <http://dx.doi.org/10.1002/anie.201510678>.

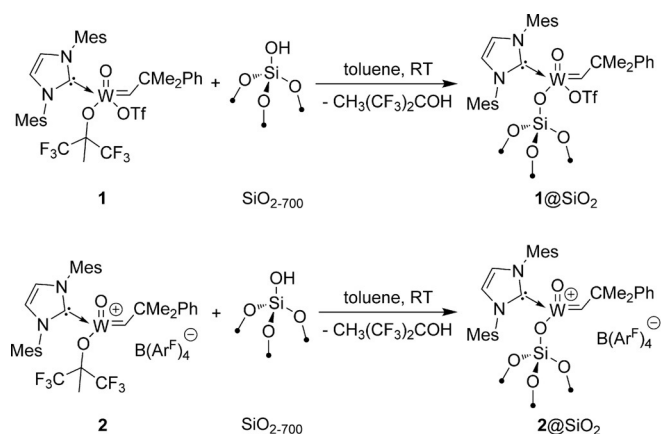

Scheme 1. Grafting **1** and **2** onto SiO_{2-700} . $\text{B(Ar}^{\text{F}})_4^- = \text{B(3,5-(CF}_3)_2\text{C}_6\text{H}_3)_4^-$, Mes = mesityl, Tf = trifluoromethanesulfonyl.

As the alkylidene signals of supported species are difficult to detect, because of their large chemical shift anisotropy and low site density,^[14] we prepared ^{13}C -enriched compounds both at the alkylidene and NHC carbene positions, **1*** and **2***, respectively. The ^{13}C -enriched silica-supported complexes **1*@SiO₂** and **2*@SiO₂** were synthesized and characterized by ^{13}C CPMAS and two-dimensional (2D) ^1H - ^{13}C HETCOR NMR spectroscopy (see the Supporting Information). Alkylidene signals were observed at $\delta = 300$ and 296 ppm for **1*@SiO₂** and **2*@SiO₂**, respectively, and the NHC carbene was observed at $\delta = 186$ ppm for **1*@SiO₂** and $\delta = 181$ ppm for **2*@SiO₂**. The spectroscopic characterization of **1@SiO₂** and **2@SiO₂**, combined with elemental (C, H, B and F; see the Supporting Information) analyses, are in agreement with the proposed structures $[(\equiv\text{SiO})\text{W(=O)(=CHCMe}_2\text{Ph)(IMes)(OTf)}]$ and $[(\equiv\text{SiO})\text{W(=O)(=CHCMe}_2\text{Ph)(IMes)}^+][\text{B(Ar}^{\text{F}})_4^-]$ as the main species in **1@SiO₂** and **2@SiO₂**, respectively.

To harness the potential of **1@SiO₂** and **2@SiO₂** in alkene metathesis, we first tested them with the benchmark substrates *cis*-4-nonene and 1-nonene (Table 1).^[4c,d,5a,b,12,15] Both materials are active in self-metathesis of *cis*-4-nonene and 1-nonene at 30 °C, but they significantly differ in activity. **1@SiO₂** showed moderate activity with *cis*-4-nonene, while **2@SiO₂** displays high activity, similar to some of the best silica-supported tungsten alkylidene catalysts.^[4c,d,5a,b,12] For comparison, **1** was inactive under similar reaction conditions,

Table 1: Catalytic activity of **1@SiO₂** and **2@SiO₂** in self-metathesis of *cis*-4-nonene and 1-nonene in toluene at 30 °C.

Substrate	Catalyst	mol %	TOF _{3min} ^[a]	Time to equilibrium ^[b]
<i>cis</i> -4-nonene	1@SiO₂	0.1	10 (3 %)	5 h (490)
<i>cis</i> -4-nonene	2@SiO₂	0.1	90 (27 %)	5 min (510)
<i>cis</i> -4-nonene	2@SiO₂	0.02	120 (7 %)	1 h (2510)
1-nonene	1@SiO₂	0.02	4 (< 1 %)	26 % in 24 h (1300)
1-nonene	2@SiO₂	0.02	420 (25 %)	5 h (4530)
1-nonene	2@SiO₂	0.002	2460 (15 %)	74 % in 24 h (37 090)
1-nonene	2@SiO₂	0.001	830 (2 %)	60 % in 24 h (61 070)

[a] TOF at 3 min, given in min^{-1} and the corresponding conversion is given within parentheses. [b] TON given within parentheses. Also given is the percent conversion for cases in which equilibrium was not achieved.

and **2** showed high activity [$\text{TOF} = 170 \text{ min}^{-1}$ ($\text{TOF} = \text{turn-over frequency}$), with fast equilibrium conversion, ca. 3 min]. The catalyst **2@SiO₂** can however be recycled more than three times without loss of catalytic activity. In addition, quantification of the number of active sites indicated that more than 95 % of the tungsten centers in **2@SiO₂** are active (see the Supporting Information). More importantly, **2@SiO₂** displayed an unprecedented activity for the metathesis of 1-nonene, a terminal olefin. TOFs as high as 2460 min^{-1} could be measured at a 50 ppm loading, about two orders of magnitude higher than the best well-defined silica-supported catalyst known to date under the same reaction conditions. In contrast, the molecular catalyst **2** showed faster deactivation in the metathesis of 1-nonene at a 0.02 % catalyst loading, with the conversion reaching only 80 %. This difference presumably arises from the low stability of the methyldiene species generated from **2** and illustrates the advantage of site isolation of the corresponding supported catalysts, which prevents deactivation through dimerization.^[9b] This exceptionally high stability allowed a decrease in the catalyst loading to 10 ppm in the 1-nonene metathesis with **2@SiO₂**, thus reaching a TON of about 61 000, at the expense of the TOF, which fell to 830 min^{-1} . This loss of activity (TOF) is attributed to poisoning of active species with adventitious impurities not removed by the purification protocol.

The activity of **2@SiO₂** in self-metathesis, ring-closing metathesis, and cross-metathesis with functionalized substrates was also investigated (Table 2). **2@SiO₂** displayed high activity for functionalized substrates, which is generally challenging for supported catalysts. With ethyl oleate, fast equilibrium conversion is observed at a 0.1 mol % loading. Decreasing the catalyst content to 10 ppm allows a maximum TON of about 12 000 with a $\text{TOF}_{3\text{min}}$ of 400 min^{-1} . **2@SiO₂** is also active for the ethenolysis of ethyl oleate where TONs of up to 930 were achieved. Ring-closing metathesis of diallyl ether proceeded with a TON of 780, while the molecular precursor **2** was inactive,^[6c] and likely results from the increased stability provided by grafting.

The heterogeneous nature of **2@SiO₂** allowed us to investigate its activity in gas-phase reactions under flow conditions. Remarkably, the catalyst **2@SiO₂** achieved more than 1 200 000 turnovers in the self-metathesis of propene within 6 days, with a metathesis selectivity greater than 99 %, and with only about 40 % deactivation over that period.

In summary, grafting neutral and cationic tungsten oxo alkylidene NHC complexes onto SiO_{2-700} afforded the well-defined surface species $[(\equiv\text{SiO})\text{W(=O)(=CHCMe}_2\text{Ph)(IMes)(OTf)}]$ and $[(\equiv\text{SiO})\text{W(=O)(=CHCMe}_2\text{Ph)(IMes)}^+]$.

Table 2: Catalytic activity of **2@SiO₂** with functionalized substrates in toluene.

Substrate	<i>T</i> [°C]	mol %	TON ^[a]
ethyl oleate	70	0.001	11 874 (1 h)
diallyl ether	30	0.1	780 (24 h)
diallyl diphenylsilane	30	0.1	880 (24 h)
ethyl oleate ethenolysis	60	0.1	930 ^[b] (1 h)

[a] Time is given within parentheses. [b] 82 % selectivity for ethenolysis, 18 % of homodimerization products.

[B(Ar^F)₄][−]. Both complexes are active in alkene metathesis, but the cationic species displayed unprecedented activity and stability in the metathesis of olefins, coupled with improved functional-group tolerance by comparison with other silica-supported complexes. Most remarkable are the high activity and stability with terminal olefins, thus allowing over a 1 million TON in propene self-metathesis with 2@SiO₂ to be achieved. These results may open a new perspective for the use of well-defined catalysts in chemical processes. The results provide further evidence that enhancing the dissymmetry at the metal center by using a strong σ-donating ligand such as an NHC in silica-supported d⁰-metal alkylidene complexes leads to an increased activity in olefin metathesis and that site isolation provided by the support leads to exceptionally high stability.

Acknowledgments

We are grateful to Dr. R. Verel for his assistance with NMR measurements, Dr. Wolfgang Frey for single-crystal X-ray analysis, and Dr. P. Zhizhko for performing reproducibility tests. A.F. thanks the Holcim Stiftung for a Habilitation Fellowship. The authors are grateful to the Scientific Equipment Program of ETH Zürich and the Swiss National Science Foundation (R'Equip grant 206021_150709/1) for financial support.

Keywords: metathesis · N-heterocyclic carbene · structure elucidation · supported catalysts · tungsten

How to cite: *Angew. Chem. Int. Ed.* **2016**, *55*, 4300–4302
Angew. Chem. **2016**, *128*, 4372–4374

- [1] a) R. R. Schrock, *Angew. Chem. Int. Ed.* **2006**, *45*, 3748–3759; *Angew. Chem.* **2006**, *118*, 3832–3844; b) R. H. Grubbs, *Angew. Chem. Int. Ed.* **2006**, *45*, 3760–3765; *Angew. Chem.* **2006**, *118*, 3845–3850; c) S. J. Meek, R. V. O'Brien, J. Llavaria, R. R. Schrock, A. H. Hoveyda, *Nature* **2011**, *471*, 461–466; d) B. K. Keitz, K. Endo, P. R. Patel, M. B. Herbert, R. H. Grubbs, *J. Am. Chem. Soc.* **2012**, *134*, 693–699; e) C. Wang, F. Haefner, R. R. Schrock, A. H. Hoveyda, *Angew. Chem. Int. Ed.* **2013**, *52*, 1939–1943; *Angew. Chem.* **2013**, *125*, 1993–1997; f) R. K. M. Khan, S. Torker, A. H. Hoveyda, *J. Am. Chem. Soc.* **2013**, *135*, 10258–10261.
- [2] a) B. Haberlag, M. Freytag, C. G. Daniliuc, P. G. Jones, M. Tamm, *Angew. Chem. Int. Ed.* **2012**, *51*, 13019–13022; *Angew. Chem.* **2012**, *124*, 13195–13199; b) A. Fürstner, *Angew. Chem. Int. Ed.* **2013**, *52*, 2794–2819; *Angew. Chem.* **2013**, *125*, 2860–2887.
- [3] C. Copéret, A. Comas-Vives, M. P. Conley, D. Estes, F. Nunez-Zarur, A. Fedorov, V. Mougél, H. Nagae, P. A. Zhizhko, *Chem. Rev.* **2016**, *116*, 323–421.
- [4] a) D. V. Peryshkov, R. R. Schrock, M. K. Takase, P. Muller, A. H. Hoveyda, *J. Am. Chem. Soc.* **2011**, *133*, 20754–20757; b) D. V. Peryshkov, R. R. Schrock, *Organometallics* **2012**, *31*, 7278–7286; c) M. P. Conley, V. Mougél, D. V. Peryshkov, W. P. Forrester, D. Gajan, A. Lesage, L. Emsley, C. Copéret, R. R. Schrock, *J. Am. Chem. Soc.* **2013**, *135*, 19068–19070; d) M. P. Conley, W. P. Forrester, V. Mougél, C. Copéret, R. R. Schrock, *Angew. Chem. Int. Ed.* **2014**, *53*, 14221–14224; *Angew. Chem.* **2014**, *126*, 14445–14448; e) V. Mougél, M. Pucino, C. Copéret, *Organometallics* **2015**, *34*, 551–554.
- [5] a) T. Weskamp, F. J. Kohl, W. Hieringer, D. Gleich, W. A. Herrmann, *Angew. Chem. Int. Ed.* **1999**, *38*, 2416–2419; *Angew. Chem.* **1999**, *111*, 2573–2576; b) M. Scholl, T. M. Trnka, J. P. Morgan, R. H. Grubbs, *Tetrahedron Lett.* **1999**, *40*, 2247–2250; c) J. Huang, E. D. Stevens, S. P. Nolan, J. L. Petersen, *J. Am. Chem. Soc.* **1999**, *121*, 2674–2678; d) G. C. Vougioukalakis, R. H. Grubbs, *Chem. Rev.* **2010**, *110*, 1746–1787; e) V. M. Marx, A. H. Sullivan, M. Melaimi, S. C. Virgil, B. K. Keitz, D. S. Weinberger, G. Bertrand, R. H. Grubbs, *Angew. Chem. Int. Ed.* **2015**, *54*, 1919–1923; *Angew. Chem.* **2015**, *127*, 1939–1943.
- [6] a) M. R. Buchmeiser, S. Sen, J. Unold, W. Frey, *Angew. Chem. Int. Ed.* **2014**, *53*, 9384–9388; *Angew. Chem.* **2014**, *126*, 9538–9542; b) S. Sen, R. Schowner, D. A. Imbrich, W. Frey, M. Hunger, M. R. Buchmeiser, *Chem. Eur. J.* **2015**, *21*, 13778–13787; c) R. Schowner, W. Frey, M. R. Buchmeiser, *J. Am. Chem. Soc.* **2015**, *137*, 6188–6191.
- [7] a) C. Copéret, M. Chabanas, R. P. Saint-Arroman, J. M. Basset, *Angew. Chem. Int. Ed.* **2003**, *42*, 156–181; *Angew. Chem.* **2003**, *115*, 164–191; b) S. L. Wegener, T. J. Marks, P. C. Stair, *Acc. Chem. Res.* **2012**, *45*, 206–214; c) M. M. Stalzer, M. Delferro, T. J. Marks, *Catal. Lett.* **2015**, *145*, 3–14.
- [8] a) C. Copéret, *New J. Chem.* **2004**, *28*, 1–10; b) C. Copéret, *Dalton Trans.* **2007**, 5498–5504.
- [9] a) M. Chabanas, A. Baudouin, C. Copéret, J. M. Basset, *J. Am. Chem. Soc.* **2001**, *123*, 2062–2063; b) F. Blanc, C. Copéret, J. Thivolle-Cazat, J. M. Basset, A. Lesage, L. Emsley, A. Sinha, R. R. Schrock, *Angew. Chem. Int. Ed.* **2006**, *45*, 1216–1220; *Angew. Chem.* **2006**, *118*, 1238–1242; c) B. Rhers, A. Salameh, A. Baudouin, E. A. Quadrelli, M. Taoufik, C. Copéret, F. Lefebvre, J. M. Basset, X. Solans-Monfort, O. Eisenstein, W. W. Lukens, L. P. H. Lopez, A. Sinha, R. R. Schrock, *Organometallics* **2006**, *25*, 3554–3557; d) F. Blanc, J. Thivolle-Cazat, J. M. Basset, C. Copéret, A. S. Hock, Z. J. Tonzetich, A. Sinha, R. R. Schrock, *J. Am. Chem. Soc.* **2007**, *129*, 5779–5779.
- [10] a) A. Poater, X. Solans-Monfort, E. Clot, C. Copéret, O. Eisenstein, *J. Am. Chem. Soc.* **2007**, *129*, 8207–8216; b) X. Solans-Monfort, C. Copéret, O. Eisenstein, *J. Am. Chem. Soc.* **2010**, *132*, 7750–7757; c) X. Solans-Monfort, C. Copéret, O. Eisenstein, *Organometallics* **2012**, *31*, 6812–6822; d) X. Solans-Monfort, C. Copéret, O. Eisenstein, *Organometallics* **2015**, *34*, 1668–1680; e) V. Mougél, C. B. Santiago, P. A. Zhizhko, E. N. Bess, J. Varga, G. Frater, M. S. Sigman, C. Copéret, *J. Am. Chem. Soc.* **2015**, *137*, 6699–6704.
- [11] a) S. J. Malcolmson, S. J. Meek, E. S. Sattely, R. R. Schrock, A. H. Hoveyda, *Nature* **2008**, *456*, 933–937; b) I. Ibrahim, M. Yu, R. R. Schrock, A. H. Hoveyda, *J. Am. Chem. Soc.* **2009**, *131*, 3844–3845; c) A. H. Hoveyda, S. J. Malcolmson, S. J. Meek, A. R. Zhugralin, *Angew. Chem. Int. Ed.* **2010**, *49*, 34–44; *Angew. Chem.* **2010**, *122*, 38–49; d) E. M. Townsend, J. Hyvl, W. P. Forrester, R. R. Schrock, P. Müller, A. H. Hoveyda, *Organometallics* **2014**, *33*, 5334–5341.
- [12] V. Mougél, C. Copéret, *Chem. Sci.* **2014**, *5*, 2475–2481.
- [13] During the course of this study we could determine the crystal structure of **1**. Details are given in the Supporting Information (see Figure S54).
- [14] a) F. Blanc, C. Copéret, A. Lesage, L. Emsley, *Chem. Soc. Rev.* **2008**, *37*, 518–526; b) F. Blanc, J. M. Basset, C. Copéret, A. Sinha, Z. J. Tonzetich, R. R. Schrock, X. Solans-Monfort, E. Clot, O. Eisenstein, A. Lesage, L. Emsley, *J. Am. Chem. Soc.* **2008**, *130*, 5886–5900.
- [15] F. Allouche, V. Mougél, C. Copéret, *Asian J. Org. Chem.* **2015**, *4*, 528–532.

Received: November 18, 2015

Published online: March 1, 2016