

New Ferroelectric Liquid Crystal Materials: (+)-4-(5-Alkyl-1,3-dioxan-2-yl)phenyl 4-(2-Methylbutoxy)benzoates

Yuichiro HARAMOTO* and Hiroyoshi KAMOGAWA

Department of Applied Chemistry, Yamanashi University, Takeda 4, Kofu 400

(Received June 20, 1989)

(+)-4-(5-Alkyl-1,3-dioxan-2-yl)phenyl 4-(2-methylbutoxy)benzoates (**9**) and their oxathiane (**10**) and dithiane (**11**) analogs have been synthesized. The mesomorphic behavior of these compounds was measured. Compounds **9** exhibited a ferroelectric liquid-crystal behavior (e.g. $R=n\text{-C}_{10}\text{H}_{21}$: 51 SmC* 57.5 °C), while the corresponding 1,3-oxathianes (**10**) and 1,3-dithianes did not.

In recent years 2,5-disubstituted 1,3-dioxanes, 1,3-oxathianes, and 1,3-dithianes have been reported as new types of nematic liquid-crystal materials.^{1–10}

In view of the increasing attention being paid to new types of liquid-crystal displays using ferroelectric liquid crystals, we have synthesized various ferroelectric liquid-crystal compounds, such as several structural types of optically active liquid-crystal compounds with 1,3-dioxane, 1,3-oxathiane, and 1,3-dithiane rings.^{11–15} In a previous paper,¹³ we reported that (+)-4-(2-methylbutoxycarbonyl)phenyl 4-(5-alkyl-1,3-dioxan-2-yl)benzoates exhibit a ferroelectric liquid-crystal behavior, but (+)-4-(2-methylbutoxy)phenyl 4-(5-alkyl-1,3-dioxan-2-yl)-benzoates (**12**) do not. The title compounds (**9**) were only different from compounds (**12**) regarding the direction of the ester bond. In this paper, we wish to report on the syntheses and mesomorphic behavior of these compounds.

Results and Discussion

(+)-4-(5-Alkyl-1,3-dioxan-2-yl)phenyl 4-(2-methylbutoxy)benzoates (**9**) and the corresponding 1,3-oxathianes (**10**) and 1,3-dithianes (**11**) were synthesized via the following route.

In step 1→2,3 the reaction temperature was kept within the range 80 to 85 °C in order to obtain compounds **2** and **3** in nearly equal yields.

In step (2, 3) → (4, 5) a mixture of compounds **2** and **3** was used. Compounds **4** and **5** were separated by column chromatography, though which **4** and **5** were eluted with hexane and ether, respectively. During esterification from **6** and **7**, 1,8-diazabicyclo[5.4.0]undec-7-ene (DBU) was used as a base. Compounds **9**, **10**, and **11** were synthesized by acid-catalyzed ring-formation reactions of compounds **1**, **4**, and **5** with aldehyde **8**, respectively. Compounds **9**, **10**, and **11** were purified by column chromatography and recrystallized from hexane.

Since each product obtained as a white powder contained about 5–20% cis isomer, these products were chromatographed on preparative thin-layer chromatography (prep. TLC) in order to obtain analytically pure trans isomers. In the ¹H NMR data for compounds **9**, **10**, and **11**, the C-2 proton signals of the

1,3-dioxane, 1,3-oxathiane, and 1,3-dithiane rings for the trans and cis isomers appeared separately within a range of about 0.05 ppm. For example, the C-2 proton signals of the trans isomers appeared at $\delta=5.45$ (compound **9-1**), 5.75 (**10-1**), and 5.20 (**11-1**), and the corresponding signals of the cis isomers appeared at $\delta=5.50$, 5.80, and 5.15, respectively.

Mesomorphic properties were determined using a



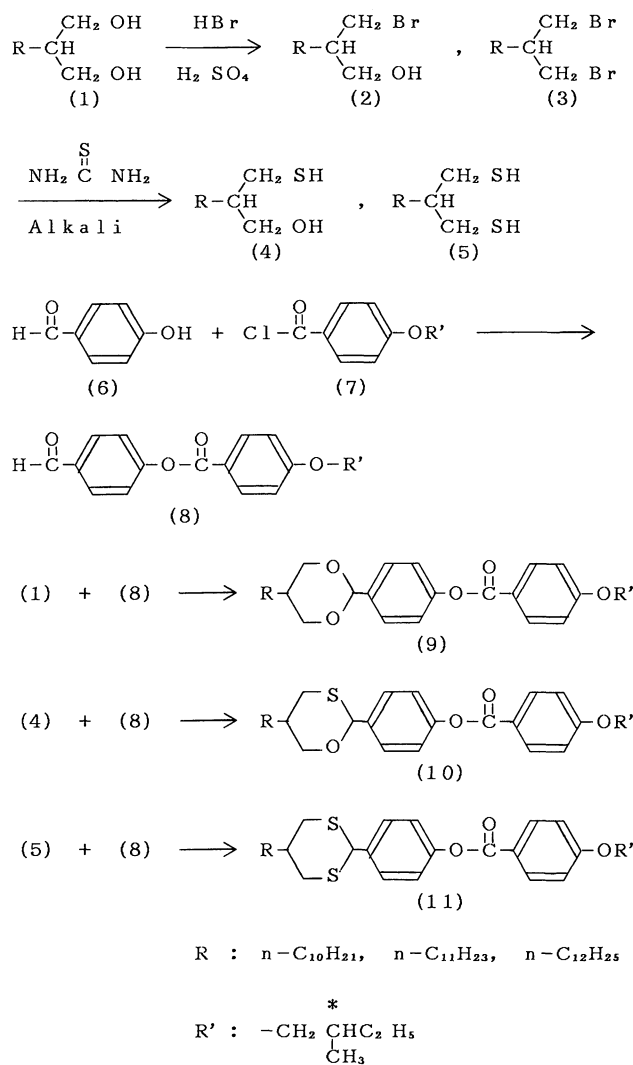


Fig. 1.

Table 1. Mesomorphic Ranges for Compounds **9**, **10**, **11**, and **12**

	R	X Y	Mesomorphic range/°C ^{a)}
9-1	<i>n</i> -C ₁₀ H ₂₁	O O	$ \begin{array}{c} \xrightarrow{69} \text{N}^* \xrightarrow{123} \text{I} \\ \text{C} \uparrow \quad \downarrow \text{SmC}^* \\ \text{Sm} \xleftarrow{51} \end{array} $
9-2	<i>n</i> -C ₁₁ H ₂₃	O O	$ \begin{array}{c} \xrightarrow{76} \text{N}^* \xrightarrow{124} \text{I} \\ \text{C} \uparrow \quad \downarrow \text{SmC}^* \\ \text{Sm} \xleftarrow{61} \end{array} $
9-3	<i>n</i> -C ₁₂ H ₂₅	O O	$ \begin{array}{c} \xrightarrow{82} \text{N}^* \xrightarrow{118} \text{I} \\ \text{C} \uparrow \quad \downarrow \text{SmC}^* \\ \text{Sm} \xleftarrow{65} \end{array} $
10-1	<i>n</i> -C ₁₀ H ₂₁	S O	$ \begin{array}{c} \xrightarrow{88} \text{N}^* \xrightarrow{122} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{47} \end{array} $
10-2	<i>n</i> -C ₁₁ H ₂₃	S O	$ \begin{array}{c} \xrightarrow{83} \text{N}^* \xrightarrow{120} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{61} \end{array} $
10-3	<i>n</i> -C ₁₂ H ₂₅	S O	$ \begin{array}{c} \xrightarrow{87} \text{N}^* \xrightarrow{114} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{65} \end{array} $
11-1	<i>n</i> -C ₁₀ H ₂₁	S S	$ \begin{array}{c} \xrightarrow{92} \text{N}^* \xrightarrow{138} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{58} \end{array} $
11-2	<i>n</i> -C ₁₁ H ₂₃	S S	$ \begin{array}{c} \xrightarrow{85} \text{N}^* \xrightarrow{137} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{71} \end{array} $
11-3	<i>n</i> -C ₁₂ H ₂₅	S S	$ \begin{array}{c} \xrightarrow{87} \text{N}^* \xrightarrow{135} \text{I} \\ \text{C} \swarrow \quad \searrow \text{Sm} \\ \text{Sm} \xleftarrow{81} \end{array} $

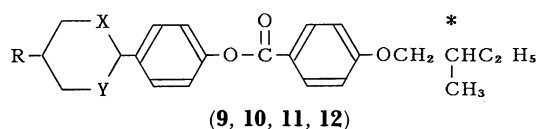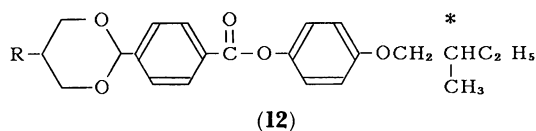

	R	Mesomorphic range/°C ^{a)}
12-1	<i>n</i> -C ₁₀ H ₂₁	$ \text{C} \xrightarrow{66} \text{SmB} \xrightarrow{100} \text{SmA} \xrightarrow{136} \text{I} $
12-2	<i>n</i> -C ₁₁ H ₂₃	$ \text{C} \xrightarrow{113} \text{SmA} \xrightarrow{137} \text{I} $
12-3	<i>n</i> -C ₁₂ H ₂₅	$ \text{C} \xrightarrow{70} \text{SmB} \xrightarrow{97} \text{SmA} \xrightarrow{137} \text{I} $

a) C: crystal, Sm: smectic, N*: chiral nematic, I: isotropic.

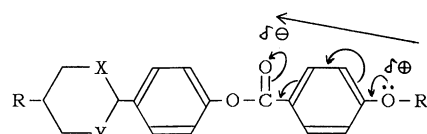


Fig. 2

micro melting-point apparatus equipped with polarizers and a differential scanning calorimeter (DSC). The phase was identified by comparing the observed textures with those found in the literature.^{16,17}

Mesomorphic ranges of compounds **9** and **12** are given in Table 1.

Among the smectic phases listed in this table, only SmC* of compounds **9** could be driven in homogeneous cells ($d=1.7\ \mu\text{m}$, applied voltage=10 V). This indicates that only compounds **9** are ferroelectric liquid-crystal compounds. 1,3-Oxathiane and 1,3-dithiane analogues which correspond to compounds **9** did not exhibit the SmC* phase. This must support the previous result¹³ that the 1,3-dioxane structure is more favorable for a transition to SmC* than the structures of 1,3-oxathiane or 1,3-dithiane are.

Compounds **12**, having the direction of the ester bond just reversed to that of compounds **9**, did not exhibit the SmC* phase. This seems to originate in the appearance of a chiral nematic phase (cholesteric phase). Generally, there are many examples of a transition from the chiral nematic phase to the SmC* phase.¹⁸ In both the chiral nematic phase and the SmC* phase, the chiral alkoxy group seems to orient in a way that may be favorable for a transition from the chiral nematic phase to the SmC* phase.

In all compounds **9**, **10**, and **11** the chiral nematic phase (cholesteric phase) appeared. The chemical structural feature of these compounds is that the chiral group (OR') is conjugated with the phenylcarbonyl group. The *p*-alkoxyphenylcarbonyl group has a dipole moment due to a resonance effect, exhibited as follows (Fig. 2).

Therefore, this chemical structure has a strong dipole moment contiguous to the chiral group. This must be one factor for the appearance of the chiral nematic phase.

The spontaneous polarizations of compounds **9** were too small to detect.

The responses of the optical transmission for compounds **9+1**, **9+2**, and **9+3** were 8, 4, and 7 ms, respectively, values that belong to a large class of ferroelectric liquid-crystal materials. This must originate in the small spontaneous polarization. The tilt angles for compounds **9+1**, **9+2**, and **9+3** are 13°, 21°, and 25°, respectively.

The $\Delta H_{\text{N}^*-\text{I}}$ of compounds **9+2**, **10+2**, and **11+2** were 1.58, 1.73, and 2.12 kJ mol⁻¹, and their $\Delta S_{\text{N}^*-\text{I}}$ were 3.98, 4.40, and 5.16 J K⁻¹ mol⁻¹, respectively.

The $\Delta H_{\text{C}-\text{N}^*}$ of these compounds were 28.65, 31.15,

and 39.42 kJ mol⁻¹, and their ΔS_{C-N^*} were 87.50, 110.12, and 82.09 J K⁻¹ mol⁻¹, respectively.

Experimental

IR, ¹H NMR, and mass spectra were obtained with a Hitachi 215 spectrophotometer, a JNM-PMX 60 spectrometer, and a Hitachi M-80B spectrometer, respectively.

Elemental analyses were carried out with a Perkin-Elmer 250 instrument.

The transition temperatures and mesomorphic phases were determined by means of both a Mitamura Rikenn micro melting point apparatus equipped with polarizers and a Rigaku Denki DSC CN8059L1, CN8208A2. Optical studies were performed on an Olympus polarizing microscope in conjunction with a Mettler FP-82 hot stage and a control unit using a function generator on a Hewlett Packard 3310B and a SONY-TECTRONICS 468 oscilloscope.

Mixtures of 2-Alkyl-3-bromo-1-propanol (2) and 2-Alkyl-1,3-dibromopropane (3). The same procedure as that mentioned in a previous paper¹¹⁾ was used.

2-Alkyl-3-mercapto-1-propanol (4) and 2-Alkyl-1,3-propanedithiol (5). The same procedure as that mentioned in a previous paper¹¹⁾ was used. Compounds **4** were colorless, transparent liquids and **5** were yellow, transparent liquids.

(+)-4-Formylphenyl 4-(2-Methylbutoxy)benzoate (8). To a solution of compound **6** (0.03 mol), and 1,8-diazabicyclo-[5.4.0]undec-7-ene (0.03 mol) in anhyd *N,N*-dimethylformamide (30 ml) was added compound **7** (0.03 mol) under a nitrogen atmosphere, followed by stirring at 30–40 °C for 18 h. The solution was poured into ice water and extracted twice with ether (each 200 ml). The extract was washed with cold 2% aq. HCl, dried over anhyd Na₂SO₄, and evaporated in vacuo at 40 °C. The residue was extracted with hexane, and concentrated under pressure. Transparent liquid was obtained in 60–70% yield.

IR (CHCl₃) 2800–3000 (alkyl), 1720, 1680 (C=O), 1290 (ether) cm⁻¹.

¹H NMR (CDCl₃) δ =0.7–2.2 (m, 9H, OCH₂ C₄ H), 3.9 (d, 2H, OCH₂), 6.8–8.4 (m, 8H, ArH), 10.05 (s, 1H, CHO).

(+)-4-(5-Alkyl-1,3-dioxan-2-yl)phenyl 4-(2-methylbutoxy)benzoate (9). To a solution of compound **1** (0.004 mol) and compound **8** (0.004 mol) in anhyd CHCl₃ (200 ml) cooled in an ice bath were added BF₃·(C₂H₅)₂O (0.5 g) and Molecular Sieves (3A, 1/15; 3 g). The mixture was stirred at 0–5 °C for 8 h, and then at 20–25 °C for 16 h. The solution was washed with 10% aq. NaHCO₃ (400 ml), dried over anhyd. Na₂SO₄, and evaporated in vacuo. The crude product was purified by column chromatography and recrystallized from hexane, and then chromatographed on prep. TLC to give the pure trans isomer.

IR (CHCl₃) 2800–3000 (alkyl), 1740 (C=O), 1600 (Ar), 1290 (ether) cm⁻¹.

¹H NMR (CDCl₃) δ =0.7–2.2 (m, alkyl), 3.3–4.5 (m, 6H, OCH₂), 5.45 (s, 1H, CH), 6.8–8.4 (m, 8H, ArH).

(+)-4-(5-Alkyl-1,3-oxathian-2-yl)phenyl 4-(2-Methylbutoxy)benzoate (10). Compounds **10** were synthesized according to the same procedure as that for compounds **9**.

IR (CHCl₃) 2800–3000 (alkyl), 1740 (C=O), 1600 (Ar), 1280 (ether) cm⁻¹.

¹H NMR (CDCl₃) δ =0.6–2.2 (m, alkyl), 2.9 (d, 2H, CH₂S), 3.2–4.3 (m, 4H, CH₂O), 5.75 (s, 1H, CH), 6.8–8.4 (m, 8H, ArH).

(+)-4-(5-Alkyl-1,3-dithian-2-yl)phenyl 4-(2-Methylbutoxy)-

benzoate (11). Compounds **11** were synthesized according to the same procedure as that for compounds **9**.

IR (CHCl₃) 2800–3000 (alkyl), 1740 (C=O), 1600 (Ar), 1280 (ether) cm⁻¹.

¹H NMR (CDCl₃) δ =0.7–2.2 (m, alkyl), 2.7–2.95 (m, 4H), 3.9 (d, 2H, CH₂O), 5.20 (s, 1H, CH), 6.9–8.4 (m, 8H, ArH).

9-1: Yield, 20%. Found: C, 75.35; H, 9.07%. Calcd for C₃₂H₄₆O₅: C, 75.26; H, 9.08%. MS (*m/z*) 510 (M⁺).

9-2: Yield, 14%. Found: C, 75.11; H, 9.27%. Calcd for C₃₃H₄₈O₅: C, 75.53; H, 9.22%. MS (*m/z*) 524 (M⁺).

9-3: Yield, 28%. Found: C, 75.74; H, 9.41%. Calcd for C₃₄H₅₀O₅: C, 75.80; H, 9.36%. MS (*m/z*) 538 (M⁺).

10-1: Yield, 24%. Found: C, 72.75; H, 8.83%. Calcd for C₃₂H₄₆SO₄: C, 72.96; H, 8.80%. MS (*m/z*) 526 (M⁺).

10-2: Yield, 19%. Found: C, 72.89; H, 8.99%. Calcd for C₃₃H₄₈SO₄: C, 73.29; H, 8.95%. MS (*m/z*) 540 (M⁺).

10-3: Yield, 23%. Found: C, 73.61; H, 9.15%. Calcd for C₃₄H₅₀SO₄: C, 73.60; H, 9.08%. MS (*m/z*) 554 (M⁺).

11-1: Yield, 28%. Found: C, 70.50; H, 8.58%. Calcd for C₃₂H₄₆S₂O₃: C, 70.80; H, 8.54%. MS (*m/z*) 542 (M⁺).

11-2: Yield, 27%. Found: C, 70.95; H, 8.72%. Calcd for C₃₃H₄₈S₂O₃: C, 71.18; H, 8.69%. MS (*m/z*) 556 (M⁺).

11-3: Yield, 35%. Found: C, 71.67; H, 8.96%. Calcd for C₃₄H₅₀S₂O₃: C, 71.53; H, 8.83%. MS (*m/z*) 570 (M⁺).

References

- 1) Y. Haramoto and H. Kamogawa, *J. Chem. Soc., Chem. Commun.*, **1983**, 75.
- 2) Y. Haramoto, A. Nobe, and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **57**, 1966 (1984).
- 3) Y. Haramoto, K. Akazawa, and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **57**, 3173 (1984).
- 4) Y. Haramoto and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **58**, 477 (1985).
- 5) Y. Haramoto and H. Kamogawa, *Chem. Lett.*, **1985**, 79.
- 6) Y. Haramoto and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **58**, 1821 (1985).
- 7) Y. Haramoto and H. Kamogawa, *Mol. Cryst. Liq. Cryst.*, **131**, 101 (1985).
- 8) Y. Haramoto and H. Kamogawa, *Mol. Cryst. Liq. Cryst.*, **131**, 201 (1985).
- 9) Y. Haramoto, M. Sano, and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **59**, 1337 (1986).
- 10) D. Demus and H. Zschke, (to V. E. W. Kombinat Mikroelektronik), Jpn. Patent Appl. No. 54-160916, Dec. (1979).
- 11) Y. Haramoto, Y. Tomita, and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **59**, 3877 (1986).
- 12) Y. Haramoto and H. Kamogawa, *Chem. Lett.*, **1987**, 755.
- 13) Y. Haramoto and K. Kawashima, and H. Kamogawa, *Bull. Chem. Soc. Jpn.*, **61**, 431 (1988).
- 14) Y. Haramoto and H. Kamogawa, *Mol. Cryst. Liq. Cryst. Lett.*, **5**, 117 (1988).
- 15) Y. Haramoto and H. Kamogawa, *Mol. Cryst. Liq. Cryst.*, **173**, 89 (1989).
- 16) D. Demus and L. Richter, "Textures of Liquid Crystals," Verlag Chemie, Weinheim, New York (1978).
- 17) G. W. Gray and J. W. Goodby, "Smectic Liquid Crystals Textures and Structures," Heyden & Sons Inc., Philadelphia (1984).
- 18) T. M. Leslie, *Ferroelectrics*, **58**, 9 (1984).