

Short communication

Hydrolysis of the terminal dimethylacetal moiety on the spacers
bound to carboxy groups containing glucans

Pavol Farkaš*, Slavomír Bystrický

Institute of Chemistry, Slovak Academy of Sciences, Dúbravská cesta 9, 845 38 Bratislava, Slovak Republic

Received 11 September 2007; received in revised form 23 November 2007; accepted 8 January 2008

Available online 16 January 2008

Abstract

Series of carboxymethylglucan (CMG) and oxidized glucan (OXG) derivatives containing spacers of different length with terminal dimethylacetal groups were treated with different acid media. The kinetics of acid hydrolysis was monitored via carbonyl groups formation measurements. Pseudo-first order rate constants k_1 and second-order rate constants k_2 were calculated, $k_1 = k_2[\text{H}^+]$. Observed overall yields and reaction rates varied with different linkers and flexibility of whole linker moiety. Derivatives of OXG hydrolysed about five times faster than analogous derivatives of CMG.

© 2008 Elsevier Ltd. All rights reserved.

Keywords: Glucan; Dimethyl acetal; Hydrolysis; Linker; Conjugate**1. Introduction**

Construction of saccharide-protein conjugates is challenging. The effective biological functionality of the glycoconjugates depends on the proper chemistry of the conjugate construct. Usage of heterobifunctional spacer (linker) molecules resulted in a great improvement. Highly reactive spacers are those containing a nucleophile group (amino, hydrazine) at one end and a carbonyl group at the other. However, the carbonyls should be protected to prevent cross-reactions of the end groups. A diacetal moiety which can be simply converted to carbonyl by mild acid hydrolysis is well known for this. The conversion is quantitative as expected with small molecules (Zhang, Yergey, Kowalak, & Kováč, 1998). The situation may be different with high molecular weight polymers. Unexpectedly, we observed different performance of hydrolysis of acetals after spacers were attached to polysaccharide molecules.

Recently we have reported the preparation of two glucan derivatives with spacer-arm linkers containing dimethylacetals as latent carbonyl groups (Farkaš & Bystrický, 2007). Two polysaccharides: carboxymethylated β -(1 \rightarrow 3)-D-glucan (CMG) and C6 oxidized β -(1 \rightarrow 3)-D-glucan (OXG), bearing three different length spacer-arms are examined here for acid catalyzed hydrolysis of acetals (see Fig. 1).

2. Experimental*2.1. Preparation of glucan derivatives*

We chose two types of model polysaccharides, for our purposes, namely carboxymethyl glucan (CMG) with degree of carboxymethylation 0.87, $M_w = 120,000$, and oxidized glucan (OXG), $M_w = 47,000$, with degree of carboxylation 0.45 prepared according to the literature (Machová, Kogan, Alföldy, Šoltés, & Šandula, 1995; Painter, Cesaro, Delben, & Paloeti, 1985). The glucan carboxy-derivatives were transformed to amides by the specific linker attachment (Farkaš & Bystrický, 2007). Carboxymethyl-glucans with different linkers were desig-

* Corresponding author. Tel.: +421 2 59410261; fax: +421 2 59410222.
E-mail address: chempalo@savba.sk (P. Farkaš).

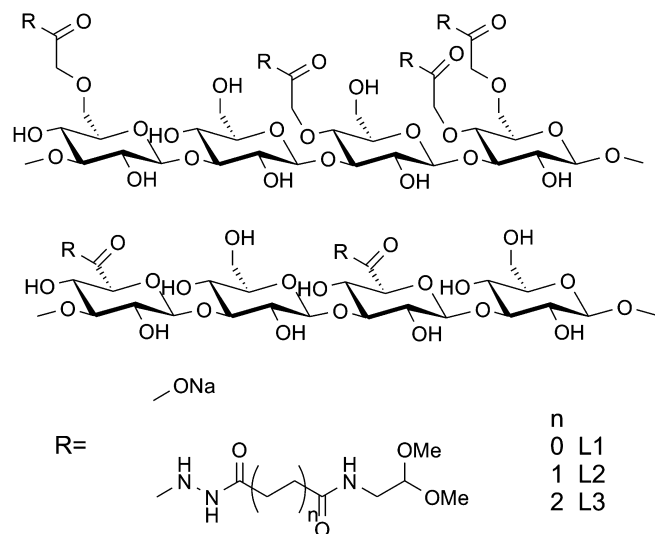


Fig. 1. Derivatives of carboxymethylated glucan (CMG) and oxidized glucan (OXG).

nated CMG-L1, CMG-L2, CMG-L3, and those prepared from oxidized glucan, were designated OXG-L1, OXG-L2, OXG-L3. For these polysaccharides the unbound linker dimethylacetal ends have latent reactive carbonyl groups.

2.2. General procedure for hydrolysis experiments

Acid hydrolysis was performed as follow: Solutions of ~7 mg of CMG-LX or OXG-LX in 10 mL water were incubated at 50 or 80 °C in an oil bath. 5 mL of the Dowex-50 W H⁺ suspension or a 0.05 mol L⁻¹ HCl was then added. 0.5 mL samples were taken out at defined time intervals and the reaction was quenched by the addition of 0.5 mL solution of 0.1 mol L⁻¹ NaHCO₃. The samples were kept in the refrigerator until the analyses were carried out.

2.3. Carbonyl group determination

Samples with carbonyl groups were examined by NMR spectroscopy. ¹H NMR spectra were measured in D₂O at 25 °C on Bruker 300 MHz Avance DPX spectrometer. ¹H NMR spectra confirmed that aldehydes form as the products of hydrolysis. Two new signals replaced a singlet of methoxy group, and triplet of acetal hydrogen. The triplet of the aldehyde group appears at 8.49 ppm and triplet of hydrated form at 5.32 ppm (*J* = 5.33 Hz). The integral ratio of the signals is approximately 0.09:1, thus more than 90% of the aldehyde is in the hydrated form.

The content of aldehyde groups was quantitatively determined by alkaline ferricyanide assay. The determination of the content of carbonyl groups is based on the reduction of ferricyanide ions in alkaline solution (Park & Johnson, 1949). Freshly prepared solution of D-glucose was used as the standard.

2.4. High-performance size exclusion chromatography

Size exclusion chromatography (SEC) experiments were performed with a system from Laboratorní přístroje (Prague, Czech Republic) containing two columns connected in series (250 × 8 mm) packed with Biospher GM 300 and Biospher GM 1000 sorbents from Labio, a.s. (Prague, Czech Republic). Biospher GM is a co-polymer of glycidyl-methacrylate and ethylenedimethacrylate accompanied by special porogens. The separation process was monitored with a differential refractometric detector. The mobile phase used was 0.1 M NaNO₃ solution. A set of pullulans was used for molecular weight calibration of SEC system.

3. Results and discussion

First, we tested reaction conditions known from literature on CMG derivatives. According the hyaluronic acid acetals hydrolysis authors used 0.025 mol L⁻¹ HCl and 25 °C (Bulpitt & Aeschliman, 1999). The results under these conditions show only 4% hydrolysis of acetal after 1 h and only 20% hydrolysis after 24 h. Then we tested 0.05 mol L⁻¹ trifluoroacetic acid and 100 °C (Zhang et al., 1998). Under these conditions we obtained 99–100% conversion after half an hour with all CMG derivatives, with a small decrease in the molecular weight of the products. After 24 h the carbohydrate chains were significantly hydrolysed and oligosaccharides with *M_w* of 300–1200 Da were obtained. In both cases the pH was not strictly constant but varied slightly during the course of the reaction.

To simplify the manipulation and isolation of the products and to determine the rate of hydrolysis at constant pH we used Dowex H⁺ resin. Despite the wide utilization of

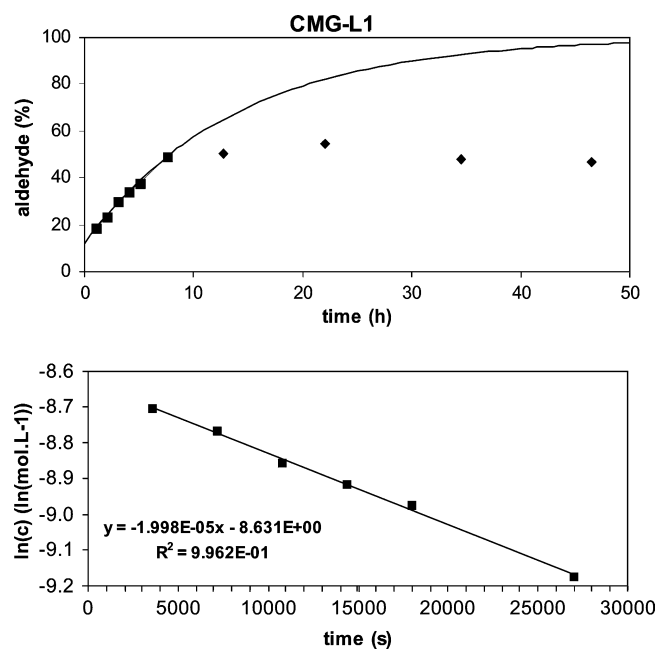


Fig. 2. Hydrolysis of CMG-L1 derivative with Dowex H⁺ at 80 °C, pH 1.56.

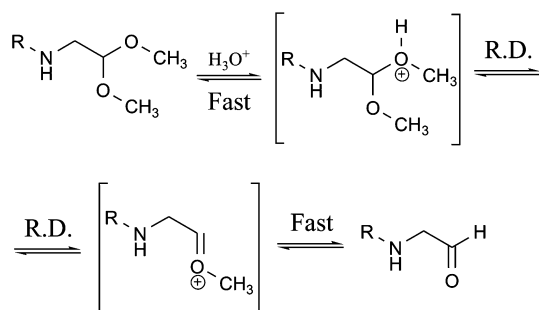


Fig. 3. Mechanism of the acetal hydrolysis.

this procedure, no quantitative studies have been reported with polysaccharides so far. We tried to obtain the rate of the hydrolysis of the two glucan derivatives (CMG and OXG) armed with the potentially functional carbonyl linkers. The representative time course of hydrolysis is presented in Fig. 2.

The reaction started from some small amount of carbonyls as some carbonyls can be present in equilibrium probably due to auto-hydrolysis by close-by carboxyl groups in the polysaccharide chain. A few similar results have been reported for small molecules that have two carboxyl groups sterically close to an acetal group (Dean & Kirby, 2002). For our samples the hydrolysis initially proceeded rapidly, so the carbonyl concentration increased exponentially, reaching a maximum at ~8 h. Then, steady state was observed for the next 24 h. The appearance of aldehyde follows first-order kinetics. Pseudo-first order rate constants, k_1 were evaluated from the linear least squares fit of the semilogarithmic plot. See Fig. 2.

The appropriate equation can be applied for pseudo-first order (k_1) and second-order (k_2) constants: (see Fig. 3)

$$k_1 = k_2[H_3O^+]$$

The calculated rate constants of hydrolyses k_1 and k_2 are given in Table 1.

For comparison, the rate of hydrolysis was measured using hydrochloric acid. Clearly the rate constants are higher for Dowex H^+ then hydrochloric acid. Only for the CMG-L3 the values of k_2 are almost the same, 2.2 or 1.8 for Dowex or HCl, respectively. Shorter linkers L1 and L2 have higher values for Dowex, but not for hydrolysis with HCl.

Table 1
Hydrolysis data of CMG derivatives at 80 °C

Derivative	Amidation (%)	Group 1, Dowex H^+				Group 2, HCl			
		pH	$10^5 k_1$ (s^{-1})	$10^2 k_2$ (L/mol. min)	M_w^* (kDa)	pH	$10^6 k_1$ (s^{-1})	$10^1 k_2$ (L/mol. min)	M_w (kDa)
CMG-L1	11.5	1.56	2.0	4.3	85	1.91	3.8	1.8	11
CMG-L2	18.5	1.56	3.0	6.6	45	1.92	2.8	1.3	36
CMG-L2	21.4	—	—	—	—	1.88	2.5	1.3	—
CMG-L3	20.5	1.63	0.88	2.2	75	2.01	3.0	1.8	50

* M_w -values after the termination of hydrolyses.

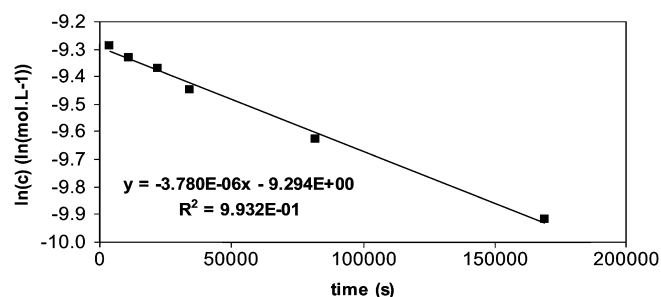
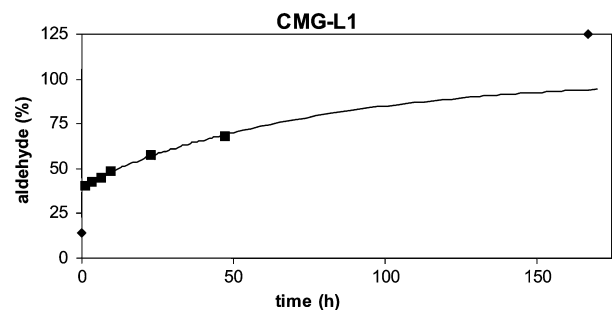


Fig. 4. Hydrolysis of CMG-L1 derivative with hydrochloric acid at 80 °C, pH 1.91.

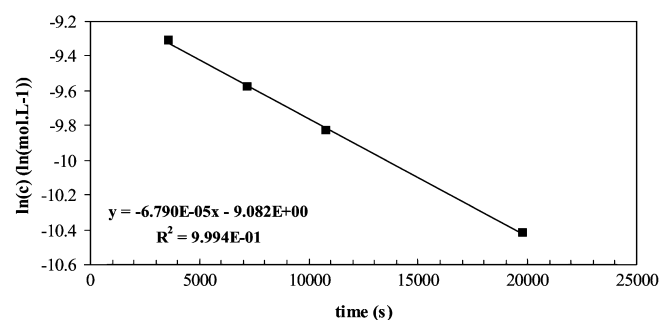
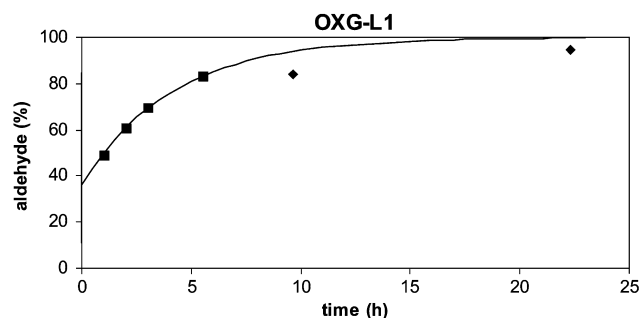


Fig. 5. Hydrolysis of OXG-L1 derivative with Dowex H^+ at 80 °C, pH 1.43.

Table 2
Hydrolysis data of OXG derivatives with Dowex H+ at 50 °C and 80 °C

Derivative	Amidation (%)	Group 3, 50 °C				Group 4, 80 °C		
		pH	$10^6 k_1$ (s ⁻¹)	$10^2 k_2$ (L/mol. min)	M_w^* (kDa)	pH	$10^6 k_1$ (s ⁻¹)	$10^1 k_2$ (L/mol. min)
OXG-L1	20.6	1.96	5.0	2.8	20	1.43	6.8	1.1
OXG-L2	29.0	1.96	4.8	2.6	20	1.43	6.8	1.1
OXG-L3	32.3	1.76	4.8	1.7	25	1.43	6.3	1.0

* M_w -values after the termination of hydrolyses.

The values of rate constant decreased slightly with the increasing length of spacers.

A possible explanation of this finding can be that the longer spacer imparts more flexibility and enhance the potential of carbonyls to interact with neighboring (adjacent) hydroxyls of glucans (see Fig. 4).

Thus the second series of compounds – derivatives of OXG with the same linkers placed nearer to the glucan skeleton have restricted flexibility compare to CMG derivatives. The result of measurement of carbonyl contents during hydrolyses of OXG derivatives (at similar conditions) are shown in Fig. 5.

As can be seen, the starting value is higher and the final yield reaches 90%, much higher then for the CMG derivatives. Fig. 5 illustrates the straight lines of logarithmic plot confirming pseudo-first order of the hydrolysis kinetics also here. The calculated values of rate constants at two temperatures: 50 and 80 °C are given in Table 2.

The pH independent second-order rate constants k_2 even at lower temperature (50 °C) are higher here then at CMG. Hydrolyses of OXG derivatives are faster and evidently more effective then the CMG derivatives.

HP SEC molecular weight analyses of the products were done after the treatment with NaBH₄. Standard reduction of aldehyde groups was done to overcome unwanted reactions and grouping of reactive macromolecules.

As expected, the molecular masses of products were not the same as the starting materials (Tables 1 and 2) due to the accompanied random hydrolyses of the glucan chains. The HPSEC peak of the product is shifted to a lower M_w and is broader than that of starting material. This is evidence of the larger molecular mass distribution of products. The decrease in M_w is not dramatic, reaching 50%. The chain hydrolysis also contributes slightly to the amounts of carbonyl groups. The maximum contribution from this is 10% which is an estimate of the error.

In conclusion, using the Dowex H⁺ resin hydrolyses more efficiently then the use of mineral acid. The most important finding from our studies is the significant role

of the steric arrangement and flexibility of whole-length linker-arms for hydrolysis of pendant acetal groups. These factors are important in the selection of the most potent way of polysaccharide modification for effective conjugation chemistry.

Acknowledgements

This work was supported by APVV 0032-06 and VEGA 2/7029/27 Grants of the Slovak Grant Agencies.

Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at [doi:10.1016/j.carbpol.2008.01.005](https://doi.org/10.1016/j.carbpol.2008.01.005).

References

- Bulpitt, P., & Aeschliman, D. (1999). New strategy for chemical modification of hyaluronic acid: Preparation of functionalized derivatives and their use in the formation of novel biocompatible hydrogels. *Journal of Biomedical Materials Research*, 47, 152–169.
- Dean, K. E. S., & Kirby, A. J. (2002). Concerted general acid and nucleophilic catalysis of acetal hydrolysis. A simple model for the lysozyme mechanism. *Journal of Chemical Society, Perkin Transactions*, 2, 248–432.
- Farkaš, P., & Bystrický, S. (2007). Efficient activation of carboxyl polysaccharides for the preparation of conjugates. *Carbohydrate Polymers*, 68, 187–190.
- Machová, E., Kogan, G., Alföldy, J., Šoltés, L., & Šandula, J. (1995). Enzymatic and ultrasonic depolymerization of carboxymethylated b-1,3-D-glucans derived from *Saccharomyces cerevisiae*. *Journal of the Applied Polymer Science*, 55, 699–704.
- Painter, T. J., Cesaro, A., Delben, F., & Paloeti, S. (1985). New glucuronoglucans obtained by oxidation of amylose at position 6. *Carbohydrate Research*, 140, 61–68.
- Park, J. T., & Johnson, M. J. (1949). A submicrodetermination of glucose. *J. Biol. Chem.*, 181, 149–151.
- Zhang, J., Yergey, A., Kowalak, J., & Kováč, P. (1998). Linking carbohydrates to proteins using *N*-(2,2-dimethoxyethyl)-6-hydroxy hexanamide. *Tetrahedron*, 54, 11783–11792.