

(2-Methylidene-1,3-dithiolo[4,5-*d*])tetrathiafulvalene (DT-TTF): New Unsymmetrical TTFs condensed with 1,3-Dithiol-2-ylidene Moieties

Yohji Misaki,^a Hiroyuki Nishikawa,^a Hideki Fujiwara,^a Kazuya Kawakami,^a Tokio Yamabe,^{* a} Hideki Yamochi^b and Gunzi Saito^b

^a Department of Hydrocarbon Chemistry and Division of Molecular Engineering, Kyoto University, Yoshida, Kyoto 606, Japan


^b Department of Chemistry, Kyoto University, Kitashirakawa, Kyoto 606, Japan

The synthesis and properties of the unsymmetrical tetrathiafulvalenes condensed with 1,3-dithiol-2-ylidene moieties are described; the electrical properties of several cation radical salts are also presented.

The structural feature of organic superconductors based on bis(ethylenedithio)tetrathiafulvalene (BEDT-TTF) is a two-dimensional arrangement of BEDT-TTF molecules through a S...S intermolecular interaction.¹ From this point of view modification of BEDT-TTF² is of particular interest for the development of new two-dimensional organic metals and superconductors.³ Very recently we have succeeded in the synthesis of several alkyl derivatives of bis(2-methylidene-1,3-dithiolo[4,5-*d*])tetrathiafulvalene (BDT-TTF), which are TTFs condensed with two 1,3-dithiol-2-ylidene moieties instead of the ethylenedithio substituents in BEDT-TTF.⁴ Among these BDT-TTFs, tetramethyl-BDT-TTF **1a** is expected to form conducting salts with more enhanced dimensionality than BEDT-TTF. However, **1a** is not suitable to prepare the cation radical salts owing to its extreme insolubility in common organic solvents. In this context synthesis of the

unsymmetrical derivative of **1a** seems to be available in order to overcome its solubility problem. Furthermore, such unsymmetrical donors have also received current interest because several organic superconductors based on unsymmetrical dimethyl(ethylenedithio)diselenadithiafulvalene (DMET)⁵ and methylenedithiotetrathiafulvalene (MDT-TTF) donors⁶ have recently been prepared. In this communication we report the synthesis of the unsymmetrical TTF derivative possessing a half unit of **1a** (MeDT-TTFs, **2**), and characterization of their redox behaviour and electrical properties of the cation radical salts of the ethylenedithio derivative of **2**.†

† Very recently the selenium analogues of DT-TTFs have also been prepared by Kato *et al.* (S. Aonuma, Y. Okano, H. Sawa, R. Kato and H. Kobayashi, *J. Chem. Soc., Chem. Commun.*, in the press)

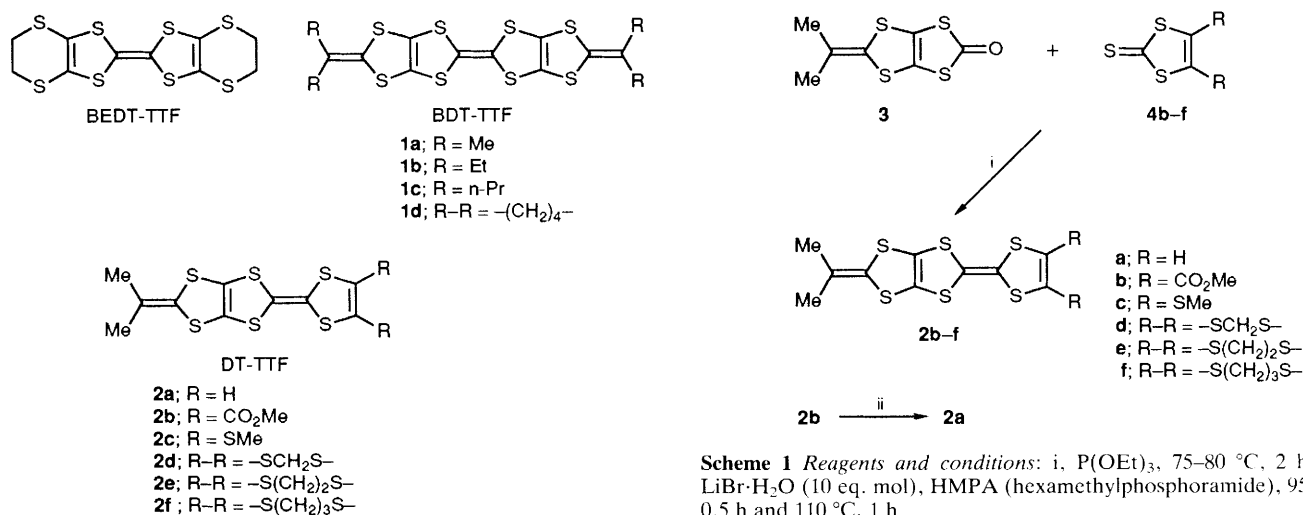

Scheme 1 Reagents and conditions: i, P(OEt)₃, 75–80 °C, 2 h; ii, LiBr·H₂O (10 eq. mol), HMPA (hexamethylphosphoramide), 95 °C, 0.5 h and 110 °C, 1 h

Table 1 Redox potentials of **1a–f** in PhCN [V vs. SCE (saturated calomel electrode), Pt electrode, 25 °C]

Compound	E_1	E_2	E_3	$E_2 - E_1$
2a	+0.45	+0.76	+1.41 ^a	0.37
2b	+0.62	+0.91	+1.51 ^a	0.29
2c	+0.50	+0.75	+1.39 ^a	0.25
2d	+0.51	+0.83	—	0.32
2e	+0.51	+0.79	+1.39 ^a	0.28
2f	+0.50	+0.78	+1.45 ^a	0.28
1b	+0.52	+0.73	+1.27 ^{a,b}	0.21

^a Irreversible step. Anodic peak potentials. ^b Two-electron transfer process.

The new unsymmetrical donors **2b–f** were synthesized as shown in Scheme 1. Isopropylidene-1,3-dithiol[4,5-*d*]-1,3-dithiol-2-one **3** and 2 equimolar amounts of the appropriate 1,3-dithiole-2-thiones **4b–f** were allowed to react in neat triethylphosphite at 75–80 °C for 2 h under argon atmosphere. The precipitates were filtered off and then were column chromatographed on silica gel with CS₂–n-hexane (1:1, v/v) as the eluent. In all cases, the main products were the target molecules, and the symmetrical ones **5b–f** were obtained as minor products while **1a** was not obtained at all. The unsubstituted derivative of **2** (**2a**) was prepared by treatment of **2b** with an excess of LiBr·H₂O in HMPA at 90–100 °C in 67% yield.[‡]

The cyclic voltammeteries of **2** were carried out by using tetra-n-butylammonium perchlorate as a supporting electrolyte in benzonitrile. All of these donors showed two pairs of reversible redox waves and one pair of irreversible waves except for **2d** which showed only two reversible waves. The redox potentials are summarized in Table 1 together with those of tetraethyl-BDT-TTF **1b** instead of **1a**. The first oxidation potentials (E_1) of **2a, b** were between those of corresponding symmetrical donors (**1b** and **5a, b**), as is often

[‡] Selective data for the DT-TTF compounds. **1a**: 67% yield; reddish brown microcrystals; m.p. 167 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 6.30 (2H, s); MS *m/z* 320 (M⁺). **1b**: 67% yield; purple microcrystals; m.p. 212 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 3.85 (6H, s); MS *m/z* 436 (M⁺). **1c**: 47% yield; orange plates; m.p. 164–166 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 2.42 (6H, s); MS *m/z* 412 (M⁺). **1d**: 36% yield; gold microcrystals; m.p. 195 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 4.94 (2H, s); MS *m/z* 396 (M⁺). **1e**: 37% yield; m.p. 201 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 3.29 (4H, s); MS *m/z* 410 (M⁺). **1f**: 23% yield; orange microcrystals; m.p. 200–202 °C (decomp.); ¹H NMR δ 1.72 (6H, s), 2.76 (6H, m); MS *m/z* 424 (M⁺).

the case with most unsymmetrical donors.⁷ While the E_1 values of **2c–f** were almost equal to those of **1b** and **5c–f**.

Preparation of cation radical salts with various inorganic acceptors was examined, and ClO₄[−] and IBr₂[−] salts of the ethylenedithio derivatives **2d** were obtained. Preliminary experiments on electrical properties of these salts revealed that the room temperature conductivities were 15 and 0.47 S cm^{−1} for ClO₄[−] and IBr₂[−] salts, respectively, both of which exhibited metallic conductive behaviour down to 88 K. We are currently engaged in preparation of superior quality single crystals suitable for X-ray crystallographic analysis and detailed investigations on the electrical properties at low temperature.

One of the authors (Y. M.) is indebted to the Inamori Foundation for support of this work.

Received, 26th May 1992; Com. 2/02718F

References

- J. M. Williams, H. H. Wang, T. J. Emge, U. Geiser, M. A. Beno, P. C. W. Leung, K. D. Carlson, R. J. Thorn, A. J. Schultz and M.-H. Whangbo, *Prog. Inorg. Chem.*, 1987, **35**, 51.
- R. Kato, A. Kobayashi, Y. Sasaki and H. Kobayashi, *Chem. Lett.*, 1984, 993; T. Nakamura, S. Iwasawa, H. Nakano, K. Inoue, T. Nogami and H. Mikawa, *Bull. Chem. Soc. Jpn.*, 1987, **60**, 365; T. Suzuki, H. Yamochi, G. Srdanov, K. Hinkelmann and F. Wudl, *J. Am. Chem. Soc.*, 1989, **111**, 3108; R. Kato, H. Kobayashi and A. Kobayashi, *Synth. Met.*, 1991, **42**, 2093.
- Proceedings of the International Conference of Science and Technology of Synthetic Metals (ICSM '90), Tübingen, ed. M. Hanack, S. Roth and H. Schier, *Synth. Met.*, 1991, **41–43**; Proceedings of the ISSP International Symposium, Tokyo, *The Physics and Chemistry of Organic Superconductors*, ed. G. Saito S. Kagoshima, Springer-Verlag Berlin, Heidelberg, 1990.
- Y. Misaki, H. Nishikawa, K. Kawakami, T. Uehara and T. Yamabe, *Tetrahedron Lett.*, 1992, **33**, 432.
- K. Kikuchi, M. Kikuchi, T. Namiki, K. Saito, I. Ikemoto, K. Murata, T. Ishiguro and K. Kobayashi, *Chem. Lett.*, 1987, 931.
- G. C. Papavassiliou, G. A. Mousdis and J. S. Zambounis, *Synth. Met.*, 1988, **27**, B379.
- H. Nakano, K. Yamada, T. Nogami, Y. Shiota, A. Miyamoto and H. Kobayashi, *Chem. Lett.*, 1990, 2129; T. Mori, H. Inokuchi, A. M. Kini and J. M. Williams, *Chem. Lett.*, 1990, 1279.