

Photosynthesis of CH₄ at a TiO₂ Surface from Gaseous H₂O and CO₂

Franz Saladin, Lars Forss and Ivo Kamber*

Paul Scherrer Institute, Laboratory for Energy and Process Technology, 5232 Villigen PSI, Switzerland

UV irradiation of the gas/solid interface of microcrystalline TiO₂ in the presence of water and carbon dioxide in the gas phase at 343 K leads to photoreduction of carbon dioxide to form carbon monoxide, hydrogen and methane.




The imitation of the most important chemical reaction on earth, natural green plant photosynthesis, as a model for a storage reaction for solar energy has attracted much attention in recent years. Chemically storing solar energy under greenhouse-gas neutral conditions could well become a major contribution in solving the world's energy problems ecologically. In contrast to natural systems where atmospheric carbon dioxide is converted into relatively complicated sugar molecules, artificial systems usually yield single-carbon molecules. Some exceptions however, where new carbon-carbon bonds are formed, have also been observed.¹ Up to date the photocatalytic reduction of gaseous carbon dioxide on TiO₂ to methane has been observed with mixed CeO₂-TiO₂ catalysts calcined at 1023 K,² with TiO₂ aggregates anchored on Vycor glass¹ and on single-crystal rutile degassed at 725 K.³ We report here the first photocatalytic reduction of gaseous carbon dioxide to methane in the presence of water over pure, untreated microcrystalline TiO₂ powder at moderate temperatures.

TiO₂ samples (Degussa P25, 30% rutile, 70% anatase) were prepared by immersing quartz wool in a sonicated suspension of TiO₂ in H₂O. These samples contained approximately 50 mg of semiconductor powder on 200 mg quartz wool. CO₂ (Carbagas, 99.998%) was used as received. Deionised water ($\leq 0.06 \mu\text{S cm}^{-1}$) was used without further treatment. The experiments were carried out in a closed loop reactor constructed of glass tubing (total volume 1.85 l). The illuminated part of the reactor was made of quartz. Gas circulation was maintained using a bypass regulated diaphragm pump. The full output of a 1000 W Xe short arc lamp filtered by a CuSO₄ solution to cut off radiation above 700 nm was used as light source. A gas chromatograph (GC) was connected by a switching valve to the reactor allowing for automated online measurement of the gas composition. Detection limits for CO, CH₄, O₂ and N₂ are 10 ppm (0.8 μmol) and for H₂ 35 ppm (3.0 μmol). Acetic acid, formaldehyde and methanol can not be detected with this setup. The temperature of the illuminated semiconductor can not be measured directly with a thermocouple because of the different absorptivity and emissivity of the thermocouple compared with TiO₂. The temperature was therefore determined indirectly from the gas temperature. The accuracy of the method is about ± 10 K. In the dark experiments the reaction zone was heated with a heatgun.

To start an experiment, the TiO₂ sample was inserted into the reactor which was then evacuated and flushed with CO₂ until the air contamination was in the order of the impurities of the CO₂ used (< 8 ppm N₂, < 2 ppm O₂). Gas circulation was started, enough water was added through a septum to saturate the CO₂, and irradiation was started. The gas composition was analysed at least every hour by GC. Whereas CH₄ was detected 30 min after irradiation started, CO was only detectable after 1 hour of irradiation. H₂ could be detected after 3.5 hours of irradiation. The steady state gas temperature reached was 332 K from which a temperature of 343 K of the semiconductor was deduced. The experiment was run for 25 hours. Under these conditions, average production rates of 2.7 $\mu\text{mol h}^{-1}$ CO, 1.4 $\mu\text{mol h}^{-1}$ H₂ and 0.1 $\mu\text{mol h}^{-1}$ CH₄, respectively, have been obtained. Product formation was sustained throughout the whole experiment with an initial decrease of the rates as seen in Fig. 1. During the irradiation, the semiconductor turned grey. In a dark experiment under otherwise identical conditions, no reaction products were found at 343 K after 5 hours. At 553 K, CO₂ can be reduced to CO even in the dark as seen in Fig. 2. The

average production rate, however, was only 0.2 $\mu\text{mol h}^{-1}$, much lower than under irradiation and neither CH₄ nor H₂ could be observed. The CO production rate decreased constantly until it almost reached zero after 25 hours.

Our tentative model to explain the photocatalytic reduction of CO₂ involves the following four reactions [eqns. (1)–(4)] at the surface of TiO₂.



Photoreduction of TiO₂⁴ [eqn. (1)] yields partially reduced TiO_{2- δ} which serves as an electron pool. This reaction is followed by three dark reactions: the reduction of H₂O to H₂ [eqn. (2)],⁵ the reduction of CO₂ to CO [eqn. (3)] and the analogue to the Sabatier reaction forming CH₄ [eqn. (4)]. The latter reaction does not necessarily imply direct hydrogenation of CO₂. In reactions (2) and (3) TiO_{2- δ} is reoxidized. At 343 K the reduction of CO₂ occurs as a purely photochemical reaction. This is confirmed by the absence of product formation without illumination and the linear rise of product concentrations with

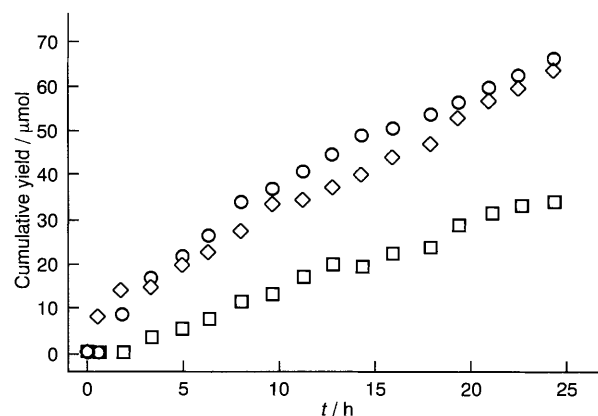


Fig. 1 Product formation at the gas/solid interface of irradiated TiO₂ at 343 K in the presence of H₂O and CO₂. (○) CO, (□) H₂, (◇) CH₄ (×20).

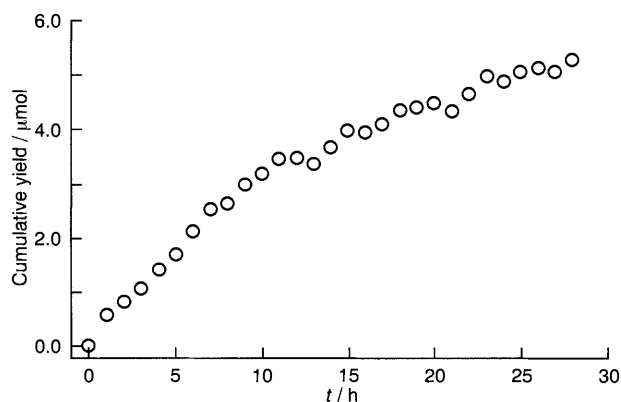


Fig. 2 CO formation on TiO₂ at 553 K in the dark

time. The dark reaction at 553 K can be explained by a reaction of CO₂ with initially present oxygen deficient semiconductor TiO_{2-δ} [eqn. (3)], as has been proposed for the CO₂ reduction with SrTiO₃.⁶ As TiO_{2-δ} becomes oxidized and the photolytic step [eqn. (1)] is missing, the reaction eventually stops as seen in Fig. 2. From the total amount of CO produced in this experiment we calculate δ to be of the order of 10⁻⁴ in our starting material. This reaction does not proceed at 343 K and therefore seems to need an activation energy of more than about 3 kJ mol⁻¹. At present it is not clear whether TiO_{2-δ} should be described as Ti^{III} or metallic Ti⁰ containing samples. For the semiconductor before irradiation we prefer the first description whereas for the samples that turned grey during the irradiation the second description seems more appropriate as titanium(III) samples are generally blue. Another point still open for discussion is that we only find about 45% of the oxygen in the form of CO on the product side. As we failed to detect any oxygen during illumination we ascribe the missing oxygen to photoadsorption.⁷

We have demonstrated for the first time the formation of CH₄ as a product of the photoreduction of CO₂ at TiO₂ at moderate temperatures. The overall reaction involves photolytic and thermal steps. To investigate the mechanism in detail a

miniaturised reactor is under construction that will allow for simultaneous optical characterisation of the samples. It will also allow for *in situ* FTIR measurements to identify surface species.

This work was supported by the Swiss Federal Office of Energy.

Received, 1st December 1994; Com. 4/07344D

References

- 1 M. Anpo and K. Chiba, *J. Mol. Catal.*, 1992, **74**, 207.
- 2 K. Ogura, M. Kawano, J. Yano and Y. Sakata, *J. Photochem. Photobiol. A: Chem.*, 1992, **66**, 91.
- 3 H. Yamashita, N. Kamada, H. He, K. Tanaka, S. Ehara and M. Anpo, *Chem. Lett.*, 1994, **5**, 855.
- 4 H. Inoue, T. Matsuyama, B. Liu, T. Sakata, H. Mori and H. Yoneyama, *Chem. Lett.*, 1994, **3**, 653.
- 5 G. Lu, A. Linsebigler and J. T. Yates Jr., *J. Phys. Chem.*, 1994, **98**, 11733.
- 6 J. C. Hemminger, R. Carr, W. J. Low and G. A. Somorjai, *Adv. Chem. Ser.*, 1980, **184**, 233.
- 7 N. Serpone, R. Terzian, D. Lawless and J. M. Herrmann, *Adv. Electron Transfer Chem.*, 1993, **3**, 33.