

Synthesis and functionalization of a highly fluorescent and completely water-soluble poly(*para*-phenyleneethynylene) copolymer for bioconjugation

Kangwon Lee,^a Jae Cheol Cho,^a Jennifer DeHeck^b and Jinsang Kim^{*abcd}

Received (in Cambridge, UK) 15th February 2006, Accepted 15th March 2006

First published as an Advance Article on the web 4th April 2006

DOI: 10.1039/b602267g

Bioconjugation of a highly fluorescent water-soluble poly(*para*-phenyleneethynylene) (PPE) copolymer with ionic and non-ionic side chains is achieved by means of chain-end modification, providing a design principle for biosensor development.

Conjugated polymers are emerging materials for many modern technologies. One of the attractive applications of conjugated polymers is sensor design, because an environmental change at a single site can affect the properties of the collective system, producing large signal amplification.^{1,2} In particular, the detection of biological analytes such as DNA, proteins and biological warfare agents has been receiving wide scale attention recently.³ Receptors can be rationally designed and covalently connected to a conjugated polymer main chain.

A conjugated polymer should be water-soluble, highly fluorescent and have appropriate functional groups for conjugation with biological receptors to be a good molecular biosensor, because most target biological analytes are analyzed in an aqueous environment. However, by their nature, conjugated polymers have a hydrophobic and rigid main chain, which results in poor solubility in water and subsequent fluorescent quenching by micelle formation in an aqueous phase.⁴ Even worse, once the polymer dries completely, it is extremely difficult to re-dissolve it in water again due to its strong aggregation. To address this problem, many research groups have been working on developing water-soluble conjugated polymers. Khan *et al.* very recently reported an effective method to suppress the aggregation of poly(*para*-phenyleneethynylene)s in water by introducing branched ethylene oxide units as a side chain.⁵

Here we describe the synthesis and functionalization of a completely water-soluble conjugated polymer, poly{[1,4-bis(1,3-bis(2-(2-(2-methoxyethoxy)ethoxy)ethoxy)propan-2-yloxy) benzene]-*alt*-[2,5-diethynylbenzene-2,4-(bis(3-propoxy-sulfonic acid)) sodium salt]} (**PPE-R₁**, Scheme 1), to improve the emissive property even further and give bioconjugation capability. The copolymer, **PPE-R₁**, is composed of alternating ionic sulfonate units and bifurcated non-ionic ethylene oxide units on the main chain to provide water solubility and prevent micelle formation.

Conventional palladium-catalyzed Sonogashira–Hagihara copolymerization was used. We developed a method to introduce a carboxylic acid group, a versatile functional group for bioconjugation, at the end of the PPE chain. The chemically modified polymer, with a carboxylic acid group at both ends, was subsequently conjugated with a model peptide, pentatyrosine.

Monomer synthesis for the PPE copolymer starts by reacting 1,4-dimethoxybenzene with I₂ (I₂, HIO₃, H₂SO₄, AcOH, 85%). Demethylation (BBr₃, CH₂Cl₂, –78 °C to room temperature, 90%) was then achieved by means of BBr₃. The resulting diiodohydroquinone was reacted with the tosylated bifurcated ethylene oxide molecule,^{5,6} followed by the reaction with trimethylsilylacetylene and a subsequent deprotection reaction to give monomer **1**. A diiodo compound, **2**, having sulfonic acid sodium salt units, was prepared according to the literature⁷ (Scheme 1). The copolymerization of **1** and **2** was carried out in the presence of a palladium catalyst (tetrakis(triphenylphosphine)palladium, Pd(PPh₃)₄) at 50 °C in a water/DMF cosolvent system (50/50 v/v). The synthesized **PPE-R₁** showed excellent solubility in water or methanol but poor solubility in common organic solvents such as THF and chloroform. The *in situ* end-capping reaction was undertaken by adding 4-ethynylbenzoic acid with additional palladium catalyst.⁸ The crude polymer solution was precipitated in acetone, filtered, and washed with ethyl acetate and THF to remove diacetylene side product. Further purification of the polymer was achieved by dialysis against de-ionized water for 3 days. The *in situ* end-capping reaction of **PPE-R₁** with carboxylic groups was investigated by ¹H NMR spectroscopy (Fig. 1). Two aromatic proton peaks from the main chain of **PPE-R₁** appeared at 7.27 and 7.20 ppm. After the *in situ* end-capping reaction, two new peaks emerged at 7.73 and 7.49 ppm, corresponding to the aromatic protons of the end-capper, confirming that the carboxylic group was chemically attached. The molecular weight of the functionalized PPE (**PPE-R₁-COOH**), confirmed by ¹H NMR end-group analysis, was 13 000. We also prepared **PPE-R₂** as a control which does not have the bifurcated ethylene oxide units.


Fig. 2 illustrates the absorption and emission spectra of the prepared PPEs. The absorption spectra of **PPE-R₂**, unlike that of **PPE-R₁** and **PPE-R₁-COOH**, shows a pronounced shoulder in the longer wavelength region, typical of an aggregation band. **PPE-R₂** also shows a broad emission spectrum with the suppressed 0–0 band at λ_{max} = 460 nm and a long tail, a characteristic shape of excimer/aggregation-like emission caused by polymer aggregation, as expected.⁹ On the contrary, the emission spectra of **PPE-R₁** and **PPE-R₁-COOH** are narrow with a well-defined 0–0 band at λ_{max} = 460 nm. We achieved a high quantum yield of PPE in

^aDepartment of Materials Science and Engineering, University of Michigan, Ann Arbor, MI, 48109, USA

^bDepartment of Chemical Engineering, University of Michigan, Ann Arbor, MI, 48109, USA

^cMacromolecular Science and Engineering, University of Michigan, Ann Arbor, MI, 48109, USA

^dBiomedical Engineering, University of Michigan, Ann Arbor, MI, 48109, USA. E-mail: jinsang@umich.edu; Fax: (+1) 734-763-4788; Tel: (+1) 734-936-4681

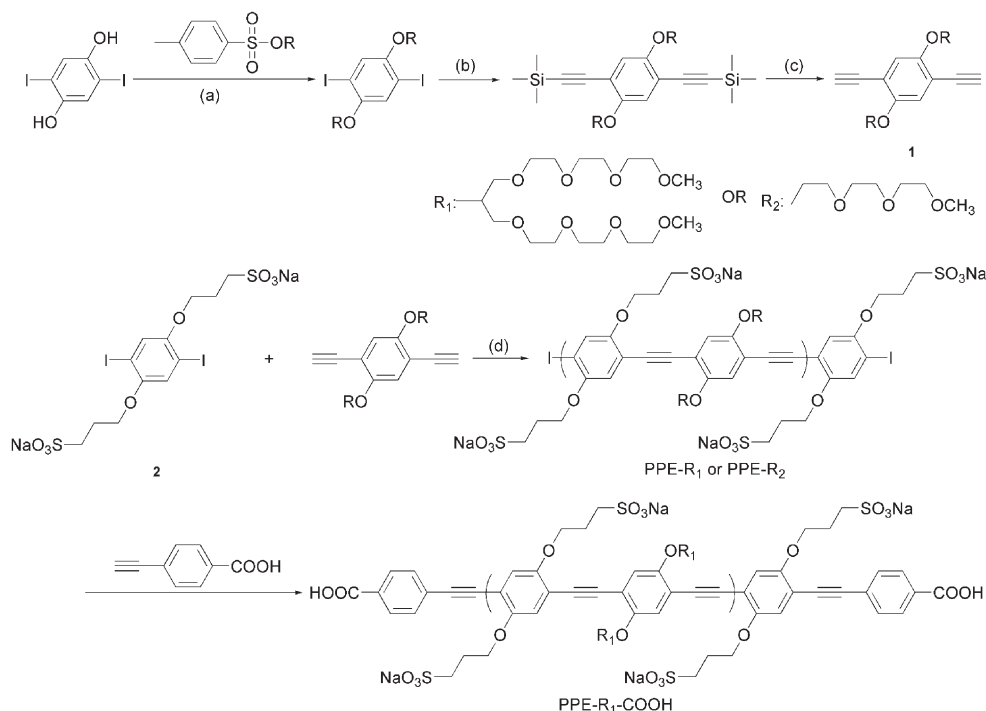

Scheme 1 Polymer synthesis: (a) DMF, K₂CO₃, 75 °C, 72 h; (b) THF, Pd(PPh₃)₄, DIPA (diisopropylamine), CuI; (c) KOH, water/methanol.

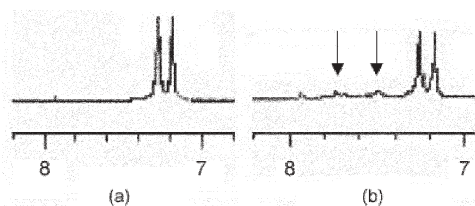


Fig. 1 ¹H NMR spectra of PPE-R₁ in D₂O (a) before and (b) after end-capping.

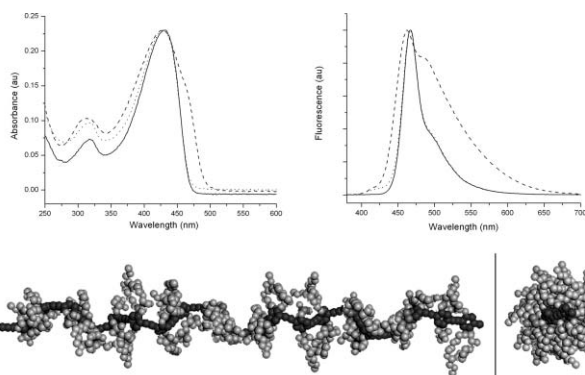



Fig. 2 Top: Normalized absorption and emission spectra of the polymers: PPE-R₁ (solid); PPE-R₁-COOH (dotted); PPE-R₂ (dashed). Bottom: molecular modelling of PPE-R₁ simulated by Materials Studio 3.0 (Accelrys®). The dark black chain indicates the polymer backbone (left: side view, right: edge view).

water by adding ionic and bulky non-ionic side chains. The absolute quantum yield of PPE-R₁ in water (1 mg L⁻¹) was 53%.¹⁰ Conversely, the absolute quantum yield of PPE-R₂ in water

(1 mg L⁻¹) was only 19%, suggesting that the ionic side chain, sulfonic acid sodium salts, provide additional water-solubility but that the bulky non-ionic side group is required to prevent aggregation. Molecular modelling of PPE-R₁, presented in Fig. 2, shows that the hydrophobic PPE backbone is sheathed by the bulky ethylene oxide side chain, effectively preventing aggregation.¹¹

Chemical modification of PPE-R₁ was done by an *in situ* end-capping reaction at the end of the copolymerization. We selected 4-ethynylbenzoic acid as an end-capper because a carboxylic group is of practical use for bioconjugation.¹² The absolute quantum yield of the resulting PPE-R₁-COOH was 45%, lower than that of PPE-R₁. This drop in the quantum yield is believed to be due to the carboxylic acid group being directly connected to the conjugated backbone. We have made various water-soluble PPE copolymers with carboxylic acid side chains in every other repeating unit. We consistently observed that the fluorescent quantum yields of PPEs with directly connected carboxylic acid side groups are always substantially lower than those of PPEs with carboxylic acid side chains connected to the conjugated backbone through a non-conjugated linker group.¹³ The reason why PPE-R₁-COOH has only a slightly smaller quantum yield than PPE-R₁ is likely to be because there are only two carboxylic acid groups at the ends of the conjugated backbone.

We carried out the peptide conjugation reaction on the carboxylic acid groups of PPE-R₁-COOH by using 4-chloro-trityl resin bound with pentatyrosine as a model peptide (Scheme 2). We chose 4-chloro-trityl polystyrene (PS) resin because the cleavage reaction can be undertaken using mild conditions, meaning that the PPE backbone is not damaged. After cleavage of the pentatyrosine from the resin, the quantitative coupling reaction of PPE-R₁-COOH with the pentatyrosine was

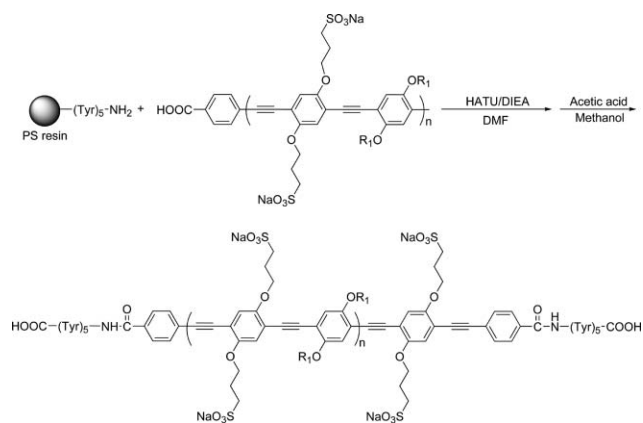

Scheme 2 Peptide-PPE coupling reaction.

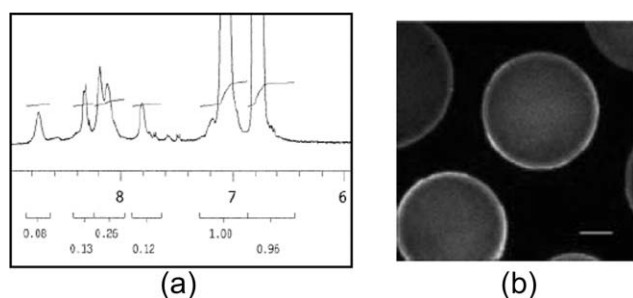


Fig. 3 (a) ^1H NMR spectrum of pentatyrosine-PPE in DMSO (b) A confocal image of pentatyrosine-PPE (scale bar: 20 μm).

confirmed by NMR. New aromatic proton peaks at 7.8–8.8 ppm, corresponding to pentatyrosine, are shown in Fig. 3 (a). It was confirmed that pentatyrosine units were coupled at both ends of the **PPE- R_1 -COOH** by end-group analysis.¹⁴ Fig. 3 (b) shows a confocal microscope image of photoluminescent 4-chloro-trityl resin reacted with **PPE- R_1 -COOH**. The image was taken after 3 stringent rinses of the resin with methanol, DMF, water and dichloromethane to remove any unreacted copolymers. The filtrate of the washing step to remove unbound polymers hardly showed any fluorescence, confirming that almost every polymer chain end has a carboxyl group that had reacted with the PS resin. After cleaving the pentatyrosine from the resin, the resulting peptide-conjugated PPE does not have any carboxylic acid directly bound to the conjugated backbone.¹⁵

In conclusion, we have established a simple and practical approach for the bioconjugation of a conjugated polyelectrolyte and a pentatyrosine, a model biological molecule. We designed and synthesized completely water-soluble and highly fluorescent sulfonated PPE with bifurcated ethylene oxide side chains. End-functionalized PPE, prepared by *in situ* chemical modification during polymerization, was successfully attached to a model peptide, pentatyrosine on a 4-chloro-trityl PS resin. This study provides a design principle for the preparation of functionalized, water-soluble, fluorescent, conjugated polymers for bioconjugation. Bio/synthetic hybrid conjugated polymers have a large potential as molecular biosensors to detect biological analytes quickly and selectively.

J. K. gratefully acknowledges support from the National Science Foundation (BES 0428010), the University of Michigan

College of Engineering start-up fund and the University of Michigan Rackham grant from the Horace H. Rackham School of Graduate Studies. J. K. and K. L. also acknowledge the Ilju Foundation for the Ilju scholarship.

Notes and references

- For a comprehensive review of water-soluble conjugated polymers, see: B. Liu and G. C. Bazan, *Chem. Mater.*, 2004, **16**, 4467; M. Pinto and K. S. Schanze, *Synthesis*, 2002, **9**, 1293. For a comprehensive review of conjugated polymer-based chemical sensors, see: D. T. McQuade, A. E. Pullen and T. M. Swager, *Chem. Rev.*, 2000, **100**, 2537.
- J. H. Wosnick, C. M. Mello and T. M. Swager, *J. Am. Chem. Soc.*, 2005, **127**, 3400; H. A. Ho, K. Doré, M. Boissinot, M. G. Bergeron, R. M. Tanguay, D. Boudreau and M. Leclerc, *J. Am. Chem. Soc.*, 2005, **127**, 12673.
- B. Liu and G. C. Bazan, *Proc. Natl. Acad. Sci. U. S. A.*, 2005, **102**, 589; K. P. R. Nilsson and O. Inganäs, *Nat. Mater.*, 2003, **2**, 419; S. Zhang and T. M. Swager, *J. Am. Chem. Soc.*, 2003, **125**, 3420; H. A. Ho, M. Boissinot, M. G. Bergeron, G. Corbeil, K. Doré, D. Boudreau and M. Leclerc, *Angew. Chem., Int. Ed.*, 2002, **41**, 1548–1551.
- (a) J. J. Lavigne, D. L. Broughton, J. N. Wilson, B. Erdogan and U. H. F. Bunz, *Macromolecules*, 2003, **36**, 7409; (b) C. Tan, E. Atas, J. G. Müller, M. R. Pinto, V. D. Kleiman and K. S. Schanze, *J. Am. Chem. Soc.*, 2004, **126**, 13685; (c) L. Chen, D. W. McBranch, H. Wang, R. Helgeson, F. Wudl and D. G. Whitten, *Proc. Natl. Acad. Sci. U. S. A.*, 1999, **96**, 12287.
- A. Khan, S. Müller and S. Hecht, *Chem. Commun.*, 2005, 584.
- U. Lauter, W. H. Meyer, V. Enkelmann and G. Wegner, *Macromol. Chem. Phys.*, 1998, **199**, 2129.
- C. Tan, M. R. Pinto and K. S. Schanze, *Chem. Commun.*, 2002, 446; W. Chen, A. G. Joly, J. Malm, J. Bovin and S. Wang, *J. Phys. Chem. B*, 2003, **107**, 6544.
- P. Samorí, V. Francke, K. Müllen and J. P. Rabe, *Chem.-Eur. J.*, 1999, **5**, 2312.
- S. A. Jenekhe, *Adv. Mater.*, 1995, **7**, 309; J. Kim and T. M. Swager, *Nature*, 2001, **411**, 1030; J. Kim, I. A. Levitsky, T. McQuade and T. M. Swager, *J. Am. Chem. Soc.*, 2002, **124**, 7710.
- Absolute quantum yield was measured with excitation at 365 nm in deionized water using PTI QuantaMaster[®] spectrofluorometers with an integrating sphere. Fully dried **PPE- R_1** completely dissolves in pure water with a solubility exceeding approximately 1 mg ml⁻¹. Until this paper, the best quantum yield of PPE-based polyelectrolyte was 57%, according to the results of Jiang *et al.*: D.-L. Jiang, C.-K. Choi, K. Honda, W.-S. Li, T. Yuzawa and T. Aida, *J. Am. Chem. Soc.*, 2004, **126**, 12084. While they introduced dendritic side chains into PPEs by a complicated synthetic route in order to overcome aggregation, we synthesized PPEs using a simple method. To our knowledge, ours is the highest quantum yield ever reported of water-soluble conjugated polymers prepared through a simple synthetic route.
- There is another method to overcome the aggregation of conjugated polyelectrolytes in water using a surfactant. See ref. 4a; L. Chen, S. Xu, D. McBranch and D. Whitten, *J. Am. Chem. Soc.*, 2000, **122**, 9302; H. D. Burrows, V. M. M. Lobo, J. Pina, M. L. Ramos, J. Seixas de Melo, A. J. M. Valente, M. J. Tapia, S. Pradhan and U. Scherf, *Macromolecules*, 2004, **37**, 7425; M. J. Tapia, H. D. Burrows, A. J. M. Valente, S. Pradhan, U. Scherf, V. M. M. Lobo, J. Pina and J. Seixas de Melo, *J. Phys. Chem. B*, 2005, **109**, 19108.
- For comprehensive reading, see: G. Hermanson, *Bioconjugate Techniques*, Academic Press, San Diego, CA, 1996.
- K. Lee, T. Yucel, D. J. Pochan and J. Kim, manuscript in preparation.
- The ratio of the integration values in the ^1H NMR corresponding to the phenyl rings in the PPE backbone and the *tert*-butyl group in pentatyrosine was in accordance with the calculated value. It is assumed that the polymer chains lay down on the large PS resin surface, such that every carboxyl group of the polymer has reacted with an amine group. For papers on NMR end-analysis, see: S. Jo, H. Shin and A. G. Mikos, *Biomacromolecules*, 2001, **2**, 255; X. Kong and S. A. Jenekhe, *Macromolecules*, 2004, **37**, 8180.
- Due to the hydrophobic tyrosine unit, solubility of the PPE-pentatyrosine bioconjugate in water significantly decreased. However, the PPE-peptide is completely soluble in DMSO and other organic solvents.