

Synthesis and molecular structure of vanadium(III) dithiolate complexes: a new class of alkene polymerization catalysts

Zofia Janas,^a Lucjan B. Jerzykiewicz,^a Raymond L. Richards^b and Piotr Sobota^{*a}

^a Faculty of Chemistry, University of Wrocław, 14 F. Joliot-Curie, 50-383 Wrocław, Poland.
E-mail: plas@wchuwr.uni.wroc.pl

^b Nitrogen Fixation Laboratory, John Innes Centre, Norwich Research Park, Norwich, UK NR4 7UH


Received (in Basel, Switzerland) 3rd February 1999, Accepted 24th April 1999

The synthesis and catalytic activity in ethylene polymerization of new vanadium complexes of 2,2'-oxydiethanethiolate [O(CH₂CH₂S)₂]²⁻ are described; the complexes [V(μ-DIPP)₂{O(CH₂CH₂S)₂}Li(MeCN)₂] and [V(DIPP){O(CH₂CH₂S)₂}(py)] [DIPP = (OC₆H₃Prⁱ₂-2,6)⁻] have been structurally characterized.

The synthetic development of well defined single-site vanadium catalysts for alkene polymerization is of extremely high industrial importance^{1,2} because such catalysts are able to produce high molecular weight polymers with narrow molecular weight distribution as well as α-olefin copolymers with high α-olefin incorporation.^{3,4} A recent trend has been the incorporation of sulfur-containing ligands: e.g. (TBP)TiCl₂/MAO catalyst [TBP = 2,2'-thiobis(6-*tert*-butyl-4-methylphenoxide), MAO = methylaluminoxane] was ten-fold more effective in ethylene polymerization than are metallocenes catalysts.^{5,6} Moreover, it is well known that vanadium-based enzyme *nitrogenase* in which vanadium is thought to be bound to sulfur-, oxygen- and nitrogen-donor ligands is able to convert acetylene into ethylene and ethane.⁷ These aspects of vanadium catalysis prompted us to prepare novel vanadium compounds with thiolate ligands such as 2,2'-oxydiethanethiolate [O(CH₂CH₂S)₂]²⁻ and study their reactions with alkenes, particularly their potential as precursors of new ethylene polymerization catalysts.


Studies of the oxidation state of active vanadium catalysts for ethylene polymerization by different investigators has led to the proposal that V^{III} and V^{IV} represent the important oxidation states in the ethylene polymerization process.^{8,9} Herein we report the synthesis, structural characterization and catalytic activity of the vanadium(III) heterodinuclear complexes [V(μ-DIPP)₂{O(CH₂CH₂S)₂}Li(L)₂] **1**, **2** and the mononuclear complex [V(DIPP){O(CH₂CH₂S)₂}(py)] **3** [DIPP = (OC₆H₃-Prⁱ₂-2,6)⁻, py = C₅H₅N; L = THF **1** or MeCN **2**].

Dark pink [V(μ-DIPP)₂{O(CH₂CH₂S)₂}Li(THF)₂] **1** was prepared by reaction of [V(μ-DIPP)₂(DIPP)₂Li(THF)]¹⁰ with an excess of O(CH₂CH₂SH)₂ in a mixture of hexane-THF [eqn. (1)].

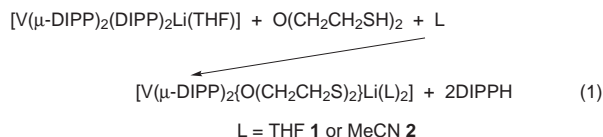

Recrystallization of **1** from MeCN gave new X-ray quality red crystals of [V(μ-DIPP)₂{O(CH₂CH₂S)₂}Li(MeCN)₂] **2** [eqn. (1)]. Addition of pyridine to toluene solutions of compounds **1** and **2** breaks up the heterodinuclear structures forming the monomeric species [V(DIPP){O(CH₂CH₂S)₂}(py)] **3** in 85% yield [eqn. (2)].

Complex **3** can be also prepared but in lower yield (53%), by reaction of [V(DIPP)₃(py)₂]¹¹ with 1 equiv. of O(CH₂CH₂SH)₂ in toluene. The temperature independent (80–293 K) magnetic moments of 2.6 and 2.7 μ_B per vanadium atom in **2** and **3** respectively, are consistent with non-interacting d² centres.

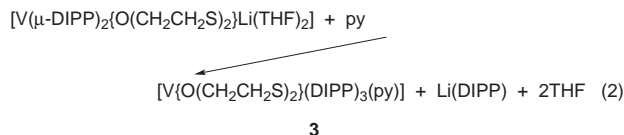

The crystal structure of the heterodinuclear complex **2** is shown in Fig. 1.† Complex **2** contains a five-coordinate V^{III} center adopting a slightly distorted trigonal bipyramidal geometry. Two sulfur atoms from the O(CH₂CH₂S)₂²⁻ ligand and an aryloxy oxygen O(21) of DIPP occupy the equatorial positions. The second aryloxy oxygen O(11) and the ether oxygen O(1) from the O(CH₂CH₂S)₂²⁻ group fill the axial sites. Both aryloxy oxygen atoms are engaged in the bridging interaction to Li, inducing distortion from the ideal trigonal bipyramidal geometry. A similar double-bridged V(μ-DIPP)₂Li unit is present in the starting material [V(μ-DIPP)₂(DIPP)₂Li(THF)]. The average V–S(thiolate) distance in **2** is 2.290(4) Å, within the range expected for V–S single bonds and comparable to other vanadium(III) thiolato complexes.^{12–15}

The X-ray analysis of **3** reveals a mononuclear complex [V(DIPP){O(CH₂CH₂S)₂}(py)] with slightly distorted trigonal-bipyramidal coordination around the vanadium centre (Fig. 2).† The V–S and V–O(aryloxy) bond distances in the equatorial plane [V–S 2.2970(9), 2.2987(8) Å; V–O 1.8619(13) Å] do not differ significantly from those found in complex **2**. The V–N

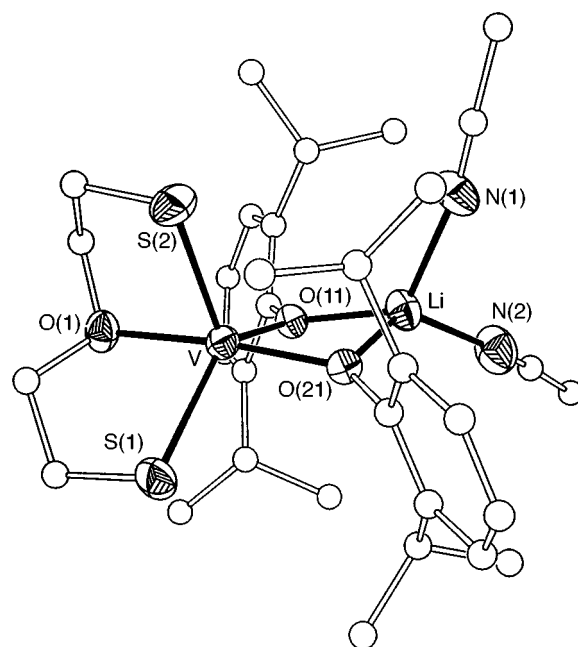


Fig. 1 The molecular structure of **2** (the displacement ellipsoids are drawn at the 30% probability level; the C bonded H atoms are excluded for clarity; the C atoms are represented by circles of arbitrary radii). Selected bond lengths (Å): V–S(1) 2.294(1), V–S(2) 2.286(2), V–O(1) 2.154(2), V–O(11) 1.917(2), V–O(21) 1.977(2), V–Li 2.830(5), Li–O(11) 1.942(6), Li(1)–O(21) 1.903(5), Li–N(1) 2.030(6), Li–N(2) 2.015(6).

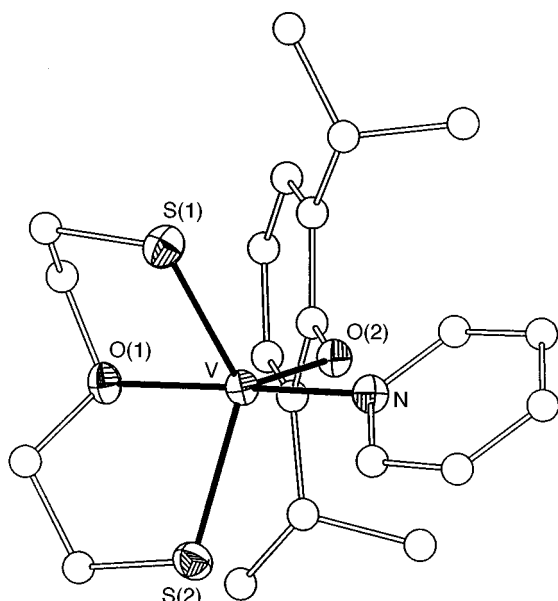


Fig. 2 The molecular structure of **3** (the displacement ellipsoids are drawn at the 30% probability level; the C bonded H atoms are excluded for clarity; the C atoms are represented by circles of arbitrary radii). Selected bond lengths (Å): V–S(1) 2.2970(9), V–S(2) 2.2987(8), V–O(1) 2.1195(14), V–O(2) 1.8619(13), V–N 2.1306(17).

Table 1 Polymerization^a of ethylene with vanadium–MgCl₂–AlEt₂Cl catalysts

Catalyst system	T/K	Productivity ^{b/} kg(g V h) ⁻¹	M _w /M _n	d/g cm ⁻³
1/MgCl ₂ /AlEt ₂ Cl	323	39	2.7	0.964
3/MgCl ₂ /AlEt ₂ Cl	323	20	3.8	0.961

^a Conditions: [V]₀ = 0.02 mmol dm⁻³, [Al] = 10 mmol dm⁻³, Mg : V = 10, P_{ethylene} = 0.6 MPa. ^b Mass in kg of polymer formed per g of vanadium atoms in 1 h.

distance is also near the values observed in the other V^{III}-pyridine complexes.¹¹ Compounds **1** and **3**, in combination with AlEt₂Cl and MgCl₂, are highly active towards ethylene polymerization.¹⁶ Yields and polymer characterization data are listed in Table 1. The amount of polyethylene (PE) produced by the catalysts is comparable to the catalyst based on VCl₃.¹⁷ The molecular weight distribution M_w/M_n of the PE obtained in the first catalytic system is < 3, and in the second one is > 3. These findings indicate that the polymerization process in 1/MgCl₂/AlEt₂Cl proceeds on a single vanadium site in a homogeneous system, however for 3/MgCl₂/AlEt₂Cl a heterogeneous system appears to operate. Hence, the catalytic activity of the 1/MgCl₂/AlEt₂Cl system is almost twice that of the 3/MgCl₂/AlEt₂Cl system.

To our knowledge complexes **1** and **3** represent the first examples of vanadium-thiolate catalyst precursors for ethylene polymerization. We suggest that the V{O(CH₂CH₂S)₂} moiety is maintained in the catalyst assembly and that the geometry of such catalytic species plays an important role in determining the reactivity. It is worth noting that vanadium catalysts are very important in ethylene–propylene rubber production.¹⁸

The authors thank the State Committee for Scientific Research for financial support of this work (Grant No. 3 T09A 131 15), and Dr Krzysztof Szczegot of the University of Opole for preliminary polymerization tests.

Notes and references

† Crystal data for **2** and **3**: The crystals were sealed in glass capillaries under a dinitrogen stream. Preliminary examination and data collections were carried out on a KUMA KM-4 four-circle diffractometer¹⁹ using graphite-

monochromated Mo-Kα radiation (0.71073 Å) with ω-2θ scan mode. The structures were solved by direct methods (SHELXS97)²⁰ and refined on F² by full-matrix least-squares (SHELXL97).²¹ The carbon bonded H-atoms were included in calculated positions and refined using a riding model with isotropic displacement parameters equal to 1.2 U_{eq} of the attached C atom. *Crystal structure analyses*: **2**: C₃₂H₄₈LiN₂O₃S₂V, M = 630.72, monoclinic, space group C2/c, a = 27.297(5), b = 18.880(4), c = 17.444(3) Å, β = 126.76(3)°, U = 7203(2) Å³, Z = 8, D_c = 1.163 Mg m⁻³, μ = 0.422 mm⁻¹, F(000) = 2688. A total of 4086 reflections with 2θ ≤ 50° were collected, of which 3463 had I ≥ 2σ(I). Final residuals are R₁ = 0.0357, wR₂ = 0.1007 and GOF = 1.075 for 380 variables.

3: C₂₁H₃₀NO₂S₂V, M = 443.52, monoclinic, space group P2₁/n, a = 10.022(3), b = 12.156(4), c = 18.628(4) Å, β = 98.44(3)°, U = 2244.8(11) Å³, Z = 4, D_c = 1.312, μ = 0.643 mm⁻¹, F(000) = 936. A total of 3526 reflections with 2θ ≤ 50° were collected, of which 3108 had I ≥ 2σ(I). Final residuals are R₁ = 0.0269, wR₂ = 0.0760 and GOF = 1.124 for 248 variables.

CCDC 182/1237. See <http://www.rsc.org/suppdata/cc/1999/1015/> for crystallographic files in .cif format.

- V. J. Murphy and H. Turner, *Organometallics*, 1997, **16**, 2495; F. J. Feher and J. F. Walzer, *Inorg. Chem.*, 1991, **30**, 1689; F. J. Feher, J. F. Walzer and R. L. Balnski, *J. Am. Chem. Soc.*, 1991, **113**, 3618; F. J. Feher and R. L. Balnski, *Organometallics*, 1993, **12**, 958; *J. Am. Chem. Soc.*, 1992, **114**, 5886.
- S. Scheuer, J. Fischer and J. Kress, *Organometallics*, 1995, **14**, 2627.
- W. L. Carrick, *J. Am. Chem. Soc.*, 1958, **80**, 6455; W. L. Carrick, R. W. Kluiber, E. F. Bonner, L. H. Wartman, F. M. Rugg and J. J. Smith, *J. Am. Chem. Soc.*, 1960, **82**, 3883; D. L. Christman, *J. Polym. Sci., Polym. Chem. Ed.*, 1972, **10**, 472; M. H. Lehr and C. J. Carmen, *Macromolecules*, 1969, **2**, 217; M. H. Lehr, *Macromolecules*, 1968, **1**, 178.
- Y. Doi, N. Tokuhiko, M. Nunomura, H. Miyake and K. Soga, in *Transition Metals and Organometallics as Catalysts for Olefin Polymerization*, ed. W. Kaminsky and H. Sinn, Springer-Verlag, Berlin, 1998; V. E. Junghanns, V. A. Gumboldt and G. Bier, *Makromol. Chem.*, 1962, **58**, 18; V. A. Gumboldt, J. Helberg and G. Schleitzer, *Makromol. Chem.*, 1967, **101**, 229.
- W. Kaminsky, *J. Chem. Soc., Dalton Trans.*, 1998, 1413; M. Bochmann, *J. Chem. Soc., Dalton Trans.*, 1996, 255.
- T. Miyatake, K. Mizunuma and M. Kakugo, *Makromol. Chem., Macromol. Symp.*, 1993, **66**, 203; S. Fokkman, T. P. Spaniol, H.-C. Kang, W. Massa and J. Okuda, *Organometallics*, 1996, **15**, 5069.
- See for example R. R. Eady and G. J. Leigh, *J. Chem. Soc., Dalton Trans.*, 1994, 2739 and refs. therein.
- F. J. Karol, K. J. Cann and B. E. Wagner, in *Transition Metals and Organometallics as Catalysts for Olefin Polymerization*, ed. W. Kaminsky and H. Sinn, Springer, New York, 1988, pp. 149–161.
- P. D. Smith, J. L. Martin, J. C. Huffman, R. L. Bansemer and K. G. Caulton, *Inorg. Chem.*, 1985, **24**, 2997.
- W. C. A. Wilisch, M. J. Scott and W. H. Armstrong, *Inorg. Chem.*, 1988, **27**, 4335.
- S. Gambarotta, F. Van Bolhuis and M. Y. Chiang, *Inorg. Chem.*, 1987, **26**, 4303.
- C. R. Randall and W. H. Armstrong, *J. Chem. Soc., Chem. Commun.*, 1988, 986.
- S. C. Davies, D. L. Hughes, Z. Janas, L. B. Jerzykiewicz, R. L. Richards J. R. Sanders and P. Sobota, *Chem. Commun.*, 1997, 1261.
- G. Henkel, B. Krebs and W. Schmidt, *Angew. Chem., Int. Ed. Engl.*, 1992, **31**, 1366.
- R. W. Wiggins, J. C. Huffman and G. Christou, *J. Chem. Soc., Chem. Commun.*, 1983, 1313; D. Szymies, B. Krebs and G. Henkel, *Angew. Chem., Int. Ed. Engl.*, 1983, **22**, 885; J. R. Dorfman and R. H. Holm, *Inorg. Chem.*, 1983, **22**, 3179.
- In a typical test of ethylene homopolymerization the catalyst was prepared by milling a *n*-hexane slurry of [MgCl₂(THF)₂] with the vanadium compound and AlEt₂Cl as the cocatalyst. In all cases studied an immediate exotherm indicated polymerization; reaction temperatures were kept at 323 K and pressure at 0.6 MPa. After 1 h the reactor was opened and the polymer was filtered off, washed with acidic methanol and water, and dried *in vacuo*.
- K. J. Cann, D. L. Miles and F. J. Karol, *US Pat.*, 4 670 526, 1987; X. Bai, *US Pat.*, 5 410 003, 1995.
- F. J. Karol, *Macromol. Symp.*, 1996, **154**, 83.
- Kuma Diffraction. Kuma KM4 software. User's Guide, version 6.1 Kuma Diffraction, Wrocław, Poland, 1996.
- G. M. Sheldrick, *Acta Crystallogr., Sect. A*, 1990, 467.
- G. M. Sheldrick, SHELXL97, Program for the Refinement of Crystal Structures, University of Göttingen, Germany, 1997.