

Highly active meso–microporous TaON photocatalyst driven by visible light

Seigo Ito, K. Ravindranathan Thampi,* Pascal Comte, Paul Liska and Michael Grätzel

Received (in Cambridge, UK) 31st August 2004, Accepted 27th September 2004

First published as an Advance Article on the web 24th November 2004

DOI: 10.1039/b413250e

TaON was found to be *ca.* 20 times more active as a visible light activated photocatalyst for the oxidation of methanol, when compared to the well studied UV-visible activated TiO₂ (P25) catalyst.

Photocatalysis using semiconductors is an actively studied current topic, because of its scope for industrial and scientific applications.^{1,2} One such application is the total or partial mineralization of contaminants in air and water. Most of the studies have used TiO₂ (band gap = 3.2 eV for anatase and 3.0 eV for rutile) as the photocatalyst, due to its stability and the relatively high activity compared to other photocatalysts. Yet, the potential of photocatalysis in practical applications has not been fully realized due to the inactivity of TiO₂ under visible light irradiation and other system constraints or inefficiencies. The efficiency of TiO₂ photocatalytic systems is rather dismal (often less than 2%). Therefore, it is important to discover a new visible-light-driven photocatalyst,^{3–6} which is much more active than the UV-only active TiO₂. So far, in our knowledge, the best visible-light-driven photocatalyst has been carbonate-doped TiO₂, whose activity was four times higher than pure TiO₂ (ST-01 grade, Ishihara Sangyo), when illuminated under a xenon lamp using wavelengths longer than 350 nm.⁴

In this work, we have fabricated a strikingly active visible-light-driven TaON photocatalyst, for oxidation of an organic molecule in water and its activity was found to be *ca.* 20 times better than that of UV-only active TiO₂ (Degussa P25). P25 is, in fact, reported to be more active than ST-01,⁷ and over the years has become a benchmark photocatalyst for comparison of catalytic activity.¹ TaON photocatalyst was earlier reported for photocatalytic hydrogen generation from water and methanol.^{5,6} In this report, we show that the meso–microporous structure of TaON could significantly aid the photoactivity of the material to obtain superior catalytic activity.

The nitriding of Ta₂O₅ (Fluka) to TaON was performed at 850 °C for 15 h under a flow (0.3 L min⁻¹) of nitrogen gas bubbled through 500 mL of NH₄OH aq (28%), which was replaced with a new solution after half the synthesis time (7.5 h). 3 wt% Pt was loaded on TaON (100 mg) by the photocatalytic reduction of H₂PtCl₄ in Ar purged 20% aqueous ethanol solution (10 mL) under visible light irradiation, for 2 h. The resulting photocatalysts were dried in a rotary evaporator until they became powdered and kept in vacuum at 60 °C for a further period of 2 h. Methanol was selected for the photocatalytic reaction studies, because it is a simple toxic molecule to be removed from certain industrial waters. Photocatalytic experiments were carried out under

simulated sunlight (Atlas Suntest CPS+ model lamp), using a batch reactor (volume 60 ml) containing 100 mg of photocatalyst and 10 ml of a 20% aqueous methanol solution purged with O₂. The intensity of the simulated sunlight was equivalent to 1 sun as determined by a calibration cell. A UV cut-off film (<400 nm, University Products) was used, when required, to wrap the batch reactors to admit only the visible light fraction into the reactor. The solution was stirred with a magnetic bar during the photoreaction. The amount of CO₂ produced by the reaction was measured by gas chromatography.

Fig. 1 shows the photocatalytic oxidation of 20% (v/v) methanol in water, under simulated sunlight. TiO₂ showed considerable activity under full sunlight exposure, but did not exhibit any significant activity with only visible light irradiation (only a trace of CO₂ was observed, resulting from the light absorption up to 410 nm by the rutile component). TaON showed very high activity under visible light, when compared to TiO₂ (P25) exposed to

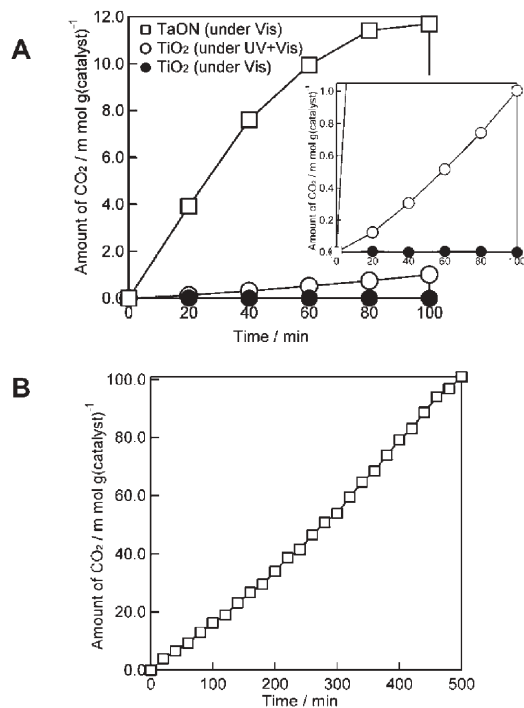


Fig. 1 Photocatalytic oxidation of methanol (20% in H₂O) to CO₂ under simulated sunlight; (A) batch tests of TaON/Pt (3 wt%) (with an UV cut-off filter; Vis (>400 nm)), TiO₂ (P25) under UV + Vis and TiO₂ (P25) under Visible, and (B) the amount of CO₂ produced by TaON/Pt (Vis) during 500 min with O₂ addition after every 60 min. Inset in (A) is a magnified image of (A) at the low end of Y-scale.

*ravindranathan.thampi@epfl.ch

simulated full beam sunlight. The activity of TaON (Vis) was found to be 19.3 times higher than that of TiO₂ (P25) (UV + Vis) after 60 min of reaction. The batch mode activity of TaON photocatalyst reached a plateau at 100 min, since most of the available O₂ in the batch reactor was consumed to form CO₂, within this time. Separate experiments were carried out to ascertain the involvement of TaON in the reaction. Fig. 1(B) shows typical data from one such run, where the reaction was allowed to continue for 500 min and the TaON generated 101×10^{-3} mol of CO₂ per gram of catalyst, by the photooxidation of methanol in water. One gram of TaON corresponds to only 4.7×10^{-3} mol. Therefore, the turnover number recorded within 500 min works out to be 21.5 (mol(CO₂) per mol(TaON)). This is an indication that the observed methanol oxidation is indeed catalytic and that TaON is sufficiently stable for photocatalytic applications. Studies to evaluate the long-term stability of TaON as a catalyst and methods to immobilize it on solid transparent substrates⁸ are currently progressing.

Fig. 2 shows the pore-size distribution of Ta₂O₅ and TaON. The diameter of channels inside TaON, which were observed as holes on its surface in SEM images (Fig. 3(B)),⁶ has in fact a size distribution between 10 and 100 nm (Fig. 2(A)) with a distribution maximum centered at 28.6 nm. As the surface of Ta₂O₅ is smooth without many pores (Fig. 3(A)), NH₃ could only act slowly on the surface and transform the oxide into an oxynitride. The reaction proceeds from Ta₂O₅ to TaON through an intermediate, with an accompanying molecular volume change, causing pore generation. As the porosity becomes very high, the material becomes friable and breaks down to smaller particles (Fig. 3(B)). This mechanism seems credible when the enlarged surface area of the oxynitride is also considered. Ta₂O₅ and TaON showed BET areas of 0.691 and 4.64 m² g⁻¹, respectively. The enhanced surface area of TaON comes from the newly formed micropores (<2 nm). These

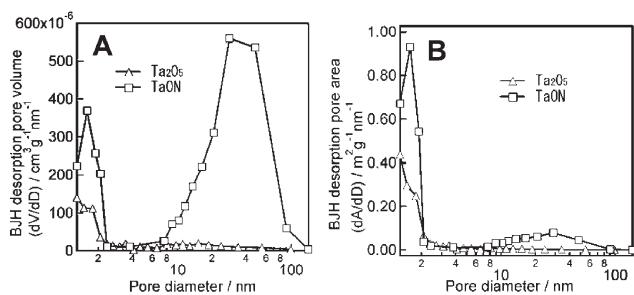


Fig. 2 Pore-size distribution of Ta₂O₅ and TaON: (A) BJH pore volume distribution (dV/dD) and (B) pore area distribution (dA/dD).

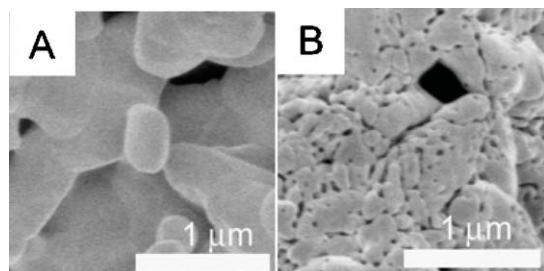


Fig. 3 SEM of Ta₂O₅ (A) and TaON (B).

micropores could act as a reservoir for organic molecules, and the pore volume of TaON originates from mesopores, which can efficiently transport the reactant and product molecules between the inside and the outside regions of particles.⁹ An efficient transport of this nature should improve the catalytic activity of the material. Often inefficient molecular transport leads to poor catalytic activity.¹⁰

One of the major factors affecting the activity of a photocatalyst is its BET surface area, because, in general, the surface interactions yield sorption isotherms of a Langmuirian nature.¹ A photocatalyst with large surface area generally shows higher catalytic activity, provided all other reaction conditions are comparable and well controlled. However, since the surface area of TaON was observed to be ten times smaller than that of TiO₂ (P25, ca. 55 m² g⁻¹), some other factors must be favorably influencing the activity of TaON. The first reason is attributed to the larger number of absorbable photons in the visible light of the simulated sunlight. The second reason could be its meso-microporous structure: the micropores could seize the reactant molecules like a molecular sieve and the mesopores transport them easily to the numerous active sites available on the catalyst surface.⁹ Removal of the reaction products from the active sites is also facile, when the catalyst is sufficiently porous. Since it was reported that small pores (10 nm) hindered the transport of molecules (I⁻),¹¹ the smaller micropores are believed to be contributing only very little to the molecular transport. The movement of molecules would be smooth through the mesopores. The third reason for the relatively better activity of TaON photocatalyst may be that the quantum yield of electron-hole recombination is smaller in this new catalyst, when compared to TiO₂. In TiO₂, the quantum yield of electron-hole recombination is substantially larger than that of radical generation.¹² This aspect needs more detailed studies.

In summary, TaON showed superior photocatalytic activity for oxidation of methanol under simulated sunlight. To our knowledge, for this reaction, no other visible-light-driven photocatalyst has surpassed the activity of the benchmark TiO₂ (P25) catalyst under full beam sunlight irradiation. The photocatalytic activity of this meso-microporous TaON was 19.3 times higher than that of TiO₂ (P25) under the simulated sunlight. The reaction over TaON has been shown to be photocatalytic and not stoichiometric. This TaON photocatalyst may become useful in processes related to the purification of contaminated water. In future, other meso-microporous nitride materials may become useful materials in photocatalysis. A reduction in the level of Pt loading or finding an alternative to Pt will be helpful. Future research will focus on this aim.

Funding was provided by the Swiss confederation (CTI/Top Nano 21: Project No. 5904.1), for a collaborative study with Christ AG (Switzerland). The authors thank Dr Gvadecak, Mr B. Senior, Dr G. Rothenberger and Dr R. Bashyam (EPFL) for TEM, SEM, RDS and XPS, respectively. We also thank Mr Kuze (Graduate School of Materials Science, Nara Institute of Science and Technology, Japan) for XRD and Mr Kandavelu (EPFL) for his help in the laboratory.

Seigo Ito, K. Ravindranathan Thampi,* Pascal Comte, Paul Liska and Michael Grätzel
Laboratory of Photonics and Interfaces (LPI), Institute des Sciences et Ingenierie Chimiques (ISIC), Ecole Polytechnique Fédérale de Lausanne (EPFL), CH-1015, Lausanne, Switzerland.

Notes and references

- 1 A. Mills, R. H. Davis and D. Worsley, *Chem. Soc. Rev.*, 1993, **22**, 417; A. L. Linsebigler, G. Lu and J. T. Jr. Yates, *Chem. Rev.*, 1995, **95**, 735; M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, *Chem. Rev.*, 1995, **95**, 69.
- 2 A. Fujishima, K. Hashimoto and T. Watanabe, *TiO₂ Photocatalysis – Fundamentals and Applications*, BKC, Inc., Tokyo, Japan, 1999.
- 3 R. Asahi, T. Morikawa, T. Ohwaki, K. Aoki and Y. Taga, *Science*, 2001, **293**, 269; Z. Zou, J. Ye, K. Sayama and H. Arakawa, *Nature (London)*, 2001, **414**, 625; S. Sakthivel and H. Kisch, *Angew. Chem., Int. Ed.*, 2003, **42**, 4908; H. Irie, Y. Watanabe and K. Hashimoto, *Chem. Lett.*, 2003, **32**, 772; K. Domen, J. N. Kondo, M. Hara and T. Takata, *Bull. Chem. Soc. Jpn.*, 2000, **73**, 1307; A. Kudo, *Catal. Surv. Asia*, 2003, **7**, 31; H. G. Kim, D. W. Hwang and J. S. Lee, *J. Am. Chem. Soc.*, 2004, **126**, 8912; W. Zhao, W. Ma, C. Chen, J. Zhao and Z. Shuai, *J. Am. Chem. Soc.*, 2004, **126**, 4782.
- 4 T. Ohno, T. Tsubota, K. Nishijima and Z. Miyamoto, *Chem. Lett.*, 2004, **33**, 750.
- 5 G. Hitoki, T. Tanaka, J. N. Kondo, M. Hara, H. Kobayashi and K. Domen, *Chem. Commun.*, 2002, 1698.
- 6 M. Hara, T. Takata, J. N. Kondo and K. Domen, *Catal. Today*, 2004, **90**, 313.
- 7 T. Ohno, K. Sarukawa, K. Tokieda and M. Matsumura, *J. Catal.*, 2001, **201**, 82.
- 8 M. R. Dhananjeyan, J. Kiwi and K. Ravindranathan Thampi, *Chem. Commun.*, 2000, 1443.
- 9 L. Zhang and J. C. Yu, *Chem. Commun.*, 2003, 2078.
- 10 Y. Kado, M. Atobe and T. Nonaka, *Ultrason. Sonochem.*, 2001, **8**, 69.
- 11 Z. Kebede and S.-E. Lindquist, *Sol. Energy Mater. Sol. Cells*, 1998, **51**, 291.
- 12 L. Davydov and P. G. Smirniotis, *J. Catal.*, 2000, **191**, 105.