

# A new approach to grafting a monolayer of oriented $Mn_{12}$ nanomagnets on silicon†

Benoit Fleury,<sup>a</sup> Laure Catala,<sup>\*a</sup> Vincent Huc,<sup>a</sup> Christophe David,<sup>b</sup> Wang Zhao Zhong,<sup>b</sup> Pascale Jegou,<sup>c</sup> Laurent Baraton,<sup>c</sup> Serge Palacin,<sup>c</sup> Pierre-Antoine Albouy<sup>d</sup> and Talal Mallah<sup>\*a</sup>

Received (in Cambridge, UK) 24th December 2004, Accepted 8th February 2005

First published as an Advance Article on the web 25th February 2005

DOI: 10.1039/b419271k

The functionalisation of a Si(100) silicon wafer allows for the oriented grafting of a monolayer of  $Mn_{12}$  nanomagnets using a two-step procedure.

The discovery of the blocking and the quantum tunnelling of the magnetization in molecular systems was a major breakthrough in the area of molecular magnetism.<sup>1</sup> The first complex where these phenomena were observed is  $[Mn_{12}O_{12}(CH_3COO)_{16}(H_2O)_4]$  ( $Mn_{12}$ -ac), described by Lis in 1980.<sup>2</sup> The blocking of magnetization is due to the high spin ground state of the molecule ( $S = 10$ ) and the uniaxial magnetic anisotropy responsible for a relatively high barrier to the reorientation of the magnetization below 8 K.<sup>3</sup> Such behaviour leads to a magnetic bistability that may be utilised to store information (even if it occurs below 4 K in the case of  $Mn_{12}$  derivatives), where a bit of information has the size of one molecule (around 1.2 nm).

One of the very first steps for reaching such a goal is to organize the molecules as a monolayer on a substrate in order to address a single molecule. Different approaches have been reported recently: (i) using the Langmuir–Blodgett technique;<sup>4</sup> (ii) grafting on a gold substrate by using a thiol modified  $Mn_{12}$  complex;<sup>5</sup> (iii) deposition of the biphenyl derivative of  $Mn_{12}$  and nanopatterning on polycarbonate films;<sup>6</sup> and (iv) deposition of monolayer and multilayers on gold.<sup>7</sup> Very recently, grafting  $Mn_{12}$ -ac on Si(100) has been reported.<sup>8</sup>

The next step is to conceive an approach where grafting leads to an orientation of the molecules on the substrate. We show here that by using a mixed  $Mn_{12}$  complex (*i.e.* containing two different carboxylate groups) it is possible to graft a monolayer in an oriented manner on a silicon substrate.  $Mn_{12}$ -ac is made of a  $Mn_{12}O_{12}$  (4 Mn(IV) and 8 Mn(III)) core which has a disk-like shape surrounded by 16 acetate groups: 8 in equatorial and 8 in axial positions and 4 water molecules (see Scheme 1).


The Mn(III)-O long distances (Jahn–Teller effect) are those with the axial ligands. Christou and co-workers elegantly demonstrated that due to  $pK_a$  differences between carboxylic acids it is possible (i) to substitute the acetate groups by other carboxylates in solution keeping the oxide core intact, and (ii) to prepare mixed complexes from the selective substitution of the axial or the equatorial carboxylates.<sup>9,10</sup> We took advantage of this particular reactivity and selected a  $Mn_{12}$  complex possessing dichloroacetate groups in axial positions and *tert*-butyl acetate groups in equatorial positions, *i.e.*  $Mn_{12}O_{12}(CHCl_2COO)_8(tBuCH_2COO)_8(H_2O)_3$  (**1**).<sup>10†</sup> Reacting **1** with a carboxylic acid-functionalised silicon wafer induces a selective substitution of either axial or equatorial carboxylates of the molecule by carboxylic acid groups originating from the substrate. The choice of axial chlorinated carboxylates allows to probe the ligands exchange by X-ray photoelectron spectroscopy (XPS).

Direct immersion of a Si–H(100) surface§ in neat distilled undecylenic acid (110 °C, 12 h under Ar) leads to thermal grafting of the acid *via* its alkene end.<sup>11,12</sup> The hypothesis of formation of silyl esters emitted in the case of this coupling agent, was discarded by complementary experiments.<sup>13</sup> Attenuated transmission reflection infra-red (ATR-FTIR) spectroscopy shows that most of the available Si–H functions have reacted as the intensity of the

† Electronic supplementary information (ESI) available: Spectroscopic data of deposited and grafted  $Mn_{12}$  sample (Figs. S1–S6). See <http://www.rsc.org/suppdata/cc/b419271k/>

\*laurecatala@icmo.u-psud.fr (Laure Catala)

mallah@icmo.u-psud.fr (Talal Mallah)

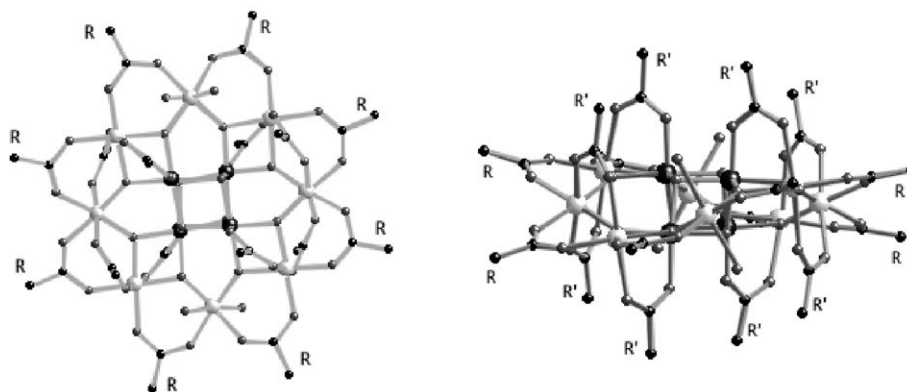

Scheme 1

2111  $\text{cm}^{-1}$  peak (Si–H stretching vibrations) decreased (see ESI).<sup>†</sup> Indeed, only 50% of the Si–H functions may react for steric reasons.<sup>14</sup> Furthermore, the spectrum showed the presence of methylene stretching vibrations at 2855 and 2927  $\text{cm}^{-1}$  (see ESI)<sup>†</sup> as well as the carbonyl stretching of the carboxylic acid at 1718  $\text{cm}^{-1}$  (see ESI).<sup>†</sup> No C–H vibration due to terminal alkene groups could be observed, thus ascertaining the absence of grafting *via* silyl ester groups.

Grafting of **1** was achieved by immersion of the previous modified substrate in a degassed  $10^{-4}$  M toluene solution of the complex for 1 h.<sup>¶</sup> The obtained wafer was thoroughly sonicated three times ( $3 \times 10$  min) in 30 ml of distilled toluene to remove any physisorbed molecules. ATR-FTIR spectra show that the band at 1718  $\text{cm}^{-1}$  almost vanishes after the immersion of the substrate in the  $\text{Mn}_{12}$  solution which is the first evidence for the grafting of molecules by carboxylate substitution (see ESI).<sup>†</sup>


XPS studies were carried out<sup>||</sup> on: (i) native silica where free molecules of **1** were merely deposited by evaporation of a droplet ( $10^{-3}$  M in toluene) on the substrate to serve as a reference; (ii) the acid-functionalised Si(100) substrate with grafted  $\text{Mn}_{12}$ . The XPS spectra of the references show all the expected characteristics (see binding energies in Table 1) already reported elsewhere.<sup>15</sup> The Mn2p spectrum has two peaks at 653.8 and 642.2 eV, corresponding to the excitation from the  $2p_{1/2}$  and  $2p_{3/2}$  levels, respectively. Since the Mn2p excitations are generally not sensitive to the oxidation state of the Mn atoms, the Mn3s spectrum was registered (native silica). The spectra obtained for the grafted  $\text{Mn}_{12}$  sample reveal the same features as the reference sample (Table 1). The energy difference ( $\Delta E$ ) between the Mn3s peaks of the reference and the grafted sample are equal to 5.4 and 5.5 eV, respectively (Fig. 1), close to the value reported for manganites with the average oxidation state of 3.3.<sup>16</sup> This is the best evidence for the integrity of the grafted complex.

The ATR-FTIR and XPS data insure that **1** has been grafted on the substrate but do not give evidence that the sample analyzed is a monolayer of  $\text{Mn}_{12}$  molecules (some physisorbed molecules may be present on top of the first grafted monolayer despite the sonication process). In order to give such a proof we performed two additional studies. The first one consists in repeating exactly the same chemical process used for the grafting experiment on a substrate functionalised by undecane instead of undecanoic acid (*i.e.*, carboxylic groups from the surface were replaced by methyl groups). The XPS spectra of a sample obtained without the sonication process show all the signals expected for  $\text{Mn}_{12}$

**Table 1** Binding energies (eV) obtained from X-ray photoelectron spectroscopy

	Peaks attribution	Deposited $\text{Mn}_{12}$ <sup>a</sup>	Grafted $\text{Mn}_{12}$
O 1s	COO–/COOH	532.0	532.0
	Mn–O	530.3	530.0
C 1s	CH <sub>2</sub> , CH <sub>3</sub>	284.3	284.5
	C–Cl	287.6	287.6
	C··O	288.7	288.8
Cl 2p	$2p_{1/2}$	201.8	201.9
	$2p_{3/2}$	200.2	200.3
Mn 2p	$2p_{1/2}$	654.6	653.8
	$2p_{3/2}$	642.8	642.2
Mn3s ( $\Delta E$ )	3s multiplet	5.4 eV	5.5 eV

<sup>a</sup> All spectra have been recorded on a silicon wafer.

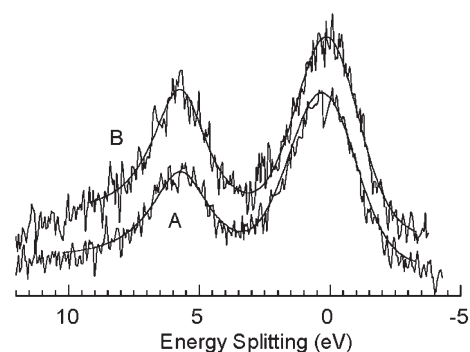


**Fig. 1** Energy splitting of the Mn3s multiplet for deposited  $\text{Mn}_{12}$  on native silica (A) and grafted on Si(100) (B).

demonstrating that the molecules can be physisorbed. However, after sonicating the substrate no XPS signal is present anymore. This is the best evidence that sonication leads to the complete removal of physisorbed molecules while molecules linked by coordination bonds are still present. Thus, only one monolayer of **1** is present on the acid functionalised Si substrate. The definitive evidence comes from X-ray reflectivity studies before and after the grafting of the  $\text{Mn}_{12}$ . From the surface electronic density modification observed by X-ray reflectivity, we deduced an average value of 1.5 nm for the thickness of the  $\text{Mn}_{12}$  layer. (see ESI).<sup>†</sup>

Atomic force microscopy (AFM) imaging was performed on the acid functionalised and on the  $\text{Mn}_{12}$  grafted substrates (Fig. 2).<sup>\*\*</sup> Fig. 2 shows that the average roughness of the acid functionalised Si substrate is lower than 0.5 nm on a large scale which is consistent with a very flat organic monolayer.

For the  $\text{Mn}_{12}$  grafted substrate, the topological image shows a homogeneous layer on a large scale (see ESI)<sup>†</sup> with a roughness between 1 and 1.5 nm. One cannot exclude that the tip measures a thickness corresponding to the length of the organic layer and the grafted  $\text{Mn}_{12}$ . Indeed, the presence of the  $\text{Mn}_{12}$  monolayer may well perturb the underlying organic part and create some holes.

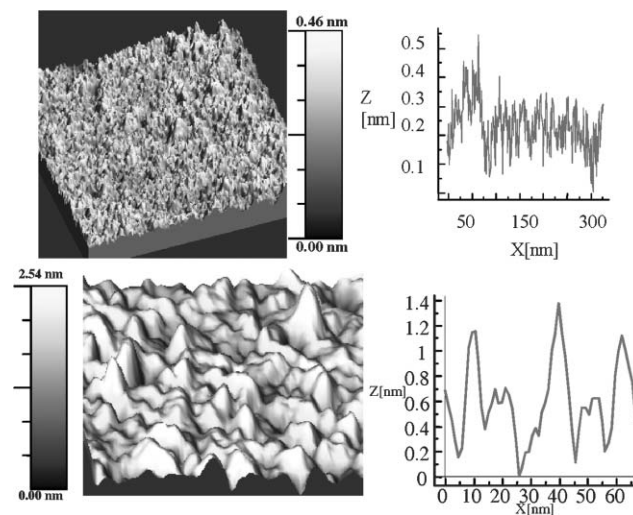

**Fig. 2** (Top) AFM image ( $400 \times 400$  nm) of grafted undecanoic acid on Si(100) wafer and topological profile, (down) AFM image ( $70 \times 70$  nm) of grafted  $\text{Mn}_{12}$  on Si(100) wafer and topological profile.

In order to check the orientation of the grafted molecules, a quantitative analysis of the Mn2p and the Cl2p XPS signals was performed. The Mn/Cl ratios extracted from the XPS data (see ESI)† provide information on the nature of the substituted carboxylates:†† if only equatorial *tert*-butyl acetates were exchanged upon grafting on the acid-functionalised Si surface, no difference in the Mn/Cl ratio should be observed between the free and grafted Mn<sub>12</sub> clusters (theoretical value Mn/Cl = 0.75), whereas axial substitution should lead to a minimum of four remaining dichloroacetates (Mn/Cl = 1.5) out of the eight present on the non-grafted cluster. If substitution occurred in a random way, an average value of 6 remaining dichloroacetates would be expected, thus leading to a ratio Mn/Cl = 1. Hence, the value of Mn/Cl = 0.74 ± 0.04 obtained on the grafted substrate means that the substitution proceeds only through replacement of equatorial *tert*-butyl acetate groups. Such a result may be at a first glance surprising because one may expect a substitution of the axial carboxylate groups less tightly linked to the Mn atoms because of the Jahn–Teller effect. However, this cannot actually be the case because the substrate is functionalised by carboxylic acid groups and not carboxylate groups. As already stated by Christou,<sup>10</sup> the driving force of the reaction is the formation of the weakest acid, hence *tert*-butylacetic acid rather than dichloroacetic acid. Furthermore, the thermodynamically most stable bonds should form, *i.e.* those corresponding to the strongest Mn–carboxylate bonds which are the equatorial ones where no Jahn–Teller effect is present.

In this communication, we have shown the feasibility of grafting on a large scale a homogenous monolayer of Mn<sub>12</sub> derivative on silicon even though no lateral organisation could be observed. The Mn/Cl elements ratios obtained from the analysis of the XPS spectra are in line with a preferred orientation of the Mn<sub>12</sub> molecules with their anisotropy axes parallel to the substrate's surface. This is the first example which shows that orientation of the molecules may be achieved by chemical means. The next step is mastering the orientation of the Mn<sub>12</sub> molecules with their anisotropy axes perpendicular to the 2D substrate.

We thank the CNRS (Centre National de la Recherche Scientifique), the French programme Nanosciences (ACI NANOMAG N45-01), and the European community for financial support (Contract MRTN-CT-2003-504880/RTN Network “QuEMolNa”).

**Benoit Fleury,<sup>a</sup> Laure Catala,<sup>\*a</sup> Vincent Huc,<sup>a</sup> Christophe David,<sup>b</sup> Wang Zhao Zhong,<sup>b</sup> Pascale Jegou,<sup>c</sup> Laurent Baraton,<sup>c</sup> Serge Palacin,<sup>c</sup> Pierre-Antoine Albouy<sup>d</sup> and Talal Mallah<sup>\*a</sup>**

<sup>a</sup>Laboratoire de Chimie Inorganique, UMR CNRS 8613, Université Paris-Sud, 91405 Orsay, France. E-mail: laurecatala@icmo.u-psud.fr; mallah@icmo.u-psud.fr; Fax: (+33) (0)1 69 15 47 54; Tel: (+33) (0)1 69 15 47 49

<sup>b</sup>Laboratoire de Photonique et de Nanostructures, CNRS, route de Nozay, 91460 Marcoussis, France

<sup>c</sup>Chimie des Surfaces et Interfaces, CEA/DRECAM, CEA-Saclay, 91191 Gif sur Yvette, France

<sup>d</sup>Laboratoire de Physique des Solides, Bâtiment 510, Université de Paris-Sud, F-91405 Orsay Cedex, France

## Notes and references

‡ NMR studies in solution show species where equatorial and axial carboxylates have been exchanged. The main species in solution is **1**, since the axial *tert*-butyl resonances are so relatively weak compared to the equatorial *tert*-butyl resonance.

§ Generation of the Si–H functions proceeds through etching the wafers in a piranha bath (30% H<sub>2</sub>O<sub>2</sub>/70% H<sub>2</sub>SO<sub>4</sub>, 20 min, 120°) followed by immersion in a 10% HF solution. This procedure is repeated three times.

¶ Mn<sub>12</sub>O<sub>12</sub>(CHCl<sub>2</sub>COO)<sub>8</sub>(*t*BuCH<sub>2</sub>COO)<sub>8</sub>(H<sub>2</sub>O)<sub>3</sub> was synthesized as previously described<sup>10</sup> and single crystals, checked by X-ray diffraction and elemental analysis, were used in all experiments.

|| XPS spectra were recorded on a Vacuum Generator ESCALAB 210 using an Al K $\alpha$  source monochromatized at 1486.6 eV. The radiations were generated (20 mA, 15 kV) under UHV at 10<sup>−10</sup> mbar. Spectra were recorded at a take-off angle of 90° with respect to the sample plane.

\*\* Lateral resolution is limited by the curvature of the tip (2 nm curvature at the apex). The AFM images were taken in tapping mode (Nanoscope III, Si supersharp tip, Nanosensor at a resonance frequency of 236 KHz).

†† Mn/Cl ratios were calculated using the Mn2p<sub>3/2</sub> spectrum because of much better S/N ratio. The reproducibility of all experiments has been checked (see ESI).†

- 1 L. Thomas, L. Lioni, R. Ballou, D. Gatteschi, R. Sessoli and B. Barbara, *Nature*, 1996, **383**, 145; R. Sessoli, D. Gatteschi, A. Caneschi and M. A. Novak, *Nature*, 1993, **365**, 141; R. Sessoli and D. Gatteschi, *Angew. Chem., Int. Ed.*, 2003, **42**, 268, and references therein.
- 2 T. Lis, *Acta Crystallogr.*, 1980, **B36**, 2042.
- 3 A. Caneschi, D. Gatteschi, R. Sessoli, A. L. Barra, L. C. Brunel and M. Guillot, *J. Am. Chem. Soc.*, 1991, **113**, 5873.
- 4 M. Clemente-León, H. Soyer, E. Coronado, C. Mingotaud, C. J. Gómez-García and P. Delhaès, *Angew. Chem., Int. Ed.*, 1998, **37**, 2842.
- 5 A. Cornia, A. C. Fabretti, M. Pacchioni, L. Zobbi, D. Bonacchi, A. Caneschi, D. Gatteschi, R. Biagi, U. Del Pennino, V. Valentina De Renzi, L. Gurevich and H. S. J. Van der Zant, *Angew. Chem., Int. Ed.*, 2003, **42**, 1642.
- 6 D. Ruiz Molina, M. Mas Torrent, A. I. Balana, N. Domingo, J. Tejada, M. T. Martínez, C. Rovira and J. Veciana, *Adv. Mater.*, 2003, **15**, 42; M. Cavallini, F. Biscarini, J. Gomez-Segura, D. Ruiz and J. Veciana, *Nano Lett.*, 2003, **3**, 1527.
- 7 J. S. Steckel, N. S. Persky, C. R. Martinez, C. L. Barnes, E. A. Fry, J. Kulkarni, J. D. Burgess, R. B. Pacheco and S. L. Stoll, *Nano Lett.*, 2004, **4**, 399.
- 8 G. G. Condorelli, A. Motta, I. L. Fragala, F. Giannazzo, V. Raineri, A. Caneschi and D. Gatteschi, *Angew. Chem., Int. Ed.*, 2004, **43**, 4081.
- 9 P. Artus, C. Boskovic, J. Yoo, W. E. Streib, L.-C. Brunel, D. N. Hendrickson and G. Christou, *Inorg. Chem.*, 2001, **40**, 4199.
- 10 M. Soler, P. Artus, K. Folting, J. C. Huffman, D. N. Hendrickson and G. Christou, *Inorg. Chem.*, 2001, **40**, 4902; N. E. Chakov, W. Wernsdorfer, K. A. Abboud, D. N. Hendrickson and G. Christou, *Dalton Trans.*, 2003, 2243.
- 11 J. M. Buriak, *Chem. Rev.*, 2002, **102**, 5, 1271 and references therein.
- 12 A. B. Sieval, A. L. Demirel, J. W. M. Nissink, M. R. Linford, J. H. Van der Maas, W. H. de Jeu, H. Zuilhof and E. J. R. Sudhölter, *Langmuir*, 1998, **14**, 1759.
- 13 R. Boukherroub, J. T. C. Wojtyk, D. D. M. Wayner and D. J. Lockwood, *J. Electrochem. Soc.*, 2002, **149**, H59.
- 14 A. B. Sieval, V. van den Hout, H. Zuilhof and E. J. R. Sudhölter, *Langmuir*, 2001, **17**, 2972.
- 15 J. S. Kang, J. H. Kim, Y. J. Kim, W. S. Jeon, D. Y. Jung, S. W. Han, K. H. Kim, K. J. Kim and B. S. Kim, *J. Korean Phys. Soc.*, 2002, **40**, L402.
- 16 V. R. Galakhov, M. Demeter, S. Bartkowski, M. Neumann, N. A. Ovechkina, E. Z. Kurmaev, N. I. Lobachevskaya, Ya. M. Mukovskii, J. Mitchell and D. L. Ederer, *Phys. Rev. B*, 2002, **65**, 113102; X. Wang, Q. Cui, Y. Pan and G. Zou, *J. Alloys Compd.*, 2003, **354**, 91.