

Chemical Reviews

Volume 83, Number 1

February 1983

Polymerization of Unsaturated Compounds by Photocycloaddition Reactions¹

WENDELL L. DILLING

Environmental Sciences Research Laboratory, The Dow Chemical Company, Midland, Michigan 48640

Received November 20, 1981 (Revised Manuscript Received October 18, 1982)

Contents

I. Introduction and Scope of the Review	2
II. Cycloadditions Involving Carbon 2 + 2 Addition	3
A. Acyclic Bis- and Poly(cinnamic acid) Derivatives	3
B. Alicyclic Bis(cinnamic acid) Derivatives	4
C. <i>m</i> -Phenylenediacrylic Acid and Esters	4
D. <i>p</i> -Bis(monosubstituted vinyl)benzenes	5
1. <i>p</i> -Phenylenediacrylic Acid, Esters, and Amides	5
2. <i>p</i> -Bis(β -nitro- and β -arylvinyl)benzenes	9
3. <i>p</i> -Di-1,3-butadienylbenzenes	10
E. <i>p</i> -Bis(polysubstituted vinyl)benzenes	11
1. Cyano- <i>p</i> -phenylenediacrylate Esters	11
2. Dicyano- <i>p</i> -phenylenediacrylate Esters	13
3. Bis(α -cyano- β -arylvinyl)benzenes	13
F. 2,5-Distyrylpyridine	16
G. 2,5-Distyrylpyrazine	16
1. Crystal State	16
2. Solution Phase	19
H. Distyryl- <i>s</i> -triazines	20
I. 2,6-Naphthalenediacrylate Ester	20
J. Styrene	21
K. Bis(maleimides)	21
1. Unsubstituted	21
2. Disubstituted	23
3. Tetrasubstituted	24
L. Bis(thymine)	27
M. Bis(coumarins)	27
N. Other Cyclic Olefins	29
O. Bis(maleimides) with Aromatic Hydrocarbons (Copolymerizations)	29
III. Cycloadditions Involving Carbon 2 + 3 Addition	30
A. Benzene	30
B. Substituted Benzenes	32
IV. Cycloadditions Involving Carbon 2 + 4 Addition	32
V. Cycloadditions Involving Carbon 4 + 4 Addition	32
A. Hexaethylidenecyclohexane	32
B. Bis(anthracenes)	33
1. 2-Substituted	33
2. 9-Substituted	34
VI. Cycloadditions Involving Carbon and Oxygen 2 + 2 Addition (Copolymerizations)	37
A. Bis(benzophenones) with Tetramethylallene and Other Diolefins	37
B. Bis(benzophenones) with Furans and Derivatives	39
VII. Summary	41
VIII. Addendum	41
IX. References	45




Wendell L. Dilling was born in Bluffton, IN, in 1936 and received his B.A. degree in chemistry from Manchester College in 1958. His Ph.D. degree in organic chemistry was granted by Purdue University in 1962 where he worked with Dr. Earl T. McBee on reactions of dodecachloropentacyclo[5.3.0.0^{2,6}.0^{3,9}.0^{4,8}]decane and related compounds. He joined The Dow Chemical Company in Midland, MI, in 1962 in their special assignments program, and from 1964 to 1974 worked in their E. C. Britton Research Laboratory on exploratory organic photochemistry. From 1974 to the present he has worked in Dow's Environmental Sciences Research Laboratory in the areas of atmospheric and aquatic environmental photochemistry. The major topics of his 45 publications are synthetic and mechanistic aspects of photocycloaddition reactions, carbenium ion rearrangements in the pentacyclo[5.3.0.0^{2,5}.0^{3,9}.0^{4,8}]dec-6-yl system, pentacyclo[5.3.0.0^{2,6}.0^{3,9}.0^{4,8}]decane chemistry, monohalocarbenoid species formation and reactions, and the phototransformation of organic compounds in the atmosphere. He is active in the American Chemical Society, having served as a councilor from the Midland Section since 1976 and on the Society Committee on Publications since 1977. He was the general chairman of the 14th Central Regional ACS Meeting in 1982.

reactions have been reviewed previously.^{8,44-47}



Some side reactions that occur during the polymerizations are considered briefly in this review. These side reactions reduce the achievable molecular weight and can severely limit the applicability of these polymerizations.

Intramolecular cycloaddition (eq 13) destroys both end groups X and Y. This process is highly dependent

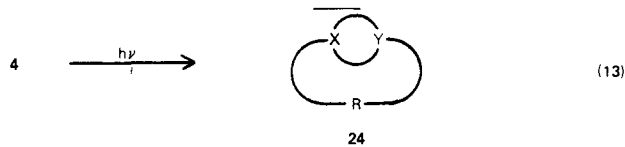

on the length and flexibility of the linkage R. Intramolecular cycloaddition can occur at any stage of the polymerization, and can involve the polymer as well as the monomer.

The presence of monofunctional impurities 1 (eq 14) or other reactive impurities 26 (eq 15) can terminate




the chain growth on one end of the growing polymer. Thus, as in other polymerization processes, the monomer purity is a critical factor.


II. Cycloadditions Involving Carbon 2 + 2 Addition

A. Acyclic Bis- and Poly(cinnamic acid) Derivatives

The dicinnamate esters 28 and 30 of ethylene glycol and 1,4-butanediol gave polymers 29 and 31, respectively, with undetermined DP's, on irradiation of the crystalline monomers either dispersed in petroleum ether (bp 40-60 °C) (eq 16) or in a solid KBr disk (eq 17).^{48,49}

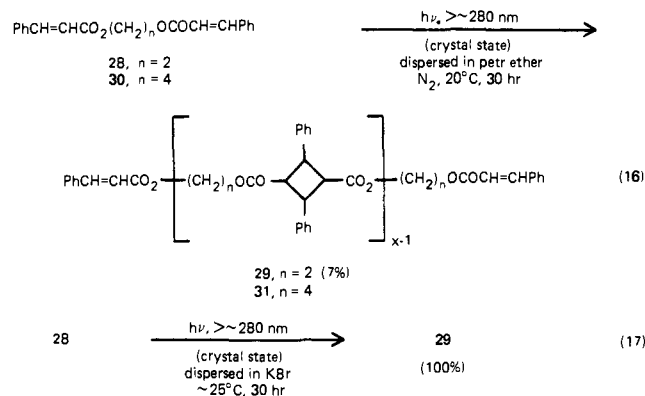


Irradiation of several different crystal forms of the tetracinnamate ester 32 of pentaerythritol in the solid state gave an amorphous oligomer or polymer, the structure of which probably was 33 (eq 18).^{50,51} The reaction presumably occurred via 2 + 2 cycloadditions, although this mechanism has not been established.^{50,51} A crystal structure determination of the α crystal form of monomer 32 showed the two nearest intermolecular double bond separations were 3.78 Å and 4.79 Å.⁵⁰ The

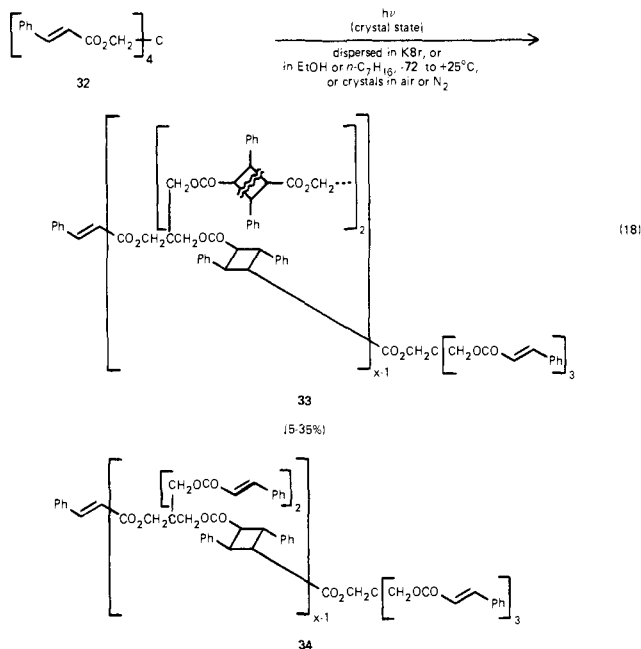


first polymerization stage was viewed as cycloaddition of these double bond pairs, forming the linear polymer 34 in a crystal lattice controlled process.⁵⁰ This linear polymer then probably cross-linked via intermolecular cycloaddition of the pendant cinnamyl groups.⁵⁰ The next shortest double bond separation, after the two noted above, was 8.14 Å.⁵⁰ This separation may have decreased following the initial linear polymerization, thus allowing the cross-linking. Alternately, local melting may have occurred leading to random conformations of the side chains, which then were able to undergo photocycloaddition giving 33.⁵⁰

The tri-, 35, or tetraesters, 32 and 36, of cinnamic or cinnamylideneacetic acids were patented as monomers

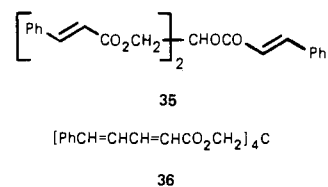


for photoresists.⁵² These polymerizations, followed by cross-linking, may proceed via photocycloaddition reactions of the cinnamate double bonds.

The bis(cinnamide) 37, which was formed in a film by photolysis of the polyamide 38 at 224 nm, re-formed the polymer 38 on photolysis at longer wavelength (eq 19).^{49,53} The original polyamide 38 was prepared by a

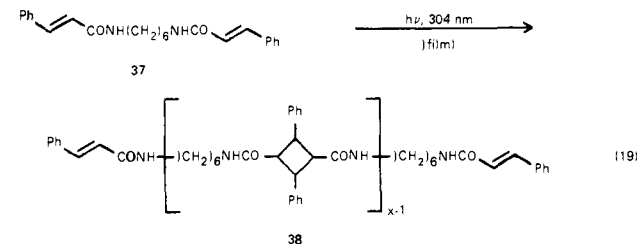


nonphotochemical polymerization.⁵³ The method of forming monomer 37 produced it in an oriented manner such that the double bonds were in the correct positions for undergoing cycloaddition (eq 19). This polymerization occurred only in the polymer matrix of 38.²³

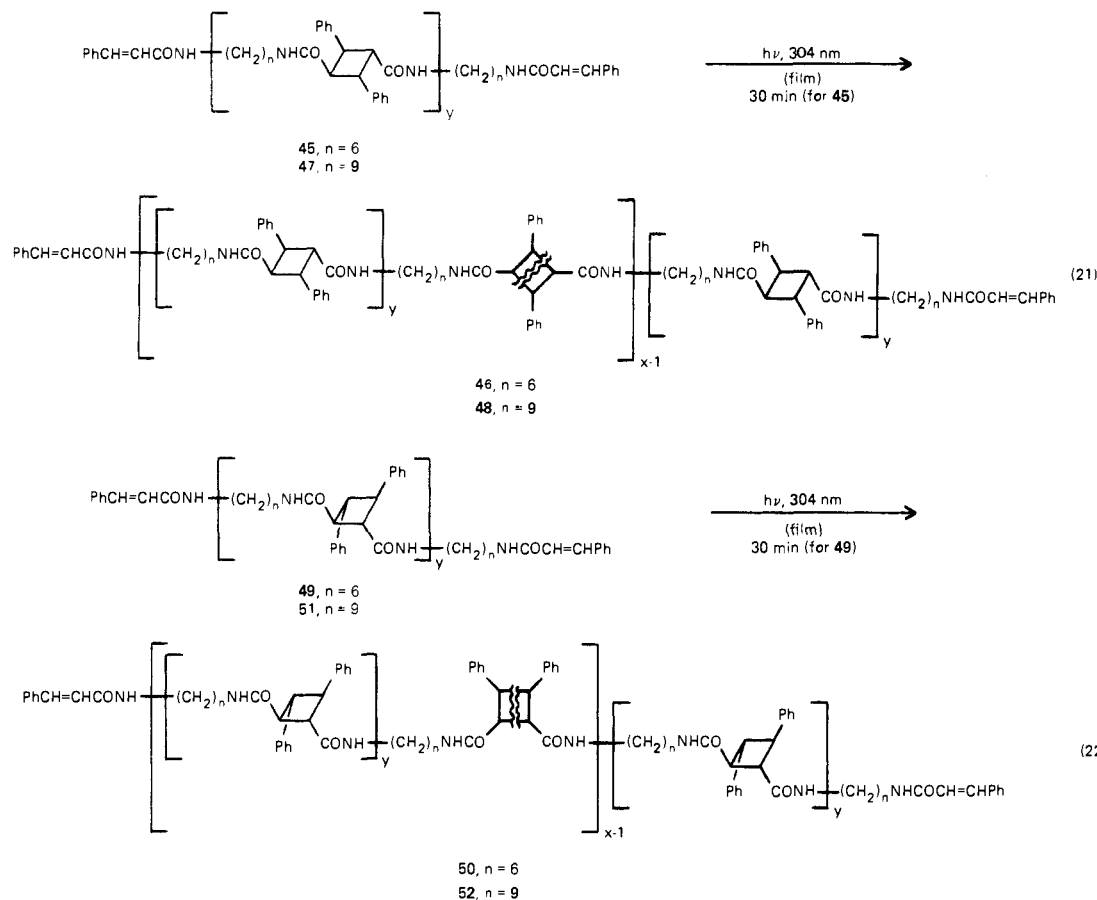

B. Alicyclic Bis(cinnamic acid) Derivatives

Irradiation of crystalline (+)-dimethylene-D-mannitol dicinnamate **39** gave the oligomers **41–44** in addition to higher molecular weight products **40** in which the probable values of x (DP's) were 6, 7, 8, and ≥ 10 (eq 20).⁵⁴ The smaller oligomers were favored at shorter

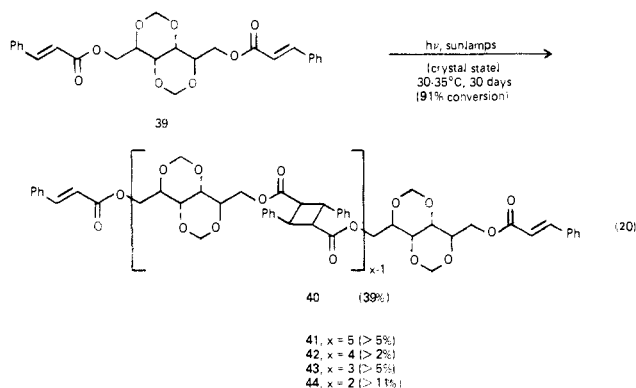


reaction times and the larger ones at longer reaction times.⁵⁴

In reactions similar to that shown in eq 19, the partially photodepolymerized α -truxillates **45** and **47** gave polymers **46** and **48**, respectively, on irradiation (eq 21).⁵⁵ Cis-trans isomerization about the carbon-carbon double bonds also occurred. In a similar manner the partially photodepolymerized δ -truxinates **49** and **51** produced polymers **50** and **52** and underwent cis-trans isomerization (eq 22).⁵⁵ A re-formation of the cyclobutane rings in these polymerizations (eq 21 and 22) has not been proven. These polymerizations initially were rapid and then decreased in rate. Most of the carbon-

carbon double bonds reacted in 30 min, and all four polymerizations occurred at about the same rate.⁵⁵

C. *m*-Phenylenediacrylic Acid and Esters

Irradiation of the diacid or diesters **53** in the crystal state or in solution (eq 23) gave low molecular weight

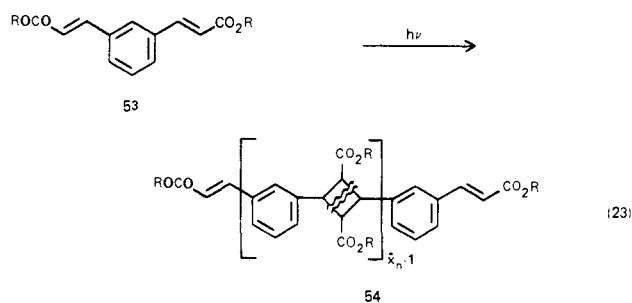

oligomers **54** (Table I).^{56–60} The products **54** formed in the crystal state had either undetermined or mixed regiochemistries,^{56,60} or head-to-tail structures.^{57,58}


The product **56** formed in the presence of picramide (**57**) was presumably the same as that formed in the absence of **57**,⁵⁸ but no data were presented to substantiate this assumption. The trinitro amine **57** was added as a spectral sensitizer for the oligomerization of **55**, which was used for preparing holographic gratings.^{58,59} The mechanism of the sensitization by **57** probably was the usual triplet energy-transfer process, followed by cycloaddition of 55^{*3} to the ground state monomer **55**.⁵⁸ The energy transfer was postulated to occur at the contact points of the crystals of **55** and **57**.⁵⁸ The diacid **55** photopolymerized with a high quantum yield.⁵⁸

TABLE I. Photopolymerization of *m*-Phenylenediacyrylic Acid and Esters 53 (Eq 23)

R of monomer 53	physical state of monomer 53	λ , nm	temp, °C	time, h	product 54	yield of 54, % ^a	ref
H, 55	crystal dispersed in H ₂ O or H ₂ O-EtOH	<i>b</i>	~ 25	72	56, probably oligomer	100	56, 57
55	film of mixed microcrystals of 55 and picramide 57 ^c	442 ^d		0.0014-0.015	56		58, 59
Me, 58	crystal dispersed in H ₂ O	<i>b</i>	-20 to -10	30	59, $\overline{M}_n = 740$, $\overline{x}_n = 3.0$		60
58	crystal dispersed in H ₂ O	<i>b</i>	-10 ^e	15 ^f	59, $\overline{M}_n = 740$, $\overline{x}_n = 3.0$		60
58	crystal dispersed in H ₂ O	<i>b</i>	15	20	59, $\overline{M}_n = 1060$, $\overline{x}_n = 4.3$	~ 97	60
58	crystal dispersed in H ₂ O	<i>b</i>	25 ^e	30	59, $\overline{M}_n = 1053$, $\overline{x}_n = 4.3$		60
58	crystal dispersed in H ₂ O or H ₂ O-EtOH	<i>b</i>	~ 25	30	59, $\overline{M}_n = 1040$, $\overline{x}_n = 4.2$	100	56, 57
58	0.42 M solution in CHCl ₃	<i>b</i>		15	59	low ^g	60
58	0.42 M solution in CHCl ₃	> 300		~ 38 ^h	59, $\overline{M}_n = 600$, $\overline{x}_n = 2.4$	~ 75 ⁱ	60
Ph, 60	crystal in KBr	<i>b</i>			61, probably oligomer		56, 57

^a Chemical yield. ^b Irradiated through quartz. ^c 1:0.8 (55:57) by weight. ^d Laser light source, 4-60 mJ cm⁻². ^e Conversion of double bonds given as a function of time. ^f Prolonged irradiation did not increase \overline{M}_n . ^g Cis-trans isomerization about the double bond occurred. ^h Conversion was ~ 75% in 10 h. ⁱ Conversion of 58.

The amorphous methyl ester oligomer 59, formed by irradiation of the monomer 58 in the crystal state at 15 °C, probably contained a mixture of at least three stereoisomeric cyclobutanes that included both head-to-head and head-to-tail units.⁶⁰⁻⁶² The head-to-head dimer 62 of 58 was formed topochemically in the or-

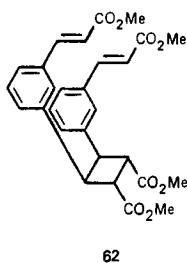

dered crystal at -10 °C during the first few hours of irradiation.^{60,62} The crystal structure of monomer 58, determined by X-ray crystallography, supported the structural assignment of the dimer 62.⁶² The double bonds of 58 that became part of the cyclobutane ring of 62 were separated by 3.960 Å.⁶² Dimerization of 58 increased the separation of the two remaining double bonds and destroyed the regular arrangement of the surrounding monomers.⁶² The crystal thus became disordered, and subsequent random photocycloaddition occurred with the formation of an amorphous oligomer that contained cyclobutane rings having variable configurations.^{60,62} The rate of this random cycloaddition in the disordered lattice was expected to be slower than that of the initial dimerization and faster at higher temperatures.⁶² Monomer 58 disappeared slightly faster at 25 °C than at -10 °C.⁶⁰ At -30 °C molecular movement was suppressed to where topochemical dimerization was the only significant reaction.⁶⁰

In contrast to oligomerization of the methyl ester 58 in concentrated solution (0.42 M, Table I), irradiation of 58 as a 0.042 M solution in CHCl₃ produced only trans-cis isomerization.⁶⁰ In concentrated CHCl₃ solution, oligomerization of 58 probably occurred via isomerization of *trans,trans*-58 to *trans,cis*-58 and *cis,cis*-58, and photocycloadditions of all three isomers to produce various regioisomeric cyclobutane rings in the oligomer 59.⁶⁰

X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photo-oligomerization ($\lambda > 410$ nm) of 58 showed that nu-


cleation began and propagation proceeded within the defect-free structure.⁵¹ In comparison to other related reactions studied, 58 had a medium reactivity.⁵¹

A study of the morphological changes in the solid state photopolymerization of 58 showed the oligomer 59 was amorphous and the crystal did not change shape during the reaction.⁶¹ In this study the oligomer 59 was indicated to contain the head-to-head cyclobutane structure.⁶¹

D. *p*-Bis(monosubstituted vinyl)benzenes


1. *p*-Phenylenediacyrylic Acid, Esters, and Amides

Irradiation of the diacid 63 in the crystal state (eq 24) at 30 °C gave a low molecular weight polymer with structures suggested as either 64⁵⁶ or 65.^{22,57,63} Irra-

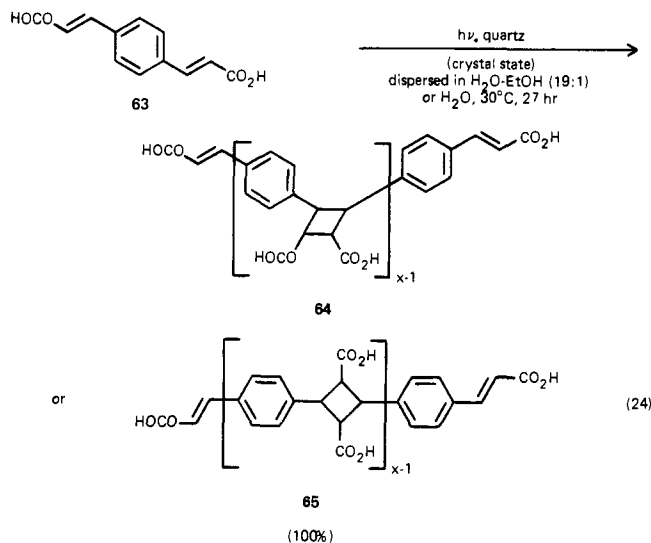

diation at -25 °C gave a high (unspecified) molecular weight polymer.⁵⁶

X-ray crystal structure determinations of the methyl,⁶⁴ ethyl,⁶⁵ and phenyl⁶⁶ esters 66 of the diacid 63 indicated the stereochemistry of the polymers 67 that resulted from the crystal state irradiations of the monomers 66 (eq 25) (Table II).^{24,56,57,63,67-73} These polymerizations occurred only in the crystal state. Little reaction was observed on irradiation of the ethyl ester 70 in the molten state at 110 °C^{63,71} or in solution;⁵⁶ a low molecular weight oligomer was isolated from the

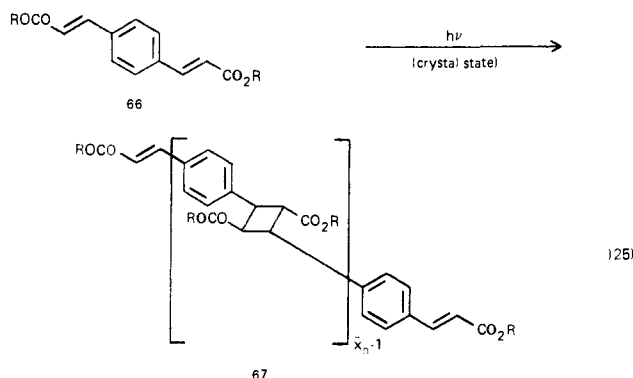

irradiation in solution as described later (eq 32). The monomer crystals were transformed directly into polymer crystals, conversions typical of topochemical processes.⁶⁷

Irradiation of the esters **68** (eq 26) and **70** at 360 nm gave low molecular weight oligomers because only the monomers absorbed light having this wavelength.^{68,71} Polymerization ceased after all monomer molecules were incorporated into the numerous oligomer units. The formation of each oligomer was initiated by the random absorption of light or localization of excitation throughout the monomer crystal. Shorter wavelength light, e.g., 310 nm, which was absorbed by both the monomers (eq 26) and the growing polymer chains (eq 29) gave higher molecular weight polymers. These processes are shown in Scheme II for the methyl ester **68** where \bar{x}_n represents here, the actual, not the average, degree of polymerization.^{68,71} In agreement with this mechanism, the molecular weight of the ethyl ester polymer **71** continued to increase after the monomer **70** had been consumed.⁷¹


In contrast to these results, the intrinsic viscosity of the methyl ester polymer **69** solutions did not increase significantly on irradiation after the monomer **68** had completely reacted.⁶⁷ The similar shapes of the conversion-time and viscosity-time curves was cited as supporting evidence for the 2 + 2 photocycloaddition mechanism.⁶⁷ Clarification of this apparent inconsistency is needed.

At -269 to -103 °C with unfiltered UV radiation and at 30–60% conversion of the ethyl ester **70**, the major reactions were dimerization⁷⁴ and addition of **70** to the dimer and low molecular weight oligomers.⁶⁹ At ~50% conversion of **70** the DP was 3–5.⁶⁹ At higher conversions the molecular weights reached ~3000 (DP ≈ 11).⁶⁹

Variable induction periods were noted in the photopolymerization of the ethyl ester **70** at -269 to -103 °C.⁶⁹ The cycloaddition probably occurred close to crystal defect sites,⁷⁴ and the rate probably depended on the number and kind of such sites.⁶⁹ The variability in the quality of different crystal samples presumably caused the variation in induction periods.⁶⁹ Microcracks developed during the induction period; these served as new defect sites.⁶⁹ The induction period disappeared after 10–15% conversion of the double bonds.⁶⁹ Other results, described later in this section indicate that photocycloaddition did not occur at defect sites.

The low temperature dependence of the polymerization of **70** was determined after 30–40% reaction had occurred.⁶⁹ An example of such data at -125 °C is given in Table II. The relative rates of disappearance of double bonds from **70** were 1.0, 2.1, 4.1, and 65 at -269,

Scheme II

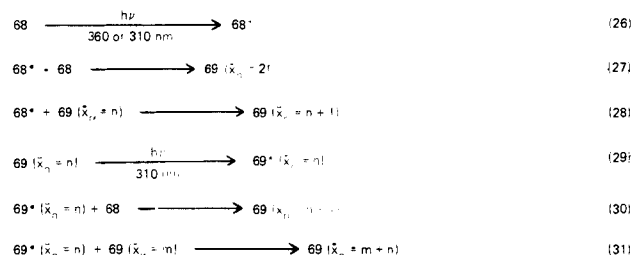

-196, -173, and -105 °C, respectively.⁶⁹ From these and other data the activation energy was found to be <20 cal mol⁻¹ at -269 to -183 °C,^{69,74} 1 kcal mol⁻¹ at -190 to -180 °C,⁷⁰ 3 kcal mol⁻¹ at -180 to -170 °C,⁷⁰ and 1.6 ± 0.3 kcal mol⁻¹ at -173 to -103 °C.^{69,74}

The following explanation was offered for these results at low temperatures. Usually no potential barrier exists to the photocycloaddition of two isolated ethylenic bonds.⁶⁹ In a crystal, however, lattice forces evidently produce a barrier that can be overcome by the energy of local vibrations close to the electronic excited molecule.⁶⁹ At very low temperatures, the amplitude of the zero vibration, ~0.1 Å, is insufficient to cause reaction in the lattice; ~1–1.5 Å is necessary.⁶⁹ The probability of photocycloaddition is proportional to the probability of a deformed region forming in the crystal and does not depend on the temperature near absolute zero.⁶⁹ An increase in rate with an increase in temperature begins in the temperature range where the population of higher vibrational levels becomes possible.⁶⁹ However, if the quantum yield for the loss of double bonds in the ethyl ester **70** was ≤2, then the low temperature of the crystal environment may not have been pertinent to the specificity of the reaction.²⁸ The quantum yield for the loss of double bonds in the methyl ester **68** at higher temperature was ≤2, i.e., a new photon was required for each cycloaddition step.

The polymerization rate of the ethyl ester **70**, as measured by the disappearance of **70**, increased slightly as the temperature increased from -50 °C to -20 °C.⁷¹ At -20 °C, 50% conversion occurred in ~5 min and 95% in ~40 min. At higher temperatures, -20 °C to 15 °C, the rate decreased with increasing temperature, especially at conversions >~75% of **70**.⁷¹ The rate decreased even further near the melting point of **70**, 100 °C.^{14,49,74} At 30–96 °C only low conversions could be achieved.⁴⁹

At 50% conversion of **70**, the molecular weight of polymer **71** decreased with increasing reaction temperature (-50 °C to +15 °C).⁷¹ At 30–96 °C only oligomers were formed.⁴⁹ A later reference stated that only dimer was formed, in low yield, at 56–96 °C.⁷⁵ At <25 °C, quantitative yields of crystalline high polymer **71** were formed; at >25 °C poor yields of amorphous, partially cross-linked polymer were produced.¹⁴ In the presence of 360 nm radiation in the KBr matrix, the oligomer **71** formed at -28 °C contained 10% fewer end groups than that formed at 20 °C; thus a higher degree of oligomerization occurred at the lower temperature.⁷¹

A crystal transition at 56 °C for **70** did not significantly alter the arrangement of the monomer in the crystal,^{71,75} and the double-bond separation actually contracted slightly.⁷⁵ The selective dimerization above 56 °C was attributed to a topochemically controlled photocycloaddition followed by local melting, which was

TABLE II. Photopolymerization of *p*-Phenylenediacylate Esters 66 in the Crystal State (Eq 25)

R of mono-mer 66	dispersion medium for monomer 66	λ , nm	temp, °C	time, h	product 67	yield of 67, %	$\Phi_{-(C=C)^a}$	ref
Me, 68	H ₂ O	<i>b</i>	3	5	69 ^c	93.2 ^d		67
68	H ₂ O	<i>b</i>	19	5	69 ^e	90.6 ^f		67
68	H ₂ O	<i>b</i>	~25	0.17-5	69 ^g	~90 ^h	0.7-1.2	67
68	H ₂ O or H ₂ O-EtOH	quartz ⁱ	30	1.5	69	55, 100		56
68	H ₂ O-EtOH (19:1)		0-5	7	69			63
68	KBr	365			69, oligomer		1.2-~2	68
68	KBr	360			69, oligomer			68
68	KBr	313			69, high polymer			68
68	KBr	310			69, high polymer			68
68	KBr			0.17 ^r	69			56
68			~25	30	69, $\bar{M}_n = 1040, \bar{x}_n = 4.2$	100		57
Et, 70	none ^j	<i>b</i>	-269 to -103		71, $\bar{M}_n = 3000, \bar{x}_n = 11$			69
70	none ^j	<i>b</i>	-145	0.21	71	4 ^k		69
70	none ^j	<i>b</i>	-145	0.21	71	23 ^{k,l}		69
70	none ^j	<i>b</i>	-145	0.77	71	34 ^k		69
70	none ^j	<i>b</i>	-125	0.12	71	27 ^{k,m}		69
70	He(1)	<i>b</i>	-269.0	0.83	71	<i>n</i>		69
70		<i>b</i>	-190	1	71	~30-40		70
70	H ₂ O	360	20		71, $\bar{x}_n = 3.0$, ^o 72	100		71
72	H ₂ O	310	20		71, nearly amorphous polymer			71
70	H ₂ O	>~280 ^p	32		71, $\bar{x}_n = 3.4$	67		71
70	H ₂ O	>~280 ^p	45		71, $\bar{x}_n = 2.3$	18		71
70	H ₂ O	>~280 ^p	62	20	71, ~30% dimer, $\bar{x}_n = 2$	40		71
70	H ₂ O		60-65	6	71, dimer, $\bar{x}_n = 2$	~30		72
70	H ₂ O or H ₂ O-EtOH	quartz	-25	1.5	71, crystalline polymer ^q	100		56, 57
70	H ₂ O or H ₂ O-EtOH	quartz	30	50	71, amorphous polymer ^r	100		56, 57
70	H ₂ O or H ₂ O-EtOH	quartz			71, $\bar{M}_n = 2200, \bar{x}_n = 8.0, 73^s$			72
73	film	277			71			72
73	film	>280			71, $\bar{M}_n = 3000, \bar{x}_n = 11$			72
70	H ₂ O-MeOH (2:3) ^t	>~280 ^p	-50	<i>u</i>	71, crystalline high polymer	100		71
70	H ₂ O-MeOH (2:3) ^t	>~280 ^p	-35	<i>u</i>	71	100		71
70	H ₂ O-MeOH (1:1) ^t	>~280 ^p	-20		71, $\bar{x}_n = 3.0$ ^v	~70		71
70	H ₂ O-MeOH (1:1) ^t	>~280 ^p	-20	1-3 ^w	71, crystalline high polymer	100		71
70	H ₂ O-MeOH (3:2) ^t	>~280 ^p	0	<i>u</i>	71	100		71
70	H ₂ O-MeOH (65:35) ^t	>~280 ^p	15	<i>u</i>	71	100		71
70	H ₂ O-EtOH (19:1)		0-5	7	71	94		63
70	KBr	360	-28		71, oligomer			71
70	KBr	360	20		71			71
70	KBr	310	20		71, polymer			71
70			<15		71, high \bar{M}_n	100		24
70			30		71, $\bar{x}_n = 2-5$			24
C ₂ D ₅ , 74	H ₂ O-MeOH (1:1)	>~280 ^p	-20		75			71
Ph, 76	H ₂ O or H ₂ O-EtOH	quartz	30	10	77, high polymer	85		56, 57, 73
76	H ₂ O-EtOH (19:1)		0-5	7	77			63

^a Quantum yield for reaction of monomer or polymer double bonds. ^b Unfiltered mercury arc lamp. ^c Intrinsic viscosity = 4.5 dl g⁻¹ at 0.5 h and 5.6 dl g⁻¹ at 5 h. ^d 80.0% conversion at 0.5 h. ^e Intrinsic viscosity = 2.7 dl g⁻¹ at 0.5 h and 5.7 dl g⁻¹ at 5 h. ^f 68.0% at 0.5 h. ^g Intrinsic viscosity as a function of time given. ^h At ~4.9 h analysis by IR showed the conversion was ~100%. Conversions at shorter reaction times also given. ⁱ All wavelengths from high pressure mercury arc that are transmitted by quartz. ^j Thin film of crystals. ^k Conversion of double bonds of monomer. ^l 13% of monomer double bonds were converted to polymer bonds prior to this reaction. ^m 39% of monomer double bonds were converted to polymer bonds prior to this reaction. ⁿ Almost all of monomer 70 reacted, 20% of monomer double bonds were converted to polymer bonds prior to this reaction by irradiation at ~25 °C. ^o Oligomer contained dimer. ^p Pyrex glass filter. ^q Reduced viscosity = 1.41. ^r Reduced viscosity = 0.16. ^s CHCl₃ soluble fraction: $\bar{M}_n \approx 1000, \bar{x}_n \approx 3.6$. ^t <1% of 70 dissolved. ^u Conversion of monomer as a function of time given. ^v Extracted from product (23% yield). ^w Conversion of monomer and formation of polymer as a function of time given.

caused by the melting point depression of the mixture of dimer and monomer.⁷⁵ Because the cycloaddition did not occur in the molten state, the reaction stopped at the dimer stage.⁷⁵

The conversion and chain growth of the methyl ester 68 both decreased with increasing temperature.⁶⁷

The effect of temperature on the photocycloaddition polymerization of these esters 66 has been discussed for three temperature regions.⁷¹ At the lowest temperatures studied, the crystal system was rigid and the polymerization proceeded until all the double bonds had re-

acted. At increased temperatures the polymerization rate increased, and the degree of polymerization decreased. This behavior was consistent with a temperature dependence of the reactions (Scheme II) that decreased in the order (27) > (28) > (30).⁷¹

In the intermediate temperature range the crystal system was rigid, but the molecules were disordered.⁷¹ Again all of the monomer 66 was consumed, but a small amount of functional groups remained even after prolonged irradiation. An increase in temperature in this region initially increased the rate of polymerization, but

TABLE III. Photopolymerization of *p*-Phenylenediacyrylate Esters 66 in the Crystal State (Eq 33)

R of monomer 66	dispersion medium for monomer 66	wave-length filter	temp, °C	time, h	product 79	yield of 79, %	ref
<i>n</i> -Pr, 80	H ₂ O or H ₂ O-EtOH	quartz	0-5	50	81, oligomer	42	56, 57, 71
<i>i</i> -Pr, 82	H ₂ O or H ₂ O-EtOH	quartz	30	49	83, oligomer	65	56, 57, 71
<i>n</i> -Bu, 84	KBr	quartz		10	85, oligomer		56, 57
C ₈ H ₁₇ , 86					87		61
PhCH ₂ , 88	KBr	quartz		10	89, oligomer		56, 57
<i>p</i> -MeC ₆ H ₄ , 90	KBr	quartz			91, oligomer		56, 57
<i>p</i> -O ₂ NC ₆ H ₄ , 92	H ₂ O or H ₂ O-EtOH	quartz	30	50	93, oligomer	89	56, 57

in the later stages decreased this rate. Again the degree of polymerization decreased with increased temperature. Apparently, disordering of the crystal occurred during the polymerization, which decreased the rates of reactions 28 and 30 (Scheme II).^{71,74}

At the highest temperatures studied the crystal system was considerably disordered.⁷¹ The polymerization was suppressed at the oligomer stage with low conversions of the monomer 66. An increase in temperature decreased the conversion and the degree of polymerization. The heat generated by the reaction and by absorption of light caused partial melting so that the crystal became sticky.⁷¹

The double bonds that reacted to form cyclobutane rings in the crystal had separations of 3.937 Å,^{14,64,76} 3.970 Å (at 25 °C),^{65,76} and 3.928 Å^{66,76} in the methyl 68, ethyl 70, and phenyl 76 esters, respectively. The separation in the ethyl ester 70 at 70 °C was 3.87 Å.⁷⁵

Polymerization of the methyl ester 68 resulted in movement of the monomeric unit in the chain growth direction with an elongation of 8.8%. The direction of the crystal axes was not retained.⁶⁷


X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photopolymerizations ($\lambda > 365$ nm) of 68, 70, and 76 showed that nucleation began and propagation proceeded within the defect-free structures.⁵¹ In comparison to other related compounds studied, the methyl ester 68 had a high reactivity, and the ethyl 70 and phenyl 76 esters had medium reactivities.⁵¹

A study of the morphological changes during the solid state polymerizations of the methyl 68, ethyl 70, and phenyl 76 esters showed that although the polymers were crystalline and crackfree, deformation did occur during the polymerizations.⁶¹ Large molecular movements also occurred during the reaction.

These and some of the other solid state polymerizations discussed in later sections were believed to be homogeneous with the formation of a small amount of product dispersed in the monomer in the early stages.⁶¹ The monomer crystal became strained by the accumulation of the product and cracked if the strain was sufficient. Crack formation during this initial stage depended on the cleavability of the monomer crystal. As the polymerization proceeded, this crystal was transformed into the polymer crystal containing a small amount of dispersed monomer. Phase separation of the polymer sometimes started at this stage. Finally, the monomer crystal was converted entirely to polymer.⁶¹


The molecular features favorable for forming polymerizable crystals have been generalized as those that produce rigid, rod-like, nearly planar shapes with the two functional groups having mutually opposite dipole directions.⁶⁵

In contrast to the crystal state photopolymerization of the ethyl ester 70, irradiation of a concentrated solution of 70 gave a low molecular weight oligomer 78 (eq 32).⁷⁷ The stereo- and regiochemistries of the photo-

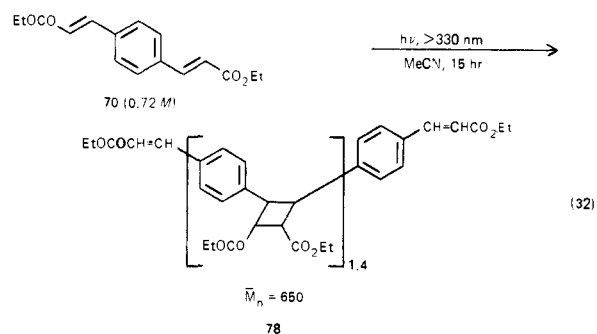

cycloaddition were different from those observed in the crystal state. Cis-trans isomerization about the double bonds was the only reaction observed in dilute solution (0.0018 M).⁷⁷ Evidence indicated photooligomerization occurred via an excimer of 70.⁷⁷

Several other esters 66 of *p*-phenylenediacyrylic acid have been polymerized by photocycloaddition reactions of the monomers in the crystal state (eq 33) (Table

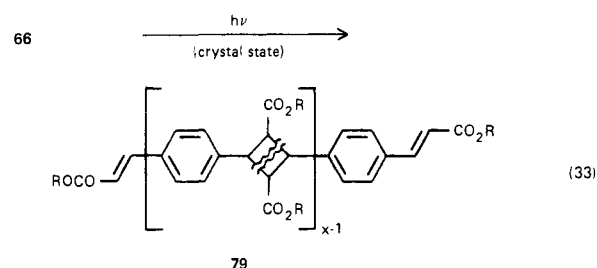


III).^{56,57,61,71} In these reactions the stereochemistries of the cycloadditions have not been determined although in some references^{57,61} the cyclobutane rings are shown as head-to-tail adducts.

The relative rates of polymerization of the esters 66 were as follows:⁷⁸ Me (68) > Et (70) > *n*-Pr (80) > *i*-Pr (82) > *n*-Bu (84). The molecular weights of the two propyl ester polymers 81 and 83 decreased when the polymerization was performed at higher temperatures.⁵⁶

Morphology studies on the isopropyl 83 and octyl 87 ester polymers showed they were amorphous and that they did not change shape during formation.⁶¹


On irradiation (eq 34), the amides 94 and 96 polymerized similarly to the esters described previously.^{56,57,63} The unsubstituted amide 95 was reported to be a high molecular weight polymer while the *N*-substituted product 97 was suggested to be an oligomer.⁵⁶ No molecular weight data were reported. In some references the polymer structures 95 and 97 were shown as

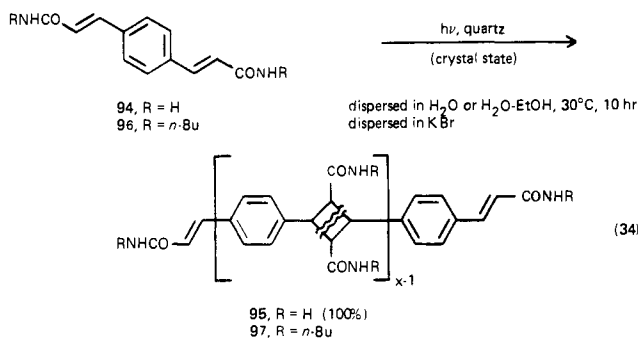

the head-to-tail cyclobutane structures.^{57,63}


2. *p*-Bis(β-nitro- and β-arylviny)benzenes

The bis(nitroethylene) derivative **98** was reported to polymerize by cycloaddition when irradiated in the crystal state (eq 35).⁵⁷ The polymer **99** was indicated

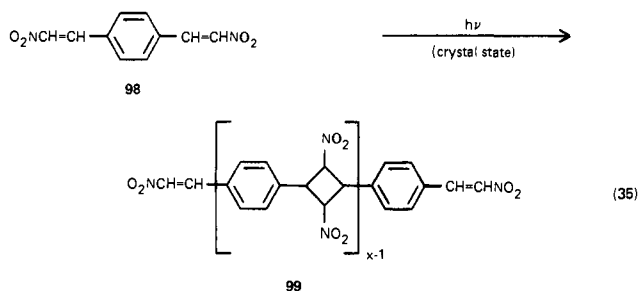

to have the head-to-tail structure, but no evidence was presented.⁵⁷



Irradiation of *p*-distyrylbenzene (**100**) in tetrahydrofuran solution (1.42×10^{-2} M) gave the oligomer **101** quantitatively (eq 36).^{14,79} Cis-trans isomerization

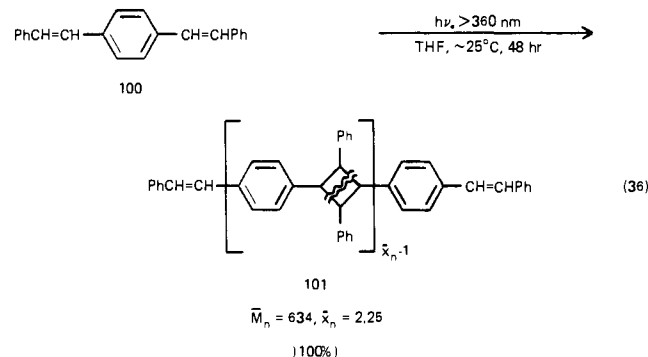

about the double bond occurred during the reaction.¹⁴

Further irradiation of the oligomer **101** in CHCl₃ solution with light of wavelength longer than 340 nm decreased the molecular weight⁷⁹ rather than increasing it as might have been expected on the basis of related reactions shown in Table II. If only the monomer **100** was excited by the light, then only reactions 37 and 38 would have occurred (Scheme III) as took place on irradiation at wavelengths longer than 360 nm.⁷⁹ The average molecular weight depended on the ratio of rate constants, k_{38}/k_{37} . If $k_{38}/k_{37} = 0$, only dimer, **101** ($\bar{x}_n = 2$), would have been formed. If $k_{38}/k_{37} = \infty$, only higher molecular weight polymers, **101** ($\bar{x}_n = n$), would have been formed. However, k_{38}/k_{37} was actually an intermediate value.⁷⁹ Under conditions where $k_{39} = 0$ and k_{38}/k_{37} was not extremely large, all of the monomer molecules **100** could not grow into high molecular weight polymers. This situation was in contrast to that where the growing polymer molecules absorbed light at


Scheme III



the same wavelengths as the monomer, as occurred with the bis(maleimides) discussed in section IIK.


In contrast to many other reactions discussed in this review, the distyrylbenzene **100** did not polymerize when irradiated in the crystal state.^{14,78} Presumably, unfavorable alignment of the molecules in the crystal lattice caused this behavior.

Several related (β-arylviny)benzenes, **102**, **104**, and **106**, were reported to polymerize via photocycloaddition in the crystal state to give the head-to-tail cyclobutane polymers (eq 40), but no evidence for these structures

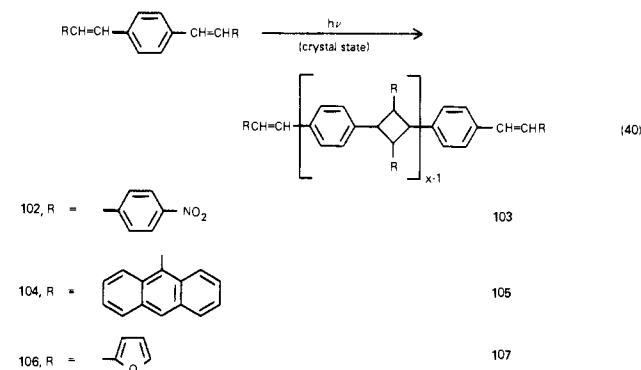

was given.⁵⁷ The bis(anthracene) derivative **104** could have polymerized via 4 + 4 cycloadditions of the anthracene moieties similarly to other anthracenes discussed in section VB. An appropriate arrangement of the monomer molecules **104** in the crystal lattice would have been required for this reaction.

X-ray diffraction studies^{76,80,81} of the crystal state bis(pyridylviny)benzene **108** photopolymerization (eq 41) (Table IV)^{14,57,68,80-83} established the *trans*-1,3-

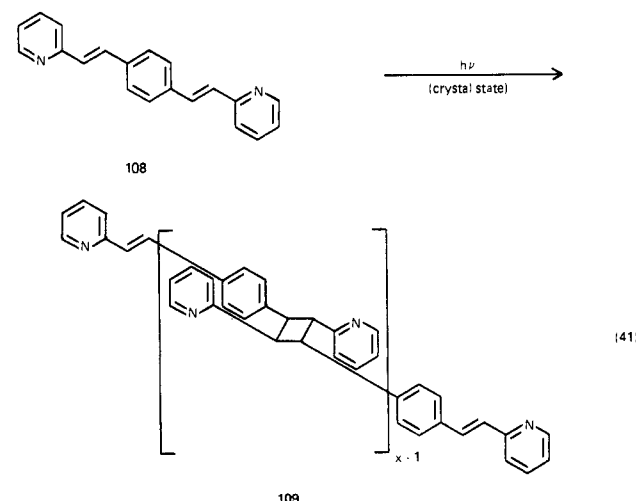

cyclobutane structure in the main chain. The monomer molecules **108** were aligned in the crystal so as to give the polymer **109**. The double bonds that underwent cycloaddition were separated by 3.910 Å.^{76,81}

Single crystal X-ray diffraction studies showed that on conversion of the monomer **108** to polymer **109**, only a slight change in unit cell dimensions occurred, the unit

TABLE IV. Photopolymerization of *p*-Bis(β -2-pyridylvinyl)benzene (108) in the Crystal State (Eq 41)

dispersion medium for monomer 108	λ , nm	temp, °C	time, h	product 109	yield of 109, %	$\Phi_{-(C=C)}$	ref
EtOH-H ₂ O (5:1)	>~280	~25	9	polymer	90		83
KBr	410			oligomer, 110			68
KBr	405			oligomer		≥ 0.04	14, 68
110, KBr	350			high polymer			68
	unfiltered ^a	~45	~100	polymer	>99		80
			9	polymer	>90		57
				polymer		0.04	81

^a High pressure mercury vapor lamp.

cell symmetry probably did not change, and the average unit cell orientation remained unchanged.⁸⁰ These observations suggested that minimal molecular rearrangement occurred during the polymerization.⁸⁰ The polymer 109 was highly oriented along the *c* axis, which had elongated 2.7% from that of the monomer.⁸¹ The divinylbenzene derivative 108 crystal had a unit cell and symmetry analogous to those of the divinylpyrazine derivative 192 (see section IIG1).⁸²

When a single spot on a crystal of the monomer 108 was irradiated, polymerization occurred only at that spot.⁸⁴ The polymerization may have proceeded from the surface to the interior of the monomer crystal.⁷⁶

Polymerization of the bis(pyridylvinyl)benzene 108 in the crystal state was slower than that of the distyrylpyrazine 192 (see later section)^{81,83} whereas oligomerizations of the two monomers in solution proceeded at approximately the same rate.⁸¹ The difference in quantum yields for the two polymerizations in the crystal state therefore were probably not caused by properties of the isolated molecules. Rather it could have resulted from slight differences in the molecular packing arrangements in the two crystals or of differences in the overlap of the nitrogen atoms with the phenyl rings.⁸¹ A molecular orbital treatment of these two reactions on the basis of the crystal structures has been used to explain the difference in quantum yields.^{14,81}

Changes in temperature (30–70 °C) had little effect on the rate of polymerization of 108, but the DP decreased markedly as the temperature increased, implying that the polymerization depended on the crystal state at the growing chain end.⁷³ Typical of stepwise polymerizations, the DP increased gradually with conversion of 108 in the early stages of the reaction.⁷³ At high conversions of 108 the DP increased sharply and continued to rise even after the monomer was completely consumed.⁷³

X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photopolymerization ($\lambda > 365$ nm) of the bis(pyridylvinyl)benzene 108 showed that nucleation began and propagation proceeded within the defect-free structures.⁵¹ No evidence was obtained for the occurrence of discrete nuclei of products.⁵¹ Fissures, but no dislocations or planar faults, were introduced on polymerization.⁵¹ In comparison to other related monomers studied, 108 had a low reactivity.⁵¹


The polymer 109 was crystalline. Molecular movement during the reaction was small, but the crystal exhibited a large shape change and developed large cracks.⁶¹

The 3- and 4-pyridyl analogues of the bis(2-pyridylvinyl)benzene 108 did not photopolymerize in the

TABLE V. Photopolymerization of *p*-Bis(β -pyridylvinyl)benzenes 111 in THF Solution (Eq 42)^{14,79}

position of attachment of pyridyl group of 111	product 112			yield of 112, %
	number	\bar{M}_n	\bar{x}_n	
2, 108	113	814	2.9	29
3, 114	115	1074	3.8	94
4, 116	117	682	2.4	73, 74


crystal state,⁸² but all three isomers underwent oligomerization in solution on irradiation (eq 42) (Table V).^{14,79}

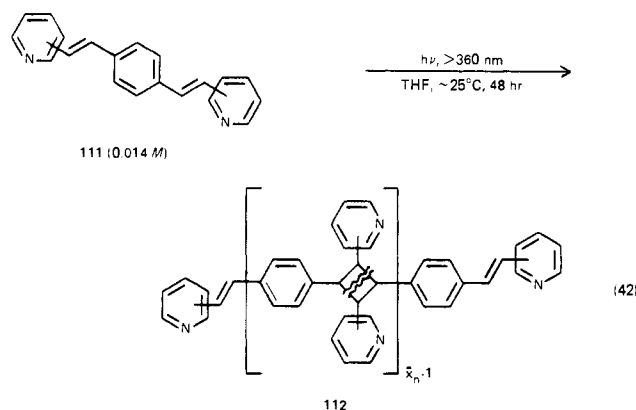

These results imply that the crystal lattices controlled the solid state reactions.¹⁴

The 2-pyridyl oligomer 113 was amorphous and differed from the crystalline oligomer 109 formed in the solid state.⁷⁹ The oligomers 113, 115, and 117 (Table V), formed in solution probably contained cyclobutane rings having various configurations.⁷⁹ Irradiation of the oligomers 112 in CHCl₃ solution with light of wavelength longer than 340 nm decreased the molecular weight.⁷⁹ Cis-trans isomerization of the monomers 111 accompanied the polymerization.¹⁴


A diphenyl derivative 118 related to the bis(2-pyridyl) monomer 108 was cited in a review as giving a cyclo-

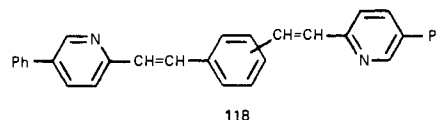

butyl polymer when irradiated in the crystal state.¹⁶ An original reference for this reaction was not found.

3. *p*-Di-1,3-butadienylbenzenes

The crystalline bis(diene ester) 119 gave a cyclobutyl polymer 120 on irradiation (eq 43).^{65,85} Low and high

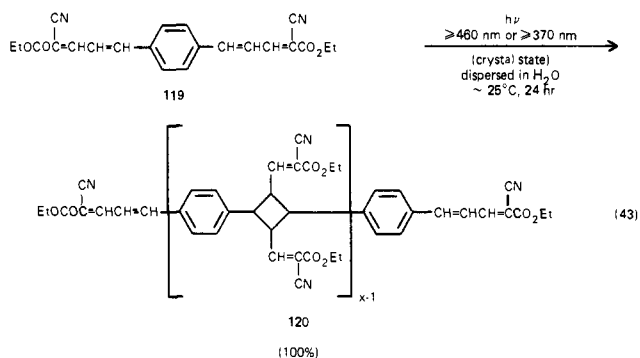


molecular weight polymers 120, having intrinsic viscosities of 0.08 and 0.65, formed on irradiation with long (≥ 460 nm) and short wavelength (≥ 370 nm) light, respectively.⁸⁵ Irradiation of low molecular weight 120 at ≥ 370 nm produced high molecular weight polymer that contained *trans*-1,3-substituted cyclobutane rings.⁸⁵ The exact stereochemistry was not reported. The molecular weight dependence on the wavelength was presumably caused by the same factors discussed previously for the ester 68 and shown in Scheme II.


E. *p*-Bis(polysubstituted vinyl)benzenes

1. Cyano-*p*-phenylenediacyrylate Esters

Irradiation of the crystalline cyano-*p*-phenylenediacyrylate ester 121 gave an amorphous cyclobutyl oligomer 122 of undefined regiochemistry (eq 44).^{51,86} An

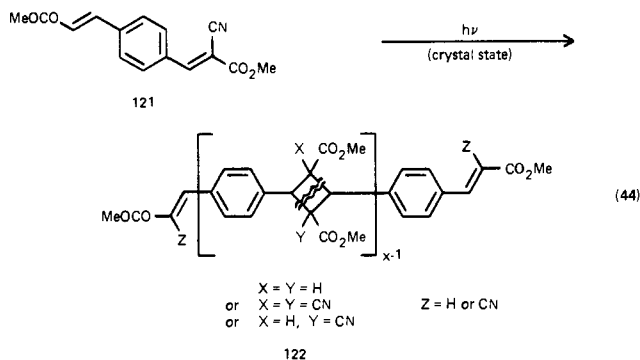

X-ray crystal structure determination showed monomer 121 had parallel stacks with both double bond separations of 3.956 Å.⁸⁶ The probable initiation reaction was formation of a mirror symmetric dimer, 123 or 124.⁸⁶

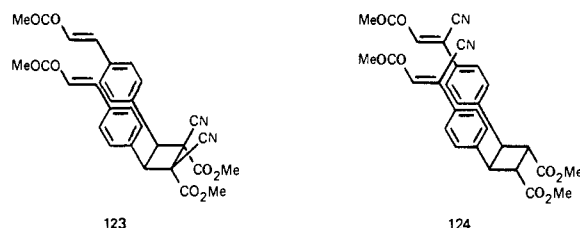


Formation of these dimers was expected to destroy the regular arrangement of the surrounding monomers and produce nonregiospecific cycloaddition to the olefinic bonds remaining in the dimers, 123 and 124, or the oligomers formed therefrom.⁸⁶

X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photo-oligomerization (> 410 nm) of 121 showed that nucleation began and propagation proceeded within the defect-free structure.⁵¹ In comparison to other related

monomers studied, the cyano dimethyl ester 121 had a high reactivity.⁵¹

Irradiation of the racemic *sec*-butyl methyl diester 125 in one of its crystal forms gave a racemic polymer^{87,86} or oligomer⁸⁹ 126 and racemic dimers 127 and 128 (eq 45). A second crystal form of 125 was stable

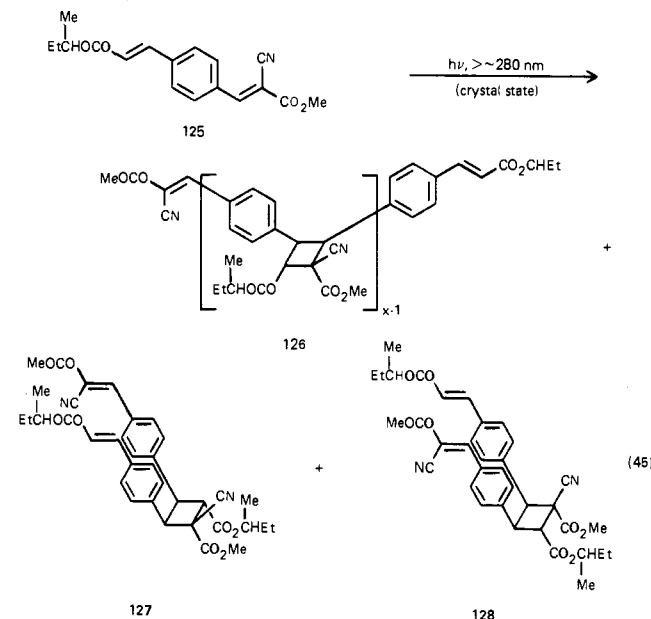

to irradiation.⁸⁹ The structure of polymer 126 was inferred from the structure of the dimers and the crystal structure of monomer 125.⁸⁹


Irradiating the optically active (*S*)-(+)-form (90% optically pure)⁸⁹ of the diester 125 gave a polymer [126, (*S*)-*s*-Bu] and two diastereomeric dimers [127 and 128, (*S*)-*s*-Bu] (1:1 ratio), all of which were optically active only because of the chiral *sec*-butyl group.^{87,90} No asymmetric induction was induced during this cycloaddition in contrast to the reaction of the ethyl ester analogue 129 (see following section) where asymmetric induction occurred.

X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photo-oligomerization (> 410 nm) of racemic 125 to give an amorphous product 126 showed that nucleation began and propagation proceeded within the defect-free structure.⁵¹ No evidence was found for the occurrence of discrete nuclei of products.⁵¹ In comparison to other related monomers studied, the monomer 125 had a medium reactivity.⁵¹

The two crystal forms of the *sec*-butyl ethyl diester 129 gave polymeric cycloadducts of different stereochemistries when irradiated in the solid state.⁸⁸ The α crystal form gave polymers of structure 130 (eq 46).⁸⁹ Trimers 131 and dimers 132 having structures analogous to that of polymer 130 were also isolated. A crystal structure determination of the α form of (*S*)-(+)-129 (134) showed the monomer molecules aligned so that the adjacent double bonds, which were separated by 4.04 Å, could combine to give the cyclobutane rings indicated in structures 130, 131, and 132.^{89,91,92}

The products formed on irradiation of the separate optical isomers of 129 and their mixtures under a variety of conditions are shown in Table VI.⁸⁷⁻⁹⁴

The effect of irradiation wavelength on the DP of 134⁹³ was similar to that noted previously for the ester 68 (Scheme II). Whereas the yield of dimer 132 was

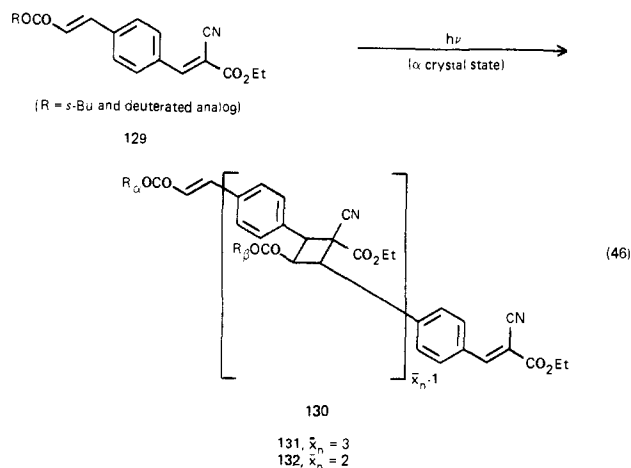

~23% on irradiation of 134 with $\lambda > 300$ nm (Table VI), it was 60% with $\lambda > 350$ nm under otherwise comparable conditions.⁸⁹


The (*R*)- and (*S*)-*sec*-butyl esters 133 and 134 each crystallized preferentially in one of two possible enantiomeric crystals because of the chiral handles.⁹³ Irradiating these crystals produced cycloadducts 130, 131, and 132 that were optically active after the *sec*-butyl groups were replaced by methyl groups.⁸⁹ The chiral environment of the reaction site, not the chiral *sec*-butyl handle, caused these asymmetric inductions.^{87,89,91,93} The asymmetric inductions were quantitative in both the initiation and propagation steps.⁸⁹

Crystals of racemic ester (133, 134) that were grown from the melt by very slow cooling gave optically active oligomers in some experiments.^{90-92,94} Enantiomeric excesses of up to 37% were achieved.⁹² No net optical rotation of the monomer occurred either before or after irradiation.

Asymmetry was induced in the crystallization of racemic ester (133, 134) by the addition of 3-15% of optically active dimer (*R*)- or (*S*)-132.⁹⁵ Irradiating these mixed crystals for 2 weeks at 5 °C gave oligomers 130, trimers 131, and dimers 132.⁹⁵ Optical activity measurements on the newly formed dimers 132 indicated an excess of the configuration opposite to that of the originally added dimer.⁹⁵ The oligomers and trimers presumably had configurations analogous to those of the newly formed dimers.

The β crystal form of 129 (136) gave polymer 137, trimers 138, and dimers 139 and 140 (eq 47).⁸⁸ Only the racemic form of the monomer 136 was studied (Table VII).⁸⁶ The structure of the polymer 137 was assigned by analogy to those of dimers 139 and 140.


Photocycloaddition of the β crystal consisting of a 50:50 mixture of (*S*) and (*R*) *sec*-butyl esters 134 and 141 (Table VII) was studied to gain information on the microstructure of the racemic crystal.⁸⁸ Only the compositions of the dimers 139 and 140 were determined although oligomers also formed presumably had analogous structures. The β crystals of the mixture of 134 and 141 were grown from various solvents at -20 to +40 °C. The ratio of dimers (*S*)-139 (*SS*) plus (*R-d*)-139 (*RR*) to (*S-R-d*)-139 plus (*R-S-d*)-139 (*RS*) formed from these mixed crystals varied from 1.00:0.93 to 1.00:2.56 whereas for the 140 type dimers the corresponding ratios [(*S*)-140 + (*R-d*)-140:(*S-R-d*)-140 + (*R-S-d*)-140] varied from 1.00:0.90 to 1.00:1.88.⁸⁸ Some order existed in the crystals as indicated by the excess

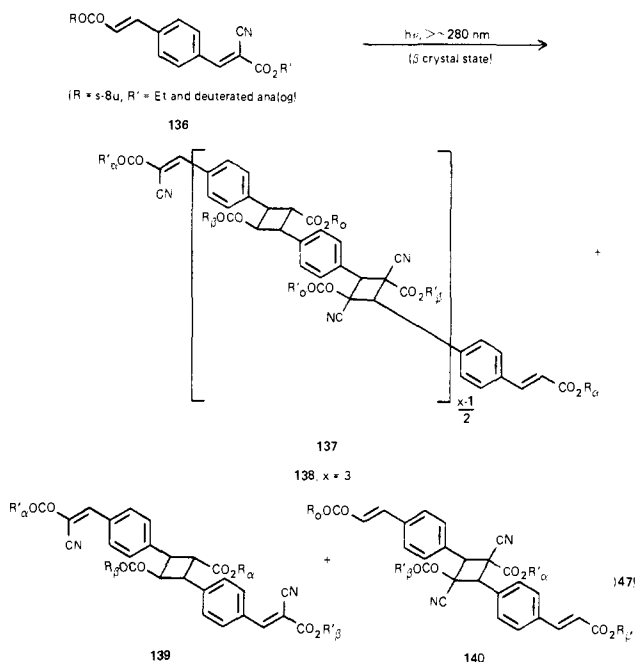

of *RS* pairs under most conditions. No significant difference occurred in rates for the reactions of 134* with 134 or 141 and for the reactions of 141* with 134 or 141 as shown by the lack of a systematic variation of the product ratios with temperature.⁸⁶ The rate of monomer disappearance at 25 °C was approximately twice that at -20 °C. More contacts leading to the 139 type dimers were present than those leading to the 140 type.⁸⁸

X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photo-oligomerization (>410 nm) of chiral 133 (or 134) to give an amorphous oligomer 130, $\bar{x}_n \approx 10$, showed that nucleation began and propagation proceeded within the defect-free structure.⁵¹ No evidence was found for the occurrence of discrete nuclei of products.⁵¹ In comparison to other monomers studied, the monomer 133 (or 134) had a medium reactivity.⁵¹

Several other esters 142 related to 129 gave cyclobutyl polymers, oligomers, trimers, and dimers 143 analogous to 130-132 (eq 48) (Table VIII).^{91,95,96}

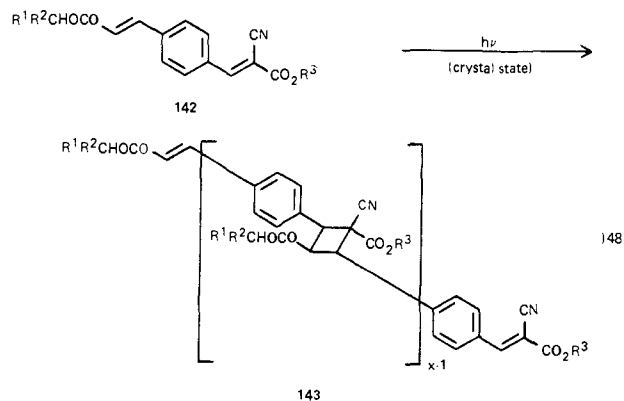


As in the reactions of the *sec*-butyl ethyl diester (133, 134), the addition of optically active *sec*-butyl ethyl dimer (*R*)- or (*S*)-132, or trimer (*R*)- or (*S*)-131, or oligomer (*R*)- or (*S*)-130 (Table VIII), gave optically active dimers 143 ($x = 2$) with an excess of the configuration opposite to that of the additives in all but one instance.⁹⁵ The oligomers and trimers presumably had

configurations similar to those of the newly formed dimers. Similar results were obtained when the photocycloaddition products of 151 and 155 were used as additives.⁹⁵ These photocycloaddition reactions served as the method of determining the absolute configuration of the monomer crystals. Special techniques were employed for growing the crystals used in these studies.

2. Dicyano-*p*-phenylenediacrylate Esters

The bis(propyl cyanoacrylate ester) 166 polymerized rapidly when irradiated in the crystal state (eq 49)

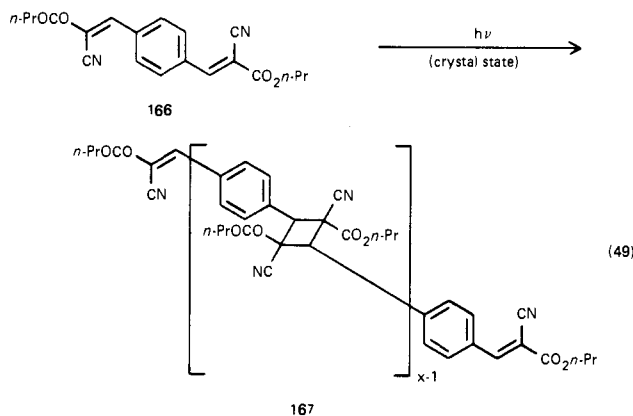

(Table IX).^{76,78,97} X-ray crystal structure determination of monomer 166 showed the double bonds that reacted to form cyclobutane rings has an intermolecular separation of 3.931 Å.^{76,98} Examination of the crystal structure of 166 led to the prediction of 167 as the structure of the polymer.


A mechanism analogous to that shown in Scheme II was proposed to account for the effect of wavelength on the DP (Table IX).⁹⁷ The incomplete oligomerization of 166 exposed to >360 nm light was attributed to disordering of the crystal during the reaction.⁹⁷ Thus some monomer molecules became isolated and could not add to neighboring monomers or oligomers. Irradiating the oligomer 168 at ~300 nm gave high polymer. Excitation of the oligomer and its addition to another oligomer occurred in a manner analogous to reaction 31 in Scheme II.⁹⁷ This polymerization of 168 was not complete, possibly because the crystal became disordered during oligomerization.⁹⁷ Only the *as*-oligomerized crystal of 168 gave high polymer. Samples recrystallized from chloroform failed to polymerize, presumably because the crystal structure was altered.⁹⁷

X-ray diffraction and low temperature electron microscopy studies of the crystal state photopolymerization (>365 nm) of the heavily faulted dicyano dipropyl ester 166 showed that nucleation began and propagation proceeded within the defect-free structure.⁵¹ Discrete nuclei of products were not found.⁵¹ The crystal imperfections present after polymerization showed no correlation with those present before irradiation.⁵¹ In comparison to other monomers studied, the monomer 166 had a high reactivity.^{51,99}

Polymerization of 166 produced a crystalline product containing fine cracks and fibrils; a large molecular movement occurred during the reaction.⁵¹

Irradiating 166 in solution with light of wavelength greater than 340 nm gave no polymer.⁹⁷

Several other bis(cyanoacrylate) esters 169 polymerized when irradiated in the crystal state (eq 50) (Table

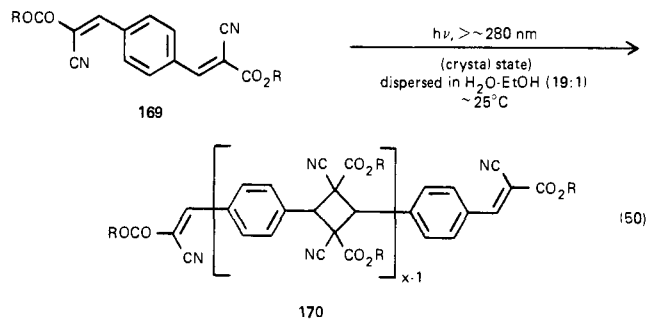

X).⁷⁸ The stereochemistry of the photocycloaddition has not been determined for these esters.

The rates of polymerization of the cyano esters 169 decreased in the order *n*-Pr (166) > Me (171) > *i*-Pr (175) > *n*-Bu (177) > Et (173).⁷⁸ The *n*-Pr ester 166 polymerized as rapidly as distyrylpyrazine 192 (see section IIG1.).⁷⁸ The *i*-Pr and *n*-Bu cyano esters 175 and 177 polymerized faster than the corresponding *p*-phenylenediacrylate esters 82 and 84.⁷⁸

The poly(*n*-Pr ester) 167 had the highest reduced viscosity of all the poly(cyano esters) 170 whereas the Me polymer 172 had the lowest.⁷⁸ The low reduced viscosity, i.e., low DP, of the latter was attributed, at least partially, to *cis*-*trans* isomerization of the olefinic bond during the polymerization.⁷⁸


Changes in the polymerization temperature of between -20 °C and ~+25 °C did not affect the yields or properties of the poly(cyano esters) 170.⁷⁸

Of all the cyano ester crystals 169, the densities of the Et, *n*-Pr, and *i*-Pr ester crystals, 173, 166, and 175 changed the least on polymerization.⁷⁸

The Et ester 173 did not polymerize on irradiation in benzene or dioxane solutions.⁷⁸ Several other compounds, such as the acid, esters, amide, nitrile, and ketone, related to 169 did not polymerize on irradiation in the crystal state.⁷⁸



3. Bis(α-cyano-β-arylvinyl)benzenes

The substituted distyrylbenzene 181 polymerized on irradiation in the crystal state (eq 51).¹⁰⁰ The polymer

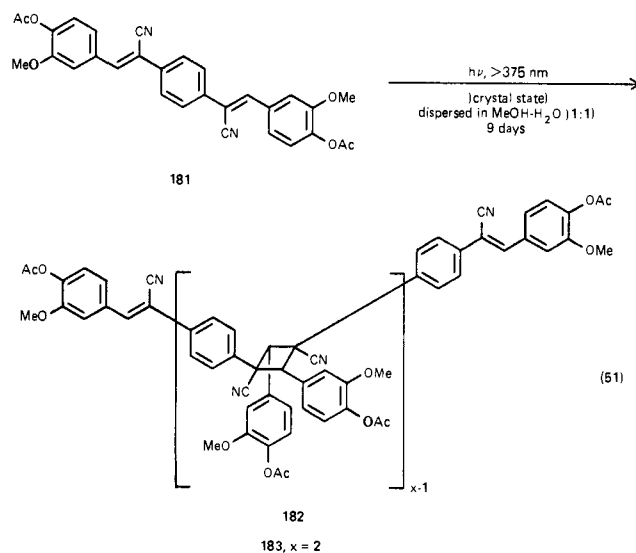

was tentatively assigned structure 182 having a *cis*-1,3-cyclobutane repeating unit.¹⁰⁰ Dimer 183, isolated on limited irradiation, was an intermediate in the polymerization.¹⁰⁰ The stereochemistry of both 182 and

TABLE VI. Photopolymerization of α Crystal Form of *sec*-Butyl Ethyl Cyano-*p*-phenylenediacrylate 129 (Eq 46)

R of monomer 129	dispersion medium for monomer 129	λ , nm	temp, °C	time, h	products	yield of product, %	ref	
(<i>R</i>)- <i>s</i> -Bu 	133	>310	5		(<i>R</i>)-130, $\bar{M}_n \approx 5000$, $\bar{x}_n \approx 15$ (<i>R</i>)-131 (<i>R</i>)-132	92		
	133 ^{a,b}	>310			(<i>R</i>)-130, polymer ^c	93		
	133	>300	5		(<i>R</i>)-130, polymer ^d (CHCl ₃ sol and insol fractions) (<i>R</i>)-132 ^d	87, 93		
	133	>~280			(<i>R</i>)-130, polymer (<i>R</i>)-131 (<i>R</i>)-132 ^d	88		
(<i>S</i>)- <i>s</i> -Bu ^{b,e} 	134	>350		336	(<i>S</i>)-130, polymer, ^f low \bar{M}_n (<i>S</i>)-132 ^{f,g}	93		
	134 ^h	>310	5		(<i>S</i>)-130, ⁱ $\bar{M}_n \approx 5000$ (~10,000 max), $\bar{x}_n \approx 15$ (~30 max) (<i>S</i>)-131 ⁱ (<i>S</i>)-132 ^j	91, 92		
	134	>300	-5		(<i>S</i>)-130, polymer (CHCl ₃ sol and insol fractions) (<i>S</i>)-131 (<i>S</i>)-132 ^k	90		
	134	H ₂ O-MeOH (9:1)	>300	-2	20-60	(<i>S</i>)-130, polymer (CHCl ₃ insol) (<i>S</i>)-130, polymer (CHCl ₃ sol, MeOH insol) (<i>S</i>)-131	~5 ~60 ~10	89
	134	H ₂ O-MeOH (9:1)	>300	-2	20	(<i>S</i>)-130, ^l $\bar{M}_n = 1665$, $\bar{x}_n = 5.1$	89	
	134	H ₂ O-MeOH (9:1)	>300	-2	53	(<i>S</i>)-130, ^l $\bar{M}_n = 3865$, $\bar{x}_n = 11.8$	89	
	134		>300	5	(<i>S</i>)-130, polymer ^d (CHCl ₃ sol and insol fractions) (<i>S</i>)-132 ^d	87, 93		
	134 ^{m,n}	>300	5	168-336	(<i>S</i>)-130, $\bar{M}_n = 1117-2380$, $\bar{x}_n = 3.4-7.3^{l,o,p}$	~40	89	
	134	H ₂ O-MeOH (9:1)	>300	6	50	(<i>S</i>)-130, ^l $\bar{M}_n = 2720$, $\bar{x}_n = 8.3$ (<i>S</i>)-130, polymer (<i>S</i>)-131 (<i>S</i>)-132 ^d	~13 ~35	89
	134	>~280			(<i>S</i>)-130, polymer (<i>S</i>)-131 (<i>S</i>)-132 ^d	88		
	134 ^e	H ₂ O-EtOH (93:7)	>310	5	(<i>S</i>)-130, ^r $\bar{M}_n = 2400$, $\bar{x}_n = 7.3$ (<i>R,S</i>)-130, ^u oligomer, $\bar{R} =$ (<i>R</i>)· or (<i>S</i>)- <i>s</i> -Bu (<i>R,S</i>)-132, ^u $\bar{R} =$ (<i>R</i>)· or (<i>S</i>)- <i>s</i> -Bu ($\bar{M}_n \approx 4000$, $\bar{x}_n \approx 12$) ^v	93	91, 92, 94	
(<i>R,S</i>)- <i>s</i> -Bu, 133, 134 ^{s,t}					(<i>R,S</i>)-130, polymer ^d (insol) (<i>R,S</i>)-130, polymer ^d (sol) ^w (<i>R</i>)-132, ^x $R_\alpha = R_\beta =$ (<i>R</i>)- <i>s</i> -Bu (<i>S</i>)-132, $R_\alpha = R_\beta =$ (<i>S</i>)- <i>s</i> -Bu (<i>R,S</i>)-132, $R_\alpha =$ (<i>R</i>)- <i>s</i> -Bu, $R_\beta =$ (<i>S</i>)- <i>s</i> -Bu (<i>S-R</i>)-132, $R_\alpha =$ (<i>S</i>)- <i>s</i> -Bu, $R_\beta =$ (<i>R</i>)- <i>s</i> -Bu	87, 93		
	133, 134 ^s				(<i>R,S</i>)-130, polymer, $R =$ (<i>R</i>)· or (<i>S</i>)- <i>s</i> -Bu ^y (<i>R,S</i>)-131, $R =$ (<i>R</i>)· or (<i>S</i>)- <i>s</i> -Bu ^y (<i>R</i>)-132, ^y (<i>S</i>)-132, ^y (<i>R,S</i>)- 132, ^y (<i>S-R</i>)-132 ^y	89		
	134 + (<i>R,S</i>)-(CD ₃ CD(CD ₂ CD ₃)), 135 mixtures, (<i>S/R</i>) = [(61/39) - (99/1)]	>310	5		(<i>R,S-d</i>)-130, oligomer (<i>R,S-d</i>)-132, ^z R_α and $R_\beta =$ (<i>S</i>)- <i>s</i> -Bu or (<i>R</i>)· or (<i>S</i>)· (CD ₃)CD(CD ₂ CD ₃)	94		

^a $[\alpha]^{25}_D = -21^\circ$. ^b Original assignment of configuration⁹³ opposite to that reported later.⁸⁸⁻⁹⁰ ^c $[\alpha]^{25}_D = +54^\circ$. ^d Optically active. ^e $[\alpha]^{25}_D = +21^\circ$. ^f Optically active after chiral *s*-Bu group removed. ^g $[\alpha]^{25}_D = -81^\circ$. ^h $[\alpha]_D = +22.7^\circ$. ⁱ $[\alpha]_D$ comparable to that of dimer formed, -109° . ^j $[\alpha]_D = -109^\circ$. ^k Some isomerized monomer, CN and CO₂Et interchanged in 134, was formed. ^l CHCl₃ soluble, MeOH insoluble. ^m 99% optically pure. ⁿ ~10% of monomer 134 recovered after irradiation. ^o Almost no CHCl₃ insoluble product formed. ^p Only one enantiomeric form. ^q >97% enantiomeric purity. ^r $[\alpha]^{25}_D = -24^\circ$. ^s Racemic mixture. ^t Special crystal grown from melt. ^u $[\alpha]_D = -35.0^\circ$ to $+5.8^\circ$ for entire reaction mixture. ^v Entire reaction product. ^w $[\alpha]^{25}_D = -24^\circ$ for soluble (*R,S*)-130 plus dimers, (*R*)-132, (*S*)-132, (*R,S*)-132, and (*S-R*)-132. ^x $[\alpha]^{25}_D = -30^\circ$ for combined dimers. ^y Enantiomer also formed. ^z 60-98% enantiomeric excess of monomer gave ~100% enantiomeric excess of (*R,S-d*)-132. 22-40% enantiomeric excess of monomer gave 85-95% enantiomeric excess of (*R,S-d*)-132. See also ref 91.

TABLE VII. Photopolymerization of β Crystal Form of *sec*-Butyl Cyano-*p*-phenylenediacyrylate 136 (Eq 47)⁸⁸

monomer 136			temp, °C	time, days	products
R		R'			
(<i>R,S</i>)- <i>s</i> -Bu ^a		Et, 133, 134			(<i>R,S</i>)-137, polymer (<i>R,S</i>)-138 (<i>R,S</i>)-139 ^b (<i>R,S</i>)-140 ^b
(<i>S</i>)- <i>s</i> -Bu	+	Et, 134	-20, 5, and 25	10-35	(R, <i>S</i> - <i>d</i>)-137, R _α and R _β = (<i>S</i>)- or (<i>R</i>)- <i>s</i> -Bu, R' _α and R' _β = Et or C ₂ D ₅ , oligomer (<i>S</i>)-139, R _α = R _β = (<i>S</i>)- <i>s</i> -Bu, R' _α = R' _β = Et ^b (<i>R</i> - <i>d</i>)-139, R _α = R _β = (<i>R</i>)- <i>s</i> -Bu, R' _α = R' _β = C ₂ D ₅ (<i>S</i> - <i>R</i> - <i>d</i>)-139, R _α = (<i>S</i>)- <i>s</i> -Bu, R _β = (<i>R</i>)- <i>s</i> -Bu, R' _α = Et, R' _β = C ₂ D ₅ (<i>R</i> - <i>S</i> - <i>d</i>)-139, R _α = (<i>R</i>)- <i>s</i> -Bu, R _β = (<i>S</i>)- <i>s</i> -Bu, R' _α = C ₂ D ₅ , R' _β = Et (<i>S</i>)-140, R _α = R _β = (<i>S</i>)- <i>s</i> -Bu, R' _α = R' _β = Et ^b (<i>R</i> - <i>d</i>)-140, R _α = R _β = (<i>R</i>)- <i>s</i> -Bu, R' _α = R' _β = C ₂ D ₅ (<i>S</i> - <i>R</i> - <i>d</i>)-140, R _α = (<i>S</i>)- <i>s</i> -Bu, R _β = (<i>R</i>)- <i>s</i> -Bu, R' _α = Et, R' _β = C ₂ D ₅ (<i>R</i> - <i>S</i> - <i>d</i>)-140, R _α = (<i>R</i>)- <i>s</i> -Bu, R _β = (<i>S</i>)- <i>s</i> -Bu, R' _α = C ₂ D ₅ , R' _β = Et
(<i>R</i>)- <i>s</i> Bu		(50:50 mixture)			

^a Racemic mixture. ^b Yield of 139 type products > yield of 140 type products.

TABLE VIII. Photopolymerization of Cyano-*p*-phenylenediacyrylate Esters 142 in the Crystal State (eq 48)

monomer 142			temp, °C	time, weeks	products 143	ref
R ¹	R ²	R ³				
Me	Me	Et, 144			145, ^a polymer 146, ^a x = 2	96
Me	Et	<i>n</i> -Pr, 147 ^{b,c}	5	2	148, oligomer 149, x = 3 150, x = 2	95
Et	Et	Me, 151 ^d	5	2	152, oligomer 153, x = 3 154, x = 2	95
		151			152, ^a polymer 154 ^e	91
Et	Et	Et, 155 ^f	5	2	156, oligomer 157, x = 3 158, x = 2	95
		155			156, ^a polymer 158 ^a	96
		144 + 155 ^d	5	2	159, oligomer, R ¹ = R ² = Me or Et, R ³ = Et 160, x = 3, R ¹ = R ² = Me or Et, R ³ = Et 146	95
		144 + 155 ^f			161, x = 2, R ¹ = R ² = Me or Et, R ³ = Et 159, ^a polymer 161 ^a	91
Et	Et	<i>n</i> -Pr, 162 ^d	5	2	163, oligomer 164, x = 3 165, x = 2	95

^a Optically active. ^b Racemic mixture. ^c Mixture with 3-15% optically active dimer (*R*)- or (*S*)-132. ^d Mixture with 3-15% optically active dimer (*R*)- or (*S*)-132, or 15% optically active trimer (*R*)- or (*S*)-131, or 8% optically active oligomer (*R*)- or (*S*)-130. ^e Max [α]_D = +106°; [α]_D for entire reaction mixture = 0 to +60°. ^f Mixture with 3-15% optically active dimer (*R*)- or (*S*)-132, or 15% optically active trimer (*R*)-131. ^g 1:1 mixture of 144 and 155.


TABLE IX. Photopolymerization of Dipropyl *p*-Phenylenedi(α-cyanoacrylate) (166) in the Crystal State (Eq 49)

dispersion medium for monomer 166	λ, nm	temp, °C	time, h	product 167	yield of 167, %	ref
H ₂ O-EtOH (19:1)	>~280	~25	0.5	high polymer	100 ^a	78, 97
	>360 ^b	~25	several	polymer		11
168 crystal ^c	~300 ^d		1	oligomer, 168 high polymer	<100	97 97

^a Conversion as a function of time given. ^b 383 nm actually used. ^c <1% 166 present. ^d 304 nm actually used.

183 was uncertain. The quantum yield for the formation of cyclobutane rings in both 182 and 183 was 0.7 ± 0.1 at 365.4 nm.¹⁰⁰


Several compounds, 184, 186, and 188, related to 181 photopolymerized in the crystal state (eq 52).¹⁰¹ The stereochemistry at the olefinic linkages of the monomers

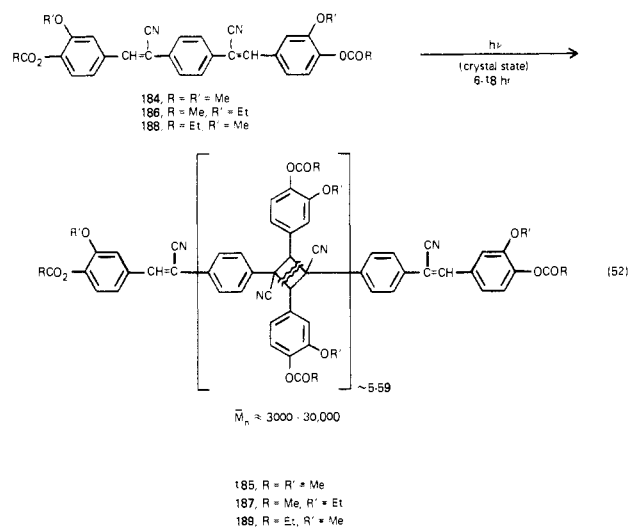

was not specified. Presumably, 184 was identical with 181. The quantum yield at ~ 320 – 400 nm for the disappearance of the olefinic double bonds of 184 as a dry layer of crystals was ~ 0.7 , i.e., one-half that reported above for 181.¹⁰¹ The molecular weights of 185, 187, and 189 were ~ 3000 – $30,000$.¹⁰¹

F. 2,5-Distyrylpyridine


The crystal state irradiation of pyridine derivative 190 gave a 1,3-cyclobutyl polymer 191 (eq 53).²⁴

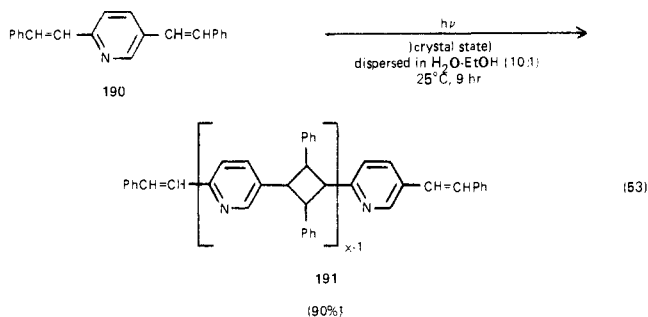

G. 2,5-Distyrylpyrazine

1. Crystal State

The photocycloaddition polymerization of *trans*,*trans*-2,5-distyrylpyrazine (192) has been studied more extensively than any other polymerization discussed in this review (ref 6, 14, 33, 49, 51, 57, 61, 68, 73, 76, 79, 81–84, 97, 99, 102–122). Nearly all of these studies have dealt with the solid state topochemical polymerization that gave the *trans*-1,3-cyclobutyl polymer 193 (eq 54)

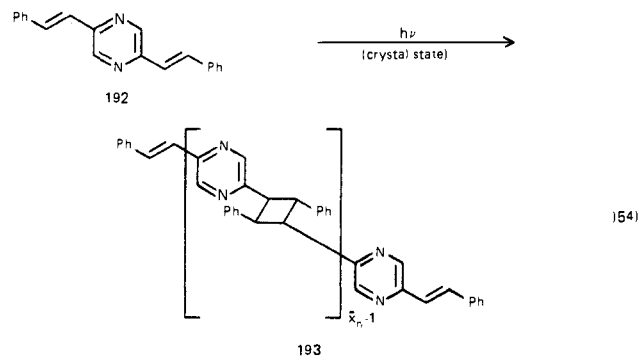

(Table XI). Polymer 193 was reported as having a

TABLE X. Photopolymerization of *p*-Phenylenebis(α -cyanoacrylate) Esters 169 in the Crystal State (Eq 50)⁷⁸

R of monomer 169	time, h	product 170	yield of 170, %
Me, 171	6-7	172, low \bar{M}_n polymer ^a	100
Et, 173	144	174, high polymer	66
	240		<66
<i>i</i> -Pr, 175	120	176, high polymer	100
<i>n</i> -Bu, 177	144	178	88
<i>n</i> -C ₈ H ₁₇ , 179	240	180	100

^a Low and high \bar{M}_n fractions isolated.

higher molecular weight, $>500,000$, than any other polymer described in this review.^{14,73}

The X-ray crystal structure of the polymerizable^{49,73,113} α -crystal form of 192 has been determined^{49,76,107} and led to the assignment of the structure of the polymer 193. The double bonds of the monomer 192 that reacted to form the cyclobutane rings of 193 were separated by 3.939 Å in the crystal.^{49,76,107} The γ -crystal form of the monomer 192 did not photopolymerize.^{49,76,113}

The quantum yield for the polymerization of 192 was reported to be between 1.2 and ~ 2 (per double bond).^{14,68,81,119} The quantum yields may have depended on the DP and/or the wavelength: ≥ 1.2 for the initial oligomerization at 436 nm and ≥ 1.6 for the transformation of the oligomer to polymer at 365 nm.⁶⁸

The di-*p*-methyl and -methoxy derivatives of 192 did not photopolymerize in the crystal state.⁸³ This lack of reactivity could have been caused by an unfavorable crystal structure or a lower intrinsic reactivity of these monomers compared with that of 192.

Irradiating monomer 192 with light of wavelengths >400 nm produced solely low molecular weight oligomers because the oligomers absorbed light only at wavelengths shorter than 380 nm.^{57,68,104,109} This explanation was analogous to that described above for diester 68 (Scheme II). Irradiating monomer 192 or the *as*-formed oligomer with short wavelength light (<380 nm) produced higher molecular weight polymer.^{68,104,109} Recrystallized oligomer did not form higher molecular weight polymer when irradiated further, presumably because it changed to a more stable crystal form.^{68,104} This evidence further supports a lattice-controlled reaction.⁶⁸

The rate of conversion of monomer 192 increased with increasing light intensity, but the molecular weight of the polymer 193, as indicated by reduced viscosity, was nearly constant at a given conversion for different light intensities.^{57,84} This behavior was in accord with the stepwise mechanism described in a later paragraph.⁸⁴

The rate of polymerization as measured by consumption of monomer 192 increased slightly as the temperature increased from -20 °C to $+50$ °C.^{57,73,84} At up to 50% conversion, this temperature dependence corresponded to an activation energy of ~ 3 kcal mol⁻¹.⁸⁴ The rate was considerably slower at -42 °C.^{57,84} The reduced viscosities at constant conversion were nearly equal for polymerizations carried out at -55 °C to 0 °C.^{73,84} At higher temperatures, up to 50 °C, the reduced viscosity and DP decreased markedly with an increase in temperature.^{57,73,84} The temperature dependence of the DP indicated that polymerization de-

TABLE XI. Photopolymerization of 2,5-Distyrylpyrazine (192) in the Crystal State (Eq 54)

dispersion medium for monomer 192	λ , nm	temp, °C	time, h	product 193	yield of 193, %	ϕ -(C=C)	ref
KBr	436			oligomer		1.2~2	68
	>435			oligomer			114, 116
	>431			oligomer			33
	>430			oligomer			109
KBr	430	<i>a</i>		oligomer, $\bar{x}_n \approx 5$, 194	~99		68
H ₂ O-MeOH (3:1)	>420	~20 ^b		oligomer, $\bar{x}_n = 6$			115
MeOH-H ₂ O (3:2)	>400	~25	~1	oligomer, $\bar{M}_n \approx 900$, $\bar{x}_n \approx 3.2$	~100		104
MeOH-H ₂ O (3:2)	>400	~25	1	oligomer, $\bar{x}_n \approx 5$, 195	100		68
oligomer ^c , KBr	365			polymer		1.6~2	68
194, KBr	350		<i>d</i>	polymer			68
195, MeOH-H ₂ O (3:2)	350	~25		polymer			68
KBr	350			polymer			68
	>345		0.0003-0.01	polymer			114
	>345 ^e		0.17-0.25	polymer			117
	>345			polymer			116
	>340			polymer			33
MeOH-H ₂ O (3:2)	340	~25	~1	polymer, $\bar{M}_n > 100,000$, $\bar{x}_n > 350$	100		104
oligomer	340			high polymer			49
	>280 ^f		10	polymer	89		83
<i>c</i> -C ₆ H ₁₂ ^g	quartz ^h	30	1	polymer	~88 ⁱ		57, 84
<i>c</i> -C ₆ H ₁₂	quartz ^j	30	1	polymer	~81 ⁱ		57, 84
<i>c</i> -C ₆ H ₁₂	quartz ^k	30	1	polymer	~14 ⁱ		57, 84
<i>n</i> -C ₆ H ₁₄	quartz	-42	0.17	polymer	~5 ⁱ		57, 84
<i>n</i> -C ₆ H ₁₄	quartz	-20	0.17	polymer	~44 ⁱ		57, 84
<i>n</i> -C ₆ H ₁₄	quartz	0	0.17	polymer	~62 ⁱ		57, 84
<i>n</i> -C ₆ H ₁₄	quartz	50	0.17	polymer	~91 ⁱ		57, 84
<i>c</i> -C ₆ H ₁₂	quartz	30	1	polymer	60.0 ⁱ		57, 84
<i>c</i> -C ₆ H ₁₂	quartz	30	1 ^l	polymer	65.8		57, 84
<i>n</i> -C ₆ H ₁₄	quartz	-25		polymer	~98		84
MeOH-H ₂ O (3:2)	quartz	30	1	polymer	99.5		84
	no filter	25		polymer			49
			0.83	high polymer ^m			49
		~25	2	polymer	100		57
<i>c</i> -C ₆ H ₁₂		~25	2	polymer ⁿ	~100		83
<i>c</i> -C ₆ H ₁₂		~25	5	polymer, high \bar{M}_n	~100		102
		~25	<i>o</i>	polymer, $\bar{M}_n = >500,000$, $\bar{x}_n = >1700$			14, 73
	<i>p</i>			polymer, $\bar{M}_n = 60,000$, $\bar{x}_n = 210$			103
H ₂ O-MeOH (3:1)		~25		polymer ^q , $\bar{x}_n = 124.8$ and 36.5			115
H ₂ O		~25		polymer, $\bar{M}_n = 10,000$, $\bar{x}_n = 35$			112
none ^r			~24	polymer	100		120
				polymer, $\bar{M}_n = 63,000$, $\bar{x}_n = 220$, and $\bar{M}_n = 10,000$, $\bar{x}_n = 35$			110
				polymer		1.2-1.6	119

^a 1.3 μE cm⁻². ^b No 192 remaining at end of reaction. ^c Unspecified. ^d 1.2 μE cm⁻². ^e Wavelength limit, <345 nm, given in ref 117 is probably a misprint. ^f Sunlight. ^g Cyclohexane. ^h Relative light intensity = 100. ⁱ Conversion as a function of time given. ^j Relative light intensity = 64. ^k Relative light intensity = 14. ^l Further data at various times given. ^m Intermediate oligomer detected. ⁿ Linear. ^o Several tens of hours. ^p UV lamp or sunlight. ^q 450-W high pressure mercury lamp excited the terminal double bond of the oligomer more selectively than 500-W xenon lamp did. Oligomers hardly accumulated throughout the whole polymerization process. ^r Single crystal.


pended on the crystal state at the growing chain end.⁷³

The decrease in DP at higher temperature was presumably caused by more random motions of the molecules in the crystal. No polymerization occurred when the molten monomer 192 was irradiated at 250 °C.⁸⁴

Irradiating crystalline 192 in the presence of initiators, presumably of the radical type, did not produce any polymer.⁸⁴ The radical inhibitors, hydroquinone and oxygen, did not retard the solid state polymerization of 192.⁸⁴

Monomer 192 polymerized faster when dispersed in methanol-water (3:2) than in cyclohexane.⁸⁴ This behavior was attributed to the greater solubility of 192 in cyclohexane and the resulting greater absorption of light by dissolved 192.⁸⁴ Only the light absorbed by crystalline 192 was effective in causing polymerization in the solid state.

Scheme IV

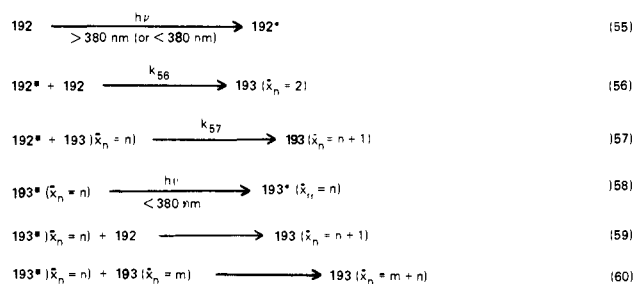

The mechanism for photopolymerization of the pyrazine 192 was a stepwise process (Scheme IV) analogous to that shown in Scheme II for diester 68.^{49,57,68,84} A relative rate constant ratio [k_{57}/k_{56} , defined by eq 61]

$$-\frac{d[192]}{dt} = k_{56}[192^*][192] + k_{57}[192^*][193] \quad (61)$$

was estimated as ~ 5 for addition of excited monomer 192^* to oligomer 193 and to ground state monomer 192 .⁶⁸ This rate constant ratio accounted for the average pentamer formation when 192 was irradiated with >400 nm light.⁶⁸ The change in distance between reacting double bonds during the polymerization may explain the difference in rate constants.^{49,68} The distance between the reacting double bond of a monomer molecule 192 and that of an adjacent oligomer 193 was expected to be shorter than the corresponding distance between the double bonds of two adjacent monomer molecules. This shortening occurred because of the twisting motion of the monomer as it became the terminal unit of an oligomer.^{49,68}

The DP increased gradually with the initial increase in conversion of the monomer 192 .^{57,73,84} Typical of stepwise polymerizations, the DP continued to increase even after all the monomer was consumed, at both -25 °C and $+30$ °C.^{57,84} The reduced viscosity of the polymer 193 increased sharply at ~ 95 – 98% conversion of the monomer.^{73,84} Polymer 193 , after residual monomer 192 and oligomer 193 had been removed, continued to increase in DP when irradiated further with a broad spectrum light source.⁸⁴ On irradiation at 350 nm, the oligomer 193 ($\bar{x}_n \approx 5$) continued to increase in molecular weight.⁶⁸ These observations were consistent with step 60 in Scheme IV.

The molecular weight distribution of 193 was broad at low monomer conversion when a broad spectrum radiation source was used.⁸⁴ In contrast, irradiation of 192 at 350 nm gave only polymer 193 ; no oligomer was detectable during the course of the reaction.⁶⁸ This result implied relatively few intermediate oligomers existed at any time under these conditions and was in qualitative agreement with $k_{57}/k_{56} \approx 5$.

Little has been reported about the nature of the excited states involved in the photocycloaddition polymerization of 192 , only that an excited complex (exciplex) may have been involved in the process.¹¹¹

The enthalpy of polymerization of monomer 192 to 193 , when both were in the crystal state, was $+3.7 \pm 0.9$ kcal mol⁻¹ of monomer.¹¹² This endothermic behavior was attributed to the endothermic change in crystal states predominating over the exothermic change in chemical bonding.¹¹² The calculated enthalpy of reaction, 192 (l) \rightarrow 193 (amorphous) was -5.4 kcal mol⁻¹ of monomer.¹¹² The probable explanation for the overall positive enthalpy change in the crystal state photopolymerization is that the molecules in the polymer crystal were looser and more disordered than those in the monomer crystal.¹¹² During the polymerization, the strain energy, caused by molecular movement, accumulated in the reacting crystal step by step and resulted in a thermodynamically unstable polymer crystal.¹¹² Part of the strain was relieved by cracking of the crystal in the later stages of the polymerization.¹¹² The conclusion was reached that the strain energy might have competed with the molecular chain growth so as to place an upper limit on the chain length.¹¹²

Considerable effort has been expended to elucidate the crystallographic features of the solid state photopolymerization of 192 . Polymer 193 as formed in the solid state was highly crystalline^{14,82,84,106} and resulted

from a reaction in which the stereochemistry was controlled by the crystal lattice of monomer 192 .^{57,106} Numerous other aspects of the reaction, such as the rate, were also undoubtedly influenced by the crystal lattice of the reactant.

The original reports on the crystallographic aspects of the polymerization of 192 indicated that the polymer 193 crystal and the monomer crystal belonged to the same space group and had the same three crystal axes.^{81,104,106} The oligomer also had the same crystal axes.⁴⁹ The degrees of orientation of the polymer were about the same whether or not the oligomer was formed in a separate step.⁴⁹ The postulate was made that the reaction proceeded by direct rearrangement of the monomer crystal to the polymer crystal.^{49,104} The c axis, the direction along which the polymer chain grew,¹⁰⁷ contracted 1.5% during the polymerization,⁸¹ while the a axis contracted 11% and the b axis expanded 13% .⁴⁹ The latter two changes were suggested to result from displacement of the phenyl rings and formation of an sp^3 bond, respectively, during the cycloaddition process.⁴⁹ The small movement along the axis in the direction of the chain growth may have been an important factor in producing a linear polymer in good yield.^{49,111} The center of gravity of 192 moved very little in the direction of chain growth.⁴⁹

A later report indicated that the space groups of 192 and 193 were different, but that the structure 193 was probably still correct.¹¹⁷ A more recent publication argued that the original space group assignment for the polymer 193 was correct.¹²⁰

Electron microscopy and X-ray diffraction studies of the crystal state photopolymerization of 192 produced conflicting results concerning the crystallographic aspects of the process.^{14,33,51,76,81,106,114,116,117} Several studies indicated that the polymerization occurred homogeneously throughout the bulk of the crystal^{14,51,76,81,106,116} in a manner similar to that described in section IID1 on diesters 66 . The relationship of the polymer 193 stereochemistry to the crystal lattice of the monomer 192 is clear for this mechanism.

Other studies indicated polymerization started preferentially at macroscopic defect sites such as cracks and edges.^{33,114} As a result of mechanical strain exerted from polymerized sites into unreacted zones, the monomer crystal cracked, thus providing new nucleation sites.¹¹⁷ The reaction did not occur in the unperturbed state according to these studies.¹¹⁴ Results indicated that formation of new polymer chains at the surface of a new polymer phase,¹¹⁷ one to three unit cells thick,⁷⁶ was faster than the addition of new monomer units to the chain ends.¹¹⁷ The polymer thus grew faster in the crystallographic b direction than in the c direction, the direction of chain growth.¹¹⁴ Overall, the steps in the polymer growth were suggested as proceeding via: (1) formation of nuclei; (2) chain growth in the c direction by addition of monomer 192 to existing chains, 193 ; (3) formation of new chains at the surface of the existing polymer phase in the b,c plane; and (4) nucleation of new layers or growth in the c direction.¹¹⁴ Different quantum yields and temperature dependencies were expected for each of these processes.¹¹⁴ The measured quantum yield^{68,119} (Table XI) would thus have been only an average of those for the various processes.¹¹⁷


Small crystals of **192** polymerized slightly faster than larger ones; both types had the same crystal structure as shown by X-ray analysis.⁸⁴ At the same conversion of monomer **192**, the larger crystals produced the higher molecular weight polymer **193**.⁸⁴ Both the faster rate and the lower molecular weight could be attributed to the smaller crystals' having more defect sites per unit weight and thus more initiation sites.

If the cycloaddition reactions of **192** did only occur at defect sites, the question arises as to how the stereospecificity was related to the monomer lattice arrangement.¹¹⁷

The most recent results of X-ray diffraction and low temperature transmission electron microscopy studies of the crystal state photopolymerization ($\lambda > 365$ nm) of α -**192** indicated that nucleation began and propagation proceeded within the defect-free structure.⁵¹ Crystal faults were frequently introduced during the irradiation.⁵¹ No evidence was found for discrete nuclei of products.⁵¹ Compared with other monomers that underwent crystal state photopolymerization, the pyrazine **192** had a high reactivity.⁵¹

The morphological changes that occurred during polymerization of **192** were similar to those noted in section IID2 for the structurally related dipyrindyl compound **108**. The crystal exhibited a large shape change and underwent significant cracking.⁶¹ The monomer **192** unit cell and symmetry were analogous to those of **108**.⁸²

A solid-solution mixed crystal of the pyrazine **192** and pyridine **108** derivatives was prepared in which the monomer ratio was 0.60:0.40 (**108**:**192**).¹²¹ An X-ray crystal structure determination showed the molecular packing modes were nearly identical with those of the pure crystals of **108** or **192**.¹²¹ In the mixed crystal the nearest intermolecular double bond separations were 3.846 Å (C_1-C_2 and C_2-C_1), 3.941 Å (C_3-C_4 and C_4-C_3), 3.752 Å (C_1-C_4), and 4.033 Å (C_2-C_3).¹²¹ The double bonds of adjacent mixed pairs **108** and **192** were not parallel.¹²¹ Irradiation of this mixed crystal gave a polymer that presumably consisted of repeating units **196**–**199** in appropriate combinations (eq 62).¹²¹

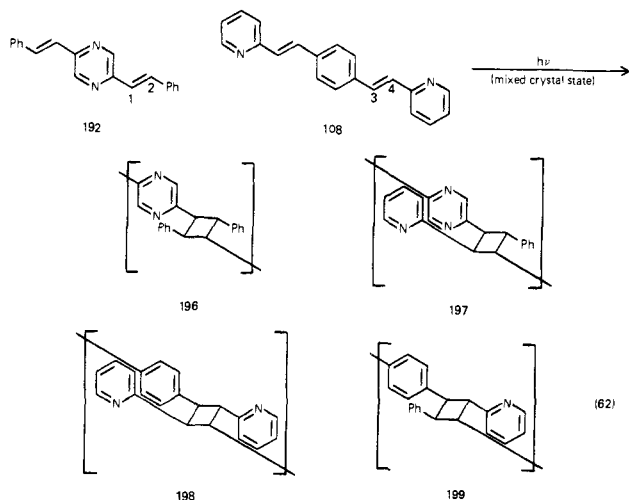

2. Solution Phase


In contrast to the crystal state photopolymerization of distyrylpyrazine **192** where high molecular weights were achievable, irradiating the monomer **192** in solu-

TABLE XII. Photopolymerization of 2,5-Distyrylpyrazine (**192**) in Solution (Eq 63)

solvent	λ , nm	time, h	product 200	yield of 200 , %	ref
CHCl ₃	>380	a	oligomer		104
CHCl ₃			oligomer		97
THF ^b	395	1	oligomer	81	79
THF ^c	>380	48 ^d	oligomer, $\bar{M}_n = 770-900$, $\bar{x}_n = 2.7-3.2$	60	14, 79
THF			oligomer		97

^a Prolonged, under N₂. ^b 0.00609 M **192**. ^c 0.0141 M **192**. ^d At ~25 °C.

tion gave only low molecular weight oligomers **200** (eq 63) (Table XII).^{14,57,79,81,84,97,104} Oligomer **200** contained

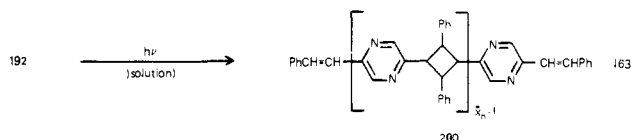

cyclobutanes having mixed stereochemistry⁷⁹ in contrast to the stereoregular cyclobutanes formed in the crystal state polymerization. The oligomer was amorphous^{14,79,104} rather than crystalline as was the product of the solid state reaction.

The mechanism proposed for the solution-phase photopolymerization of **192** at >380 nm was the same as part of that proposed for the solid state reaction (Scheme IV, eq 55–57).⁷⁹ The values of k_{56} and k_{57} were such that more oligomer **200** ($\bar{x}_n > 2$) than dimer **200** ($\bar{x}_n = 2$) was formed.⁷⁹ Because only the monomer **192** absorbed light under these conditions, the molecular weight of the oligomer **200** did not increase after all the monomer had reacted.⁷⁹ In contrast, the DP of poly-(bismaleimide) **220** continued to increase after the monomer had reacted because the monomer and polymer chromophores absorbed at essentially the same wavelengths (section IIK). Attempts to increase the DP of the oligomer **200** produced in solution by irradiating it in CHCl₃ solution at >340 nm led instead to reformation of monomer **192** and a decrease in molecular weight.⁷⁹

As in the crystal state reaction (eq 54), initiators did not promote polymerization of **192**.⁸⁴

The pyrazine **192** and pyridine **108** derivatives had about equal reactivities in solution.⁸¹ Thus some factor in the isolated molecules did not cause the much higher quantum yield for polymerization of **192** than of **108** in the crystal state.⁸¹ Slightly dissimilar molecular packings or overlaps of the nitrogen atoms with the phenyl rings in the crystals could have caused the difference.⁸¹

Molecular orbital treatment of the α -crystal form of **192** and of **108** reportedly explained the difference in quantum yields for the two polymerizations.⁸¹ Calculating the π stabilization energies of the excimers in the crystals quantitatively explained the difference in reactivities of crystalline **192** and **108**.^{99,108} However, this type of calculation also predicted that the photostable γ -crystal form of **192** would be more photoreactive than **108**.⁹⁹ Therefore some other factors need to be taken into account. The layer type of packing of γ -**192** probably suppressed molecular deformation that would have been required for a cycloaddition.⁹⁹ This calculation method did not quantitatively include a barrier

TABLE XIII. Photopolymerization of Distyryl-s-triazine Derivatives 201 (Eq 64)¹²³


X of monomer 201	solvent	time, h	product 202	conversion of double bonds 202, %
H, 203	PhMe ^a	30	204, $\overline{M}_n = 1083$, $\overline{x}_n = 3.00$	39 ^b
203	CHCl ₃	48	204	30 ^b
203	none	25	204	19 ^b
203	dispersed in H ₂ O-EtOH (1:1)	2	204	11 ^b
203	PhH	72	204	
NMe ₂ , 205			206	
NO ₂ , 207	HCONMe ₂	24	208	c
207	PhMe ^a		208	

^a Boiling. ^b Conversion as a function of time given. ^c Some monomer remained after irradiation.

to this molecular deformation.⁹⁹

H. Distyryl-s-triazines

The difunctional triazine derivatives 201 polymerized rather inefficiently when irradiated in solution or the solid state (eq 64) (Table XIII).¹²³ Cis-trans isomeri-

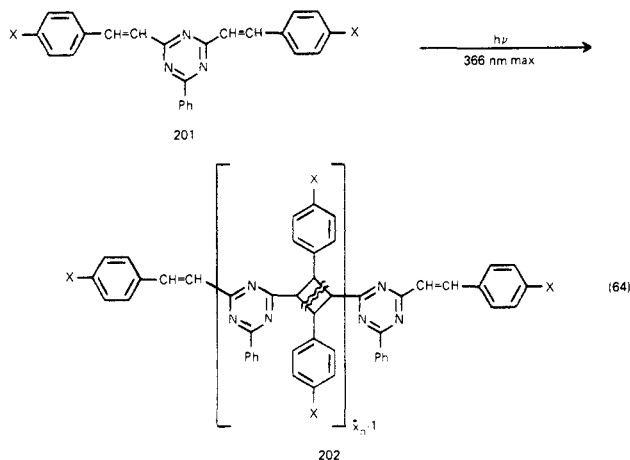

zation about the double bonds of the monomers 201 occurred during the irradiation.¹²³


The initial rates of reaction of the unsubstituted styryl derivative 203 in various solvents decreased in the following order: PhMe > no solvent > dispersion in H₂O-EtOH (1:1) > CHCl₃.¹²³ The maximum conversion of double bonds in 203 occurred at intermediate

irradiation times, shown in Table XIII, for the H₂O-EtOH dispersion and probably for the PhMe solution.¹²³ Further irradiation caused the re-formation of double bonds, probably because of a reversal of the forward reaction (eq 64).¹²³

The molecular weight, as indicated by the reduced viscosity of polymer solutions, of polymer 204, formed in PhH solution, increased sharply during the first 4 h of irradiation of 203.¹²³ The molecular weight then increased linearly at a slower rate for the next 68 h of irradiation.¹²³ Over this same time span, the molecular weight of 204 prepared in PhMe solution first increased to a maximum at ~50 hours and then decreased, again presumably because of decomposition of the polymer.¹²³


I. 2,6-Naphthalenediacrylate Ester

Irradiating crystals of the naphthalenediacrylate ester 209 gave a cyclobutyl polymer 210 (eq 65) in a process similar to that exhibited by the pyrazine derivative 192.¹¹⁷ The crystal structure of 209 was analogous to that of 192 about the carbon-carbon double bond.^{117,124} The double bonds of 209 that reacted to form the cyclobutane rings of 210 were separated by 3.76 Å in the crystal state.¹²⁴ A polymer phase, which separated during the irradiation, grew perpendicularly to the boundary of the monomer crystal.¹¹⁷ Analogous to the polymerization of 192, the nucleation and growth of polymer 210 in different crystallographic directions probably exhibited different quantum yields and rates.¹¹⁷

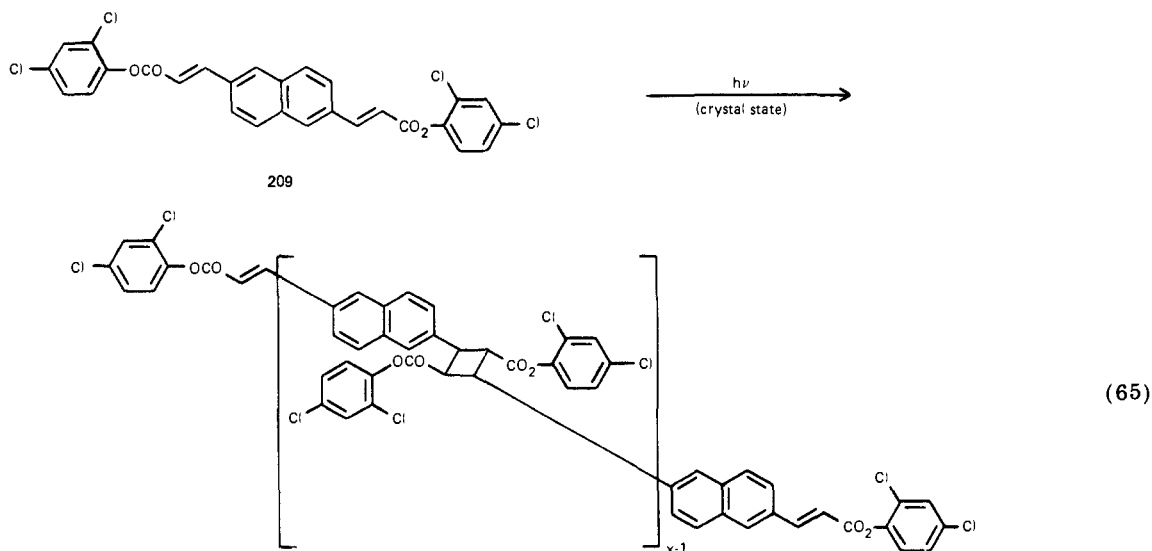


J. Styrene

Among the products of the photopolymerization of styrene (211) were several trimers that probably were formed by two successive cycloaddition reactions (eq 66).¹²⁵⁻¹²⁷ The structures of the unsaturated trimers

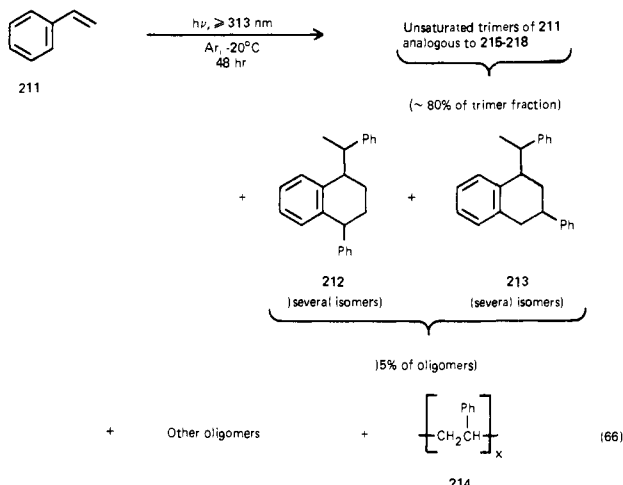

were not reported, but were described as analogous to several unsaturated dimers, the structures of which were postulated as 215-218.¹²⁵ These dimers and several

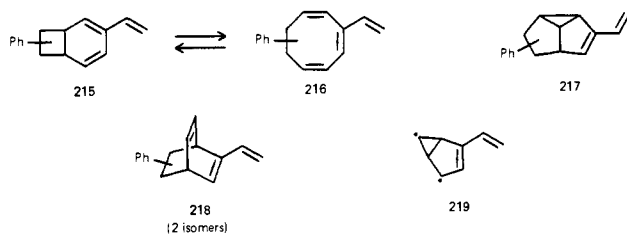


others were isolated from the irradiation of 211 under conditions slightly different from those shown in eq 66.¹²⁵ Dimers 215-217 and two isomers of 218 constituted 13-15% and 6-7%, respectively, of the dimer fraction.¹²⁵

Dimer 215 could have resulted from a 2 + 2 cycloaddition of two monomer 211 molecules, 217 from a 2 + 3 cycloaddition via intermediate 219, and 218 from a 2 + 4 cycloaddition.¹²⁵ Presumably the vinyl groups, or other olefinic linkages, of dimers 215-218 could have reacted with a molecule of styrene (211) to give the trimers in processes similar to those in which 215-218 were formed. Higher molecular weight oligomers may have also formed in analogous processes.


K. Bis(maleimides)

1. Unsubstituted

The photochemical intermolecular polymerization and intramolecular cyclization of *N,N'*-bis(maleimides) 220 have been studied extensively (eq 67) (Table

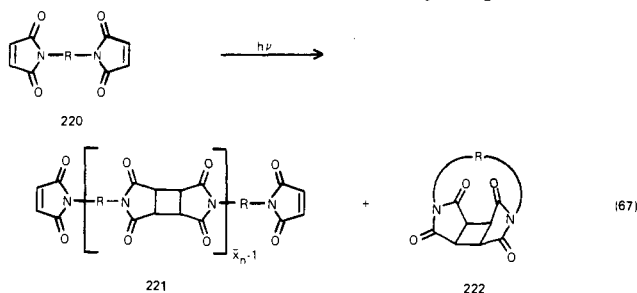

Scheme V

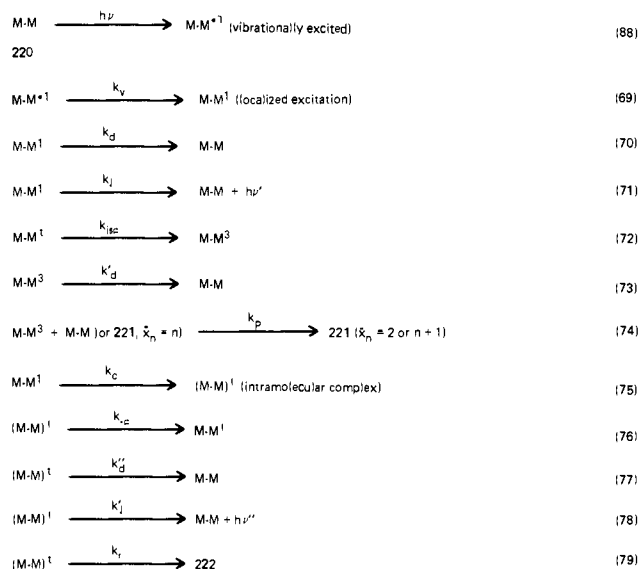

XIV).^{10,12,128-133} The competition between these two processes was examined for several derivatives.^{10,128,129,132}

Intermolecular oligomerization to 224 was the only unsensitized reaction exhibited by the dimethylene derivative 223. Molecular models indicated that the intramolecular product 225 would be very strained.¹³² However, 225 apparently was a product from the benzophenone-sensitized photoaddition.¹²⁹ The hypothetical *m*-phenylene product 258, from 256, would be even more strained than 225. The trimethylene bis(imide) 226 and the hetero analog 220 ($R = CH_2OCH_2$) in solution gave only the corresponding cyclized products 222.¹³² The next four higher homologues 229, 232, 235, and 238 also gave primarily the intramolecular products 231, 234, 237, and 240, respectively,¹³² except at high concentrations.¹⁰

The sudden increase in yield of the oligomers 242, 245, 248, 251, and 254, which contain segments of eight, nine, ten, eleven, and twelve methylene groups, respectively, was attributed to the availability of more conformations than were possible for the lower homologues.¹³² The probability that the molecule will reach a conformation suitable for cyclization within the lifetime of the reactive excited singlet state decreased rapidly with increasing chain length.¹³²

The quantum yield for intramolecular addition, Φ_{222} , varied considerably more than the chemical yield of 222 did.¹³²

The yield of oligomer increased from 5% to 100% when the initial concentration of the hexamethylene bis(imide) 235 was increased from 0.005 or 0.01 to 1 M (Table XIV). At 10^{-3} M 235 no oligomer was formed.¹³²

The presence of oxygen in solutions of 220 did not affect the reaction.^{10,128,132} At long irradiation times, the oligomers underwent crosslinking.¹³²

Φ_{222} was not dependent on the radiation wavelength (300-350 nm) or on the temperature (15-55 °C).¹³² The quantum yields for cyclization of 235, Φ_{237} , decreased with increasing solvent polarity, whereas the chemical yields remained constant, implying that the rates of deactivation processes leading back to 235 increased as the solvent polarity increased.¹³² Adding benzophenone as a sensitizer increased the yield of oligomer 236.¹³² No ultraviolet spectroscopic evidence was observed for the

TABLE XIV. Photopolymerization and Photocyclization of Bis(Unsubstituted Maleimides) 220 (Eq 67)

R of monomer 220	phase	concn of 220, M	sensitizer, concn, M	λ , nm	temp, °C	time, h	atm over soln	product ^a 221	yield of 221, %	product 222	yield of 222, %	Φ_{222}^b	$\tau_{220}^{*1, c}$	Φ_{220}^{*3}	ref
(CH ₂) ₂ , 223	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	224	100	225	0				132
223	MeCN soln	0.01	Ph ₂ CO, 0.005	~350		3.5		224		225					129
(CH ₂) ₃ , 226	crystal		none					227 ^d		228	0				131
(CH ₂) ₄ , 229	CH ₂ Cl ₂ soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	230	15	231	85				132
229	CH ₂ Cl ₂ soln	0.01	none	300 ± 5	20,30			230		231		0.42 ± 0.02	7.35 × 10 ⁻¹⁰	0.045 ± 0.01	132
(CH ₂) ₅ , 232	CH ₂ Cl ₂ soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	233	2	234	98				132
232	CH ₂ Cl ₂ soln	0.01	none	300 ± 5	20,30			233		234		0.54 ± 0.02	7.7 × 10 ⁻¹⁰	0.045 ± 0.01	132
(CH ₂) ₆ , 235	CH ₂ Cl ₂ soln	0.005	none			~4	N ₂	236	5	237	95				10
235	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	236	5	237	95				132
235	CH ₂ Cl ₂ or MeCN soln	0.05	none	300, 310, or 350	30-40	~4	N ₂	236	10	237	90				132
235	CH ₂ Cl ₂ soln	0.05	none					236	15	237	85				10
235	CH ₂ Cl ₂ or MeCN soln	0.05	none					236 ^d		237	85				128
235	CH ₂ Cl ₂ or MeCN soln	0.1	none	300, 310, or 350	30-40	~4	N ₂	236	20	237	80				132
235	CH ₂ Cl ₂ soln	1	none					236	100	237	0				10
235	C ₆ H ₁₄ CH ₂ Cl ₂ (3:2) soln	0.01	none	300 ± 5	20,30			236		237		0.50			132
235	CH ₂ Cl ₂ soln	0.01	none	300 ± 5	20,30			236		237		0.42 ± 0.02	8.8 × 10 ⁻¹⁰	0.12 ± 0.02	132
235	MeCN soln	0.01	none	300 ± 5	20,30			236		237		0.34 ± 0.02	5.66 × 10 ⁻¹⁰	0.04 ± 0.01	132
235	MeCN soln	0.05	Ph ₂ CO, 0.005	~350				236 ^{d,e}	15-20	237	0				129
235	crystal		none	~350	~25-30			236 ^d		237	0				133
(CH ₂) ₇ , 238	CH ₂ Cl ₂ soln	0.01	none	300, 310, 350	30-40	~4	N ₂	239	20	240	80				132
238	CH ₂ Cl ₂ soln	0.01	none	300 ± 5	20,30			239		240		0.15 ± 0.02		0.15 ± 0.02	132
(CH ₂) ₈ , 241	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	242	90	243	10				132
(CH ₂) ₉ , 244	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	245	100	246	0				132
(CH ₂) ₁₀ , 247	CH ₂ Cl ₂ or MeCN soln	10 ⁻⁴	none	300, 310, or 350	30-40	~4	N ₂	248	100	249	0				132
247	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	248	100	249	0				132
(CH ₂) ₁₁ , 250	<i>f</i>		Ph ₂ CO					248 ^d		249	0				130
(CH ₂) ₁₁ , 250	<i>f</i>		none					251 ^d		252	0				132
(CH ₂) ₁₂ , 253	CH ₂ Cl ₂ or MeCN soln	10 ⁻⁴	none	300, 310, or 350	30-40	~4	N ₂	254	100	255	0				132
253	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	254	100	255	0				132
<i>m</i> -C ₆ H ₄ , 256	CH ₂ Cl ₂ or MeCN soln	0.01	none	300, 310, or 350	30-40	~4	N ₂	257 ^d	100	258	0				128,132
256	MeCN soln	0.01	Ph ₂ CO, 0.005	~350		3.5		257 ^e		258	0				129
<i>p</i> -C ₆ H ₄ , 259	<i>f</i>		Ph ₂ CO					260 ^d		261	0				130


^a Oligomer except as noted. ^b < 10% conversion of 220. ^c Lifetime of excited singlet state. ^d Polymer. ^e Probable structure. ^f Presumably in soln. ^g Insol and sol fractions. Fraction sol in DMSO: $\bar{M}_n \approx 10,000$, $\bar{x}_n \approx 37$.

formation of a strong ground state interaction between the two maleimide moieties of **220**.¹³²


The mechanism proposed for polymerization and cyclization of **220** is shown in Scheme V.¹³² Polymers **221** were the only products reported from the photosensitized reactions of **235** and **247** in solution and the crystal state reactions of **226** and **235**.^{129-131,133} Monomers **247**, **256**, and **259** exhibited partial cross-linking by vinyl polymerization under the sensitized conditions shown in Table XIV.¹³⁰

2. Disubstituted

The cyclobutyl polymer from bis(methylmaleimide) **262** apparently had the head-to-tail structure **263** (eq 80),¹²⁹ although no structural evidence was presented.

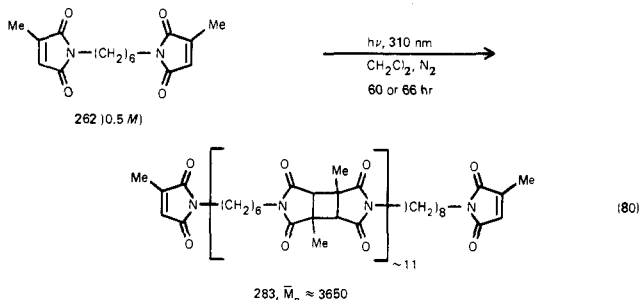


When irradiated, the bis(bromomaleimide) **264** polymerized to **265** possessing mainly anti stereochemistry about the cyclobutane ring (eq 81).¹³⁴ Structure **265**

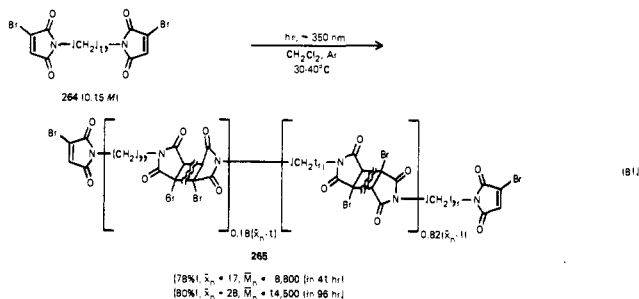

describes the overall composition of the polymer and does not represent a block structure of anti units and syn units. The regiochemistry of the photocycloaddition was not reported.

Another publication described the cycloaddition polymer from **264** as having the head-to-head regiochemistry shown in **266** (eq 82).¹² This reaction oc-

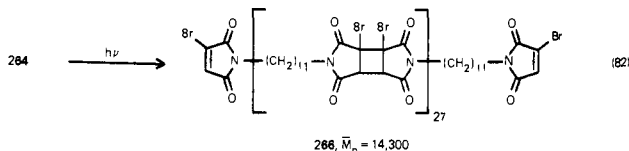

curred on direct irradiation via the triplet state, under unspecified conditions.¹² No structural evidence for **266** was given.

Several other bis(monosubstituted maleimides) **267** reportedly polymerized via photocycloaddition (eq 83)

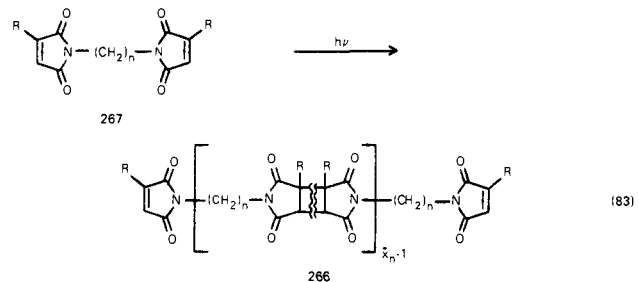
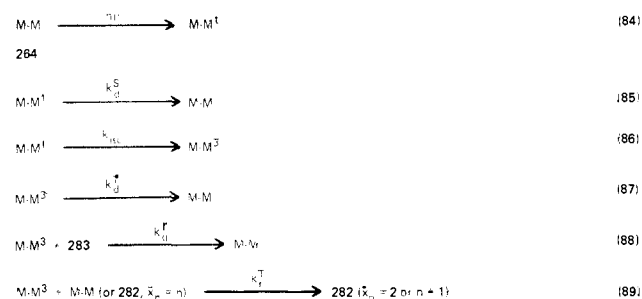


TABLE XV. Photopolymerization of Bis(Monosubstituted Maleimides) **267** (Eq 83)

monomer 267	R	n	phase	concn of 267 , M	sensitizer	λ , nm	temp, °C	time, h	atm over soln	product 268	yield of 268 , %	$\Phi_{-(C=C)}$	$\tau_{267^{*3}}$, s	ref
Me 6, 262	Me	6	crystal		Ph ₂ CO	~350	~25-30	0.5		269 ^b	84		10,130	10,130
Me 9, 270	Me	9	crystal		Ph ₂ CO	~350	30-40	17	Ar	271 ^b	100		10,130	29,133
Me 11, 272	Me	11	CH ₂ Cl ₂ soln	0.15		~350	30-40	65	Ar	273 ^b	70		134	134
Cl 6, 274	Cl	6	CH ₂ Cl ₂ soln	0.1	Ph ₂ CO ^c	~350	~25-30	0.5		275, $\bar{x}_n = 11-12$	74		10,130	29,133
Br 3, 276	Br	3	crystal			~350	~25-30			277	80		134	134
Br 6, 278	Br	6	CH ₂ Cl ₂ soln	0.1		~350	30-40	93	Ar	281, $\bar{M}_n = 9500$, $\bar{x}_n = 19$	76 ^f		1.36 × 10 ⁻⁷	135
Br 10, 280	Br	10	CH ₂ Cl ₂ soln	0.1		~350	30-40	165	Ar	281, $\bar{M}_n = 9700$, $\bar{x}_n = 20$	88 ^h		1.13 × 10 ⁻⁷	135
Br 11, 264	Br	11	CH ₂ Cl ₂ soln	10 ⁻³		350	20	20	d	282	76 ^f		0.849 × 10 ⁻⁷	135
264			CH ₂ Cl ₂ soln	5 × 10 ⁻³		350	20	20	d	282, $\bar{M}_n = 2570$, $\bar{x}_n = 5.11^e$	<8			135
264			CH ₂ Cl ₂ soln	0.01		350	20	20	d	282, $\bar{x}_n = 11^g$	<8			135
264			CH ₂ Cl ₂ soln	0.15		350	25	6	d		0.0949 ± 0.0016			135
264			CH ₂ Cl ₂ soln	0.1		350	35	10	d		0.151 ± 0.004			135
264			CH ₂ Cl ₂ soln	7.5 × 10 ⁻³		338 ± 5	20	20	d		<8			135
264			CH ₂ Cl ₂ soln	0.02		338 ± 5	20	20	d		<8			135
264			CH ₂ Cl ₂ soln	0.05		338 ± 5	20	20	d		<8			135

^a Presumably in CH₂Cl₂ solution. ^b Cross-linked. ^c 0.01 M. ^d Degassed. ^e Data at shorter reaction times also given. ^f Conversion of double bonds. ^g \bar{x}_n as a function of time given. ^h Conversion of double bonds given as a function of time.

Scheme VI


(Table XV).^{29,130,131,133-135}

Benzophenone sensitization produced cross-linked methylmaleimide polymers **269** and **271**,^{10,130} and the lattice-controlled crystal state reactions of **262**, **276**, and **278** may have produced cross-linked polymers.¹³³ Polymer **275** from chloromaleimide **274** was not cross-linked, presumably because the chlorine atom changed the multiplicity of the intermediate formed in the polymerization from the multiplicity that occurred with the methyl derivatives **262** and **270**.¹⁰ This proposal¹⁰ is rather surprising because all three polymerizations were sensitized by benzophenone.

A mechanistic and kinetic study of the polymerization of the bromo derivative **264** showed the reactive species was the triplet bromomaleimide moiety (M^3).¹³⁵ The polymerization was sensitized with benzophenone and quenched by oxygen or 3,3,4,4-tetramethyl-1,2-diazetene 1,2-dioxide (**283**).¹³⁵ The proposed mechanism is outlined in Scheme VI.¹³⁵ The rate constants determined for the addition reaction, k_r^T , and the sum of all unimolecular deactivation processes, k_d^T , were $2.4 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ and $6.8 \times 10^6 \text{ s}^{-1}$, respectively.¹³⁵ The quantum yield for intersystem crossing, Φ_{ics} , was 0.355 ± 0.008 , and the lifetime of the reactive excited state τ_{287*3} (Table XV) was longer than expected for an excited singlet state.¹³⁵

3. Tetrasubstituted

The bis(dimethylmaleimides) **284** with nine and eleven methylene groups in the connecting link, **286** and **288**, gave polymers **285** having anti stereochemistry about the cyclobutane ring (eq 90) (Table

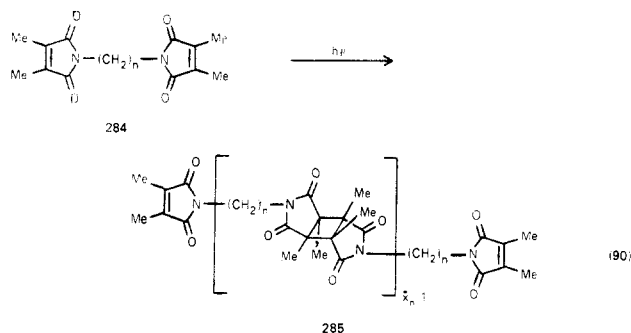XVI).^{12,131,134,136}


The quantum yields for polymerization [$\Phi_{-(C=C)}$] of **286** and **288** were rather insensitive to wavelength or the length of the methylene chain connecting the maleimide moieties.¹³⁶ The polymerization was sensitized with acetophenone or benzophenone and quenched with ferrocene (**290**) or the diazetine dioxide **283**.¹³⁶

Kinetic studies were in agreement when based on the

rate of conversion of monomer **288** and on molecular weight determinations for the polymer **289** as a function of conversion.^{134,136}

The low quantum yields, less than one, for the disappearance of monomers **286** and **288** [$\Phi_{-(C=C)}$] were cited as evidence that the polymerizations were not chain processes.¹³⁶ The condition that k_d^T must not be much larger than k_r^T [monomer], as was shown for **286** and **288**,¹³⁶ must also be established for one to confirm the nonchain character of the polymerizations.

Several other bis(disubstituted maleimides) **291** were photopolymerized in either the crystal state or in solution giving cyclobutane moieties of unspecified stereochemistries (eq 91) (Table XVII).^{12,29,129-131,133-135,137}

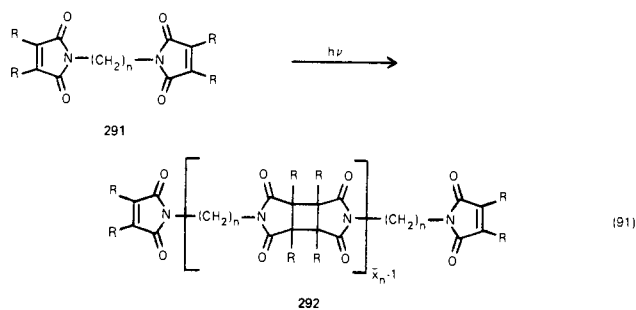

All crystal state polymerizations described in Table XVII were lattice-controlled processes in which some cross-linking may have occurred.^{131,133} Crystals of higher homologues of dichloromaleimide **302**, i.e., **291**, $R = \text{Cl}$, $n = 4, 5, 6, 7, 8$, and 11 , failed to polymerize when irradiated, presumably because of unfavorably aligned molecules in the crystal lattice.¹³³

The molecular weights obtained for polymers **309** and **313**, 30,000 and 60,000, respectively (Table XVII), were higher than those for other homologues, **305**, **307**, and **311**, on benzophenone-sensitized photopolymerization.^{130,137} This behavior was attributed to **309** and **313** remaining in solution whereas the other polymers precipitated during formation.¹³⁰

Polymerization of tetrahydrophthalimide **300** was sensitized by acetophenone and quenched by oxygen, the diazetine dioxide **284**, or ferrocene (**290**).¹³⁵ The long lifetimes for the excited state of **300** implied a triplet-state reaction.¹³⁵ The same conclusion was reached regarding photopolymerization of the chloro monomer **308**, which was sensitized by benzophenone and quenched by oxygen or **284**.¹³⁵

Kinetic data for monomers **286**, **288**, **300**, and **308** were consistent with a triplet-state mechanism analogous to that shown for the bromomaleimide **264** in Scheme VI.^{135,136} Rate constants for the cycloaddition (k_r^T) and deactivation (k_d^T) processes were determined (Table XVIII).^{135,136}

In acetonitrile the ratio of the rate constants for deactivation to that for cycloaddition (k_d^T/k_r^T) was higher in the presence of ferrocene (0.057 M for **286**, 0.0628 M for **288**, 0.165 M for **300**) than in the absence of a quencher (0.0184 M for **286**) or in the presence of the diazetine dioxide **283** (0.0205 M for **288**, 0.12 M for **300**).^{135,136} These higher ratios were attributed to occurrence of a higher deactivation rate constant (triplet to singlet) in the presence of ferrocene.^{135,136} This explanation may hold for the dimethylnonamethylene derivative **286** where the ratio in the absence of a quencher was determined from the dependence of the

TABLE XVI. Photopolymerization of Bis(dimethylmaleimides) 284 in Solution (Eq 90)

<i>n</i> of monomer 284	solvent	concn of 284, M	λ , nm	temp, °C	time, h	atm over soln	product 285	yield of 285, %	$\Phi_{-(C=C)}$	$\Phi_{284^{*3}d}$	τ_{284^{*3}, s^b}	ref
9, 286	CH ₂ Cl ₂	0.004	352 ± 20			<i>c</i>	287	≤10 ^d			1.70 × 10 ^{-6 e}	136
286	CH ₂ Cl ₂	0.011	352 ± 20			<i>c</i>	287	≤10 ^d			1.13 × 10 ^{-6 e}	136
286	CH ₂ Cl ₂	0.02	352 ± 20			<i>c</i>	287	≤10 ^d			0.76 × 10 ^{-6 e}	136
286	CH ₂ Cl ₂	0.1	~350	25	2.5	<i>c</i>	287, $\bar{M}_n = 2860, \bar{x}_n = 7.64^{f,g}$	88.9 ^d				136
286	CH ₂ Cl ₂	0.02	334	20		<i>c</i>	287	≤8 ^d	0.23			136
286	CH ₂ Cl ₂	0.01	313	20		<i>c</i>	287	≤8 ^d	0.17	0.182		136
286	CH ₂ Cl ₂	0.02	313	20		<i>c</i>	287	≤8 ^d	0.24	0.182		136
286	CH ₂ Cl ₂	0.1	313	20		<i>c</i>	287	≤8 ^d	0.33	0.182		136
286	MeCN	0.002	352 ± 20			<i>c</i>	287	≤10 ^d		0.29	8.45 × 10 ^{-7 h,i}	136
286	MeCN	0.01	352 ± 20			<i>c</i>	287	≤10 ^d		0.29	6.72 × 10 ^{-7 h,i}	136
286	MeCN	0.025	352 ± 20			<i>c</i>	287	≤10 ^d		0.29	4.82 × 10 ^{-7 h,i}	136
286	MeCN	0.02	334	20		<i>c</i>	287	≤8 ^d	0.23			136
286	MeCN	0.01	313	20		<i>c</i>	287	≤8 ^d	0.19	0.180		136
286	MeCN	0.02	313	20		<i>c</i>	287	≤8 ^d	0.24	0.180		136
286	MeCN	0.05	313	20		<i>c</i>	287	≤8 ^d	0.30	0.180		136
286	MeCN	0.02	297	20		<i>c</i>	287	≤8 ^d	0.22			136
11, 288	CH ₂ Cl ₂	0.004	352 ± 20			<i>c</i>	289	≤10 ^d			1.90 × 10 ^{-6 e}	136
288	CH ₂ Cl ₂	0.008	352 ± 20			<i>c</i>	289	≤10 ^d			1.40 × 10 ^{-6 e}	136
288	CH ₂ Cl ₂	0.012	352 ± 20			<i>c</i>	289	≤10 ^d			1.07 × 10 ^{-6 e}	136
288	CH ₂ Cl ₂	0.10	350		23	<i>c</i>	289, $\bar{M}_n = 32,550, \bar{x}_n = 81^{f,j}$	98.8 ^d				131,134
288	CH ₂ Cl ₂	0.15	~350	30-40	48	Ar	289, $\bar{M}_n = 17,900, \bar{x}_n = 45$	90				134
288	CH ₂ Cl ₂	0.15	~350	30-40	72	Ar	289, $\bar{M}_n = 20,800, \bar{x}_n = 52$	90				12,134
288	CH ₂ Cl ₂	0.1	~300	25	4.66	<i>c</i>	289, $\bar{M}_n = 3,700, \bar{x}_n = 9.22^f$	89.0 ^d				136
288	MeCN	0.004	352 ± 20			<i>c</i>	289	≤10 ^d			7.36 × 10 ^{-7 e}	136
288	MeCN	0.011	352 ± 20			<i>c</i>	289	≤10 ^d			4.98 × 10 ^{-7 e}	136
288	MeCN	0.022	352 ± 20			<i>c</i>	289	≤10 ^d			3.25 × 10 ^{-7 e}	136
288	MeCN	0.002	352 ± 20			<i>c</i>	289	≤10 ^d			6.64 × 10 ^{-7 h}	136
288	MeCN	0.011	352 ± 20			<i>c</i>	289	≤10 ^d			5.27 × 10 ^{-7 h}	136
288	MeCN	0.025	352 ± 20			<i>c</i>	289	≤10 ^d			3.91 × 10 ^{-7 h}	136
288	MeCN	0.02	334	20		<i>c</i>	289	≤8 ^d	0.21			136
288	MeCN	0.02	313	20		<i>c</i>	289	≤8 ^d	0.21			136
288	MeCN	0.02	297	20		<i>c</i>	289	≤8 ^d	0.23			136

^a Quantum yield for intersystem crossing of 284*¹. ^b Lifetime of triplet state. ^c Degassed. ^d Conversion of double bonds. ^e In presence of 283. ^f Further data at shorter reaction times given. ^g Reduced viscosity of polymer solution much higher at higher conversion. ^h In presence of ferrocene (290). ⁱ Similar data at 25 °C given in ref 131. ^j Similar data given in ref 131. The scale in Figure 6 of this reference apparently is in error by a factor of 10.

TABLE XVII. Photopolymerization of Bis(Disubstituted Maleimides) 291 (Eq 91)

monomer 291		phase	concn of 291, M	sensitizer, concn, M	λ , nm	temp, °C	time, h	atm over soln	product 292	yield of 292, %	$\Phi_{-(C=C)}$	τ_{291}^{*3} , s	ref
R	n												
Me	3, 293	crystal			~350	~25-30	0.5		294				131,133
Me	6, 295	CH ₂ Cl ₂ soln			310		60	N ₂	296, $\overline{M}_n \approx 3300$, $\overline{x}_n \approx 10$				129
	295	crystal			~350	~25-30			296				133
Me	11, 288								297, $\overline{M}_n = 20,800$, $\overline{x}_n = 52$				12
(CH ₂) ₂ ^a	3, 298	crystal			~350	~25-30	1		299				29,131,133
(CH ₂) ₂ ^a	9, 300	CH ₂ Cl ₂ soln	0.002		350	20		b	301			2.47×10^{-6c}	135
	300	CH ₂ Cl ₂ soln	0.010		350	20		b	301			2.17×10^{-6c}	135
	300	CH ₂ Cl ₂ soln	0.020		350	20		b	301			1.75×10^{-6c}	135
	300	CH ₂ Cl ₂ soln	0.15		~350	30-40	72	Ar	301, $\overline{M}_n = 2500$, $\overline{x}_n = 5.9$	28			134
	300	CH ₂ Cl ₂ soln	0.15		~350	30-40	166	Ar	301, $\overline{M}_n = 5100$, $\overline{x}_n = 12$	50			134
	300	CH ₂ Cl ₂ soln	0.02		313	20		b	301		0.03		135
	300	CH ₂ Cl ₂ soln	0.1		310	25	72		301, $\overline{x}_n = 4.41^d$	76.1 ^e			135
	300	MeCN soln	0.002		350	20		b	301			1.35×10^{-6c}	135
	300	MeCN soln	0.011		350	20		b	301			1.23×10^{-6c}	135
	300	MeCN soln	0.025		350	20		b	301			0.98×10^{-6c}	135
	300	MeCN soln	0.002		350	20		b	301			4.30×10^{-6f}	135
	300	MeCN soln	0.011		350	20		b	301			4.05×10^{-6f}	135
	300	MeCN soln	0.022		350	20		b	301			3.50×10^{-6f}	135
	300	MeCN soln	0.02		334	20		b	301		0.074		135
	300	MeCN soln	0.02		313	20		b	301		0.08		135
Cl	3, 302	crystal			~350	~25-30			303				29,131,133
Cl	7, 304	CH ₂ Cl ₂ soln	0.049	Ph ₂ CO, 0.026	~350	30-40	114	N ₂	305, $\overline{M}_n = 4130$, $\overline{x}_n = 10$	73			137
	304	CH ₂ Cl ₂ soln	0.052	Ph ₂ CO, 0.033	~350	30-40	112	N ₂	305, $\overline{M}_n = 1600$, $\overline{x}_n = 4$	51			137
	304	CH ₂ Cl ₂ soln	0.195	Ph ₂ CO, 0.137	~350	30-40	121	N ₂	305, $\overline{M}_n = 4160$, $\overline{x}_n = 9.7$	100			130,137
Cl	8, 306	CH ₂ Cl ₂ soln	0.068	Ph ₂ CO, 0.055	~350	30-40	112	N ₂	307, $\overline{M}_n = 2000$, $\overline{x}_n = 5$	86			130, 137
Cl	9, 308	CH ₂ Cl ₂ soln	0.0015		350	20		b	309			2.25×10^{-5c}	135
	308	CH ₂ Cl ₂ soln	0.005		350	20		b	309			1.81×10^{-5c}	135
	308	CH ₂ Cl ₂ soln	0.008		350	20		b	309			1.57×10^{-5c}	135
	308	CH ₂ Cl ₂ soln	0.15		350	25	80	b	309, $\overline{M}_n = 1510$, $\overline{x}_n = 3.31^d$	71.2 ^e			135
	308	CH ₂ Cl ₂ soln	0.005		334				309		0.04		135
	308	CH ₂ Cl ₂ soln	0.01	Ph ₂ CO, 0.027	350		100	N ₂	309, $\overline{M}_n \approx 6000$, $\overline{x}_n \approx 14$				129
	308	CH ₂ Cl ₂ soln	0.039	Ph ₂ CO, 0.027	~350	30-40	113	N ₂	309, $\overline{M}_n = 3800$, $\overline{x}_n = 8$	75			137
	308	CH ₂ Cl ₂ soln	0.044	Ph ₂ CO, 0.027	~350	30-40	117	N ₂	309, $\overline{M}_n = 6300$, $\overline{x}_n = 14$	100			130,137
	308	CH ₂ Cl ₂ soln	0.20 ^g	Ph ₂ CO, 0.12	~350	30-40	120	N ₂	309, $\overline{M}_n = 30,000$, $\overline{x}_n = 66$	98			130,137
Cl	10, 310	CH ₂ Cl ₂ soln	0.043	Ph ₂ CO, 0.007	~350	30-40	111	N ₂	311, $\overline{M}_n = 2700$, $\overline{x}_n = 6$	48			130,137
	310	CH ₂ Cl ₂ soln	0.051	Ph ₂ CO, 0.036	~350	30-40	118	N ₂	311	82			130,137
	310	CH ₂ Cl ₂ soln	0.127	Ph ₂ CO, 0.165	~350	30-40	115	N ₂	311	90			137
Cl	11, 312	CH ₂ Cl ₂ soln	0.15		~350	30-40	72	Ar	313, $\overline{M}_n = 1960$, $\overline{x}_n = 4.1$	69			134
	312	CH ₂ Cl ₂ soln	0.15		~350	30-40	200	Ar	313, $\overline{M}_n = 3880$, $\overline{x}_n = 8.0$	69			134
	312	CH ₂ Cl ₂ soln			350		~123		313	~91 ^{d,e}			131
	312	CH ₂ Cl ₂ soln	0.12	Ph ₂ CO, 0.10	~350	30-40	74	N ₂	313, $\overline{M}_n = 7000$, $\overline{x}_n = 15$	76 ^e			12,137
	312	CH ₂ Cl ₂ soln	0.16	Ph ₂ CO, 0.11	~350	30-40	118	N ₂	313, $\overline{M}_n = 60,000$, $\overline{x}_n = 120$	98 ^e			12,130,137
Cl	12, 314	CH ₂ Cl ₂ soln	0.183	Ph ₂ CO, 0.183	~350	30-40	115	N ₂	315	63			137

^a Cyclohexenedicarboximide. ^b Degassed. ^c In presence of 284. ^d Further data at shorter reaction times given. ^e Conversion of double bonds. ^f In presence of 291. ^g Reference 130 reported this concn as 0.020 M.

TABLE XVIII. Rate Constants for Cycloaddition (k_r^T) and Deactivation (k_d^T) of Bis(dimethylmaleimide) **286**, **288**, **300**, and **308** Triplets

compound	quencher	CH ₂ Cl ₂ soln		MeCN soln		ref
		k_r^T , M ⁻¹ s ⁻¹	k_d^T , s ⁻¹	k_r^T , M ⁻¹ s ⁻¹	k_d^T , s ⁻¹	
286	283	2.2×10^7	4.1×10^5	1.93×10^7	1.10×10^6	136
286	290					136
288	283	2.55×10^7	3.2×10^5	4.75×10^7	9.75×10^5	136
288	290			2.26×10^7	1.42×10^6	136
300	283	4.5×10^6	3.8×10^5	6.1×10^6	7×10^5	135
300	290			1.35×10^6	2.23×10^5	135
308	283	1.4×10^6	4×10^4			135

TABLE XIX. Photosensitized Polymerization of Bis(coumarin) Ethers **318** (Eq 93)¹⁴⁰

n of monomer 318	concn of 318 , M	concn of Ph ₂ CO, M	time, h	product 319	yield of 319 , %
10, 320 11, 322	0.05	2.98 ^a	65	321 ^b 323 ^c	80

^a Absorbed 50% of light. ^b Intrinsic viscosity = 0.25. ^c Intrinsic viscosity = 0.38.

reaction quantum yield on the monomer concentration. However, only the ratio was determined, not the individual rate constants. For the dimethylundecamethylene derivative **288** the 2.10-fold decrease in k_r^T is larger than the 1.46-fold increase in k_d^T . The reported value of k_d^T for tetrahydrophthalimide derivative **300** was smaller in the presence of ferrocene than in its absence although the latter value may have been in error because the quenching rate constant (k_q^T) with **283** may not have been diffusion controlled.¹³⁵


The quantum yield for the singlet to triplet conversion for monomer **286**, Φ_{isc} , was higher in the presence of ferrocene than in its absence (Table XVI).

The rate constant for singlet state deactivation (k_d^S in Scheme VI) was nearly zero for the undecamethylene monomer **288**.¹³⁴

Polymerization of monomers **300** and **312** did not occur by either simple zero- or first-order kinetics, but the data could be fit to an equation containing both zero and first order terms.¹³⁵ The rate constants k_r^T and k_d^T were the same order of magnitude for **312**.¹³¹

L. Bis(thymine)

Photocycloadditions of pyrimidine derivatives have been studied extensively. Polymerization of a difunctional pyrimidine derivative has also been observed. Crystal state irradiation of the trimethylenebis(thymine) **316** gave an uncharacterized insoluble polymer **317** (eq 92),¹³⁸ the structure of which was inferred from

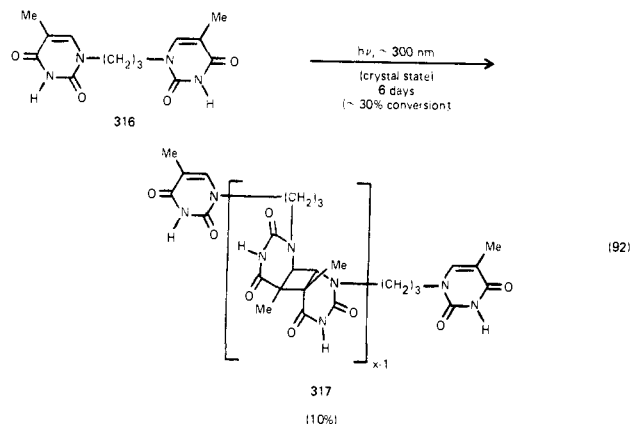

an X-ray crystal structure determination of the monomer **316**.¹³⁹

TABLE XX. Photosensitized Polymerization of Bis(coumarin) Ethers **318** (Eq 94)¹⁴¹

n of monomer 318	concn of Ph ₂ CO, M	time, h	product, 324
10, 320	1.75	67.5	325 , $\bar{M}_n = 5900$, $\bar{x}_n = 12$
11, 322	0.030	64.75	326 ^a
322	0.322	51	326 , $\bar{M}_n = 7900$, $\bar{x}_n = 17$ ^b
322	0.322	64.75	326 ^c
322	2.988	64.75	326 ^d


^a Intrinsic viscosity = 0.14. ^b Intrinsic viscosity = 0.38. ^c Intrinsic viscosity = 0.24. ^d Intrinsic viscosity = 0.28.

In water or aqueous acetone solution, the monomer **316** gave an intramolecularly cyclized cis head-to-head cyclobutane derivative.¹³⁸


The crystal structure of **316** was such that either intramolecular cyclization to a trans head-to-head cyclobutane derivative or intermolecular cycloaddition to **317** could have occurred.¹³⁹ The intramolecular separation, 3.501 Å, of the double bonds was shorter than the intermolecular separation, 3.688 Å.¹³⁹ However, the thymine moieties were aligned so their π orbitals probably interacted more intermolecularly than intramolecularly.¹³⁹ Orientation of the orbitals participating in the cycloaddition may, thus, have had more influence than the distance between the reacting atoms.¹³⁹

M. Bis(coumarins)

The benzophenone-sensitized photopolymerization of the bis(coumarin) ethers **318** gave products **319** that contained *anti*-cyclobutane moieties (eq 93) (Table

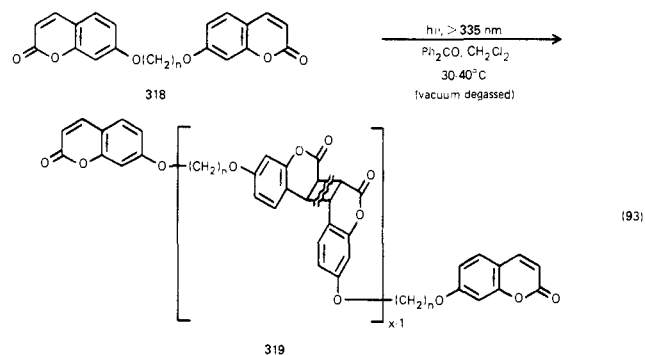

XIX).¹⁴⁰ The regiochemistry was not reported.¹⁴⁰

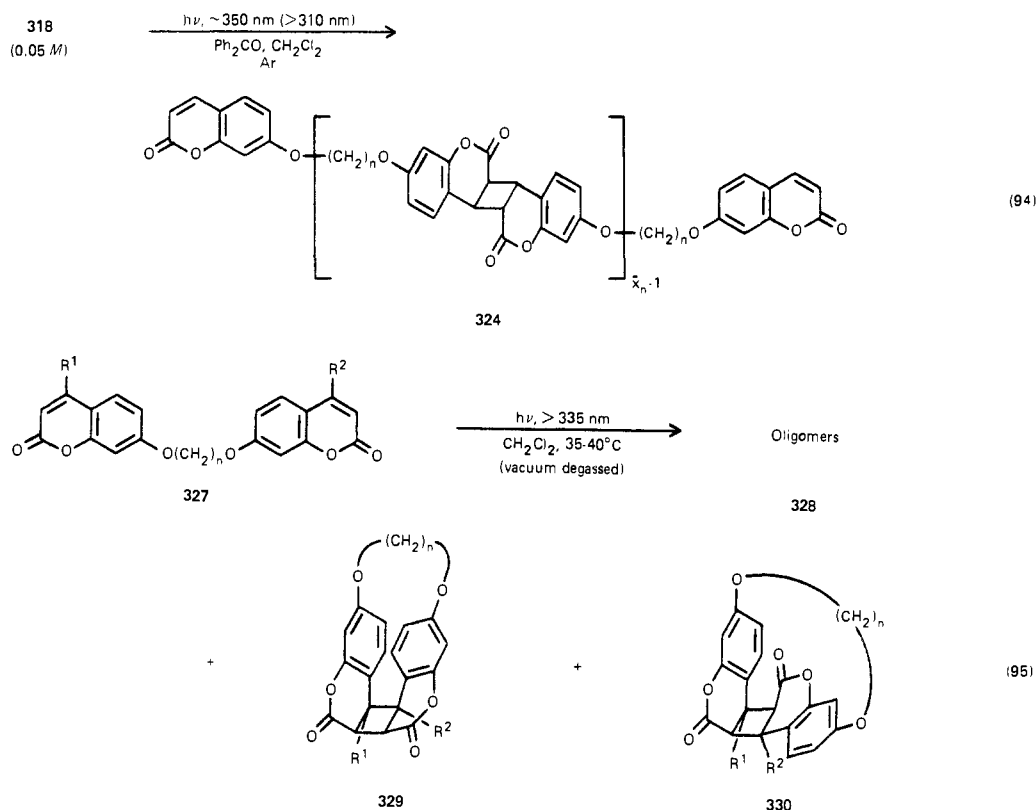TABLE XXI. Photopolymerization and Photocyclization of Bis(coumarin) Ethers 327 (Eq 95)¹⁴⁰

monomer 327			concn of 327, M	time, h	oligomeric product 328	yield of 328, %	ratio 329:330
R ¹	R ²	n					
H	H	2, 331	>0.002		332 ^a		85 (333):15 (334) ^b
H	H	3, 335	0.01	72	336	3	41 (337):59 (338)
H	H	4, 339	0.01	39	340	3-15 ^{c,d}	42 (341):58 (342) ^e
H	H	5, 343	0.01	15.5	344	3-15 ^c	40 (345):60 (346)
H	H	6, 347	0.01	29.75	348	3-15 ^c	30 (349):70 (350)
H	H	7, 351	0.01	52.75	352	3-15 ^c	40 (353):60 (354)
H	H	8, 355	0.01	91	356	3-15 ^c	28 (357):72 (358)
H	H	9, 359	0.01	115.5	360	11 ^f	33 (361):67 (362) ^g
H	H	10, 320	0.01	160	363	3-15 ^c	32 (364):68 (365)
H	H	11, 322	0.01	142	366	15	33 (367):67 (368)
H	H	2-11	0.05		h	30	
H	H	2-11	0.1		h	35	
Me	H	4, 369	0.01	44	370	3-15 ^c	30 (371):70 (372)
		369	0.05		370	30	
		369	0.1		370	35	
Me	Me	5, 373	0.01 ⁱ	65	374	3-15 ^c	3 (375):97 (376)
		373	0.05		374	30	
		373	0.1		374	35	


^a Insoluble polymeric material. ^b At 0.002 M 331. ^c Yield was within stated range. ^d 100% conversion of 339. ^e 341 (34.6% yield) and crude 342 (36% yield) isolated. ^f 89% conversion of 359. ^g 361 (19% yield) isolated. ^h As in above entries. ⁱ This reaction also performed under N₂ or Ar atmosphere instead of solution being vacuum degassed.

Several patents reported that under slightly different conditions (eq 94) the same reactions gave the anti head-to-tail cyclobutane polymers 324 (Table XX).¹⁴¹

Direct irradiation of these same bis(coumarins) 318 and several other homologues 327 gave mainly the intramolecularly cyclized products 329 and 330 and the intermolecular oligomeric photoproducts 328 (eq 95) (Table XXI).¹⁴⁰ Although oligomers 328 presumably were formed by 2 + 2 cycloadditions, no data were reported concerning the structures.

As expected, increased concentrations of the monomers 327 led to a larger fraction of oligomers 328.¹⁴⁰ Although no systematic study was reported, the amount of intermolecular products 336, 360, and 366 increased with increasing length of the methylene chain. At 0.002


Scheme VII

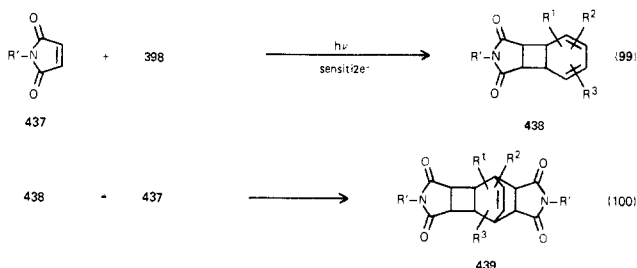

In general, as the length of methylene chain of 327 increased, the ratio of head-to-tail cyclomer 330 to M the ethylene glycol ether 331 gave only intramolecular products 333 and 334.

head-to-head cyclomer **329** increased, presumably because the two attachment points of **330** became easier to span. The high proportion of head-to-tail dimethylcyclomer **376** was attributed to the steric effect of the vicinal *cis* methyl groups.¹⁴⁰


Anti head-to-head stereochemistry was suggested for polyesters **378** obtained by irradiating bis(coumarin) esters **377** with a sensitizer (eq 96) (Table XXII).^{29,131}

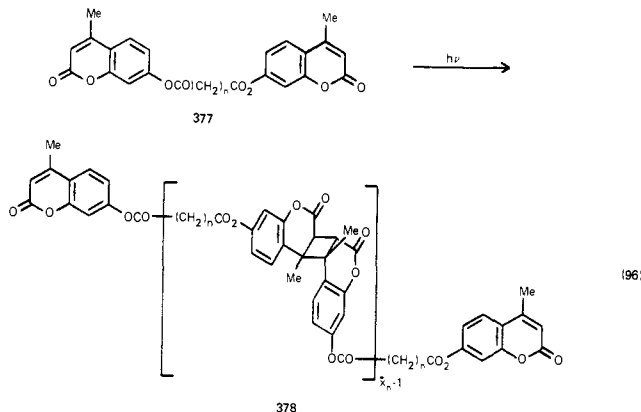

Two of these monomers, **379** and **381**, and their dimethyl homologues reportedly gave anti head-to-tail cyclobutane polymers **390** under similar conditions (eq 97) (Table XXIII).¹⁴¹

N. Other Cyclic Olefins

Irradiating the diene ether **397** gave an uncharacterized polymer, whereas a diastereomer of **397** gave an intramolecular 2 + 2 photocycloaddition product.¹⁴² This difference is easily explained on examination of

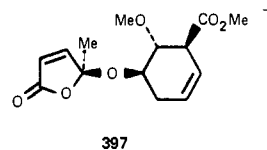

molecular models. Although the diastereomer of **397** could have readily assumed a conformation allowing the intramolecular cycloaddition, **397** could not. The polymer from **397** presumably contained cyclobutane linkages, although no supporting evidence was presented.

O. Bis(maleimides) with Aromatic Hydrocarbons (Copolymerizations)

Irradiating bis(maleimides) **220** in aromatic hydrocarbon solvents **398** in the presence of acetophenone gave copolymers **399** (eq 98) (Table XXIV).¹⁴³⁻¹⁴⁷ These results were in distinct contrast to those from homopolymerizing some of the same monomers **220** described in section IIK1. Structure **399** illustrates the three types of bonding possible for each bis(succinimide) unit rather than representing a regular sequence of monomer units.

Scheme VII shows the mechanism thought to occur in this copolymerization.^{143,144} Initially, a photosensitized cycloaddition of **437** with **398** gave the diene **438** (eq 99), which underwent a nonphotochemical Diels-Alder reaction with the dienophile **437** to give the bicyclooctene **439** (eq 100). Each maleimide moiety **437** of the bis(maleimide) **220** presumably reacted independently. Each thus could have participated in the

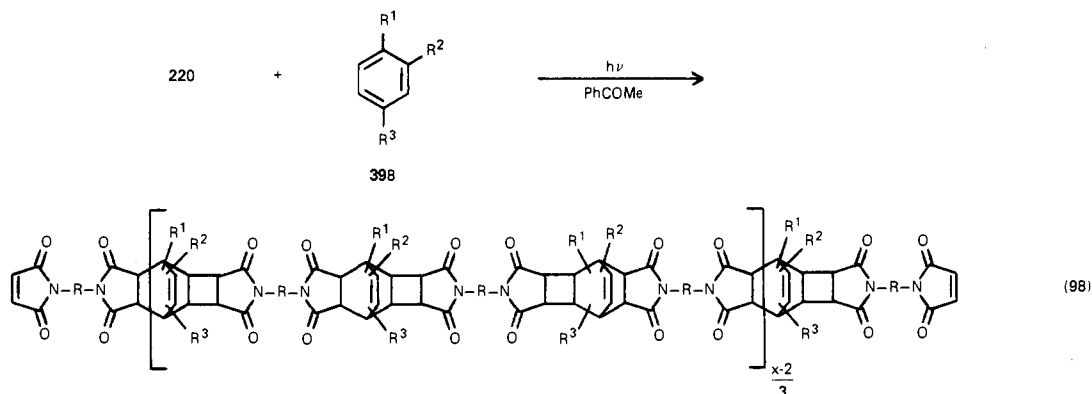
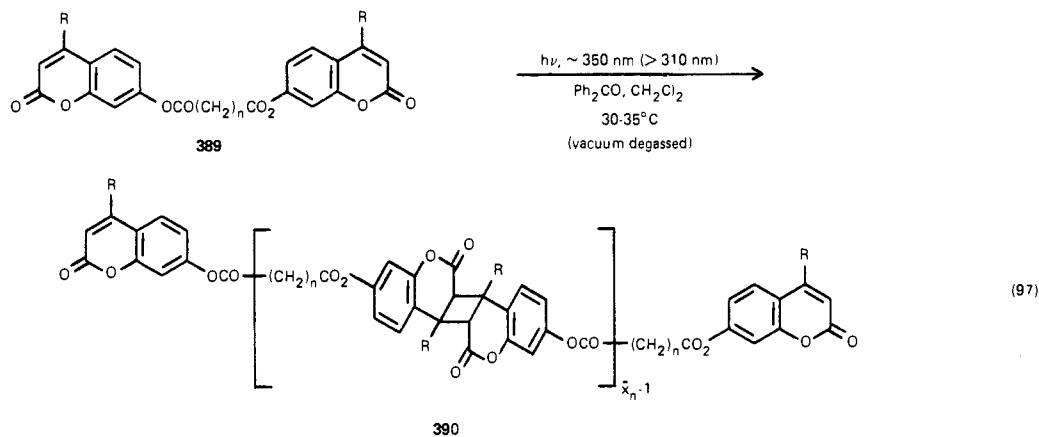


TABLE XXII. Photosensitized Polymerization of Bis(methylcoumarin) Esters 377 (Eq 96)

<i>n</i> of mono-mer 377	solvent	sensi-tizer	λ , nm	product 378	ref
7, 379		Ph ₂ CO		380	131
8, 381		Ph ₂ CO		382	131
10, 383	CH ₂ Cl ₂	<i>a</i>	>335	384, $\overline{M}_n = 6000$, $\overline{x}_n = 11$	29
383		Ph ₂ CO		384	131
11, 385	CH ₂ Cl ₂	<i>a</i>	>335	386, $\overline{M}_n = 9400$, $\overline{x}_n = 16.8$	29
385		Ph ₂ CO		386	131
12, 387	CH ₂ Cl ₂	<i>a</i>	>335	388, $\overline{M}_n = 22,300$, $\overline{x}_n = 38.8$	29
387		Ph ₂ CO		388, $\overline{M}_n = 22,000$, $\overline{x}_n = 38$	131

^a Not reported.

TABLE XXIII. Photosensitized Polymerization Bis(coumarin) Esters 389 (Eq 97)¹⁴¹

<i>n</i>	monomer 389 R	concn of 389, M	concn of Ph ₂ CO, M	time, h	product 390
7	H, 391	0.1	0.015	96	392, $\overline{M}_n = 2420$, $\overline{x}_n = 5.08$
7	Me, 379	0.096	0.06	67	393, $\overline{M}_n = 7700$, $\overline{x}_n = 15$
8	H, 394	0.055	0.008	36	395 ^a
	394	0.062	0.032	53	395 ^b
	394	0.067	0.061	48	395
8	Me, 381	0.095	0.060	63	396, $\overline{M}_n = 10,000$, $\overline{x}_n = 19^c$

^a Intrinsic viscosity = 0.18. ^b Intrinsic viscosity = 0.12.

^c Intrinsic viscosity = 0.42.

photochemical reaction (eq 99), or each in the thermal reaction (eq 100), or one in the photoreaction and the other in the thermal reaction.^{144,145} The three bis(succinimide) portions of structure 399 illustrate the kind of linkages that result from these three sets of reactions.

The copolymers 399 were largely insoluble and possibly cross-linked via vinyl polymerization through the maleimide double bonds of monomer 220 and the bicyclooctene double bonds of polymer 399.¹⁴³⁻¹⁴⁶ The soluble portions of polymers 399 had low reduced solution viscosities, presumably because the higher molecular weight fractions precipitated during irradiation.¹⁴⁶

The trimethylene 409 and hexamethylene 410 copolymers were formed in slightly lower yields than the dimethylene analogue 400, probably because bis(maleimides) 226 and 235 underwent intramolecular cyclization (eq 67).^{143,144}

The higher yields from copolymerization of benzene with monomers 235 and 421, compared with those from the analogous alkylbenzene, 401, 403, 405, and 414, copolymers,^{144,145} were attributed to benzene having lesser steric effects. However, other¹⁴⁶ results for copolymerization of bis(imide) 235 with benzene and its derivatives, 401, 403, and 405, showed a slight opposite trend. The bis(imide) 421 gave no polyimide when irradiated with ethyl- (403) or isopropylbenzene (405) under conditions where toluene (401) and *tert*-butylbenzene (414) did form a polyimide.¹⁴⁵

Copolymerizations of alkylbenzenes with bis(imides) 235, 421, and 431 produced the highest yields from toluene (401) and *tert*-butylbenzene (414), and the

lowest yields from ethylbenzene (403) and cumene (405).¹⁴⁵ This behavior was attributed to a balance between inductive and steric effects of the alkyl groups.¹⁴⁵ Because the maleimide moiety 437 was electrophilic in both the 2 + 2 and 2 + 4 cycloaddition reactions (eq 99 and 100), alkyl groups on benzene should have enhanced the reactivity in the order *t*-Bu > *i*-Pr > Et > Me.¹⁴⁵ The steric effects of these alkyl groups should have retarded the rates in the same order.¹⁴⁵ This explanation required that the copolymer yields were a reliable measure of the relative rates for the various alkylbenzenes.

The complete lack of reactivity exhibited by the bis(*o*-methyl) monomer 421 with ethyl- (403) and isopropylbenzene (405) was attributed to steric retardation caused by the methyl groups of 421.¹⁴⁵

The inductive and steric arguments noted above require that the inductive effect of the *t*-Bu group outweigh the steric effect.¹⁴⁵ This situation seems unlikely because the inductive effect of the *t*-Bu group is only slightly greater than that of an isopropyl group, whereas the steric effect is considerably greater. Abstraction of a hydrogen atom from the alkyl group by an extraneously generated radical or an excited-state species may have contributed to the observed relative yields of copolymers from the four alkylbenzenes. The relative ease of this reaction is *i*-Pr > Et > Me > *t*-Bu. Occurrence of this side reaction would have reduced the yield of copolymer 399.

The low yields of copolymers 426 and 430 were attributed to the lack of a substituent ortho to the maleimide ring in monomers 425 and 429, similar to results observed in nonpolymerizing systems.^{143,144} A related monomer 427 that contained ortho substituents gave a higher yield of copolymer 428. Diene 438 was isolated from the polymerization of bis(imide) 427 with benzene.¹⁴⁴

Unexpectedly high yields of copolymers of sulfone 431 were obtained, possibly because the sulfone linkage has an electron-withdrawing effect.^{144,145} A charge-transfer interaction between the bis(maleimide) 431 and the alkylbenzenes was suggested as possibly occurring.¹⁴⁵

III. Cycloadditions Involving Carbon 2 + 3 Addition






A. Benzene

One of the earliest reported polymerizations achieved by photocycloaddition reactions was polymerization of benzene in the presence of a small amount of an olefin.¹⁴⁸ Irradiating benzene (13) that contained minor quantities of cyclooctene (440) or the 1:1 adduct 441 gave oligomer and polymer (442) in low conversion (eq 101).¹⁴⁸ Several fractions (443-446) of various molecular weights were isolated; the major one had a molecular weight of ~1500, 444.¹⁴⁸


The polymer structure as originally reported consisted entirely of head-to-head units, as in the 2:1 adduct 448. However, the polymer probably contained both head-to-head and head-to-tail structures, as in 447. Polymer 442 also may have contained some bicyclo-[2.2.0]hexane units.¹⁴⁸

Conditions similar to those in which polymer 442 was formed, e.g., reaction of 13 with 440, gave the 2:1 adducts 447 and 448, two other unidentified 2:1 (13:440)


TABLE XXIV. Photosensitized Copolymerization of Bis(maleimides) 220 and Aromatic Hydrocarbons 398 (Eq 98)

R of monomer 220	monomer 398			solvents-sensitizers	concn	concn	λ , nm	temp, °C	time, h	product 399	yield of 399, %	ref
	R ¹	R ²	R ³		of 220, M	of PhCOMe, M						
(CH ₂) ₂ , 223	H	H	H, 13	13, Me ₂ CO ^a	0.2	0.2	>280		18	400	~95	143, 144, 147
223			13	13, CHCl ₃ or EtOH ^b	c	0.3		20	20	400	73	146
223	Me	H	H, 401	401, CHCl ₃ or EtOH ^b	c	0.3		20	20	402	55	146
223	Et	H	H, 403	403, CHCl ₃ or EtOH ^b	c	0.3		20	20	404	60	146
223	<i>i</i> -Pr	H	H, 405	405, CHCl ₃ or EtOH ^b	c	0.3		20	20	406	45	146
223	Me	Me	H, 407	407, CHCl ₃ or EtOH ^b	c	0.3		20	20	408	51	146
(CH ₂) ₃ , 226			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	409	~80	143, 144, 147
(CH ₂) ₆ , 235			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	410	~70	143, 144, 147
235			13	13	c	0.3		20	20	410	56	146
235			401	401, Me ₂ CO ^a	0.2	0.2	>280		24	411	40	145, 147
235			401	401	c	0.3		20	27	411	73	146
235			403	403, Me ₂ CO ^a	0.2	0.2	>280		24	412	-23	145, 147
235			403	403	c	0.3		20	18	412	80	146
235			405	405, Me ₂ CO ^a	0.2	0.2	>280		24	413	28	145, 147
235			405	405	c	0.3		20	18	413	62	146
235	<i>t</i> -Bu	H	H, 414	414, Me ₂ CO ^a	0.2	0.2	>280		24	415	34	145, 147
235			407	407	c	0.3		20	20	416	71	146
235	Me	H	Me, 417	417	c	0.3		20	26	418	61	146
(CH ₂) ₁₀ , 247			13	13, CHCl ₃ or EtOH ^b	c	0.3		20	30	419	30	146
247			405	405, CHCl ₃ or EtOH ^b	c	0.3		20	60	420	5	146
421			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	422	~65	143, 144, 147
			401	401, Me ₂ CO ^a	0.2	0.2	>280		40	423	45	145, 147
421			414	414, Me ₂ CO ^a	0.2	0.2	>280		40	424	44	145, 147
425			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	426	~15	143, 144, 147
			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	428	~80	143, 144, 147
427			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	428	~80	143, 144, 147
			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	430	~30	144, 147
429			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	430	~30	144, 147
			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	432	~85	144, 147
431			13	13, Me ₂ CO ^a	0.2	0.2	>280		18	432	~85	144, 147
			401	401, Me ₂ CO ^a	0.2	0.2	>280		5	433	89	145, 147
431			403	403, Me ₂ CO ^a	0.2	0.2	>280		5	434	50	145, 147
431			405	405, Me ₂ CO ^a	0.2	0.2	>280		5	435	60	145, 147
431			414	414, Me ₂ CO ^a	0.2	0.2	>280		5	436	85	145, 147

^a Minimum amount required to dissolve monomer 220. ^b 1 part to 2 parts 398 by weight. ^c 2.5-5% solution.

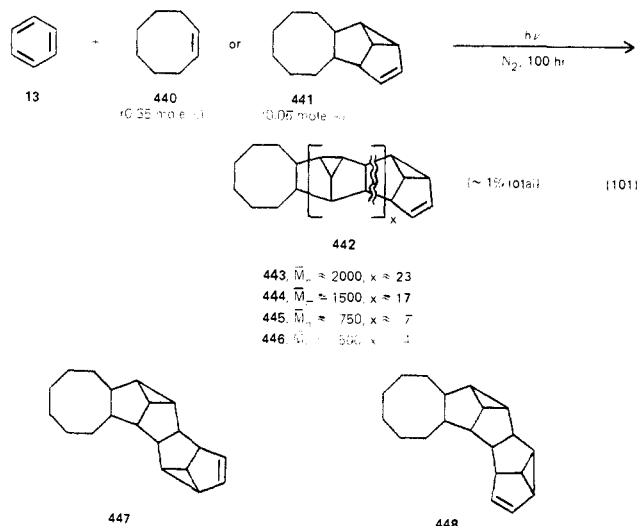


Scheme VIII

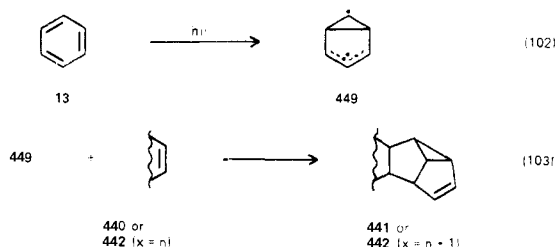

adducts, and trace amounts of a 1:2 (13:440) adduct.¹⁴⁹ Photoaddition of benzene to the 1:1 adduct 441 gave the 2:1 adducts 447 and 448.¹⁴⁹

The mechanism suggested for the benzene polymerization involved its excitation to a diradical state 449 (eq 102) and subsequent addition of the latter to the olefinic linkage of 440 in an initiation step or to the polymer 442 in a propagation step (eq 103) (Scheme VIII).¹⁴⁹ 1,3 Cycloadditions to benzene are allowed concerted processes.¹⁵⁰ Woodward-Hoffmann rules cannot be applied to photoreactions involving benzene rings because the molecular orbitals Ψ_2 and Ψ_3 are degenerated as are Ψ_4 and Ψ_5 .¹⁵⁰

Irradiating a mixture of benzene and norbornadiene (450) gave a polymer 451 of unspecified structure (eq 104).¹⁴⁹ Whether this polymer 451 consisted mainly




of benzene (13) units or diene 450 units, or both was not clear. Because both monomers 13 and 450 were difunctional, any of the three possibilities could have occurred. Molecular weight determinations indicated the polymer 451 had a DP of 24-28.

B. Substituted Benzenes

The styrene trimer(s) analogous to the 2 + 3 dimer 217, formed via diradical 219,¹²⁵ was discussed in section IIIH.

Several intramolecular 2 + 3 photocycloadditions have been reported for substituted benzenes containing olefinic linkages in the side chain.¹⁵¹

Two of these reactions gave excessive polymer deposits (eq 105 and 106).¹⁵¹ The structures of these

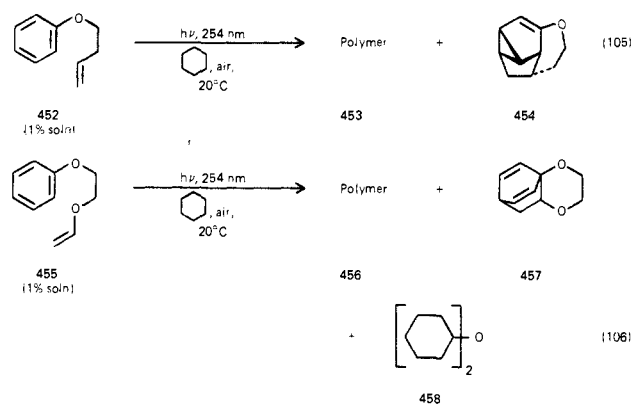

polymers, 453 and 456, were not reported, although they may have been intermolecular analogues of the intramolecular products 454 and 457. Quantum yields for disappearance of starting compounds 452 and 455 were greater, the latter ~ 20 times, than those for the formation of the corresponding cyclization products 454 and 457.¹⁵¹ The latter two quantum yields were very low.

IV. Cycloadditions Involving Carbon 2 + 4 Addition


The only unrefuted polymerization or oligomerization reported as occurring via a photochemical 2 + 4 cycloaddition involved formation of the styrene trimer(s) analogous to the 2 + 4 dimers 218¹²⁵ discussed in section IIIJ.

The original reports indicated the crystal-state photopolymerization of certain conjugated diacetylenes via 2 + 4 cycloadditions gave polyacenes. Later work showed these polymers were not polyacenes and the polymerizations were not cycloaddition reactions.¹⁵²

V. Cycloadditions Involving Carbon 4 + 4 Addition


A. Hexaethyldienecyclohexane

The radialene 459 reportedly underwent photochemical oligomerization to approximately a hexamer, the structure of which was postulated as 460 (eq 107).¹⁵³

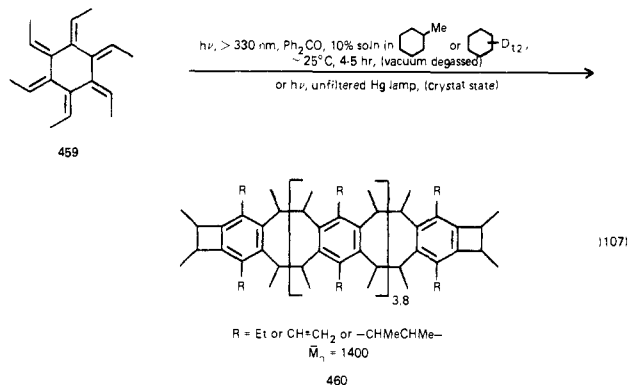

The same product was reported for both the benzophenone-sensitized reaction in solution and the direct irradiation in the crystal state. The crystal structure of the monomer was reported.¹⁵³ The rate of the crystal state reaction was independent of temperature in the range -75°C to 20°C .¹⁵³

Scheme IX

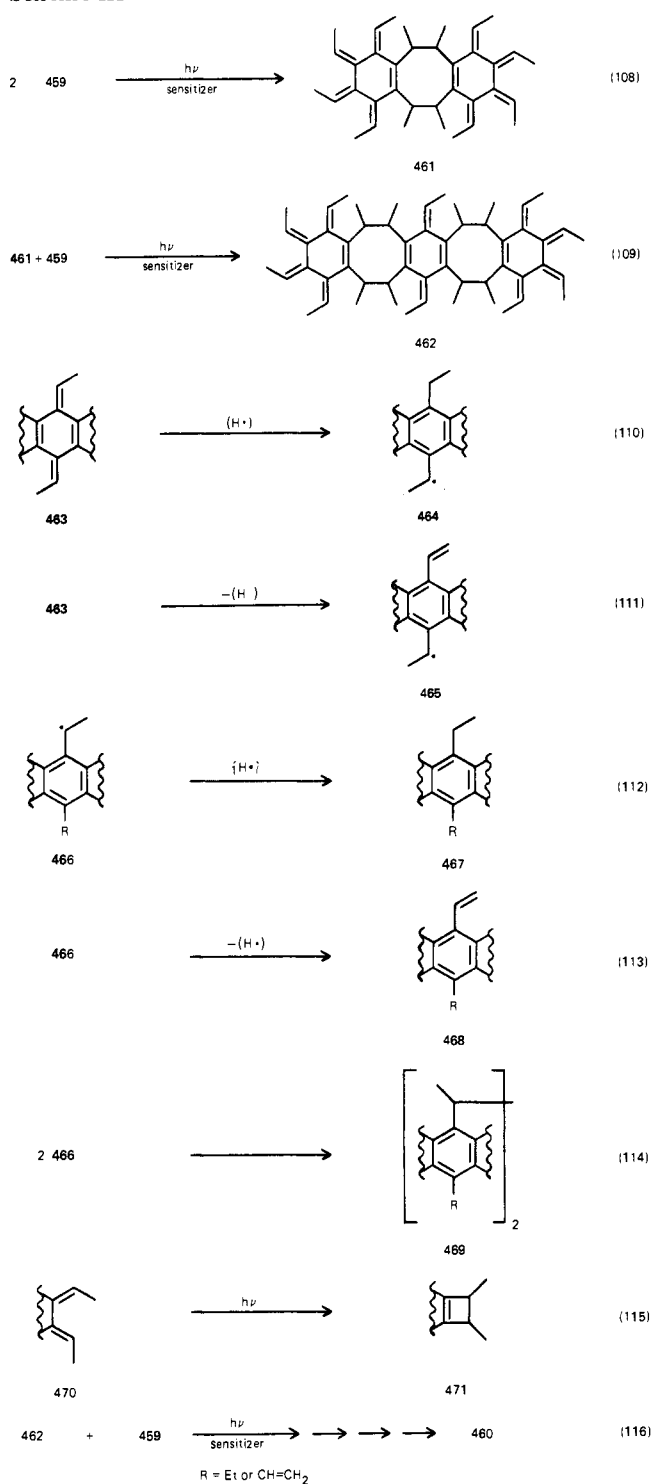


The suggested reaction path leading from monomer **459** to oligomer **460** (Scheme IX) involved 4 + 4 cycloadditions (eq 108, 109, and 116), various hydrogen atom additions (eq 110 and 112) and abstractions (eq 111 and 113), a radical coupling (eq 114), and cyclization of butadienes to cyclobutenes (eq 115).¹⁵³ Numerous other structural features could be envisaged for the oligomer in addition to those shown in **460** because of the high degree of functionality of the monomer **459**. The DP of 5.8 shown in structure **460** is valid only for $R = \text{Et}$ and $\text{CH}=\text{CH}_2$. The number of repeating units in **460** requires modification if bridging groups ($R = -\text{CHMeCHMe}-$) occur.

B. Bis(anthracenes)


1. 2-Substituted

Irradiating the nonamethylene bis(anthracene) **472** in dilute solution gave two intramolecular cyclic products **474** and **475** and an intermolecular reaction product that presumably was polymeric, **473** (eq 117).¹⁵⁴

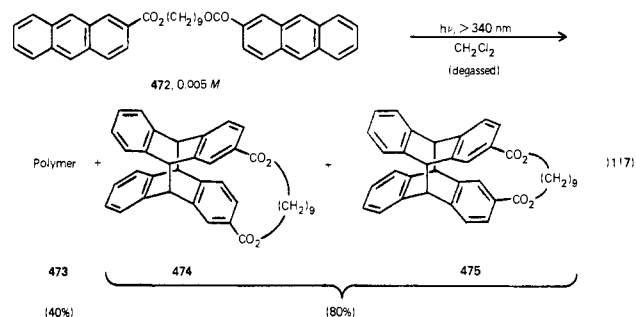


The pentamethylene and heptamethylene homologues of **472** gave only intramolecular products analogous to **474** and **475**.¹⁵⁴ The intermolecular reaction presumably occurred via 4 + 4 photocycloaddition reactions similar to the intramolecular reactions.

Rate constants have been reported for inter- and intramolecular processes for bis(anthracenes) **476** in their excited singlet states under unspecified conditions (eq 118) (Table XXV).¹⁵⁵ Both polymerization and cy-

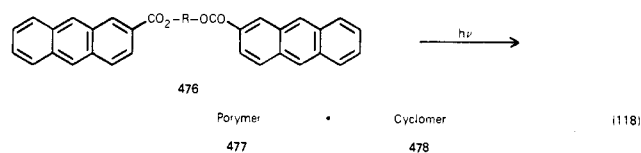


clization presumably occurred via 4 + 4 cycloadditions. Neither product structure was reported. The rate of the intermolecular process was nearly independent of the nature of R in monomer **476**.¹⁵⁵ The rate of the intramolecular process decreased slightly with increasing length of connecting link R .

Polyurethane **481**, which contained anthracene-carboxamide end groups, polymerized by "photodimerization" of the end groups, presumably via 4 + 4 cycloaddition at the 9,10-positions of the anthracene moieties (eq 119).¹⁵⁶ Polyurethane **481** was prepared

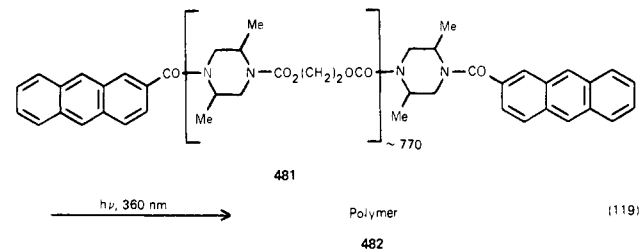


by copolymerizing 0.13 mol percent of the photodimer of the anthracene **483** and 99.87 mol percent of 2,5-

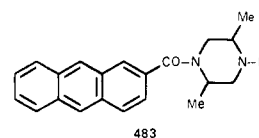

dimethylpiperazine with ethylene glycol bis(chloroformate), to give presumably the same polymer **482** formed in reaction 119, followed by short-wavelength photolysis to cleave the dianthracenes to the free an-

TABLE XXV. Rate Constants for Inter- and Intramolecular Processes of Di-2-anthracenecarboxylic Esters 476 (Eq 118)¹¹⁵

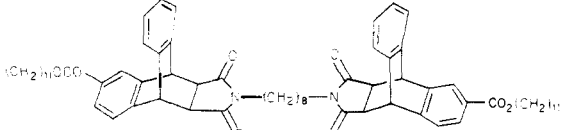R of monomer 476	rate constant for 476* ¹ ^a	
	polymerization (→477) + other intermolecular deactivation processes, M ⁻¹ s ⁻¹	cyclomerization (→478) + other intramolecular deactivation processes, s ⁻¹
(CH ₂) ₉ , 472	7.7 × 10 ⁹	2 × 10 ⁸
(CH ₂) ₁₆ , 479	8 × 10 ⁹	1 × 10 ⁸
 , 480	7 × 10 ⁹	4 × 10 ⁷

^a Excited singlet state of 476.


anthracene end groups of 481.¹⁵⁶ Because the original polymer was a rigid matrix, after the short-wavelength photolysis the freed anthracene moieties were oriented favorably for readdition (eq 119).¹⁵⁶ The molecular weight of the polyurethane 481 was not reported; its structure was deduced from the relative amounts of its constituents as noted above and by assuming that short-wavelength photolysis completely dissociated the dianthracene links.

The rate of reaction 119 was faster than a similar photocycloaddition reaction of the model compound, 483, that was oriented in a polyurethane matrix similar to the polyurethane portion of 481.¹⁵⁶ The same kind of orientation process employed in preparing 481 was used.¹⁵⁶ The rate of reaction 119, however, was much slower than that of photocycloaddition of anthracene 483 oriented in a poly(methyl methacrylate) matrix having a low glass transition temperature.¹⁵⁶

Irradiating mixtures of bis(anthracenes) 472 and 480 gave copolymers of unspecified structure,¹⁵⁵ presumably of the 4 + 4 type. The ratios of monomers in the starting reaction mixtures controlled the ratios of monomers in the polymers.¹⁵⁵

2. 9-Substituted

The bis(9-substituted anthracenes) 484 shown in Table XXVI reportedly polymerized by head-to-tail 4 + 4 photocycloaddition (eq 120).^{131,157-162} This regio-

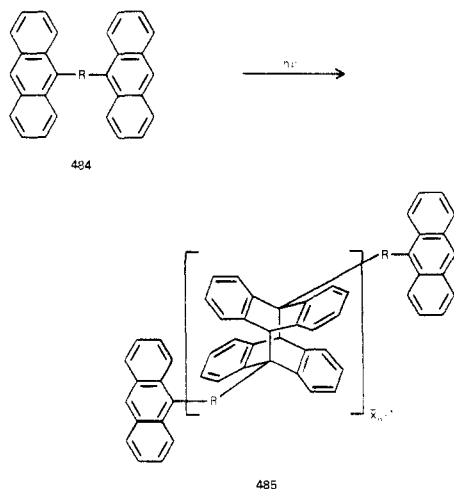

chemical assignment, at least for the anthracene-carboxylic esters, apparently was based on the analogous photodimerization of the model compound, methyl

anthracene-9-carboxylate, which formed only the head-to-tail adduct.¹⁵⁷ The other anthracene polymers 511 and 513 were also tentatively assigned head-to-tail regiochemistries.¹⁵⁹

Polyether 484 [R = CO₂(CH₂CH₂O)₃CO], irradiated under the same conditions as was monomer 500 (Table XXVI), gave an insoluble, cross-linked but otherwise uncharacterized polymer.¹⁶¹ Part of the polymerization may have occurred via photocycloaddition.





Although monomers 490¹⁶⁰ and 510¹⁵⁹ underwent inter- and intramolecular cycloaddition, 512¹⁵⁹ exhibited primarily an intermolecular reaction. A plot of 1/Φ_{dimerization} vs. 1/concn for the diester 490 in CH₂Cl₂ solution showed a sharp break at 0.012 M 490 (Φ_{dim} = 0.045).¹⁶⁰ At higher concentrations Φ_{dim} increased significantly, e.g., 0.10 at 0.03 M 490, indicating the occurrence of an intermolecular reaction.¹⁶⁰ In contrast, at much lower concentrations Φ_{dim} decreased only slightly, e.g., 0.041 at 5.0 × 10⁻⁴ M 490, indicating an intramolecular or concentration independent reaction.¹⁶⁰

Because of the rigid connecting chain between the anthryl groups of monomer 512, it exhibited more intermolecular reaction than did monomer 510 in which the flexible connecting chain allowed more intramolecular cycloaddition.¹⁵⁹ The intramolecular process was ~5 times faster in 510 than in 512.¹⁵⁹ The extent of intramolecular reaction was determined by measuring the initial rates of photocycloaddition at low monomer concentrations and extrapolating these rates to zero initial concentration.¹⁵⁹

At high conversion, *p*-phenylene monomer 512 was slightly more reactive than monomer 510 (Table XXVI), but at up to ~25% conversion, the reverse was true.¹⁵⁹ Pseudo-first-order kinetics were expected at low anthryl group concentrations, ~10⁻⁴ M.¹⁵⁹ A first-order kinetic plot for monomer 512 was generally linear to ~90% conversion whereas a similar plot for 510 showed that the reaction was retarded in the later stages compared to the rate expected if first-order kinetics had prevailed throughout the reaction.¹⁵⁹ Existence of the trianthryl analogue in dianthryl monomer 510 may have accounted for the observed kinetic behavior. Negative deviations from first-order kinetics were expected because photodimerized anthryl groups in the polymer would restrict movement and thus reactivity of the remaining anthryl groups.¹⁵⁹

Several polyanthryl derivatives related to 510 and 512 were studied similarly to those described above.¹⁵⁹ However, these polymer cross-linking reactions are

TABLE XXVI. Photopolymerization of Bis(9-Substituted anthracenes) 484 (Eq 120)

R of monomer 484	phase	concn of 484, M	λ , nm	temp, °C	time, h	atm over sample	product 485	conversion of 484, %	ref
CO ₂ (CH ₂) ₆ OCO, 486	CH ₂ Cl ₂ soln	0.2	366		48	Ar	487		158
CO ₂ (CH ₂) ₈ OCO, 488	CH ₂ Cl ₂ soln	0.1	>320	50-60	36	a	489	80	161
CO ₂ (CH ₂) ₉ OCO, 490	CH ₂ Cl ₂ soln	0.05			~12		491, $\bar{x}_n = 7^b$	97	160
490	CH ₂ Cl ₂ soln	0.2			~63		491, $\bar{x}_n = 12^b$	93	160
490	CH ₂ Cl ₂ soln	0.2	~350		24		491		131, 157
CO ₂ (CH ₂) ₁₀ OCO, 492	CH ₂ Cl ₂ soln	0.2	366		48	Ar	493, $\bar{M}_n = 21,000$, $\bar{x}_n = 36$		158
492	CH ₂ Cl ₂ soln	0.2	~350		24		493		131, 157
CO ₂ (CH ₂) ₁₁ OCO, 494	CH ₂ Cl ₂ soln	0.2	~350		41		495, $\bar{M}_n = 52,000$, $\bar{x}_n = 87$		131, 157, 160
CO ₂ (CH ₂) ₁₂ OCO, 496	CH ₂ Cl ₂ soln	0.2	~350		24		497, $\bar{M}_n = 28,000$, $\bar{x}_n = 46$		131, 157
496	CH ₂ Cl ₂ soln	0.2	>320	50-60	36	a	497	82	161
496 ^c	film ^d		365	20	2.0	N ₂	497	37 ^b	162
496 ^c	film ^d		365	60	2.0	N ₂	497	52 ^b	162
CO ₂ CH ₂ -  -CH ₂ -  -CO ₂ CH ₂ , 498	CH ₂ ClCH ₂ Cl soln	0.1	>320	50-60	9	a	499	86	161
CO ₂ (CH ₂) ₄ OCO(CH ₂) ₄ CO ₂ (CH ₂) ₄ OCO, 500	CH ₂ Cl ₂ soln	0.2	>320	50-60	48	a	501	81	161
CO ₂ (CH ₂) ₄ OCO(CH ₂) ₈ CO ₂ (CH ₂) ₄ OCO, 502	CH ₂ Cl ₂ soln	0.2	>320	50-60	48	a	503	59	161
502 ^c	film ^d		365	20	1.5	N ₂	503	25 ^b	162
502 ^c	film ^d		365	40	1.5	N ₂	503	27 ^b	162
502 ^c	film		365	60	1.5	N ₂	503	50 ^b	162
CO ₂ (CH ₂) ₄ OCO(CH ₂) ₁₂ CO ₂ (CH ₂) ₄ OCO, 504	CH ₂ Cl ₂ soln	0.2	>320	50-60	48	a	505	51	161
504 ^c	film ^d		365	20	1.5	N ₂	505	30 ^b	162
504 ^c	film ^d		365	40	1.5	N ₂	505	15 ^b	162
504 ^c	film ^d		365	60	1.5	N ₂	505	30 ^b	162
CO ₂ (CH ₂) ₄ OCNH(CH ₂) ₆ NHCO ₂ (CH ₂) ₄ OCO, 506 ^c	film ^e		365	~25	1.0	N ₂	507	22 ^b	162
506 ^c	film ^d		365	~25	1.0	N ₂	507	53 ^b	162
506 ^c	film ^d		365	20	1.0	N ₂	507	52 ^b	162
506 ^c	film ^d		365	40	1.5	N ₂	507	29 ^b	162
506 ^c	film ^d		365	60	1.2	N ₂	507	12 ^b	162
CO ₂ (CH ₂) ₄ OCO(CH ₂) ₁₀ NHCO ₂ (CH ₂) ₄ OCO, 508 ^c	film ^d		365	20	1.5	N ₂	509	54 ^b	162
508 ^c	film ^d		365	40	1.5	N ₂	509	24 ^b	162
508 ^c	film ^d		365	60	1.5	N ₂	509	10 ^b	162
CH ₂ CH(CH ₂ OH)CH ₂ OCO(CH ₂) ₂ CO ₂ CH ₂ CH-(CH ₂ OCOCH ₂ CH ₂ COCl)CH ₂ , 510 ^f	PhMe soln	~2 × 10 ⁻⁴	370	30 ± 2	(3.2) ^g	N ₂	511	88 ^b	159
CH ₂ CH(CH ₂ OH)CH ₂ OCO-  -CO ₂ CH ₂ CH(CH ₂ OH)CH ₂ OCO-  -CO ₂ MeICH ₂ , 512	PhMe soln	~2.6 × 10 ⁻⁴	370	30 ± 2	(3.0) ^g	N ₂	513	91 ^b	159

512

^a Degassed. ^b Data at shorter reaction times also reported. ^c Prepared by photolysis of corresponding polymer 485 at 300 nm, <5% conversion. ^d Preformed polymer 485 annealed at 80 °C for 2 h and slowly cooled; irradiated at 300 nm at 20 °C to prepare 484. ^e Preformed polymer 507 annealed at 80 °C for 2 h and cooled quickly; irradiated at 300 nm at 20 °C to prepare 506. ^f Mixture with trianthryl analog; acid chloride moiety may have hydrolyzed to acid.

outside the scope of this review.

The monomers in Table XXVI that were irradiated as films were actually several of the indicated monomer units joined together by dianthracene links. These monomers were formed by 300 nm irradiation of the preformed polymers 485, prepared by a nonphotochemical polymerization.¹⁶² This short wavelength radiation restored <5% of the anthracene moieties from the dianthracene links, thus accounting for the oligomeric nature of the monomers. Preformed polymer 497 had a lower molecular weight than did preformed 503 or 505.¹⁶²

Residual casting solvent reduced the rates of redimerization of anthroate groups in the films (Table XXVI). It acted as a plasticizer so that reactive groups in the monomer were mobile and not aligned for ready cycloaddition.¹⁶²

The thermal history of the preformed polymers significantly affected the rate and extent of redimerization of anthroate moieties in the films.¹⁶² The two different reaction rates of bis(carbamate) 506 at ~25 °C (Table XXVI) was attributed to the different rates at which the preformed polymers 507 cooled after being annealed at 80 °C.¹⁶² The slower rate at which the quickly cooled sample dimerized presumably was a consequence of the strain in the polymer caused by this cooling. Relaxation of the strain when the polymer was photolyzed to monomer positioned the anthroate groups so that they could not easily dimerize. The slowly cooled polymer was largely relaxed before the monomerization process. Heating monomer 506 at 80 °C in a film and then cooling it to 20 °C completely destroyed its ability to undergo photocycloaddition.¹⁶²

The effect of temperature on the rates at which the monomers repolymerized in films (Table XXVI) was studied extensively.¹⁶² In principle, increasing temperature could increase the rate because of the usual activation energy requirement or because of increased polymer chain segment mobility for those reactions in which preformed ground state complexes (sandwich dimers) did not control the rate of polymerization. Alternately, increasing temperature could also decrease the rate for those reactions in which preformed ground state complexes were intermediates in the cycloaddition by destroying these complexes.

Monomers 506 and 508, at 20 °C and 40 °C and 504, at 20 °C, initially photorepolymerized rapidly because of preformed ground state complexes.¹⁶² Monomer 508 exhibited a higher rate at 40 °C than at 20 °C. These reactions decreased in rate after only unpaired anthroate groups were available for reaction and the polymer lacked segment mobility. At 60 °C, both 506 and 508 photopolymerized slowly because the ground state complexes had been destroyed.


Esters 496 and 502 did not form stable ground state complexes.¹⁶² Later stages of the photopolymerizations of 496 at 20 °C and 60 °C were faster than the corresponding reactions for the bis(carbamates) 506 and 508 because the polyester possessed greater segment mobility than the polycarbamate did.

Although tetraester 504 reacted to the same extent at 20 °C and 60 °C after 1.5 h (Table XXVI), it initially reacted much faster at 20 °C.¹⁶²

The nonmethylene dianthroate 490 underwent a singlet state, photocycloaddition polymerization as

shown by a 10.5 ns lifetime for its excited state at infinite dilution.¹⁶⁰ This lifetime was determined by extrapolating a plot of $1/\tau$, obtained by quenching the polymerization with *t*-Bu₂NO, vs. concentration of 490. The fluorescence lifetime of 490 at 10⁻⁵ M was 10 ns.¹⁶⁰ Photopolymerizations of the other α,ω -polymethylenedi-9-anthroates, 492, 494, and 496, also presumably occurred via singlet states.¹³²

Irradiating a series of bis(9-anthrylmethyl) derivatives 514 gave polymers 515 that formed by 4 + 4 cycloaddition (eq 121) (Table XXVII).^{157,158,163,164} These 4

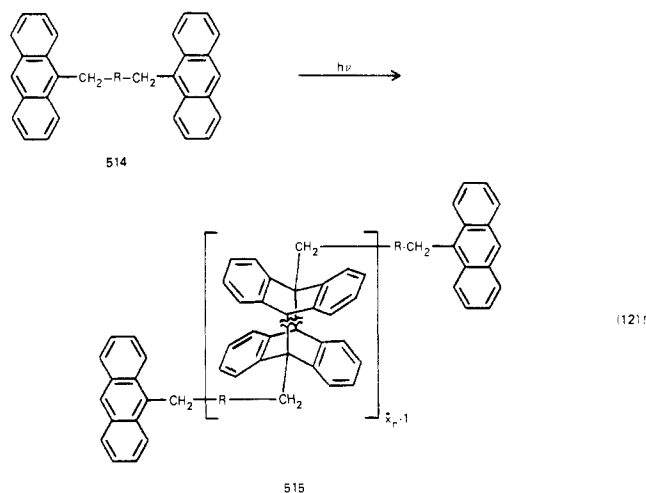

+ 4 cycloadditions may have occurred via both head-to-tail and head-to-head reactions.¹⁵⁷ The model compound, 9-(acetoxymethyl)anthracene, gave a 4:1 mixture of head-to-tail and head-to-head cycloadducts, respectively.¹⁵⁷

A head-to-tail encounter of the anthryl groups in the ionene 526 was implied as a necessary condition for photodimerization of this monomer.¹⁶⁴ However, no structural evidence was presented to corroborate this implication.

A 1,5-sigmatropic shift of a methylene hydrogen atom to the 10-position of the anthracene nucleus was suggested as a side reaction that limited the molecular weights of diesters 516, 518, 520, 522, and 524.¹⁵⁷ Steric hindrance to formation of head-to-head adducts from the diesters in Table XXVII was also cited as a possible reason for the lower molecular weights.¹⁵⁷ The higher molecular weights of the related polyesters 495 and 497 (Table XXVI) were attributed to the unfeasibility of a 1,5 shift.¹⁵⁷

The lower molecular weight of the heptamethylene diester polymer 523, formed in the argon-purged solution, compared with that formed in the vacuum degassed solution (6000 vs. 12,000) was attributed to formation of more endo peroxides in the former.¹⁵⁷ Endo peroxide formation across the 9,10-positions of an anthracene ring would terminate chain growth on that end of a polymer chain. Removing oxygen from solutions by vacuum degassing is usually more effective than purging argon through the solution.

Photocycloaddition of the ionene 526 may have occurred inter- or intramolecularly.¹⁶⁴ The photoreaction of 526 below the critical micelle concentration (CMC) may have been an intermolecular reaction by analogy with a more thoroughly studied polyanthrylionene.¹⁶⁴ The initial conversion rates of the 526 anthryl groups in both water and KCl solution were independent of the

TABLE XXVII. Photopolymerization of Bis(9-anthracenes) 514 (Eq 121)

R of monomer 514	solvent	concn of 514, M	λ , nm	temp, °C	time, h	atm over solution	product 515	yield of 515, %	ref
$\text{OCO}(\text{CH}_2)_4\text{CO}_2$, 516	CH_2Cl_2	0.1	~350	30-40	69	Ar	517, $\bar{M}_n = 6800$, $\bar{x}_n = 13$	157, 158 ^a	
$\text{OCO}(\text{CH}_2)_5\text{CO}_2$, 518	CH_2Cl_2	0.2	~350	30-40	48	Ar	519, $\bar{M}_n = 5435$ or 6400, $\bar{x}_n = 10$ or 12	157, 158 ^a	
$\text{OCO}(\text{CH}_2)_6\text{CO}_2$, 520	CH_2Cl_2	0.2	~350	30-40	48	Ar	521, $\bar{M}_n = 4500$ or 4560, $\bar{x}_n = 8.1$ or 8.2	157, 158 ^a	
$\text{OCO}(\text{CH}_2)_7\text{CO}_2$, 522	CH_2Cl_2	0.2	~350		48	Ar	523, $\bar{M}_n = 6000$, ^b $\bar{x}_n = 11$	157	
522	CH_2Cl_2	0.2	~350		48	c	523, $\bar{M}_n = 12,000$, $\bar{x}_n = 21$	157	
$\text{OCO}(\text{CH}_2)_8\text{CO}_2$, 524	CH_2Cl_2	0.2	350	30-40	48	Ar	525, $\bar{M}_n = 11,600$, $\bar{x}_n = 19.9$	158 ^a	
524	CH_2Cl_2	0.2	~350		48	c	525, $\bar{M}_n = 11,600$, $\bar{x}_n = 19.9$	157	
$(\text{CH}_2)_2\text{OCOCH}_2\text{N}^+\text{Me}_2(\text{CH}_2)_6\text{N}^+\text{Me}_2\text{CH}_2\text{CO}_2(\text{CH}_2)_2$, 526	H_2O	2.50×10^{-4}	366		(58.4) ^d	Ar	527	35.1 ^e	163, 164
526	0.25 M KCl in H_2O	2.50×10^{-4}	366		(48.5) ^d	Ar	527	36.7 ^e	163, 164

^a Data given in this table from cited references is probably correct; data in U.S. patents were confusing. ^b \bar{M}_n given as 12 000 for this polymer prepared at 30-40 °C.¹⁵⁸
^c Degassed. ^d Relative light energy input. ^e Data at lower conversions also given.

TABLE XXVIII. Rate Constants for Inter- and Intramolecular Processes of Di-9-anthracenecarboxylic Esters 528 (Eq 122)¹⁵⁵


n of monomer 528 ^a	rate constants for 528* ^a	
	polymerization ($\rightarrow 529$) + other intermolecular deactivation processes, $\text{M}^{-1} \text{s}^{-1}$	cyclomerization ($\rightarrow 530$) + other intramolecular deactivation processes, s^{-1}
9, 490	6.5×10^9	1.3×10^8
16, 531	6.9×10^9	8.5×10^7

^a Structure of 528 in ref 155 showed nine methyl groups on one of the anthracene rings; the actual monomer probably does not contain methyl groups.

526 concentration (zero-order reaction) above the CMC. Thus these reactions either occurred in the micellar state or intramolecularly.¹⁶⁴

The rate of photocycloaddition of 526 was slightly faster in 0.25 M aqueous KCl solution than in water.^{163,164} This behavior was attributed to a higher local anthryl group concentration resulting from volume shrinkage of the monomer and polymer aggregates in KCl solution. This shrinkage was caused by reduced Coulombic repulsion and enhanced hydrophobic interactions.¹⁶⁴

Rate constants were reported for inter- and intramolecular processes for bis(anthracenes) 528 in their excited singlet states under unspecified conditions (eq 122) (Table XXVIII).¹⁵⁵ Both polymerization and

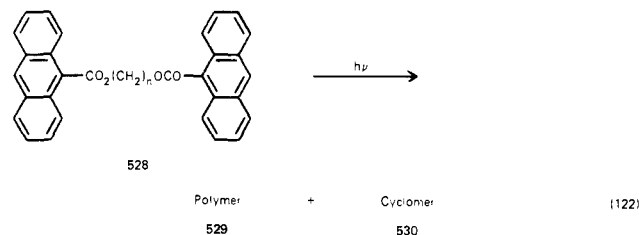


cyclization presumably occurred via 4 + 4 cycloadditions although neither structure was reported. The rate of the intermolecular process(es) was nearly independent of the number of methylene groups or the position of attachment on the anthracene nucleus (Table XXV).¹⁵⁵ The rate of the intramolecular process(es) decreased slightly with increasing length of the connecting link as was also observed for the 2-anthryl derivatives (Table XXV).

Irradiating mixtures of bis(anthracenes) 490 and 531 gave copolymers of unspecified structure,¹⁵⁵ but presumably of the 4 + 4 type. The ratios of monomers in the polymers were controlled by the ratios of monomers in the starting reaction mixtures.¹⁵⁵

VI. Cycloadditions Involving Carbon and Oxygen 2 + 2 Addition (Copolymerizations)

A. Bis(benzophenones) with Tetramethylallene and Other Diolefins

Several series of polymers were prepared in which the chain-growth step was formation of an oxetane by photocycloaddition of a carbon-carbon double bond to a carbonyl group. These are copolymerizations because the two addends are in different kinds of molecules. In all examples reported, bis(benzophenones) 532 served

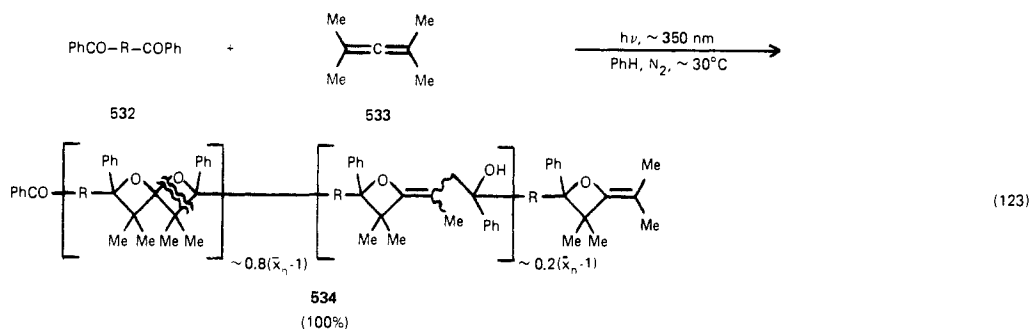TABLE XXIX. Photocopolymerization of Bisbenzophenones 532 with Tetramethylallene 533 (Eq 123)¹⁶⁶

R of comonomer 532	concn of 532 and 533, M	time, h	product 534	crude product		precipitated product	
				\bar{M}_n	\bar{x}_n	\bar{M}_n	\bar{x}_n
535	0.419	550	536	6610	17.3		
537	0.112	790	538 ^a	2200	5.8	3900	10.2
539	0.02	160 ^b	540	4400 ^{c,d}	9.3		
	0.111 ^e	22 ^b	540	10 600	22.5		
	0.129	360	540	13 000	27.5		
541	0.00922	500	542	2800	5.8	4200	8.6
	<i>f</i>		543	6400	13.2	7300	15.0
542	<i>f</i>		543	6400	13.2	7300	15.0
544	0.0301	440	545	5300	10.6	8100	16.2
546	0.0318	520	547	4100	8.0	6100	11.9
548	0.0225	510	549	2800	5.3	6300	11.9
550	0.0190	370	551	3100	5.7	6200	11.4
552	0.0363	430	553	3700	6.2	7400	12.4
554	0.033	670	555	6200	13.1		

^a May contain cyclobutanone units. ^b Light intensity was twice that of other reactions in this table. ^c Data at shorter reaction times also given. ^d \bar{M}_n near the maximum attained was achieved in ~2-3 h. ^e Data at lower concn also given. ^f Concn unspecified, >0.00922 M (based on monomer).


TABLE XXX. Photocopolymerization of Bis(benzophenones) 532 with Furan 572 (Eq 140)¹⁶⁷

R of comonomer 532	concn of 532, M	concn of 572, M	time, h	product 573	crude product		yield of 573, %
					\bar{M}_n	\bar{x}_n	
535	0.199	0.199	670	574	1250	3.5	
539	0.133 ^a	~13 ^b	530	575 ^c	617	1.39	
541	0.0187	~13	170	576 ^d	567	1.24	100


^a At 0.0282 M 539, the 2:1 adduct 589 formed in 100% yield. ^b Furan used as solvent. ^c Some 2:1 adduct 589 formed. ^d Assumed to be ~85% 2:1 adduct 578 by weight and ~15% 3:2 adduct 580.

as the carbonyl component. Tetramethylallene (533) was one of the diolefins (eq 123) (Table XXIX).^{165,166}


The polymer structures, 534 or closely related isomers, were assigned on the basis of the product structures from model compound reactions and spectroscopic data.¹⁶⁶ In addition to regioisomeric oxetanes and olefinic cis-trans isomers, the polymer apparently contained the alternate isomeric unsaturated minor unit 556.¹⁶⁶ The sequence of dioxetane or methyleneoxetane repeating units in the copolymer was not necessarily only as shown in structure 534. The sequences may



have been reversed in parts of the polymer. They presumably depended on which type of moieties (unreacted or singly reacted 533) reacted in the chain-extending steps (see Scheme X).

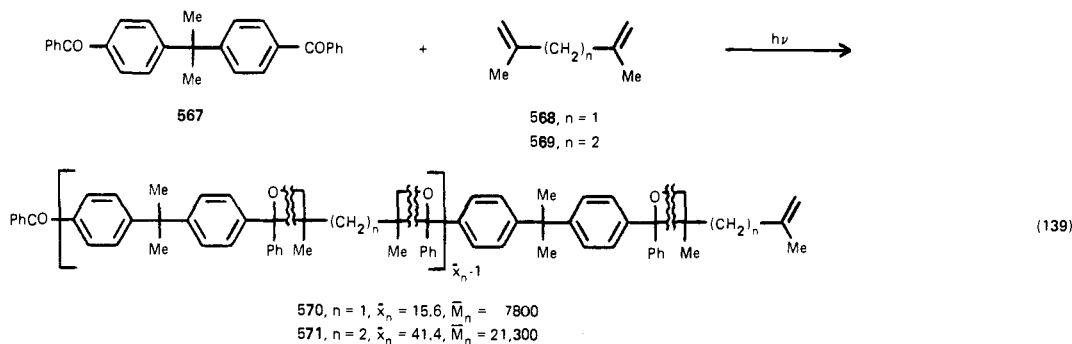

Scheme X

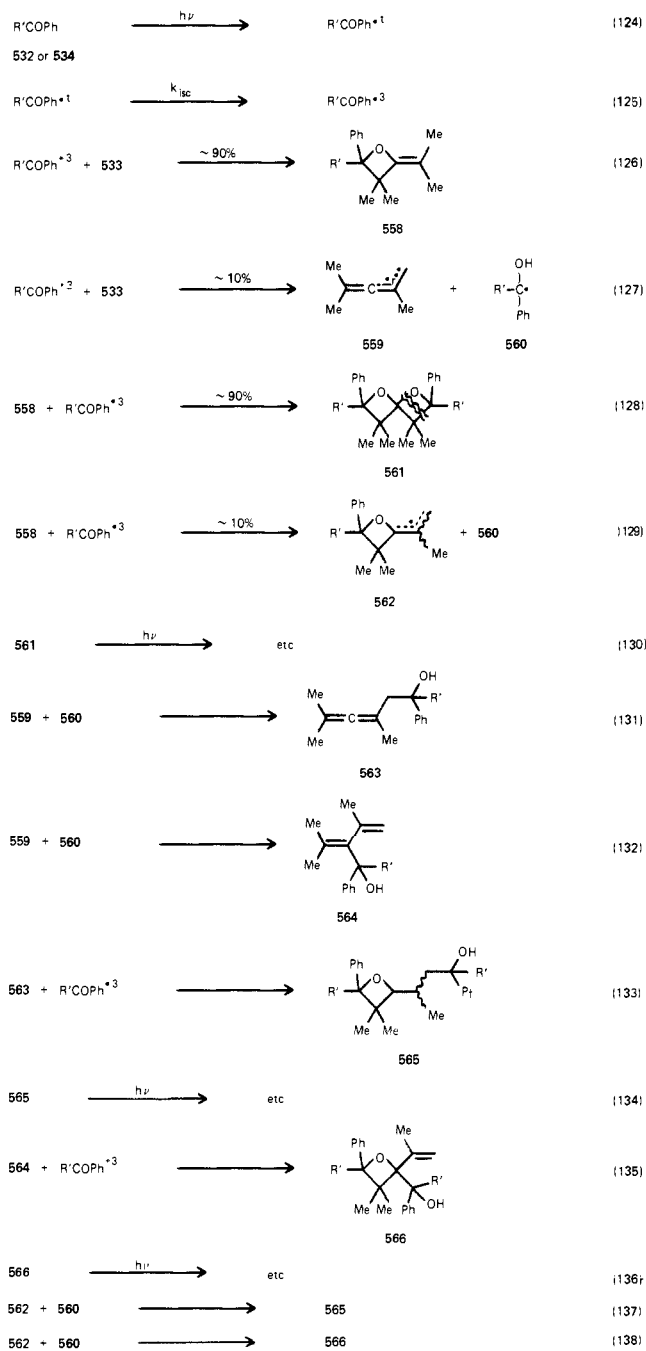

The biphenyl derivative, **532** ($\text{R} = -p\text{-C}_6\text{H}_4\text{-}p\text{-C}_6\text{H}_4-$, **557**) did not polymerize when irradiated with allene **533**, both 0.0110 M, for 1730 h under the conditions shown in eq 123.¹⁶⁶ This lack of reactivity was attributed to the π, π^* character of the lowest triplet state of this

diketone **557**.¹⁶⁶ The other derivatives of **532** in Table XXIX presumably had n, π^* lowest triplet states.

Copolymerizing the methylenebis(benzophenone) **539** with allene **533** gave polymer **540**, which achieved its maximum molecular weight in only a few hours (Table XXIX, line 3).¹⁶⁶ Continued irradiation had little effect on the DP.¹⁶⁶ The maximum molecular weight increased with increasing concentration of the monomers (Table XXIX, lines 3–5).¹⁶⁶ Cessation of polymer growth could have been caused by destruction of chain-end functionality by side reactions, by cyclization, by formation of quenching species, or by dilution of the reactive chain-end functional groups so that the excited states did not live long enough to find a reaction partner.¹⁶⁶ In one set of experiments (Table XXIX, lines 6 and 7), the DP increased with increasing concentration of oligomer **542** formed from the dimethylene monomer **541**, an observation consistent with the dilution effect.¹⁶⁶

The mechanism proposed for copolymerization of monomers **532** and **533** involved the triplet excited ketone **532**^{*3} (Scheme X).¹⁶⁶ Approximately 10% of the excited ketones abstracted allylic hydrogen atoms rather than cycloadding to a carbon-carbon double bond. The first cycloaddition of a carbonyl group to allene **533** was apparently regioselective, but the second was not. Cycloadditions of **532**^{*3} to radical coupling products **563** and **564** could have produced the products shown, **565** and **566**, respectively, or their regioisomers. Hydrogen atom abstraction presumably also occurred to a small extent in these reactions.

Bisphenol A derivative **567** copolymerized with α, ω -dienes **568** and **569** to give the polyoxetanes **570** and **571** (eq 139).²⁹ No further details, such as side reactions, were reported.²⁹

B. Bis(benzophenones) with Furans and Derivatives

Several furans and derivatives have been copolymerized with bis(benzophenones) **532**. Furan (**572**) gave low molecular weight oligomers when irradiated (eq 140) with the diketones shown in Table XXX.¹⁶⁷

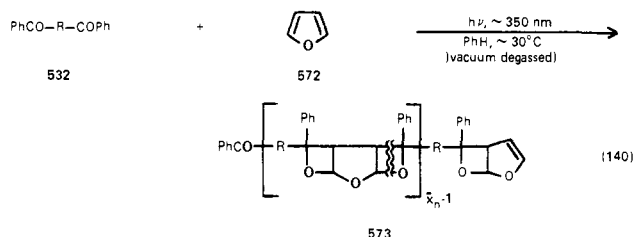




TABLE XXXI. Photocopolymerization of Bis(benzophenones) 532 with 2,5-Dimethylfuran 581 (Eq 145)¹⁶⁷

R of comonomer 532	concn of 532 and 581, M	product 582	crude product		precipitated product	
			\bar{M}_n	\bar{x}_n	\bar{M}_n	\bar{x}_n
 535	0.072	583	2400	6.3	3000	7.8
 546	0.047	584	4000	7.8	6700	13.0



The first photocycloaddition of a carbonyl group to the furan ring probably gave only a dioxabicycloheptene acetal, e.g., eq 141, 142, and 144 (Scheme XI), by analogy with the regiochemistry of model reactions.¹⁶⁷ The addition of the second carbonyl group to the furan ring was nonregiospecific, e.g., eq 143.

The sequence of acetal and non-acetal type oxetane rings in oligomer 573 could have been reversed in parts of the polymer depending on which type of molecule—unreacted or singly reacted 572—reacted in the chain-extending steps. This situation is analogous to that shown in Scheme X for the allene reactions.


The low molecular weight of the polymer 574 was attributed to the presence of unequal amounts of the comonomers 532 and 572 in the reaction mixture.¹⁶⁷ The unequal amounts arose because of the difficulty of measuring an amount of furan (572) exactly equivalent to that of the diketone 535.¹⁶⁷ Reactions of diketones 539 and 541 with excess furan solvent gave 2:1 adducts, e.g., 578, which were used for further polymerizations as described in a later section.¹⁶⁷ Small quantities of higher cooligomers formed in both reactions.

Two copolymerizations of unspecified regiochemistry

Scheme XI

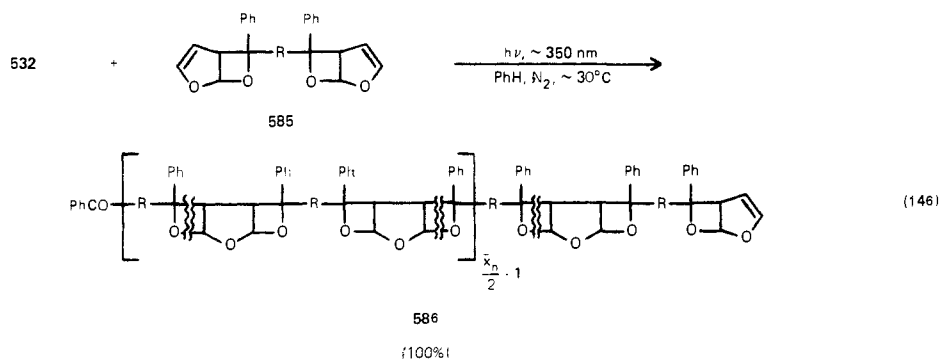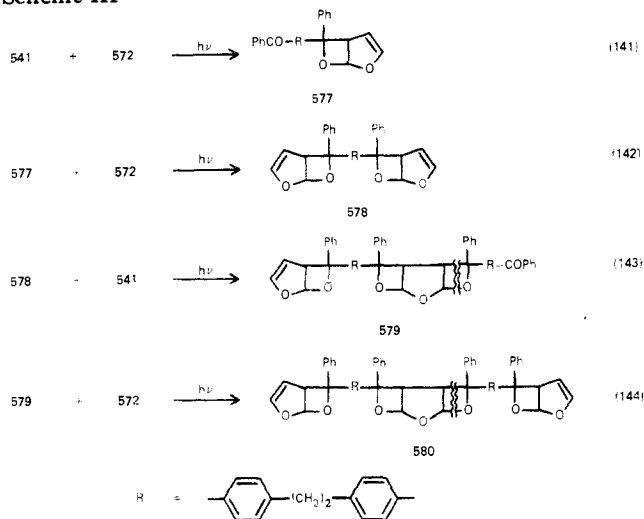

were performed using 2,5-dimethylfuran (581) instead of furan (eq 145) (Table XXXI).¹⁶⁷

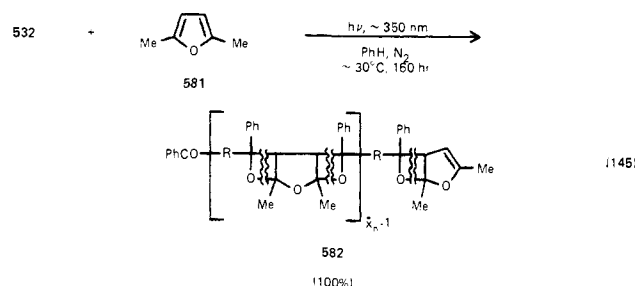













Copolymerizations of dimethylfuran 581 with the diketones 535 and 546 produced almost no cross-linking in contrast to some of the copolymerizations involving the furan derivatives described in the following paragraphs.¹⁶⁷ The lower degree of cross-linking in 581 copolymers was attributed to the absence of hydrogen atoms on carbon atoms alpha to two oxygen atoms.¹⁶⁷

Because of the poor results obtained in copolymerizations of furan (572) with diketones 532, the 2:1 adducts 585 were synthesized and photocopolymerized with the diketones 532 (eq 146) (Table XXXII).¹⁶⁷ Improving the control with which the amounts of comonomers 532 and 585 were charged to the reactor gave higher DP's than attained from the direct reaction.¹⁶⁷ The 2:1 adducts 585 were synthesized in quantitative yield by irradiating the diketones 532 in a large excess of furan as the solvent under conditions comparable to those shown in eq 146 and Table XXXII.¹⁶⁷

Table XXXI shows the DP of copolymers 586 on the basis of diketone 532 and furan (572), not the 2:1 adduct 585, as the comonomers. The DP based on the monomers 532 and 585 is one-half the value given in Table XXXII, thus the $\bar{x}_n/2$ subscript in structure 586. Interestingly, the purified, precipitated copolymers 592 and 599 had lower DP's than the crude products.

The sequence of regioisomeric oxetanes in copolymer 586 formed from the 2:1 adducts 585 was theoretically different from that formed directly from furan. In the

TABLE XXXII. Photocopolymerization of Bis(benzophenones) 532 with Furan-Bis(benzophenone) 2:1 Cycloadducts 585 (Eq 146)

R of comonomers 532 and 585 ^a	concn of 532 and 585, M	time, h	product 586	crude product		precipitated product		ref
				\bar{M}_n	\bar{x}_n^b	\bar{M}_n	\bar{x}_n^b	
 535, 587	0.0175		588	c				167
 535, 587	0.0846	410	588 ^d	4800	13.5	8000	22.6	167
 537, 589	0.0293	640	590	1800	5.1	2200	6.2	167
 539, 591	0.00975	90	592	5400	12.1	4300	9.7	167
 539, 591	0.0176	200	592					167
 541, 578	0.00843 ^e	110	593	3400	7.4	6100	13.3	167
 544, 594	0.0142	210	595	6000	12.7	6500	13.8	167
 546, 596	0.0216	120	597	7600	15.6	9000	18.5	167
 548, 598	0.00864	140	599	3700	7.4	3500	7.0	167
 550, 600	0.0172	270	601	4100	8.0	7300	14.2	167
 552, 602	0.00812	340	603	2500	4.4			167
603	0.0134 ^f		604	2900	5.1	8600	15.1	167
 554, 605 ^g			606					27

^a First compound number is for derivative of 532, and second compound number is for derivative of 585. ^b Based on diketone 532 and furan 572 as the monomer units. ^c \bar{M}_n increased linearly with irradiation time and reached plateau in 160-180 h. ^d Hydroxyl functionality increased with extent of polymerization. ^e 578 contained ~15% by weight of 3:2 adduct 580; amount calcd to give 1:1 (541:572) ratio used. ^f Concn of 603 calcd as concn of monomers. ^g Reference 167 reported no polymer formed in the irradiation of 554 with furan (572).

former, every second diketone in the chain had both carbonyl groups incorporated into acetal type oxetanes whereas the latter copolymer 573 contained a more random distribution of isomeric oxetanes. In both copolymers, each trioxatricyclononane unit contained one regiospecific oxetane and one regiorandom oxetane.

As in the reaction of biphenyl derivative 557 with the allene 533, irradiating furan (572) with 557 also gave no polymer,¹⁶⁷ presumably for the reason cited previously.

Formation of hydroxyl groups occurred in all copolymerizations of diketones 532 and furans or derivatives.¹⁶⁷ Some cross-linking took place in all except those diketones lacking benzylic hydrogen atoms. Both processes presumably occurred because of photoreduction of the triplet carbonyl group by readily abstractable hydrogen atoms.¹⁶⁷ Some hydrogen abstraction occurred even from the solvent benzene.

Thus formation of polyoxetanes via reactions 140, 145, and 146 was limited by the slowness of reactions at attainable monomer concentrations and intervention of at least three types of hydrogen abstraction reactions.¹⁶⁷

VII. Summary

Polymerization reactions occurring by photocycloaddition of bi- and polyfunctional unsaturated monomers are reviewed. Solution and solid state 2 + 2, 2 + 3, 2 + 4, and 4 + 4 cycloaddition reactions of bis(olefins), aromatic, and carbonyl monomers gave cyclobutane, bicyclo[3.1.0]hexane, cyclohexene, cyclooctadiene, and oxetane linkages when the monomers

were irradiated with ultraviolet or visible radiation. The reactive monomer moieties included cinnamic acids, cinnamate esters, cinnamides, cinnamitriles, styrenes, stilbenes, vinylnaphthalenes, vinylpyridines, vinylpyrazines, vinyltriazines, maleimides, thymines, coumarins, furans, benzenes, anthracenes, benzophenones, allenes, and ethylenes. Both direct irradiation and photosensitization have been employed for these polymerizations, which included both singlet and triplet state processes. Most processes were homopolymerizations although a few were copolymerizations.

VIII. Addendum

Since the original portion of this review was written, several additional pertinent publications have appeared or come to the author's attention. This addendum should complete coverage of this subject through 1981 and part of 1982. The same subject headings as used in the original portion of the review are maintained here for continuity.












Three additional reviews covering some aspects of photocycloaddition polymerization have appeared.¹⁶⁸⁻¹⁷⁰

II. Cycloadditions Involving Carbon 2 + 2 Addition

A. Acyclic Bis- and Poly(cinnamic acid) Derivatives

High conversions of the tetracinnamate ester 32 in the crystal state to an amorphous polymer, presumably 33 or 34, were reported.¹⁷⁰ The crystal structure of the monomer 32 apparently did not change during the po-

TABLE XXXIII. Photopolymerization of Bis(9-substituted anthracenes) 484 (Eq 120)^{a,180}

R of monomer 484	solvent	concn of 484, M	temp, °C	time, h	product 485	inherent viscosity of 485, dL g ⁻¹	yield of 485, %
	Me ₂ SO or NMP ^b	0.03	60	120	638 ^c	0.51 ^d	100, 91 ^d
	Me ₂ SO or NMP	0.05	60	110	640 ^c	0.67 ^f	100, 93 ^f
	Me ₂ SO	0.05	60	120	640 ^e	0.67 ^f	100, 94 ^f
	Me ₂ SO or NMP	0.05	60	110	642 ^g	0.75 ^h	100, 95 ^h
	Me ₂ SO	0.05	60	120	644, $\bar{M}_n = 1380$, $\bar{x}_n = 2.70$	0.09	11
	Me ₂ SO	0.025	60	24	646	0.11	12
	Me ₂ SO	0.050	~25	120	646, $\bar{M}_n = 1820$, $\bar{x}_n = 3.10$	0.12	23
	Me ₂ SO	0.050	60	120	646	0.12	22
	HOAc	0.050	~25	120	646	0.12	22
	NMP ⁱ	0.050	60	120	646	0.13	25
	Me ₂ SO	0.050	60	120	648, $\bar{M}_n = 3190$, $\bar{x}_n = 5.29$	0.15	37

^a Irradiated at $> \sim 280$ nm and under high vacuum (10^{-5} – 10^{-4} torr). ^b *N*-Methyl-2-pyrrolidone. ^c Isolated as 644 by air oxidation. ^d Of 644. ^e Isolated as 646 by air oxidation. ^f Of 646. ^g Isolated as 648 by air oxidation. ^h Of 648. ⁱ 5% LiCl added.

lymerization, and no morphological change in crystal shape occurred.¹⁷⁰

C. *m*-Phenylenediacyrylic Acid and Esters

Irradiating a 1:1 mixture, by weight, of the diacid **55** and picramide (**57**) (Table I) as an aggregate of microcrystals in a KBr matrix (>430 nm, few min–2 h) gave **56** ($\bar{M}_n \approx 1000$, $\bar{x}_n \approx 4.6$).¹⁷¹ An 80% conversion of the double bonds of **55** occurred in 1.5 h.¹⁷¹ When the amount of **57** was decreased to 0.1 or 0.01 that of **55**, very low conversions of **55** were observed.¹⁷¹ Thus, relatively large amounts of **57** were required for covering the **55** crystals so that significant sensitization could be achieved.¹⁷¹ 1,2-Benzanthraquinone and 2-nitrofluorene also sensitized this reaction, but were less effective than **57**, which sensitized the phosphorescence of **55** on excitation at 440 nm.¹⁷¹

D. *p*-Bis(monosubstituted vinyl)benzenes

1. *p*-Phenylenediacyrylic Acid, Esters, and Amides

The diacid **63** had a low reactivity, compared to similar compounds, on photopolymerization to **65** in the crystal state.¹⁷⁰

In contrast to the medium photoreactivity reported earlier for the diethyl ester **70** in the crystal state, a more recent publication cited its reactivity as high at -25 °C and low at ~ 25 °C compared to similar compounds.¹⁷⁰

A reaction model was proposed for topochemical photoreactions such as polymerization of the diethyl ester **70** (eq 25) to explain the kinetics as a function of temperature.¹⁷² The assumption was made that the extent of deviation of the two olefinic bonds from their optimal positions for reaction controlled the reaction rate under constant irradiation conditions.¹⁷² The temperature dependence of the primary photochemical process was assumed to be negligible.¹⁷² The reaction rate depended only on thermal motion of molecules in

the crystal.¹⁷² Both unidimensional and two-dimensional models were developed.¹⁷² The equation for the rate constant in the latter was, $k = \alpha(T_{\text{opt}}/T) \exp(-T_{\text{opt}}/T)$, where α is a non-temperature-dependent constant that includes light intensity, quantum yield, etc., and T_{opt} is the optimal temperature at which the maximum rate occurs.¹⁷² T_{opt} for **70** was ~ -20 °C.¹⁷²

Excimer emission from the diethyl ester **70** was observed in concentrated solutions (≥ 0.1 M, MeCN, PhH, or CHCl₃) but not in the crystal state.¹⁷³ Activation parameters were reported.¹⁷³ The structure of the mirror symmetric dimer, analogous to that of the oligomer **78**, formed on irradiating ($\lambda > 350$ nm) concentrated solutions of **70**, was cited as evidence for a stack-type excimer of **70**.¹⁷³ The same dimer was formed by irradiating ($\lambda > 340$ nm) **70** at high concentration; only ground state complexes of **70** were excited.¹⁷⁰ At unspecified temperature, the dimer yield increased on increasing the concentration (12% and 34% yields at 5% and 13% concentrations, respectively) whereas it decreased on increasing the temperature (17% and 9% yields at 5 and 45 °C, respectively) at unspecified concentration.¹⁷⁰ The excimer fluorescence intensity and dimer yields changed as functions of concentration of **70** and temperature in similar manners.¹⁷⁰

Both the *n*-propyl **80**, at 0–5 °C, and isopropyl **82**, at ~ 25 °C, diesters had low reactivities on photopolymerization in the crystal state compared with related compounds.¹⁷⁰ The bisamide **94** had a medium reactivity at ~ 25 °C.¹⁷⁰

The effect of temperature on the reaction and the continuous changes in the X-ray diffraction diagrams of monomers **68**, **70**, and **76** demonstrated that the polymerization proceeded by a diffusionless crystal-lattice-controlled mechanism.¹⁷⁰

2. *p*-Bis(β -nitro- and β -arylvinyl)benzenes


The yield of polymer **109** was 100% from crystal-state irradiation of dipyrindyl monomer **108** at ~ 25 °C.¹⁷⁰ The

effect of temperature on the reaction and the continuous changes in the X-ray diffraction diagrams of 108 demonstrated that the polymerization proceeded by a diffusionless crystal-lattice-controlled mechanism.¹⁷⁰

3. *p*-Di-1,3-butadienylbenzenes

The tetraene diester 119 had a high reactivity compared to related compounds on photopolymerization to 120 in the crystal state.¹⁷⁰


The tetraene diamide 607 had a low photoreactivity compared to related compounds on photopolymerization in the crystal state (eq 147).¹⁷⁰ The

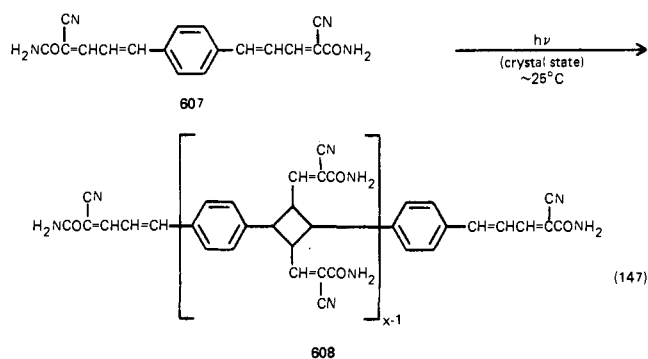

polymer 608 had a structure analogous to that of 120.¹⁷⁰

E. *p*-Bis(polysubstituted vinyl)benzenes


In contrast to the dimethyl ester 121, the corresponding crystalline diacid 609 in KBr was extremely

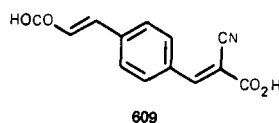

stable to light,¹⁷⁴ presumably because its crystal structure did not allow cyclobutane formation or other reactions.

1. Cyano-*p*-phenylenediacylate Esters

Irradiation of crystalline dimethyl ester 121 with a Xe lamp through quartz gave a polymer or oligomer in high conversion (eq 148).¹⁷⁴ The structure of the

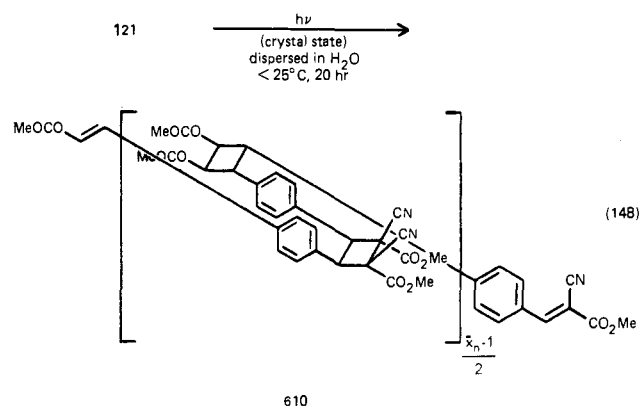

polymer may be 610, at least in part. The two types of cyclobutane rings of 610 were formed at approximately the same rate.¹⁷⁴

The molecular weight of the polymer 610 formed from crystalline monomer 121 in KBr was determined


as a function of time.¹⁷⁴ The DP increased rapidly in the first few hours; loss of monomer was detected after irradiation for 1 min.¹⁷⁴ The DP increased more slowly after the first few hours, and after 20 h, \bar{M}_n had reached 1200 ($\bar{x}_n = 4.4$).¹⁷⁴

Excimer emission was observed from monomer 121 in both the crystal state and in CHCl_3 solution.¹⁷³ In the crystal state the molecules are aligned in the overlapping sandwich form that is often implicated for excimers. The same is probably true in solution. However, the involvement of the excimer as an intermediate in the photocycloaddition process was not established.



Irradiating crystalline monomer 121, as a film, through a negative, in the 300-nm range formed an image.¹⁷⁴ The polymerization of 121 was also sensitized, thus allowing the use of longer wavelength light.¹⁷⁴ Irradiating equimolar mixed crystals of 121 and 1,2-benzanthraquinone (611) suspended in water at ≥ 430 nm for 200 h gave oligomer, presumably 610, $\bar{M}_n = 580$, $\bar{x}_n = 2.1$.¹⁷⁴ After 50 h, $\sim 82\%$ of 121 was converted to oligomer.¹⁷⁴ *p*-Nitroaniline and 2-nitrofluorene had weaker sensitizing effects; 121 conversions of $\sim 49\%$ and $\sim 44\%$, respectively, in 60 h were observed under comparable conditions.¹⁷⁴ On a synthetic scale the sensitized reactions were much slower than the unsensitized reaction.¹⁷⁴ Image formation occurred on irradiating (≥ 430 nm, 5–60 min) mixtures of monomer 121 and sensitizer 611 in a poly(methyl methacrylate) film.¹⁷⁴ Monomer 121 was more sensitive and produced a clearer image than did the *m*-phenylene diester 58.¹⁷⁴

The details of the crystal structure of the (*S*)-*sec*-butyl ethyl diester 134 (α form) have been published,¹⁷⁵ with the same conclusions noted previously. Irradiation times for photochemical polymerization, trimerization, and dimerization of 133 and 134 (Table VI) were 4–6 weeks (> 300 nm, ≤ 5 °C).^{106,107}



Irradiating the α crystal form of the (*R*)-*sec*-butyl *n*-propyl diester 613 (90% optically pure) gave cycloadducts 615–617 in which the cyclobutane configuration was (*RRRR*) (eq 149).^{176,178} See 147 in Table VIII for

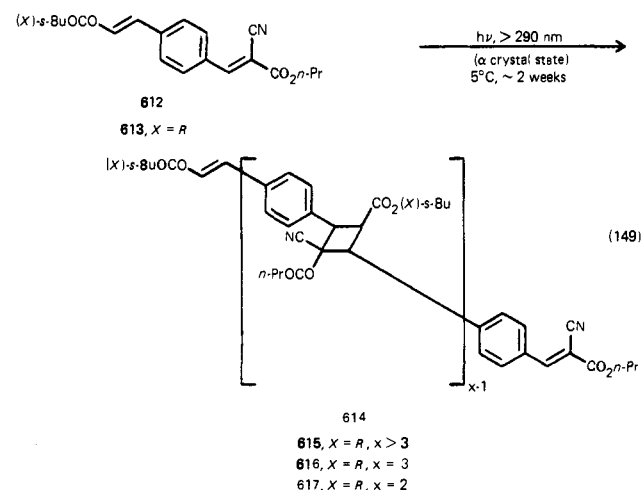

previous work on this compound. The α crystal form of the enantiomer 618 (also 90% optically pure) under the same conditions gave the enantiomeric products 620–622 [(*SSSS*) cyclobutane configuration] (eq 150).¹⁷⁸

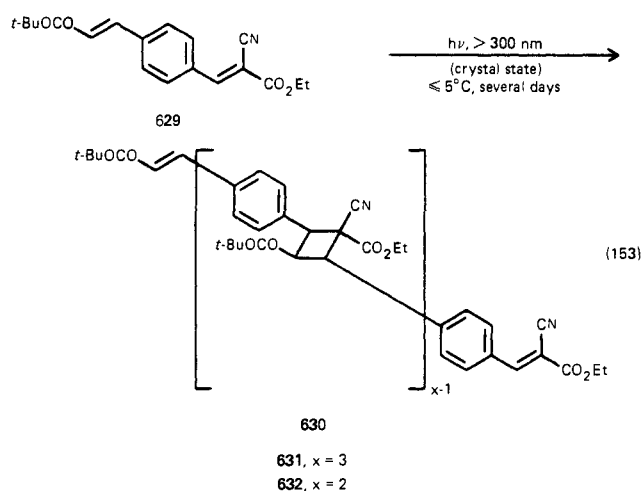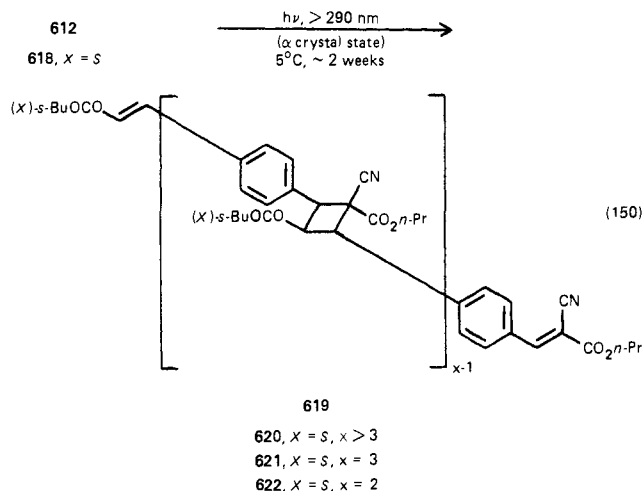

The cyclobutane configurations were reversed in the products that resulted from irradiating the β crystal forms of 613 and 618 (eq 151 and 152).¹⁷⁸ Nearly

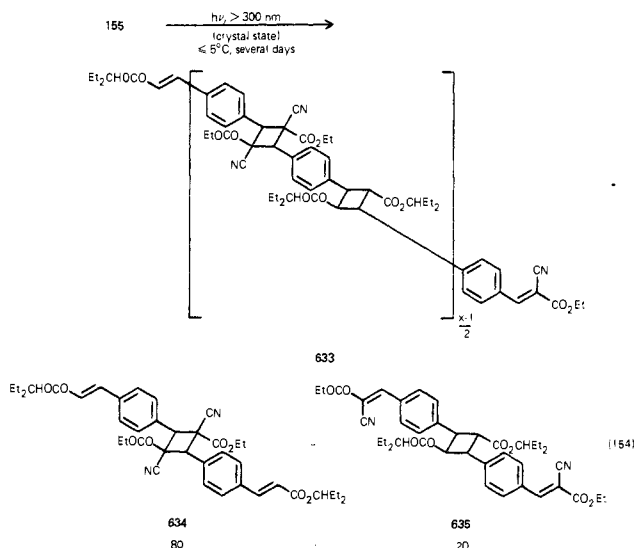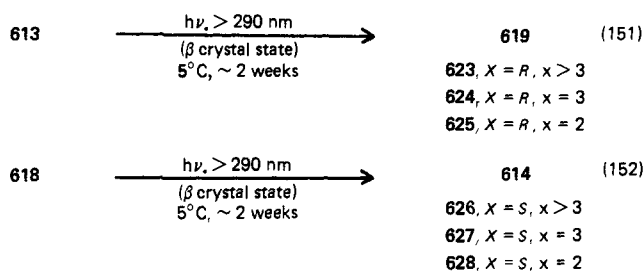

quantitative optical yields were obtained in the dimers 617, 622, 625, and 628.¹⁷⁸ The optical yields of the higher molecular weight products were not reported. The crystal structure of the β form of (*R*)-ester 613 was consistent with that expected to give the products 623–625.¹⁷⁸

More details were reported on the photocycloaddition ($>300 \text{ nm}, \leq 5^\circ \text{C}, \text{several days}$) of the 3-pentyl methyl diester 151 (Table VIII) to give 152–154.^{176,179} The structure of the dimer 154 agreed with that predicted from the crystal structure of the monomer 151 determined by X-ray analysis.¹⁷⁹ In the absence of any additives, specially grown crystals of the symmetric monomer 151 gave asymmetric cycloadducts. The enantiomeric yields depended on the perfection of the crystals and ranged from 0 to $\sim 100\%$ for the dimers 154.¹⁷⁹ The high enantiomeric yields were interpreted in terms of auto seeding, i.e., the asymmetric influence exercised on crystallization by the first chiral seed, which drives all of the supersaturated solution to crystallize in the same chirality.¹⁷⁹

Irradiating metastable crystals of the *tert*-butyl ethyl ester 629 that had been crystallized rapidly from the melt gave oligomer 630, trimer 631, and dimer 632 (eq 153).^{176,179} Slow crystallization of 629 from the melt or from solution gave a different crystal form, which, on irradiation under the same conditions as in eq 153, gave a dimer with structure 140 ($R_\alpha = R_\beta = t\text{-Bu}, R_\alpha' = R_\beta' = \text{Et}$).¹⁷⁹

In contrast to results reported earlier (Table VIII),^{95,96} irradiating the 3-pentyl ethyl diester 155 in the crystal state gave the centrosymmetric dimers 634 and 635 and corresponding higher oligomers 633 (eq 154).^{176,179}

These products resulted from irradiating the stable centrosymmetric polymorph formed by slow crystallization.¹⁷⁷ The optically active products 156–158 were derived from a chiral metastable polymorph, which was obtained on fast crystallization.¹⁷⁷

Additional details on the crystal-state photo-oligomerization ($>300 \text{ nm}, \leq 5^\circ \text{C}, \text{several days}$) of the 1:1 mixture of the isopropyl ethyl 144 and 3-pentyl ethyl 155 diesters (Table VIII) were reported.^{176,179} Irradiating the solid solution formed from 40:60 to 60:40 mixtures of 144 and 155 gave a nearly random distribution of the dimers 146 and 158 and the two heterocycloadducts 161.¹⁷⁹ The structure of the mixed crystal was isomorphous to that of the *sec*-butyl ethyl diesters 133 and 134 and was different from that of 144 or 155 alone.¹⁷⁹ Specially melt grown crystals of a 1:1 mixture of 144 and 145 gave the above products, the homooligomers 145, 156, and the heterooligomer 159, all of which were slightly enriched enantiomerically.¹⁷⁹ The low enantiomeric excesses ($\leq 7\%$), of random chirality, were probably caused by micro- and macrotwinning involving enantiomeric domains and to technical difficulties associated with growth of such crystals from melts containing two components.¹⁷⁹

Additional experiments were reported on the asymmetric induction of crystallization by chiral additives, and the subsequent oligomerization of the monomers in these crystals by photocycloaddition ($>300 \text{ nm}, 5^\circ \text{C}, \sim 2 \text{ weeks}$).¹⁷⁷ The monomers 133 and 134 (1:1 mix-

ture), 144 and 155 (1:1 mixture), 147, 151, 155, and 162 in the presence of 3–15% dimer (*R*)-132 or its enantiomer gave the same optically active oligomers, trimers, and dimers reported previously (Tables VI and VIII).^{176,177} In all instances the configuration of the product dimers present in excess was opposite to that of additive (*R*)-132 or its enantiomer.¹⁷⁷ Similar results were obtained on adding 15% trimer (*R*)-131 or 8% oligomer (*R*)-130 or their enantiomers.¹⁷⁷

For the monomers 151 and 162, a measurable asymmetric induction occurred when as little as ~0.05% (*R*)-132 was added.¹⁷⁷ The minimum amount of (*R*)-132 required to give maximum induction was ~1%.¹⁷⁷ Similar results were obtained on adding resolved dimer 158. Asymmetric induction in the crystallization was also achieved by adding 10% *sec*-butyl *n*-propyl diester dimers 617 or 628.¹⁷⁷

Several other derivatives of 142 and mixtures of these derivatives gave cyclobutyl dimers and 1:1 cross adducts when irradiated in the crystal state (>300 nm, ≤5 °C, several days).^{177,179} Although not reported, the higher oligomers analogous to these dimers and cross adducts also may have been formed. *n*-Propyl ethyl diester 142 ($R^1 = R^3 = \text{Et}$, $R^2 = \text{H}$) (636) gave a dimer analogous to 128.¹⁷⁷ In the presence of ~10% of this latter dimer, 636 gave dimer 143 ($R^1 = R^3 = \text{Et}$, $R^2 = \text{H}$, $x = 2$).¹⁷⁷ The full paper reported that the isopropyl ethyl diester 144 alone gave dimers analogous to 127 and 128¹⁷⁹ (see Table VIII⁹⁶). A 70:30 mixture of (*S*)-*sec*-butyl ethyl diester 134 and 144 gave homodimers 146 and (*S*)-132 and mixed 1:1 cross adducts analogous to 143 ($x = 2$).¹⁷⁹ A 75:25 mixture of 134 and 3-pentyl methyl diester 151 gave homodimers (*S*)-132 and 154 and mixed 1:1 cross adducts analogous to 143 ($x = 2$).¹⁷⁹ A (60 or 70):(30 or 40) mixture of 3-pentyl ethyl diester 155 and 134 gave homodimers (*S*)-132 and 158 in addition to mixed 1:1 cross adducts analogous to 143 ($x = 2$).¹⁷⁹

2. Dicyano-*p*-phenylenediacrylate Esters

The dicyano diesters had the following relative reactivities toward crystal-state photocycloaddition polymerization: very high, 166; high, 171; low, 173, 175, 177, 179.¹⁷⁰ The dimethyl ester polymer 172 contained a small number of cyclobutane rings, presumably from the *cis* form of the olefin 171.¹⁷⁰ Otherwise the polymer was stereoregular.¹⁷⁰ The effect of temperature on the reaction and the continuous changes in the X-ray diffraction diagrams of monomer 166 demonstrated that the polymerization proceeded by a diffusionless crystal-lattice-controlled mechanism.¹⁷⁰

3. Bis(α -cyano- β -arylviny)benzenes

Compared to the reactivities of similar compounds, that of monomer 181 toward crystal-state photopolymerization was high.¹⁷⁰

G. 2,5-Distyrylpyrazine

1. Crystal State

Relative to similar monomers, pyrazine 192 was very reactive toward crystal-state photocycloaddition polymerization.¹⁷⁰ Explanations offered for its reactivity and that of dipyriddy monomer 108 crystals were based on stabilization energies of the transient complex.¹⁷⁰ These energies depended on both the electronic struc-

tures of the monomers and the intermolecular arrangements in the monomer crystals.¹⁷⁰ A quantitative correlation between photoreactivities and intermolecular plane-to-plane distances in the crystals was proposed.¹⁷⁰

Excimer fluorescence has been reported for 192 crystals.¹⁷⁰

The effect of temperature on the reaction and the continuous changes in the X-ray diagrams of 192 demonstrated that the polymerization proceeded by a diffusionless crystal-lattice-controlled mechanism.¹⁷⁰

V. Cycloadditions Involving Carbon 4 + 4 Addition

B. Bisanthracenes

2. 9-Substituted

Several bis(anthrylimines) and bis(anthrylbenzimidazoles) 484 polymerized when irradiated (eq 120) (Table XXXIII).¹⁸⁰ The polyimines 638, 640, and 642 were converted to the polybenzimidazoles 644, 646, and 648, respectively, by air oxidation.¹⁸⁰ The presumed head-to-tail regiochemistry of the 4 + 4 photocycloaddition was not rigorously established.

Polymers of higher molecular weight were formed from the bis(imines) than from the bis(benzimidazoles) because the former remained in solution whereas the latter precipitated from solution when the DP reached ~3–5.¹⁸⁰

Acknowledgments. I thank Marcia L. Dilling for considerable help in editing this review.

IX. References

- (1) Organic Photochemistry. XVII. For part XVI see: Dilling, W. L.; Goersch, H. K. In "Dynamics, Exposure and Hazard Assessment of Toxic Chemicals", Haque, R., Ed.; Ann Arbor Science Publishers: Ann Arbor, MI, 1980; p 111.
- (2) Huisgen, R. *Angew. Chem.* 1968, 80, 329; *Angew. Chem., Int. Ed. Engl.* 1968, 7, 321.
- (3) Dilling, W. L. *Chem. Rev.* 1966, 66, 373.
- (4) Dilling, W. L. *Chem. Rev.* 1969, 69, 845; 1970, 70, 738.
- (5) Dilling, W. L. *Photochem. Photobiol.* 1977, 25, 605; 1977, 26, 557.
- (6) Hasegawa, M. *Kobunshi* 1968, 17, 722; *Chem. Abstr.* 1969, 70, 4622.
- (7) De Schryver, F. C.; Smets, G. *Meded. K. Vlaam. Acad. Wet., Lett. Schone Kunsten Belg., Kl. Wet.* 1969, 31, No. 7; *Chem. Abstr.* 1971, 74, 64436.
- (8) Williams, J. L. R. *Fortschr. Chem. Forsch.* 1969, 13, 227.
- (9) Phillips, D. *Photochemistry* 1971, 2, 768; 1973, 4, 889; 1974, 5, 691, 704; 1975, 6, 665; 1976, 7, 512; 1977, 8, 544.
- (10) Smets, G. *Kinet. Mech. Polyreactions, IUPAC Int. Symp. Macromol. Chem., Plenary Main Lect.* 1969 (Pub. 1971), 65; *Chem. Abstr.* 1972, 77, 34947.
- (11) Barzynski, H.; Penzien, K.; Volkert, O. *Chem.-Ztg.* 1972, 96, 545.
- (12) De Schryver, F. C.; Put, J. *Ind. Chim. Belg.* 1972, 37, 1107.
- (13) Higgins, J. G.; McCombs, D. A. *Chem. Tech.* 1972, 2, 176.
- (14) Hasegawa, M.; Suzuki, Y.; Nakanishi, H.; Nakanishi, F. *Progr. Polym. Sci. Jpn.* 1973, 5, 143.
- (15) Wegner, G. *Adv. Chem. Ser.* 1973, No. 129, 255.
- (16) De Schryver, F. C.; Smets, G. In "Reactivity, Mechanism and Structure in Polymer Chemistry", Jenkins, A. D., Ledwith, A., Eds.; Wiley: New York, 1974; p 446.
- (17) Mellor, J. M.; Phillips, D.; Salisbury, K. *Chem. Britain* 1974, 10, 160.
- (18) Wegner, G. *Chimia* 1974, 28, 475.
- (19) Green, B. S.; Lahav, M.; Schmidt, G. M. J. *Mol. Cryst. Liq. Cryst.* 1975, 29, 187.
- (20) Kaupp, G. In "Methoden Der Organischen Chemie" (Houben-Weyl), Müller, E., Ed.; Georg Thieme Verlag: Stuttgart, Germany, 1975; Vol. IV/5a, p 278.
- (21) Leppin, E. In ref 20, p 484.
- (22) Nishii, M.; Hayashi, K. *Ann. Rev. Materials Sci.* 1975, 5, 135.

- (23) Ranby, B.; Rabek, J. F. "Photodegradation, Photo-oxidation and Photostabilization of Polymers—Principles and Applications"; Wiley: London, 1975; p 239.
- (24) Wegner, G. In ref 20, Vol. IV/5b, p 1499.
- (25) De Schryver, F. C.; Boens, N. *J. Oil Colour Chem. Assoc.* 1976, 59, 171.
- (26) Goldanskii, V. I. *Annu. Rev. Phys. Chem.* 1976, 27, 85.
- (27) Julian, D. R. In "Photochemistry of Heterocyclic Compounds", Buchardt, O., Ed.; Wiley: New York, 1976; p 574.
- (28) Stevens, M. P. *ACS Symp. Ser.* 1976, No. 25, 64.
- (29) De Schryver, F. C.; Boens, N.; Put, J. *Adv. Photochem.* 1977, 10, 359.
- (30) Elias, H.-G. "Macromolecules · 2"; Stafford, J. W., translator; Plenum Press: New York, 1977; p 751.
- (31) Nakanishi, F. *Kobunshi* 1977, 26, 188; *Chem. Abstr.* 1977, 86, 121803.
- (32) Thomas, J. M.; Morsi, S. E.; Desvergne, J. P. *Adv. Phys. Org. Chem.* 1977, 15, 63.
- (33) Wegner, G. *Pure Appl. Chem.* 1977, 49, 443; In "Photochemical Processes in Polymer Chemistry—2", Smets, G., Ed.; Pergamon Press: Oxford, England, 1977; p 443.
- (34) Allen, N. S.; McKellar, J. F. *Photochemistry* 1978, 559.
- (35) Green, B. S.; Lahav, M.; Rabinovich, D. *Acc. Chem. Res.* 1979, 12, 191.
- (36) Jones, W.; Thomas, J. M. *Prog. Solid State Chem.* 1979, 12, 101.
- (37) Leonard, N. J. *Acc. Chem. Res.* 1979, 12, 423.
- (38) Thomas, J. M. *Pure Appl. Chem.* 1979, 51, 1065.
- (39) Delzenne, G. A. *J. Chim. Phys. Phys.—Chim. Biol.* 1980, 77, 483.
- (40) Hasegawa, M. *Kobunshi no Kino Sekkei to Sono Oyo, Shinpojumu* 1980, 1; *Chem. Abstr.* 1980, 93, 8544.
- (41) Hasegawa, M. *Kobunshi* 1981, 30, 781; *Chem. Abstr.* 1981, 95, 187695.
- (42) Oster, G.; Yang, N.-L. *Chem. Rev.* 1968, 68, 125.
- (43) Carless, H. A. J.; Haywood, D. J. *Chem. Commun.* 1980, 657.
- (44) Kosar, J. "Light-Sensitive Systems: Chemistry and Applications of Nonsilver Halide Photographic Processes"; Wiley: New York, 1965; p 140.
- (45) Delzenne, G. A. In "Encyclopedia of Polymer Science and Technology", Mark, H. F., Bikales, N. M., Eds.; Interscience: New York, 1976; Suppl. Vol. 1, p 401.
- (46) Delzenne, G. A. *Adv. Photochem.* 1979, 11, 1.
- (47) Reiser, A.; Egerton, P. L. *Photogr. Sci. Eng.* 1979, 23, 144.
- (48) Miura, M.; Kitami, T.; Nagakubo, K. *J. Polym. Sci., Part B* 1968, 6, 463.
- (49) Nakanishi, H.; Hasegawa, M.; Sasada, Y. *J. Polym. Sci., Part A-2* 1972, 10, 1537.
- (50) Danusso, F.; Ferruti, P.; Moro, A.; Tieghi, G.; Zocchi, M. *Polymer* 1977, 18, 161.
- (51) Nakanishi, H.; Jones, W.; Thomas, J. M.; Hasegawa, M.; Rees, W. L. *Proc. R. Soc. London, A* 1980, 369, 307.
- (52) Teijin Ltd. *Jpn. Kokai Tokkyo Koho* 81 55346, 1981; *Chem. Abstr.* 1981, 95, 186893.
- (53) Takahashi, H.; Takahashi, H.; Sakuragi, M.; Hasegawa, M. *J. Polym. Sci., Part B* 1971, 9, 685.
- (54) Bernstein, J.; Green, B. S.; Rejtö, M. *J. Am. Chem. Soc.* 1980, 102, 323.
- (55) Takahashi, H.; Sakuragi, M.; Hasegawa, M.; Takahashi, H. *J. Polym. Sci., Part A-1* 1972, 10, 1399.
- (56) Suzuki, F.; Suzuki, Y.; Nakanishi, H.; Hasegawa, M. *J. Polym. Sci., Part A-1* 1969, 7, 2319.
- (57) Hasegawa, M. *Chem. High Polym.* 1970, 27, 337.
- (58) Mizuno, T.; Hattori, S.; Tawata, M. *J. Opt. Soc. Am.* 1977, 67, 1651.
- (59) Tawata, M.; Yoneda, K.; Mizuno, T.; Hattori, S. *Meijo Daigaku Rikogakubu Kenkyu Hokoku* 1979, 19, 36; *Chem. Abstr.* 1980, 92, 85906.
- (60) Nakanishi, F.; Nakanishi, H.; Hasegawa, M.; Yamada, Y. *J. Polym. Sci., Polym. Chem. Ed.* 1975, 13, 2499.
- (61) Nakanishi, H.; Hasegawa, M.; Kirihara, H. *J. Chem. Soc. Jpn.* 1977, 1046; *Chem. Abstr.* 1977, 87, 118127.
- (62) Nakanishi, H.; Sasada, Y. *Bull. Chem. Soc. Jpn.* 1977, 50, 3182.
- (63) Hasegawa, M.; Suzuki, F.; Nakanishi, H.; Suzuki, Y. *J. Polym. Sci., Part B* 1968, 6, 293.
- (64) Ueno, K.; Nakanishi, H.; Hasegawa, M.; Sasada, Y. *Acta Crystallogr., Sect. B* 1978, B34, 2034.
- (65) Nakanishi, H.; Ueno, K.; Sasada, Y. *Acta Crystallogr., Sect. B* 1978, B34, 2209.
- (66) Nakanishi, H.; Ueno, K.; Sasada, Y. *Acta Crystallogr., Sect. B* 1978, B34, 2036.
- (67) Hasegawa, M.; Yurugi, T.; Namiki, S.; Shiobara, T.; Nakanishi, H.; Nakanishi, F. *J. Polym. Sci., Polym. Chem. Ed.* 1981, 19, 1291.
- (68) Tamaki, T.; Suzuki, Y.; Hasegawa, M. *Bull. Chem. Soc. Jpn.* 1972, 45, 1988.
- (69) Gerasimov, G. N.; Mikova, O. B.; Kotin, E. B.; Nekhoroshev, N. S.; Abkin, A. D. *Dokl. Akad. Nauk SSSR* 1974, 216, 1051; *Bull. Acad. Sci. USSR* 1974, 216, 410.
- (70) Mikova, O. B.; Gerasimov, G. N.; Abkin, A. D. *Vysokomol. Soedin., Ser. B* 1973, 15, 646.
- (71) Nakanishi, H.; Nakanishi, F.; Suzuki, Y.; Hasegawa, M. *J. Polym. Sci., Polym. Chem. Ed.* 1973, 11, 2501.
- (72) Nakanishi, F.; Hasegawa, M.; Tsai, T. *Polymer* 1975, 16, 218.
- (73) Hasegawa, M.; *Jpn. Chem. Q.* 1969, 5, 45.
- (74) Gerasimov, G. N.; Mikova, O. B.; Kotin, E. B.; Abkin, A. D. *Vsb., XI Mendeleevsk, S'ezd Obshch. Prikl. Khimii. Ref. Dokl. Soobshch.* 1974, 2, 151; *Chem. Abstr.* 1976, 84, 180742.
- (75) Nakanishi, H.; Ueno, K.; Sasada, Y. *J. Polym. Sci., Polym. Phys. Ed.* 1978, 16, 767.
- (76) Nakanishi, H.; Hasegawa, M.; Sasada, Y. *J. Polym. Sci., Polym. Phys. Ed.* 1977, 15, 173.
- (77) Nakanishi, F.; Nakanishi, H.; Hasegawa, M. *J. Chem. Soc. Jpn.* 1976, 1575; *Chem. Abstr.* 1977, 86, 71341.
- (78) Nakanishi, F.; Hasegawa, M. *J. Polym. Sci., Part A-1* 1970, 8, 2151.
- (79) Suzuki, Y.; Tamaki, T.; Hasegawa, M. *Bull. Chem. Soc. Jpn.* 1974, 47, 210.
- (80) Baughman, R. H. *J. Appl. Phys.* 1971, 42, 4579.
- (81) Nakanishi, H.; Ueno, K.; Hasegawa, M.; Sasada, Y. *Chem. Lett.* 1972, 301.
- (82) Iguchi, M.; Nakanishi, H.; Hasegawa, M. *J. Polym. Sci., Part A-1* 1968, 6, 1055.
- (83) Hasegawa, M.; Suzuki, Y.; Suzuki, F.; Nakanishi, H. *J. Polym. Sci., Part A-1* 1969, 7, 743.
- (84) Nakanishi, H.; Suzuki, Y.; Suzuki, F.; Hasegawa, M. *J. Polym. Sci., Part A-1* 1969, 7, 753.
- (85) Nakanishi, F.; Nakanishi, H. *Jpn. Kokai Tokkyo Koho* 78 149290, 1978; *Chem. Abstr.* 1979, 90, 204840; *Japan. Patent* 79 44314, 1979.
- (86) Nakanishi, H.; Sasada, Y. *Acta Crystallogr., Sect. B* 1978, B34, 332.
- (87) Addadi, L.; Cohen, M. D.; Lahav, M. *Mol. Cryst. Liq. Cryst.* 1976, 32, 137.
- (88) Addadi, L.; Gati, E.; Lahav, M.; Leiserowitz, L. *Isr. J. Chem.* 1977, 15, 116.
- (89) Addadi, L.; Lahav, M. *J. Am. Chem. Soc.* 1978, 100, 2838.
- (90) Addadi, L.; Cohen, M. D.; Lahav, M. *Charged React. Polym.* 1979, 5, 183.
- (91) Addadi, L.; Lahav, M. *Pure Appl. Chem.* 1979, 51, 1269.
- (92) Addadi, L.; Lahav, M. *Stud. Phys. Theor. Chem.* 1979, 7, 179.
- (93) Addadi, L.; Cohen, M. D.; Lahav, M. *Chem. Commun.* 1975, 471.
- (94) Addadi, L.; Lahav, M. *J. Am. Chem. Soc.* 1979, 101, 2152.
- (95) van Mil, J.; Gati, E.; Addadi, L.; Lahav, M. *J. Am. Chem. Soc.* 1981, 103, 1248.
- (96) Addadi, L.; Lahav, M. *Abstr. Pap.—Am. Chem. Soc.* 1978, 176th, POLY 12.
- (97) Suzuki, Y.; Hasegawa, M.; Kita, N. *J. Polym. Sci., Part A-1* 1972, 10, 2473.
- (98) Nakanishi, H.; Ueno, K.; Sasada, Y. *Acta Crystallogr., Sect. B* 1976, B32, 1616.
- (99) Nakanishi, H.; Ueno, K.; Hasegawa, M.; Sasada, Y.; Yurugi, T. *Prepr. Div. Org. Coat. Plast. Chem., Am. Chem. Soc.* 1975, 35, 75.
- (100) Holm, M. J.; Zienty, F. B. *J. Polym. Sci., Part A-1* 1972, 10, 1311.
- (101) Holm, M. J.; Zienty, F. B. *U.S. Patent* 3312668, 1967; *Chem. Abstr.* 1967, 67, 12151.
- (102) Hasegawa, M.; Suzuki, Y. *J. Polym. Sci., Part B* 1967, 5, 813.
- (103) Fujishige, S.; Hasegawa, M. *J. Polym. Sci., Part A-1* 1969, 7, 2037.
- (104) Hasegawa, M.; Suzuki, Y.; Tamaki, T. *Bull. Chem. Soc. Jpn.* 1970, 43, 3020.
- (105) Kanetsuna, H.; Hasegawa, M.; Mitsunishi, S.; Kurita, T.; Sasaki, K.; Maeda, K.; Obata, H.; Hatakeyama, T. *J. Polym. Sci., Part A-2* 1970, 8, 1027.
- (106) Nakanishi, H.; Nakano, N.; Hasegawa, M. *J. Polym. Sci., Part B* 1970, 8, 755.
- (107) Sasada, Y.; Shimanouchi, H.; Nakanishi, H.; Hasegawa, M. *Bull. Chem. Soc. Jpn.* 1971, 44, 1262.
- (108) Ito, T.; Higuchi, J. *Prepr. Annu. Meet. Chem. Soc. Jpn.* 28th 1973, 377.
- (109) Hasegawa, M.; Nakanishi, H.; Yurugi, T.; Ishida, K. *J. Polym. Sci., Part B* 1974, 12, 57.
- (110) Hasegawa, M.; Nakanishi, H.; Yurugi, T. *Chem. Lett.* 1975, 497.
- (111) Nakanishi, H.; Ueno, K.; Hasegawa, M.; Sasada, Y.; Yurugi, T. *Abstr. Pap.—Am. Chem. Soc.* 1975, 169th, ORPL 27.
- (112) Nakanishi, H.; Hasegawa, M.; Yurugi, T. *J. Polym. Sci., Polym. Chem. Ed.* 1976, 14, 2079.
- (113) Nakanishi, H.; Ueno, K.; Sasada, Y. *Acta Crystallogr., Sect. B* 1976, B32, 3352.
- (114) Meyer, W.; Lieser, G.; Wegner, G. *Makromol. Chem.* 1977, 178, 631.
- (115) Hasegawa, M.; Nakanishi, H.; Yurugi, T. *J. Polym. Sci., Polym. Chem. Ed.* 1978, 16, 2113.

- (116) Jones, W. *J. Chem. Res. Synop.* 1978, 142.
(117) Meyer, W.; Lieser, G.; Wegner, G. *J. Polym. Sci., Polym. Phys. Ed.* 1978, 16, 1365.
(118) Hasegawa, M. "Abstracts of Papers", ACS/CSJ Chemical Congress, Honolulu, HI, Apr 1979; American Chemical Society: Washington, D.C., 1979; POLY 153.
(119) Hasegawa, M. *Prepr. U.S.A.—Japan Joint Symp., Hawaii* 1979, April.
(120) Nakanishi, H.; Hasegawa, M.; Sasada, Y. *J. Polym. Sci., Polym. Lett. Ed.* 1979, 17, 459.
(121) Nakanishi, H.; Jones, W.; Parkinson, G. M. *Acta Crystallogr., Sect. B* 1979, B35, 3103.
(122) Nakanishi, H.; Parkinson, G. M.; Jones, W.; Thomas, J. M.; Hasegawa, M. *Isr. J. Chem.* 1979, 18, 261.
(123) Bühler, H. G.; Aeschbach, R.; Phillipou, T.; Parnaud, J.-J.; Elias, H.-G. *Makromol. Chem.* 1972, 157, 13.
(124) Enkelmann, V.; Kapp, H.; Meyer, W. *Acta Crystallogr., Sect. B* 1978, B34, 2350.
(125) Kauffmann, H. F. *Makromol. Chem.* 1979, 180, 2649.
(126) Kauffmann, H. F. *Makromol. Chem.* 1979, 180, 2665.
(127) Kauffmann, H. F. *Makromol. Chem.* 1979, 180, 2681.
(128) De Schryver, F. C.; Bhardwaj, L.; Put, J. *Angew. Chem.* 1969, 81, 224; *Angew. Chem., Int. Ed. Engl.* 1969, 8, 213.
(129) Smets, G. J.; De Schrijver, F. C. German Offen. 1963731, 1970; *Chem. Abstr.* 1970, 73, 104343; Belgium Patent 743389, 1970; U.S. Patent 3622321, 1971; French Patent 2027005.
(130) Smets, G. *J. Prakt. Chem.* 1971, 313, 546.
(131) De Schryver, F. C. *Pure Appl. Chem.* 1973, 34, 213.
(132) Put, J.; De Schryver, F. C. *J. Am. Chem. Soc.* 1973, 95, 137.
(133) Boens, N.; De Schryver, F. C.; Smets, G. *J. Polym. Sci., Part A-1* 1975, 13, 201.
(134) De Schryver, F. C.; Boens, N.; Smets, G. *J. Polym. Sci., Part A-1* 1972, 10, 1687.
(135) De Schryver, F. C.; Boens, N.; Smets, G. *Macromol.* 1974, 7, 399.
(136) De Schryver, F. C.; Boens, N.; Smets, G. *J. Am. Chem. Soc.* 1974, 96, 6463.
(137) De Schryver, F. C.; Feast, W. J.; Smets, G. *J. Polym. Sci., Part A-1* 1970, 8, 1939.
(138) Leonard, N. J.; McCredie, R. S.; Logue, M. W.; Cundall, R. L. *J. Am. Chem. Soc.* 1973, 95, 2320.
(139) Frank, J. K.; Paul, I. C. *J. Am. Chem. Soc.* 1973, 95, 2324.
(140) Leenders, L. H.; Schouteden, E.; De Schryver, F. C. *J. Org. Chem.* 1973, 38, 957.
(141) De Schrijver, F. C.; Leenders, L. German Offen 2233184, 1973; *Chem. Abstr.* 1973, 78, 137003; U.S. Patent 3729405, 1973; Belgium Patent 785465; Britain Patent 1362222; France Patent 2145472.
(142) Pearlman, B. A. *J. Am. Chem. Soc.* 1979, 101, 6404.
(143) Stevens, M. P.; Musa, Y. *American Chemical Society, Div. Polym. Chem., Preprints* 1971, 12, No. 1, 615.
(144) Musa, Y.; Stevens, M. P. *J. Polym. Sci., Part A-1* 1972, 10, 319.
(145) Kardush, N.; Stevens, M. P. *J. Polym. Sci., Part A-1* 1972, 10, 1093.
(146) Zhubanov, B. A.; Akkulova, Z. G. *Vysokomol. Soedin., Ser. B* 1973, 15, 473.
(147) Stevens, M. P. *Prepr. Div. Org. Coat. Plast. Chem., Am. Chem. Soc.* 1975, 35, 69.
(148) Bryce-Smith, D.; Gilbert, A. *Chem. Commun.* 1966, 643.
(149) Bryce-Smith, D.; Gilbert, A.; Orger, B. H. *Chem. Commun.* 1966, 512.
(150) Bryce-Smith, D. *Pure Appl. Chem.* 1973, 34, 193.
(151) Gilbert, A.; Taylor, G. N. *Chem. Commun.* 1979, 229.
(152) Wegner, G. *Makromol. Chem.* 1972, 154, 35.
(153) Yuzhakova, O. A.; Isakov, I. V.; Rider, E. E.; Gerasimov, G. N.; Abkin, A. D. *Vysokomol. Soedin., Ser. B* 1977, 19, 431.
(154) De Schryver, F. C.; De Brackeleire, M.; Toppet, S.; Van Schoor, M. *Tetrahedron Lett.* 1973, 1253.
(155) De Schryver, F. C. *Makromol. Chem., Suppl.* 1979, 3, 85.
(156) Smets, G. *Pure Appl. Chem.* 1975, 42, 509.
(157) De Schryver, F. C.; Anand, L.; Smets, G.; Switten, J. *J. Polym. Sci., Part B* 1971, 9, 777.
(158) De Schrijver, F. C.; Delzenne, G. A. German Offen. 2212427, 1972; *Chem. Abstr.* 1973, 78, 16755; U.S. Patent 3807999, 1974; U.S. Patent 3892642, 1975; Belgium Patent 780294; British Patent 1358274; French Patent 2130443.
(159) Tazuke, S.; Banba, F. *J. Polym. Sci., Polym. Chem. Ed.* 1976, 14, 2463.
(160) De Schryver, F. C.; Boens, N.; Huybrechts, J.; Daemen, J.; De Brackeleire, M. *Pure Appl. Chem.* 1977, 49, 237.
(161) Tazuke, S.; Tanabe, T. *Macromol.* 1979, 12, 848.
(162) Tazuke, S.; Tanabe, T. *Macromol.* 1979, 12, 853.
(163) Tazuke, S.; Suzuki, Y. *J. Polym. Sci., Polym. Lett. Ed.* 1978, 16, 223.
(164) Suzuki, Y.; Tazuke, S. *Macromol.* 1980, 13, 25.
(165) Andrews, D. J.; Feast, W. J. *Commun. IUPAC Symp. Leuven*, 1972.
(166) Andrews, D. J.; Feast, W. J. *J. Polym. Sci., Polym. Chem. Ed.* 1976, 14, 319.
(167) Andrews, D. J.; Feast, W. J. *J. Polym. Sci., Polym. Chem. Ed.* 1976, 14, 331.
(168) Enkelmann, V. *Lect. Notes Phys.* 1980, 113, 1.
(169) Allen, N. S. *Photochemistry* 1981, 11, 566.
(170) Hasegawa, M. *Adv. Polym. Sci.* 1982, 42, 1.
(171) Nakanishi, F.; Nakanishi, H.; Kato, M.; Tawata, M.; Hattori, S. *J. Appl. Polym. Sci.* 1981, 26, 3505.
(172) Hasegawa, M.; Shiba, S. *J. Phys. Chem.* 1982, 86, 1490.
(173) Sakamoto, M.; Huy, S.; Nakanishi, H.; Nakanishi, F.; Yurugi, T.; Hasegawa, M. *Chem. Lett.* 1981, 99.
(174) Nakanishi, F.; Tanaka, T.; Miyagawa, F.; Nakanishi, H. *Nippon Kagaku Kaishi* 1981, 412.
(175) Berkovitch-Yellin, Z. *Acta Crystallogr., Sect. B* 1980, B36, 2440.
(176) Addadi, L.; van Mil, J.; Gati, E.; Lahav, M. *Origins Life* 1981, 11, 107.
(177) van Mil, J.; Addadi, L.; Gati, E.; Lahav, M. *J. Am. Chem. Soc.* 1982, 104, 3429.
(178) van Mil, J.; Addadi, L.; Lahav, M.; Leiserowitz, L. *J. Chem. Soc., Chem. Commun.* 1982, 584.
(179) Addadi, L.; van Mil, J.; Lahav, M. *J. Am. Chem. Soc.* 1982, 104, 3422.
(180) Niume, K.; Toyofuku, K.; Toda, F.; Uno, K.; Hasegawa, M.; Iwakura, Y. *J. Polym. Sci., Polym. Chem. Ed.* 1982, 20, 663.