

High Catalytic Activity of Platinum-ZSM-5 Zeolite below 500 K  
in Water Vapor for Reduction of Nitrogen Monoxide

Hiroshi HIRABAYASHI, Hidenori YAHIRO, Noritaka MIZUNO, and Masakazu IWAMOTO\*  
Catalysis Research Center, Hokkaido University, Sapporo 060

Platinum ion-exchanged ZSM-5 zeolite efficiently reduced nitrogen monoxide to nitrogen by ethene in an oxidizing atmosphere below 500 K and the catalytic activity was not affected by the presence of 8.6 vol% water vapor.

The selective reduction of nitrogen monoxide (NO) by hydrocarbons in an oxidizing atmosphere has been reported to be catalyzed over various catalysts.<sup>1-8)</sup> Although iron or copper ion-exchanged zeolite is active below 573 K,<sup>8)</sup> the catalytic activity is still low for the exhaust gases from diesel and lean-burn gasoline engines in a state of idling and is greatly decreased by the presence of water vapor.<sup>9)</sup> Here we wish to report a pronounced catalytic activity of platinum ion-exchanged ZSM-5 zeolite below 500 K for the selective reduction of NO by ethene even in the presence of water vapor.

Parent zeolites, ZSM-5 (silica/alumina = 23.3) and mordenite (18.9) were supplied by Tosoh Corporation and they were abbreviated as MFI and MOR, respectively. Platinum, copper, and iron ion-exchanged zeolites were prepared as described previously.<sup>1,9,10)</sup> The exchange levels of the metal ions were estimated on the assumption that the oxidation numbers of Pt, Fe, and Cu ions are +2. Hereafter the sample was abbreviated as Pt-MFI-97 (cation - zeolite structure - degree of exchange). The catalytic reduction of NO was carried out with a fixed bed flow reactor (inner diameter, 7.5 mm) in 1000 ppm of NO, 1000 ppm of C<sub>2</sub>H<sub>4</sub>, and 2% of O<sub>2</sub> system (balance: He) in the presence or in the absence of 8.6 vol% water vapor. Total flow rate was 150 cm<sup>3</sup>·min<sup>-1</sup>. The catalyst of 0.0625 g (particle size, 250 - 425 μm; volume, 0.125 cm<sup>3</sup>; GHSV = 72000 h<sup>-1</sup>) was used without any diluents. The catalytic activity for NO removal was evaluated by the conversion into N<sub>2</sub>.

The catalytic activity of Pt-MFI-97, Fe-MOR-71, or Cu-MFI-105 at 473 - 523 K was somewhat changed with reaction time and approximately steady formation of N<sub>2</sub> was attained after 15, 6, or 3 h on each catalyst. Figure 1 shows the temperature dependences of their catalytic activities in the absence of water vapor. The most active temperature of Pt-MFI-97 was 485 K and the conversions into N<sub>2</sub> and N<sub>2</sub>O were 18% and 36%, respectively, at 485 K and GHSV of

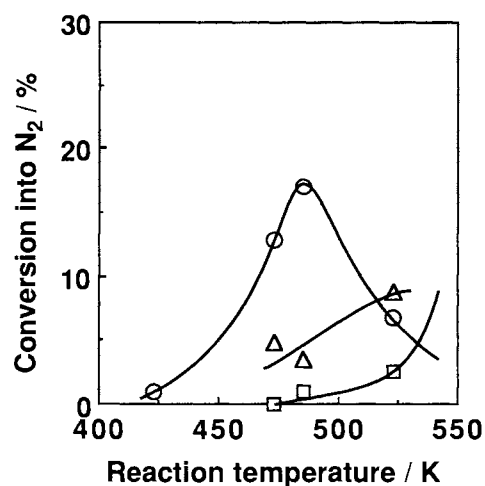


Fig. 1. Temperature dependences of the catalytic activities of (○) Pt-MFI-97, (Δ) Fe-MOR-71, and (□) Cu-MFI-105 in the absence of water vapor.

72000 h<sup>-1</sup>. Although Cu-MFI and Fe-MOR catalysts have been reported to be the most active in the range 473 - 573 K,<sup>1,9)</sup> the results of Fig. 1 show that Pt-MFI-97 is more active than these catalysts below 500 K. The conversions of C<sub>2</sub>H<sub>4</sub> at 485 K on Pt-MFI-97, Fe-MOR-71, and Cu-MFI-105 were 100, 4, and 1%, respectively. The higher ability for the oxidation of C<sub>2</sub>H<sub>4</sub> is probably the reason for the high ability to reduce NO into N<sub>2</sub>.

The effects of water vapor on the catalytic activities of Pt-MFI-97, Fe-MOR-71, and Cu-MFI-105 are depicted in Fig. 2. The catalytic activity of Pt-MFI-97 was not decreased by the introduction of 8.6% of water vapor. On the other hand, the conversions into N<sub>2</sub> on Fe-MOR-71 and Cu-MFI-105 were reduced nearly to 0% by the addition of water vapor though the activities were approximately restored by the interrupt of water addition.

It follows that Pt-MFI-97 has the bright prospect of effective reduction of NO into N<sub>2</sub> in the presence of oxygen and water vapor below 500 K.

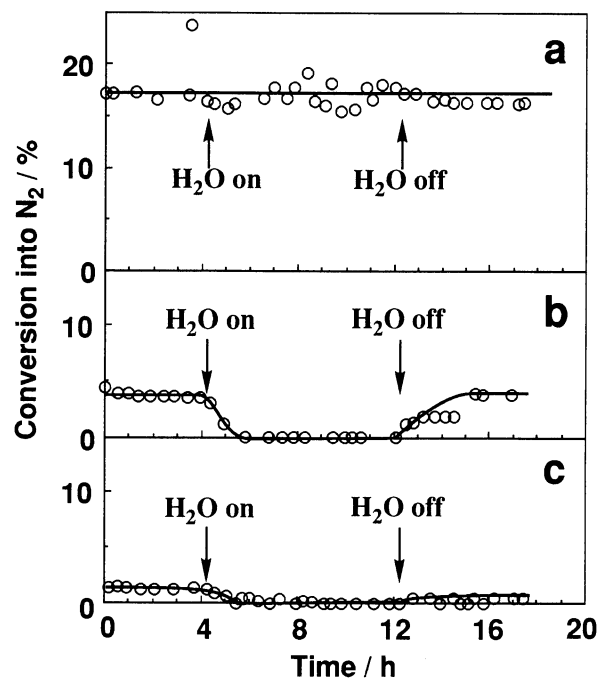


Fig. 2. Effect of water vapor (8.6 vol%) on the catalytic activities of (a) Pt-MFI-97, (b) Fe-MOR-71, and (c) Cu-MFI-105 for the selective reduction of NO. Reaction temp., 485 K.

#### References

- 1) M. Iwamoto, H. Yahiro, Y. Yu-u, S. Shundo, and N. Mizuno, *Shokubai*, **32**, 430 (1990); S. Sato, Y. Yu-u, H. Yahiro, N. Mizuno, and M. Iwamoto, *Appl. Catal.*, **70**, L1 (1991).
- 2) W. Held, A. König, T. Richter, and L. Puppe, SAE Paper 900496 (1990).
- 3) H. Hamada, Y. Kintaichi, M. Sasaki, T. Ito, and M. Tabata, *Appl. Catal.*, **64**, L1 (1990); Y. Kintaichi, H. Hamada, M. Tabata, M. Sasaki, and T. Ito, *Catal. Lett.*, **6**, 239 (1990).
- 4) M. Misono and K. Kondo, *Chem. Lett.*, **1991**, 1001.
- 5) E. Kikuchi, K. Yogo, S. Tanaka, and M. Abe, *Chem. Lett.*, **1991**, 1063; K. Yogo, S. Tanaka, M. Ihara, T. Hishiki, and E. Kikuchi, *ibid.*, **1992**, 1025.
- 6) Y. Torikai, H. Yahiro, N. Mizuno, and M. Iwamoto, *Catal. Lett.*, **9**, 91 (1991).
- 7) T. Inui, S. Kojo, M. Shibata, T. Yoshida, and S. Iwamoto, *Stud. Surf. Sci. Catal.*, **69**, 355 (1991).
- 8) S. Sato, H. Hirabayashi, H. Yahiro, N. Mizuno, and M. Iwamoto, *Catal. Lett.*, **12**, 193 (1992).
- 9) M. Iwamoto, N. Mizuno, and H. Yahiro, 10th Intern. Congr. Catal., Budapest, July 1992, Abstr., No. O88.
- 10) P. Gallezot, A. Alarcon-Diaz, J-A. Dalmon, A. J. Renouprez, and B. Imelik, *J. Catal.*, **39**, 334 (1975).

(Received August 10, 1992)