


Crystal Structures and Conducting Properties of PF₆ and AsF₆ Salts of a Novel Benzo[c]furan-Extended Donor: The Role of Inter-Column Interactions

Kazuko Takahashi,* Toshihiro Ise, Takehiko Mori,*[†] Hatsumi Mori,^{††} and Shoji Tanaka^{††}
 Department of Chemistry, Graduate School of Science, Tohoku University, Sendai 980-8578
[†]Faculty of Engineering, Tokyo Institute of Technology, O-okayama, Tokyo 152-0033
^{††}International Superconductivity Technology Center, Shinonome, Tokyo 135-0062

(Received July 28, 1998; CL-980574)


The PF₆ and AsF₆ salts of a new benzo[c]furan-extended donor have been prepared. It has been clarified that the inter-column interactions connecting the tetrameric donor columns play an important role in the conduction of these salts.

Although a large number of TTF based organic conductors have been investigated so far,¹ studies on conducting complexes based on extended-donors with a high electrical conductivity are not many² and detailed information on this regard is limited.³ In such a situation, we have recently synthesized fused heterocycle-extended donors, BEDT-BDTBS (1)⁴ and BEDT-BDTBT (2)⁵ as well as their cation radical salts, and have demonstrated that the donor to anion ratio varies remarkably from 2:3 to 3:2 by replacing only one hetero atom of the central ring of the donors from Se to S atom. In order to know further insights into the correlation between the donor structure and solid state properties of the conducting radical cation salts, we have now synthesized an oxygen analogue, BEDT-BDTBF (3) and its PF₆ and AsF₆ salts, and clarified their unusual crystal structures having one-dimensional band structure brought about by a unique inter-column interaction.



1 (X=Se): BEDT-BDTBS
 2 (X=S): BEDT-BDTBT
 3 (X=O): BEDT-BDTBF

The new donor BEDT-BDTBF (3)⁶ has been synthesized as shown in Scheme 1, starting from phthalic anhydride and 4,5-ethylenedithio-1,3-dithiole-2-thione.

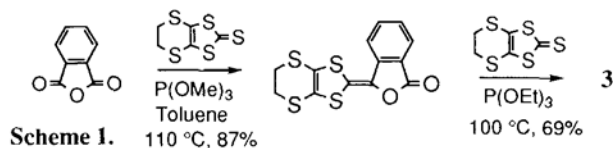

The oxidation of 3 occurred in reversible two-step one-electron process in cyclic voltammetry, exhibiting the half-wave oxidation potentials of $E_{1}^{OX} = +0.37$ and $E_{2}^{OX} = +0.53$ V vs. SCE in PhCN at 25 °C. The E_{1}^{OX} value is lower by 0.1 V than that of 2⁵ and is much the same as that of TTF. Actually 3 formed a 1:1 TCNQ complex showing a room temperature conductivity of 4.8 Scm⁻¹ on a compressed sample.

Single-crystalline PF₆ and AsF₆ salts of 3 were grown by the conventional electrochemical oxidation (0.1 μA) in chlorobenzene with 10% of EtOH at 20 °C. Both of the salts showed semiconducting temperature dependence with $E_a = 0.191$ (PF₆ salt) and 0.190 eV (AsF₆ salt) in the temperature range from

room temperature to 160 K. However, the PF₆ salt exhibited a fairly high room temperature conductivity of 7.3 Scm⁻¹ which is 26 times higher than that of the AsF₆ salt ($\sigma_{RT} = 0.28$ Scm⁻¹).

From X-ray crystal structure analysis,⁷ it has been revealed that the PF₆ and AsF₆ salts are iso-morphous with each other and have very unusual crystal structures. The unit cell contains eight donors and four anions, giving a donor to anion ratio of 2:1, from which the formal charge on BEDT-BDTBF is determined to be +0.5. The eight donors form a pair of tetramers. The tetramer is constructed with crystallographically independent four donor molecules A, B, C, and D with much the same bond lengths (Figure 1). Therefore, there is no charge separation among these donors.



Figure 1. Stacking structure of the donors A, B, C, and D.

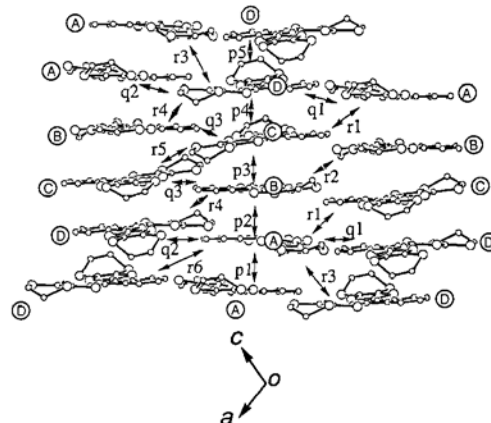


Figure 2. Donor arrangement in [BEDT-BDTBF]₂[PF₆].

There is a center of symmetry between the tetramers. Thus, the donors stack in a ABCDCBA manner along the $-a+c$ axis (Figure 2) with the interplanar distances of 3.38–3.65 Å. The PF₆ or AsF₆ anions are located in the space between the conducting $a-c$ plane. As shown in Figure 3, the overlapping modes between A and B, and C and D are quite favorable for giving a high intermolecular HOMO-HOMO bonding interaction because they are so called ring-over-bond types directing the central oxygen atom to the same side and all the S and O atoms have the same phase reversing in the phase of the remaining all carbon atoms of 3, similar to the HOMO of BEDT-TTF. In

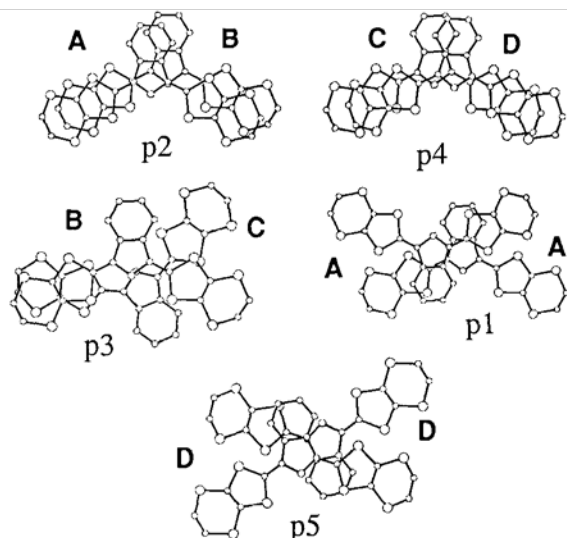


Figure 3. Overlapping modes of BEDT-BDTBF in $[\text{BEDT-BDTBF}]_2[\text{PF}_6]$ and $[\text{BEDT-BDTBF}]_2[\text{AsF}_6]$.

Table 1. Intermolecular overlap integrals^a ($S \times 10^3$) of $[\text{BEDT-BDTBF}]_2[\text{PF}_6]$ and $[\text{BEDT-BDTBF}]_2[\text{AsF}_6]$

Intra-column		Inter-column	
Anion: PF_6	AsF_6	Anion: PF_6	AsF_6
(Intra-tetramer)		q1 = -0.7	-0.2
p2 = -7.0	-6.7	q2 = -0.3	-0.3
p3 = -5.3	-5.6	q3 = 0.2	0.1
p4 = -8.0	-7.7	r1 = 0.5	0.0
		r2 = 1.6	0.3
		r3 = 1.3	0.2
(Inter-tetramer)		r4 = 0.4	0.0
p1 = -0.3	1.2	r5 = -0.3	0.1
p5 = -0.4	0.0	r6 = -0.2	-0.8

^aThe overlap modes p1–p5, q1–q3, and r1–r6 are indicated in Figure 2.

consequence, the calculated overlap integrals p2 and p4 are significantly large in the PF_6 and AsF_6 salts as shown in Table 1. The overlapping modes between B and C, A and A, and D and D are much more complicated. However, as compared with the values of p2 and p4, there is no significant difference in the value of p3, although B and C overlap only at ethylenedithio-1,3-dithiole rings. In contrast, the overlap integrals p1 (A–A) and p5 (D–D), overlapping only at the central part of the donor molecules, are less than 1/10th of p3. This is reasonable because the ethylenedithio-1,3-dithiole rings have large π -HOMO coefficients and the $2p\pi$ orbital of the central O atom is smaller than the $3p\pi$ orbitals of the S atoms. The inter-tetramer overlap integrals p1 and p5 are very small as compared with intra-tetramer ones, in consequence, the tetramerization is fairly strong in these two salts.

Quite interestingly, there exist two fairly large inter-column overlap integrals r2 and r3 along the a - and c -axis, respectively, in the PF_6 salt as shown in Table 1 and Figure 2. Of these, the r3 appears to play an important role in the conduction, because the interactions (r3) combine all the tetramers belonging to the all neighboring columns along the c -axis.⁸ The interactions (r2) are not important for the conduction, since r2 combines only one side of the neighboring column, resulting in a dimerization of the columns. Hence, the band structure of $[\text{BEDT-BDTBF}]_2[\text{PF}_6]$ is one-dimensional along the c -axis, although the donor stacks

along the $-a+c$ axis. On the other hand, the r3 as well as r2 are very small in the AsF_6 salt as shown in Table 1. Thus the high and low conductivities of PF_6 and AsF_6 salts, respectively, can be mainly ascribed to the difference in the overlap integral of r3. The lattice constants along the b - and a - axes of the AsF_6 salt are larger than those of the PF_6 salt. Therefore the large AsF_6 anion increases the unit cell volume, and then the key inter-column overlap integral r3 is significantly decreased probably by the slipping of the donor molecules along the a - or b -axis in the AsF_6 salt. In consequence, the salts with smaller tetrahedral anions, if we can grow them, are expected to show metallic properties. We have no data to answer the question why these two salts show almost identical activation energies. This may be attributed to the difference in the mobility of holes in a logical sense.

References and Notes

- J. M. Williams *et al.*, "Organic Superconductors," Prentice Hall, New Jersey, (1992); T. Ishiguro, K. Yamaji, "Organic Superconductors," Springer-Verlag Berlin, Heidelberg (1990); G. Saito, *Phosphorus, Sulfur, and Silicon*, **67**, 345 (1992).
- K. Takahashi and K. Tomitani, *J. Chem. Soc., Chem. Commun.*, **1995**, 821; K. Takahashi and T. Ise, *Chem. Lett.*, **1995**, 77; K. Takahashi, K. Tomitani, T. Ise, and T. Shirahata, *Chem. Lett.*, **1995**, 619; C. Wang, A. Ellern, J.Y. Becker, and J. Bernstein, *Adv. Mater.*, **1995**, 644; Y. Misaki, H. Fujiwara, T. Yamabe, T. Mori, H. Mori, and S. Tanaka, *J. Chem. Soc., Chem. Commun.*, **1996**, 363.
- Y. Yamashita and S. Tanaka, *Chem. Lett.*, **1993**, 73; K. Imaeda, Y. Yamashita, S. Tanaka, and H. Inokuchi, *Synth. Metals*, **73**, 107 (1995); Y. Misaki, N. Higuchi, H. Fujiwara, T. Yamabe, T. Mori, H. Mori, and S. Tanaka, *Angew. Chem., Int. Ed. Engl.*, **34**, 1222 (1995); M. R. Bryce, A. J. Moore, M. Hasan, G. J. Ashwell, A. T. Fraser, W. Clegg, M. B. Hursthouse, and A. I. Karaulov, *Angew. Chem., Int. Ed. Engl.*, **29**, 1450 (1990);
- K. Takahashi, T. Ise, T. Mori, H. Mori, and S. Tanaka, *Chem. Lett.*, **1996**, 1001.
- T. Ise, T. Mori, and K. Takahashi, *Chem. Lett.*, **1997**, 1013.
- Selected physical data of BEDT-BDTBF, **3**: orange needles, mp 249 °C (decomp); ¹H NMR (600 MHz, $\text{CDCl}_3\text{-CS}_2$) δ 3.35 (8H, s, $\text{SCH}_2\text{CH}_2\text{S}$), 7.33 (2H, mc, H-5,6 of the benzofuroquinoid, BFQ, ring), 7.43 (2H, mc, H-4,7 of the BFQ ring); ¹³C NMR ($\text{CDCl}_3\text{-CS}_2$, 150 MHz) δ 29.75 and 29.81 ($\text{SCH}_2\text{CH}_2\text{S}$), 101.6 (C-1,3 of the BFQ ring), 111.2 and 113.1 (C-4,5 of the dithiole ring), 121.2 (C-4,7 of the BFQ ring), 127.4 (C-5,6 of the BFQ ring), 130.8 (C-3a,7a of the BFQ ring), 139.1 (C-2 of the dithiole ring); UV-VIS (THF) $\lambda_{\text{max}}/\text{nm}$ (log ϵ) 469 (4.58), 441 (4.46), 362 (4.24).
- Crystal data for $[\text{BEDT-BDTBF}]_2[\text{PF}_6]$: triclinic space group $P\bar{1}$, $a = 17.456(5)$, $b = 18.586(6)$, $c = 16.788(4)$ Å, $\alpha = 100.39(2)^\circ$, $\beta = 116.46(2)^\circ$, $\gamma = 64.86(2)^\circ$, $V = 4414(4)$ Å³ and $Z = 2$, ($R = 0.064$ and $R_w = 0.068$ for observed 9702 reflections with $I > 5.00\sigma(I)$); for $[\text{BEDT-BDTBF}]_2[\text{AsF}_6]$: triclinic space group $P\bar{1}$, $a = 17.658(4)$, $b = 18.691(3)$, $c = 16.684(4)$ Å, $\alpha = 100.02(2)^\circ$, $\beta = 116.77(2)^\circ$, $\gamma = 64.98(1)^\circ$, $V = 4454(1)$ Å³ and $Z = 2$, ($R = 0.070$ and $R_w = 0.064$ for observed 9332 reflections with $I > 2.50\sigma(I)$).
- The overlap integral r3 is induced by up and down type overlaps at the ethylenedithio groups of the donors A and D belonging to the neighboring columns.