



Palladium-catalysed amination of bromofluorans and an investigation of their thermochromic behaviour

Farid Azizian^a, Amanda J. Field^b, John Griffiths^b, B. Mark Heron^{b,*}

^a St Mary Cray Research, Sun Chemical Ltd, St Mary Cray, Orpington, Kent BR5 3PP, UK

^b Department of Colour Science, School of Chemistry, University of Leeds, Leeds LS2 9JT, UK

ARTICLE INFO

Article history:

Received 24 May 2011

Received in revised form

10 June 2011

Accepted 13 June 2011

Available online 21 June 2011

Keywords:

Thermochromism

Fluoran

Benzofluoran

Colour former

Pd-catalysed amination

Functional dye

ABSTRACT

The palladium-catalysed amination of readily accessible bromofluorans and bromobenzo[*a*]fluorans has been accomplished with a series of anilines and morpholine. The resulting aminofluorans generated intense black shades upon formulation in methyl stearate containing bisphenol A. The route provides an alternative approach to various amino substituted fluorans without the need of a series of individual diphenylamine intermediates.

© 2011 Elsevier Ltd. All rights reserved.

1. Introduction

Interest in functional dye systems continues at a pace as a consequence of technological developments and more widespread applications [1–3] particularly in the areas of sensors and probes for a variety of organic and inorganic analytes [4] and dyes for solar cell applications [5]. The (thio)xanthene unit [6] forms the core of many functional dyes including rhodamines [7], rosamines [8], thiofluoresceins [9] and fluorans [10].

Transition metal-catalysed arylation [11] and amination reactions [12] have been widely employed in organic syntheses to facilitate efficient transformations that would otherwise necessitate many sequential steps. However, such transition metal-catalysed techniques have only very recently been applied to the preparation of functional dye systems such as rhodols and rosamines. In the former, a methoxymethyl (MOM) protected fluorescein monotriflate was successfully aminated at the 3'-position with a variety of amines under Pd(OAc)₂–BINAP catalysis (Scheme 1) [13] and in the latter an aryl moiety was introduced into the 9-position of a xanthene unit through PdCl₂(PPh₃)₂-mediated coupling of a triarylboroxin to a 9-trifloxyxanthene (Scheme 2) [14]. We now describe our preliminary results on the application of

the Pd-catalysed amination reaction for the direct amination of bromo-substituted fluorans and benzo[*a*]fluorans.


2. Experimental

2.1. Equipment

Unless otherwise stated, reagents were used as supplied. 2'-Bromo-6'-di(*n*-butylamino)-3'-methylfluoran (Vermillion DCF) was obtained from Sun Chemical (France) Ltd. NMR spectra were recorded on a Bruker Avance 400 MHz instrument (¹H NMR 400 MHz, ¹³C NMR 100 MHz) for sample solutions in CDCl₃ with tetramethylsilane as an internal reference unless indicated otherwise. All compounds were homogeneous by TLC, Merck TLC aluminium sheets either silica gel 60 F₂₅₄ (cat. No 105554) or neutral aluminium oxide 60 F₂₅₄ (cat. No 105550), using a range of eluent systems of differing polarity. Flash column chromatography was performed on chromatography silica gel (Fluorochem, 35–70 μm particle size distribution). All percentage yields are unoptimised. Reflectance spectra of the new thermochromic compounds in methyl stearate containing bisphenol A [ratio of fluoran:bisphenol A:methyl stearate = 5:1:15] as a thin film sandwiched between two glass microscope slides were recorded using a Datascolor Spectraflash 500 (Xe flash simulating natural daylight, diffuse illumination, collected at 8° to normal), with

* Corresponding author. Tel.: +44 0 1133432925; fax: +44 0 1133432947.

E-mail address: b.m.heron@leeds.ac.uk (B.M. Heron).

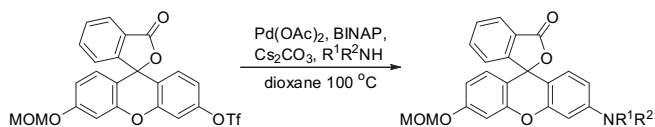

Scheme 1. Pd-Catalysed amination of a protected fluorescein.

specular excluded, UV 100%, small aperture setting, four flashes and a single measurement. FTIR spectra were recorded using a Perkin Elmer Spectrum One spectrophotometer equipped with a diamond probe ATR attachment (neat sample). Mass spectra were recorded at the National EPSRC Mass Spectrometry Service Centre, Swansea.

2.2. Synthesis of 9'-diethylamino-3'-bromobenzo[a]fluoran 2

2'-[4-(Diethylamino)-2-hydroxybenzoyl]benzoic acid **1** (5 g; 16 mmol) and 6-bromo-2-naphthol (3.57 g; 16 mmol) were heated at 120–125 °C in sulphuric acid (85%, 25 g) for 4 h. The reaction mixture was poured into ice water (75 mL) and a green/purple solid was precipitated by adding NaOH (2 M, aq, ~15 mL). The precipitate was collected by vacuum filtration and washed with water (3 × 50 mL). The precipitate was suspended in a mixture of water (25 mL), sodium hydroxide (1.25 g; 52 mmol) and toluene (75 mL) and heated under reflux for 0.5 h. The toluene layer was separated, washed with sodium hydroxide solution (3.5%, aq, 2 × 25 mL) and water (2 × 25 mL), and reduced in volume to ~25 mL. The precipitate formed on cooling was collected by vacuum filtration and washed with a small amount of cold toluene (10 mL) to afford the product as pale pink microcrystals in 27% yield, m.p. 227–230 °C, ν_{\max} (cm⁻¹) 1754.7, 1351.7, 1198.2, 665.3, δ_{H} 1.05 (6H, t, $J = 7.2$, (CH₃CH₂)₂N), 3.33 (4H, q, $J = 7.2$, (CH₃CH₂)₂N), 6.36 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.43 (1H, d, $J = 2.7$, 8'-H), 6.50 (1H, d, $J = 8.8$, 11'-H), 6.92 (1H, dd, $J = 8.8$ and 2.4, 6'-H), 7.09 (1H, d, $J = 7.2$, 7-H), 7.21 (1H, dd, $J = 8.8$ and 2.4, 2'-H), 7.45 (1H, d, $J = 8.8$, 1'-H), 7.58 (2H, m, 5-H and 6-H), 7.79 (1H, d, $J = 8.8$, 5'-H), 7.92 (1H, d, $J = 2.4$, 4'-H), 8.12 (1H, d, $J = 7.2$, 4-H), δ_{C} 12.50, 44.46, 84.22, 96.90, 105.86, 109.00, 109.05, 117.95, 119.64, 123.50, 125.25, 125.46, 136.90, 128.21, 129.45, 130.13, 130.31, 131.03, 131.48, 132.47, 135.27, 149.11, 150.65, 151.35, 155.27, 170.01, found $[M + H]^+ = 500.0850$ C₂₈H₂₂BrNO₃ requires $[M + H]^+ = 500.0856$.

2.3. Synthesis of 2'-bromo-6'-diethylaminofluoran 4

4-Bromoanisole (2.99 g; 16 mmol) was added to a solution of 2'-[4-(diethylamino)-2-hydroxybenzoyl]benzoic acid **1** (5 g; 16 mmol) in sulphuric acid (98%, 40 g) and the mixture was stirred at 10–20 °C for 5 h. The reaction mixture was then poured into ice water (150 mL) and a purple solid was precipitated by adding NaOH (10%, aq, 20 mL). The precipitate was collected by vacuum filtration and washed with water (3 × 25 mL). The solid was suspended in sodium hydroxide (10%, aq, 30 mL) and toluene (60 mL), and heated under reflux for 2 h, and then allowed to cool. The toluene layer was then separated, washed with sodium hydroxide (3.5%, aq, 2 × 25 mL) and water (2 × 25 mL), and evaporated to ~25 mL. The precipitate formed on cooling was then collected by vacuum filtration and washed with a small amount of cold toluene (10 mL)

to afford the title compound as pale pink crystals in 70% yield, m.p. 173–175 °C, ν_{\max} (cm⁻¹) 1749.4, 1348.9, 1194.5, 664.8, δ_{H} 1.17 (6H, t, $J = 7.2$, (CH₃CH₂)₂N), 3.36 (4H, q, $J = 7.2$, (CH₃CH₂)₂N), 6.36 (1H, dd, $J = 8.8$ and 2.5, 7'-H), 6.44 (1H, d, $J = 2.5$, 5'-H), 6.55 (1H, d, $J = 8.8$, 8'-H), 6.86 (1H, d, $J = 2.4$, 1'-H), 7.27 (2H, m, 4'-H and 7-H), 7.45 (1H, dd, $J = 8.8$ and 2.4, 3'-H), 7.66 (2H, m, 5-H and 6-H), 8.04 (1H, d, $J = 7.2$, 4-H), found $[M + H]^+ = 450.0701$ C₂₄H₂₀BrNO₃ requires $[M + H]^+ = 450.0705$.

2.4. 9'-Diethylaminobenzo[a]fluoran 3


2'-[4-(Diethylamino)-2-hydroxybenzoyl]benzoic acid **1** (1 g; 3.2 mmol) and 2-naphthol (0.42 g; 2.9 mmol) were added portionwise to methanesulfonic acid (98%, 6 mL), ensuring the temperature did not exceed 25 °C. The reaction mixture was then stirred at 20–25 °C for 24 h, with monitoring by TLC (silica/70% ethyl acetate in hexane). The reaction mixture was poured into ice water (20 mL) and neutralised. The precipitate was collected by vacuum filtration and washed with water (3 × 25 mL). The solid intermediate was then added to sodium hydroxide (1%, aq, 5 mL) and heated to 75–80 °C for 4 h. Vacuum filtration of the solution afforded pink crystals, which were washed with hexane containing a little diethyl ether to afford the title compound as off-white microcrystals in 67% yield, m.p. 218–220 °C (Lit. m.p. 215–217 °C [15]), ν_{\max} (cm⁻¹) 1754.3, 1352.8, 1197.1, δ_{H} 1.16 (6H, t, $J = 7.2$, (CH₃CH₂)₂N), 3.34 (4H, q, $J = 7.2$, (CH₃CH₂)₂N), 6.49 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.59 (2H, m, 8'-H and 11'-H), 7.00 (1H, d, $J = 8.8$, 1'-H), 7.21 (2H, dd, $J = 8.8$ and 2.4, 2'-H and 3'-H), 7.43 (1H, d, $J = 7.6$, 6'-H), 7.61 (2H, d, $J = 7.6$, 5'-H and 7-H), 7.78 (2H, m, 5-H and 6-H), 8.04 (1H, dd, $J = 8.8$ and 2.4, 4'-H), 8.22 (1H, d, $J = 7.6$, 4-H).

2.5. 3'-Diethylaminofluoran 5

2'-[4-(Diethylamino)-2-hydroxybenzoyl]benzoic acid **1** (5 g; 16 mmol) was added to sulphuric acid (98%, 40 g) at room temperature and dissolved. Phenol (1.49 g; 16 mmol) was then added to the foregoing cooled solution and the mixture was stirred at 10–20 °C for 5 h. The reaction mixture was then poured into ice water (150 mL) and a purple solid was precipitated by adding NaOH (10%, aq). This was collected by vacuum filtration and washed with water. The precipitate was then suspended in sodium hydroxide (10%, aq, 30 mL) and toluene (60 mL), and was heated by reflux for 2 h. The cold toluene layer was then separated, washed with sodium hydroxide (3.5%, aq, 2 × 15 mL) and water (2 × 15 mL), and evaporated to ~25 mL. The precipitate formed on cooling was then collected by vacuum filtration and washed with a small amount of cold toluene (10 mL) to afford the title compound as pale pink crystals in 62% yield, m.p. 128–130 °C, ν_{\max} (cm⁻¹) 1748.0, 1351.2, 1196.5, δ_{H} 1.16 (6H, t, $J = 7.2$, (CH₃CH₂)₂N), 3.38 (4H, q, $J = 7.2$, (CH₃CH₂)₂N), 6.37 (1H, dd, $J = 9.0$ and 2.8, 7'-H), 6.41 (1H, d, $J = 2.8$, 5'-H), 6.75 (1H, d, $J = 8.8$, 8'-H), 6.96 (1H, d, $J = 2.4$, 1'-H), 7.20 (2H, m, 4'-H and 7-H), 7.51 (2H, dd, $J = 9$ and 2.4, 2'-H and 3'-H), 7.66 (2H, m, 5-H and 6-H), 8.04 (1H, d, $J = 7.2$, 4-H), found $[M + H]^+ = 372.1590$ C₂₄H₂₁NO₃ requires $[M + H]^+ = 372.1594$.

2.6. General method for the Pd-catalysed amination of bromofluorans

Sodium *t*-butoxide (6 mmol), the bromofluoran (2 mmol), the appropriate amine (3 mmol), tri-(*t*-butyl)phosphonium tetrafluoroborate (4 mol%) and Pd₂(dba)₃ (5 mol%) were placed in a 100 mL round bottomed flask under N₂. Anhydrous toluene (25 mL), previously bubbled N₂ for 15 min, was added via a transfer needle and the mixture was heated to 70 °C until TLC examination revealed that no further reaction had occurred. The reaction

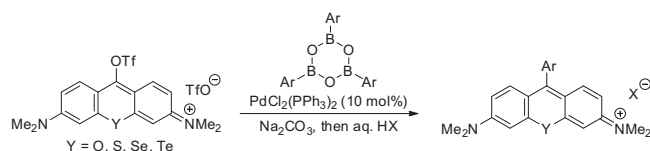

Scheme 2. Pd-Catalysed arylation of 9-trifloxyxanthenes.

mixture was poured into cold, dilute HCl (0.01 M, aq, 200 mL) and extracted with CH_2Cl_2 (2×100 mL). The combined organic extracts were washed with dilute NaOH (0.1 M, aq, 50 mL) and water (2×50 mL), dried over sodium sulphate and evaporated to afford the crude product which was purified by column chromatography (30% ethyl acetate in toluene) and recrystallisation (ethyl acetate in hexane). The following compounds were obtained by this protocol:

2.6.1. 3'-Anilino-9'-diethylaminobenzo[a]fluoran

7a from **2** and aniline after column chromatography and recrystallisation as pink microcrystals in 19% yield, m.p. 200–204 °C [16], ν_{max} (cm^{-1}) 3378.4, 1740.3, 1236.1, δ_{H} 1.15 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.33 (4H, q, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 5.90 (1H, s, NH), 6.35 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.43 (1H, d, $J = 2.8$, 8'-H), 6.51 (1H, d, $J = 8.8$, 11'-H), 6.85 (1H, dd, $J = 8.8$ and 2.4, 2'-H), 6.92 (3H, m, Ar-H, 1'-H), 7.06 (4H, m, Ar-H, 7-H), 7.13 (1H, d, $J = 2.4$, 4'-H), 7.28 (1H, d, $J = 9.0$, 6'-H), 7.55 (2H, m, 5-H and 6-H), 7.65 (1H, d, $J = 9.0$, 5'-H), 8.11 (1H, m, 4-H), δ_{C} 12.52, 44.42, 84.82, 96.90, 106.05, 108.71, 108.75, 113.20, 118.11, 118.76, 120.34, 121.21, 123.56, 124.90, 125.13, 126.15, 126.95, 128.26, 129.29, 131.21, 132.51, 135.14, 138.11, 139.39, 142.58, 149.02, 149.60, 150.85, 155.65, 170.38, found $[\text{M} + \text{H}]^+ = 513.2169$ $\text{C}_{34}\text{H}_{28}\text{N}_2\text{O}_3$ requires $[\text{M} + \text{H}]^+ = 513.2178$.

2.6.2. 9'-Diethylamino-3'-(4-methoxyanilino)benzo[a]fluoran

7b from **2** and *p*-anisidine after column chromatography as pale pink microcrystals in 58% yield, m.p. 150–154 °C, ν_{max} (cm^{-1}) 3374.7, 1736.9, 1237.0, δ_{H} 1.15 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.33 (4H, q, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.84 (3H, s, OCH_3), 5.51 (1H, s, NH), 6.35 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.43 (1H, d, $J = 2.8$, 8'-H), 6.51 (1H, d, $J = 8.8$, 11'-H), 6.75 (1H, dd, $J = 9.2$ and 2.4, 2'-H), 6.85 (2H, m, Ar-H), 6.92 (1H, d, $J = 9.2$, 1'-H), 7.05 (2H, m, Ar-H), 7.13 (1H, m, 7-H), 7.16 (1H, d, $J = 2.4$, 4'-H), 7.32 (1H, d, $J = 9.2$, 6'-H), 7.55 (2H, m, 5-H and 6-H), 7.65 (1H, d, $J = 9.2$, 5'-H), 8.11 (1H, m, 4-H), δ_{C} 12.52, 21.07, 44.42, 60.42, 84.82, 96.90, 106.06, 108.74, 113.22, 118.09, 118.72, 120.37, 121.24, 123.58, 124.87, 125.09, 126.18, 126.99, 128.23, 129.31, 131.19, 132.52, 135.16, 138.08, 139.41, 142.60, 148.99, 149.59, 150.90, 155.60, 170.35, found $[\text{M} + \text{H}]^+ = 543.2274$ $\text{C}_{35}\text{H}_{30}\text{N}_2\text{O}_4$ requires $[\text{M} + \text{H}]^+ = 543.2278$.

2.6.3. 9'-Diethylamino-3'-(4-trifluoromethylanilino)benzo[a]fluoran

7c from **2** and 4-trifluoromethylaniline after column chromatography as pale yellow microcrystals in 86% yield, m.p. 137–140 °C, ν_{max} (cm^{-1}) 3368.2, 1740.0, 1235.3, 1096.8, δ_{H} 1.16 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.35 (4H, q, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 5.95 (1H, s, NH), 6.38 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.43 (1H, d, $J = 2.8$, 8'-H), 6.51 (1H, d, $J = 8.8$, 11'-H), 6.92 (1H, dd, $J = 8.8$ and 2.4, 2'-H), 7.02 (3H, m, Ar-H, 1'-H), 7.13 (1H, m, 7-H), 7.41 (1H, d, $J = 9.0$, 6'-H), 7.47 (3H, m, Ar-H, 4'-H), 7.58 (2H, m, 5-H and 6-H), 7.75 (1H, d, $J = 9.0$, 5'-H), 8.10 (1H, d, $J = 7.2$, 4-H), δ_{C} 12.51, 78.12, 44.44, 84.78, 96.90, 105.93, 108.86, 114.22, 115.55, 116.25, 119.00, 121.44, 121.80, 123.58, 124.99, 125.30, 125.92, 126.56, 126.93, 127.23, 128.23, 129.04, 129.36, 131.38, 132.25, 135.24, 137.41, 146.33, 149.08, 150.83, 155.51, 170.33, found $[\text{M} + \text{H}]^+ = 581.2030$ $\text{C}_{35}\text{H}_{27}\text{N}_2\text{O}_3\text{F}_3$ requires $[\text{M} + \text{H}]^+ = 581.2047$.

2.6.4. 9'-Diethylamino-3'-(4-ethoxycarbonylanilino)benzo[a]fluoran

7d from **2** and ethyl 4-aminobenzoate after column chromatography and recrystallisation as fawn microcrystals in 53% yield, m.p. 99–102 °C, ν_{max} (cm^{-1}) 3349.7, 1737.6, 1686.0, 1595.2, 1280.3, 1172.8, δ_{H} 1.15 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 1.36 (3H, t, $J = 7.2$, OCH_2CH_3), 3.34 (4H, q, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 4.32 (2H, q, $J = 7.2$, OCH_2CH_3), 6.37 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.41 (1H, d, $J = 2.4$, 8'-H), 6.45 (1H, bs, NH), 6.52 (1H, d, $J = 8.8$, 11'-H), 6.95 (4H, m, Ar-H, 1'-H, 2'-H), 7.10 (1H, m, 7-H), 7.36 (1H, d, $J = 8.9$, 6'-H), 7.45 (1H,

d, $J = 2.3$, 4'-H), 7.58 (2H, m, 5-H and 6-H), 7.69 (1H, d, $J = 8.9$, 6'-H), 7.85 (2H, m, Ar-H), 8.12 (1H, m, 4-H), δ_{C} 11.49, 13.40, 20.04, 27.93, 37.79, 43.28, 43.41, 59.24, 59.36, 83.27, 83.75, 95.88, 104.93, 107.88, 112.74, 113.74, 117.35, 117.86, 120.56, 122.76, 123.04, 123.80, 126.17, 127.21, 128.33, 130.46, 131.51, 134.22, 146.59, 148.02, 149.81, 154.51, 165.71, 169.29, 170.17, found $[\text{M} + \text{H}]^+ = 585.2384$ $\text{C}_{37}\text{H}_{32}\text{N}_2\text{O}_5$ requires $[\text{M} + \text{H}]^+ = 585.2389$.

2.6.5. 9'-Diethylamino-3'-morpholinobenzo[a]fluoran

7e from **2** and morpholine after column chromatography as pale beige microcrystals in 57% yield, m.p. 140–144 °C, ν_{max} (cm^{-1}) 1750.0, 1306.9, 1227.0, δ_{H} (DMSO- d_6) 1.16 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.14 (4H, m, $-\text{CH}_2\text{NCH}_2-$), 3.34 (4H, q, $J = 7.2$, $(\text{CH}_3\text{CH}_2)_2\text{N}$), 3.83 (4H, m, $-\text{CH}_2\text{OCH}_2-$), 6.36 (1H, dd, $J = 8.8$ and 2.4, 10'-H), 6.44 (1H, d, $J = 2.4$, 8'-H), 6.54 (1H, d, $J = 8.8$, 11'-H), 6.90 (1H, dd, $J = 8.8$ and 2.4, 2'-H), 6.99 (1H, d, $J = 8.8$, 1'-H), 7.06 (1H, d, $J = 2.4$, 4'-H), 7.10 (1H, m, 7-H), 7.36 (1H, d, $J = 9.0$, 6'-H), 7.57 (2H, m, 5-H and 6-H), 7.78 (1H, d, $J = 9.0$, 5'-H), 8.12 (1H, m, 4-H), δ_{C} (DMSO- d_6) 12.94, 21.88, 29.45, 44.85, 49.65, 67.23, 85.17, 94.13, 97.33, 106.49, 109.15, 112.04, 119.58, 124.01, 125.14, 125.70, 126.14, 127.47, 128.66, 129.61, 131.85, 132.85, 135.51, 138.29, 147.72, 149.42, 150.05, 151.35, 156.05, 170.72, found $[\text{M} + \text{H}]^+ = 507.2265$ $\text{C}_{32}\text{H}_{30}\text{N}_2\text{O}_4$ requires $[\text{M} + \text{H}]^+ = 507.2278$.


2.6.6. 6'-Di-*n*-butylamino-2'-(4-methoxyanilino)-3'-methylfluoran

7g from **6** and *p*-anisidine after column chromatography as very pale red–purple microcrystals in 68% yield, m.p. 142–145 °C, ν_{max} (cm^{-1}) 3394.1, 1746.8, 1240.4, δ_{H} 0.95 (6H, t, $J = 7.2$, $(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2)_2\text{N}$), 1.33 (4H, sextet, $J = 7.2$, $(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2)_2\text{N}$), 1.56 (4H, quintet, $J = 7.2$, $(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2)_2\text{N}$), 2.40 (3H, s, CH_3), 3.26 (4H, t, $J = 7.6$, $(\text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2)_2\text{N}$), 3.42 (1H, bs, NH), 3.74 (3H, s, OCH_3), 6.32 (1H, dd, $J = 8.8$ and 2.4, 7'-H), 6.38 (1H, d, $J = 2.4$, 5'-H), 6.52 (1H, d, $J = 8.8$, 8'-H), 6.65 (2H, m, Ar-H), 6.74 (2H, m, Ar-H), 6.88 (1H, s, 1'-H), 7.16 (1H, s, 4'-H), 7.18 (1H, dd, $J = 7.2$ and 1.2, 7-H), 7.65 (2H, m, 5-H and 6-H), 8.02 (1H, dd, $J = 7.2$ and 1.2, 4-H), δ_{C} 13.98, 20.28, 23.00, 29.26, 50.79, 55.72, 83.39, 97.51, 104.46, 108.57, 114.78, 116.42, 118.09, 118.86, 118.90, 124.00, 125.04, 126.99, 128.74, 129.72, 131.12, 134.98, 139.90, 140.47, 150.81, 152.57, 152.71, 152.78, 157.96, 169.44 found $[\text{M} + \text{H}]^+ = 563.2906$ $\text{C}_{36}\text{H}_{38}\text{N}_2\text{O}_4$ requires $[\text{M} + \text{H}]^+ = 563.2910$.

3. Discussion

In order to assess the versatility of the palladium-catalysed coupling reaction three bromo-substituted fluorans were examined as substrates, 3'-bromo-9'-diethylaminobenzo[a]fluoran **2**, 2'-bromo-6'-diethylaminofluoran **4** and a commercial sample of 2'-bromo-6'-di(*n*-butylamino)-3'-methylfluoran **6** [17]. Fluorans **2** and **4** were derived from the common ketoacid **1** which was readily available from the Friedel–Crafts reaction between 3-diethylaminophenol and phthalic anhydride in toluene [18]. Heating **1** with either 6-bromo-2-naphthol or 4-bromoanisole in 85% sulphuric acid gave, after basification and purification, the requisite bromofluorans **2** and **4** in moderate yield (Scheme 3). As a consequence of reported instances where debromination had occurred during the attempted preparation of bromofluorans via this general method [19] careful structural characterisation of **2** and **4** was undertaken.

The key ^1H NMR signals employed for the characterisation of **2** were the *ortho*-coupled doublet at δ 7.45 ($J = 9.2$ Hz, 1'-H), a double doublet at δ 7.21 ($J = 9.2$ and 2.4 Hz, 2'-H) and the *meta*-coupled doublet at δ 7.92 ($J = 2.4$ Hz, 4'-H) which confirmed the position of the bromine atom. A group of mutually coupled signals resonating upfield of these signals assigned to the bromonaphthalene unit were assigned to 11'-H (δ 6.50, d, $J = 8.8$ Hz), 10'-H (δ 6.37, dd, $J = 8.8$ and

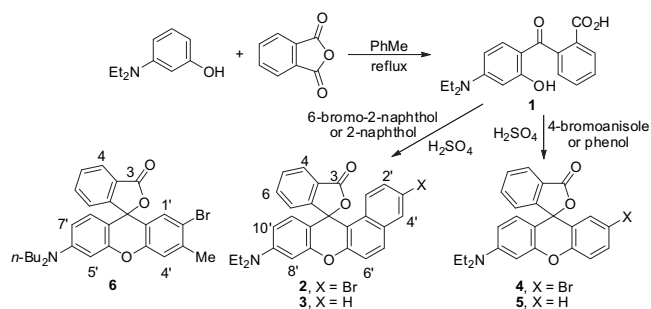

Scheme 3. Preparation of fluorans and bromofluorans.

2.6 Hz) and 8'-H (δ 6.43, d, J = 2.6 Hz) which confirmed the location of the diethylamino group on the xanthene core (Fig. 1). The presence of the lactone carbonyl was confirmed by ^{13}C NMR spectroscopy with a signal at δ 170.0 [20] and also by a C=O stretch at 1754 cm^{-1} in the infrared spectrum. Mass spectrometry gave the expected molecular ions $M + H^+ = 500.2$ and 502.2 in a ca. 1:1 ratio (Br^{79} and Br^{81}) which confirmed the incorporation of the bromine atom.

The ^1H NMR spectrum of **4** displayed a similar grouping of signals at ca. δ 6.4 assigned to the Et_2N substituted xanthene unit and the protons of the furanone moiety were assigned to signals at δ 7.27 (multiplet including 4'-H), δ 7.66 (m) and δ 8.04 (d, J = 7.2 Hz) for 7-H, 5-H and 6-H, and 4-H respectively. The incorporation of the bromine atom was confirmed by mass spectrometry with $M + H^+ = 450.2$ and 452.2 and the lactone carbonyl stretching band appeared at 1749 cm^{-1} in the infrared spectrum.

With the required bromofluorans to hand examination of their Pd-catalysed amination reaction was next explored (Scheme 2). In 1994 Buchwald et al. and Hartwig et al. independently published work on the coupling of aryl halides with amines using palladium catalysis in the presence of a base [21]. Since then, palladium-catalysed


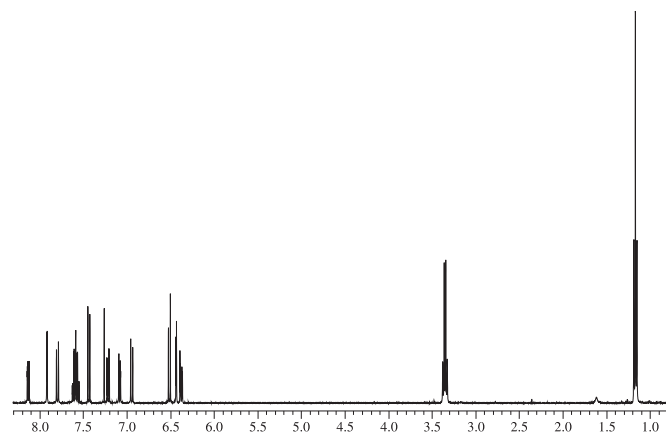


Fig. 1. ^1H NMR spectrum of 9'-diethylamino-3'-bromobenzo[a]fluoran **2**.

aminations have been widely investigated and have featured in reviews which highlight the apparent ease with which this amination occurs [12]. From the considerable body of work undertaken in this area it is apparent that an exceptionally wide range of aryl halides and amines can be coupled together and that an extensive range of catalysts, ligands and solvents have been employed.

The Pd source employed throughout this study was $\text{Pd}_2(\text{dba})_3$ since this has been widely employed in Pd-catalysed aminations [22]. The ligand employed was tris(*t*-butyl)phosphine, used as the more convenient tris(*t*-butyl)phosphonium fluoroborate salt with the free phosphine liberated *in situ* using an additional equivalent of sodium *tert*-butoxide. Thus heating a solution of **2** in anhydrous toluene (previously bubbled with nitrogen for 15 min) containing 1 eq. of the aniline, 2 eq. of *t*-BuONa, *t*-Bu₃P·HBF₄ (4 mol%) and $\text{Pd}_2(\text{dba})_3$ (5 mol%) gave, after 24 h at 70°C , a reaction mixture

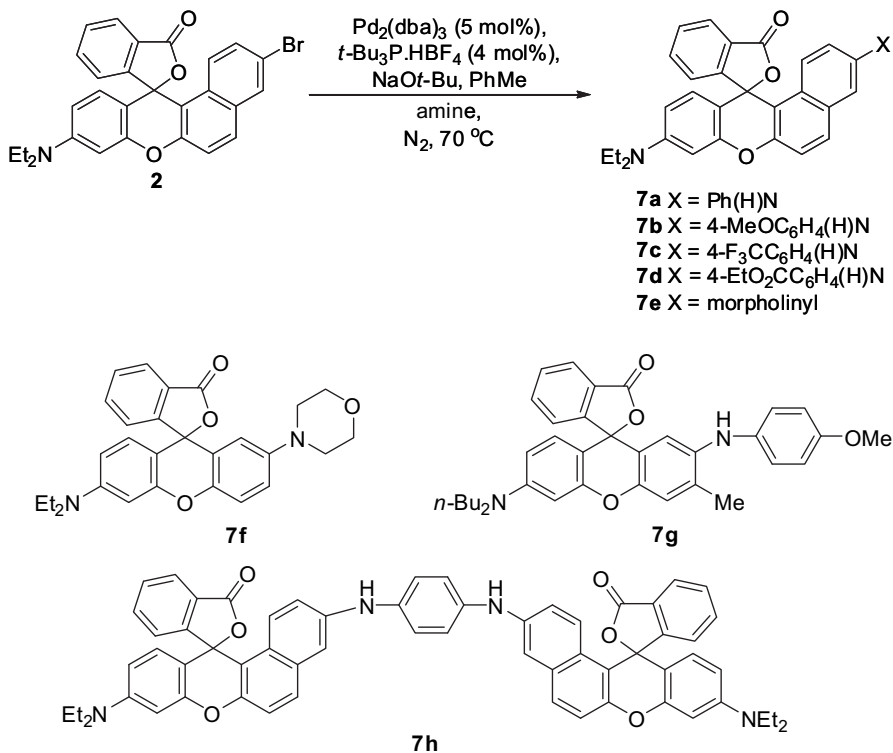

Scheme 4. Pd-catalysed amination reactions of bromofluorans.

containing none of the original bromofluoran **2** and two new components which, although poorly resolved on TLC, were separated by column chromatography. The faster running red colouring component was identified as the benzo[a]fluoran **3** (10%) by comparison of physical and spectroscopic data with an independently synthesised sample. The debromination of aromatic bromides in Pd-catalysed reactions is a frequently encountered problem [23].

The more polar purple–black colouring compound was characterised as the target 3'-anilinofluoran **7a** albeit in a disappointingly low isolated yield of 19% (Scheme 4), in spite of the relatively high conversion indicated by TLC analysis of the reaction mixture. It is likely that the low isolated yield of pure **7a** is in part attributed to a combination of the poor resolution between the two products and the chromatographic purification process which results in some ring-opening of the fluorans on the chromatography silica. The ^1H NMR spectrum for **7a** displayed a singlet for the NH group at δ 5.90 confirming the success of the coupling process. The naphthalene ring protons in close proximity to the 3'-aniline group gave rise to signals at δ 6.85 (dd, $J = 8.8$ and 2.4 Hz, 2'-H), δ 6.92 (m, 1'-H) and δ 7.13 (d, $J = 2.4$ Hz, 4'-H). The expected signals for the diethylamino-substituted xanthene unit appeared at δ 6.43 (8'-H), δ 6.35 (10'-H) and δ 6.51 (11'-H). The robustness of the lactone ring towards the amination conditions was confirmed by the presence of a low field multiplet at δ 8.11 assigned to 4-H, a low field signal at δ 170.4 in the ^{13}C NMR spectrum for the C=O group and a stretching bond at 1740 cm^{-1} (C=O) in the infrared spectrum. Additional confirmation of the amination of **2** came from the infrared stretching band for the NH group, which appeared in the expected region at 3378 cm^{-1} . There are only a very limited number of examples of 3'-anilino substituted benzo[a]fluorans described in the patent literature and these have been obtained by a more traditional and lengthy strategy involving the preparation of 6-anilino-2-methoxynaphthalene by an Ullmann reaction [24] and its subsequent reaction with a ketoacid [16].

Repeating the amination of **2** with a series of electron rich and electron deficient anilines gave the 3'-anilino benzo[a]fluorans **7b–d** in 53–86% yield and amination of **2** with morpholine gave a respectable yield of **7e** (57%). The structure of each of the new amino substituted benzo[a]fluorans **7b–7e** was confirmed by NMR spectroscopy which indicated an upfield shift of the naphthalene ring protons adjacent to the new amine function and the aniline NH (**7b–d**) appeared as a slightly broadened signal between δ 5.5 and δ 6.5. In the ^{13}C NMR spectrum the lactone C=O group resonated at ca. δ 170, typical for the fluoran unit [20].

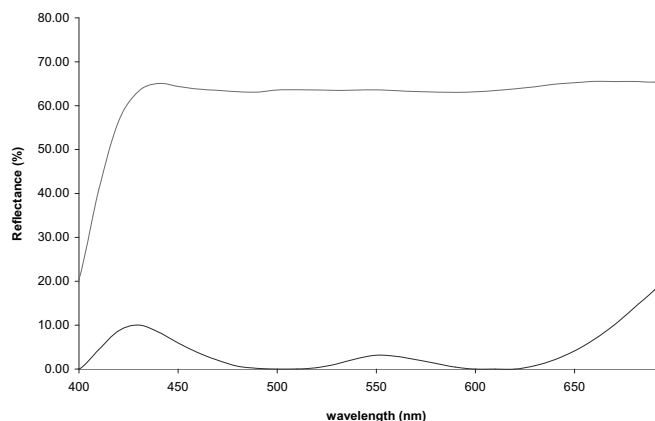


Fig. 2. Reflectance spectra of **7b** in methyl stearate containing bisphenol A at rt (lower line) and at ca. $50\text{ }^{\circ}\text{C}$ (upper line).

Amination of bromofluoran **4** with morpholine resulted in a complex reaction product from which unrecovered **4** (17%) and debrominated fluoran **5** (35%) could be isolated but the known red-developing (TLC) diaminofluoran **7f** [25] remained impure. However, treatment of **6** with *p*-anisidine proceeded smoothly under identical conditions to afford **7g** in 68% yield in spite of the sterically important proximal methyl group. Attempts to accomplish a double amination with 1,4-diaminobenzene, thereby linking two molecules of **2** together, to afford **7h** gave a complex reaction product by TLC which indicated a new purple–black colouring species had formed but which could not be resolved by chromatography. Further investigations of Pd-catalysed aminations with other secondary amines and diamines are in hand.

The colour forming properties of the new fluorans in methyl stearate containing bisphenol A as the acidic developer were next examined. At room temperature each of the new aminofluoran formulations appeared intensely coloured with **7b** appearing blue–black, **7c–e** purple–black and **7g** a green–black in agreement with established colour–structure trends [19]. Upon warming to ca. $50\text{ }^{\circ}\text{C}$ each of the foregoing formulations faded to near colourless with **7b** and **7c** displaying very weak residual pale yellow and pale pink shades, respectively. Selected reflectance spectra recorded at room temperature (rt) and at ca. $50\text{ }^{\circ}\text{C}$ are presented in Figs. 2–4 and illustrate the significant contrast between the ring-opened coloured and ring-closed colourless forms and the broad absorption over the full range of the visible spectrum confirming the near

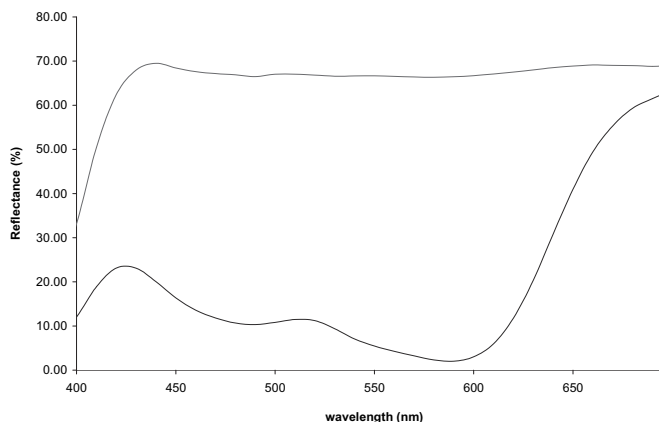


Fig. 3. Reflectance spectra of **7c** in methyl stearate containing bisphenol A at rt (lower line) and at ca. $50\text{ }^{\circ}\text{C}$ (upper line).


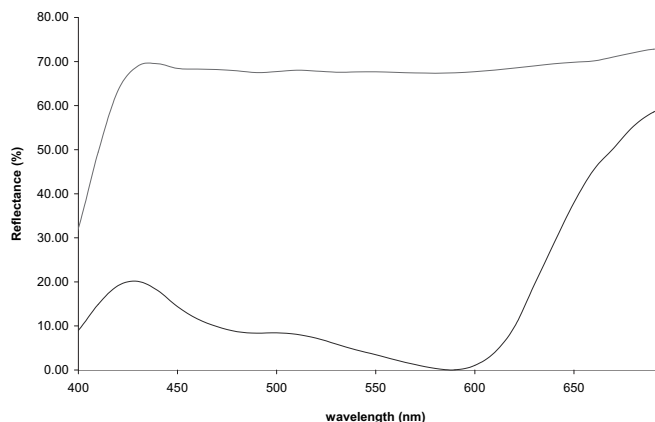


Fig. 4. Reflectance spectra of **7e** in methyl stearate containing bisphenol A at rt (lower line) and at ca. $50\text{ }^{\circ}\text{C}$ (upper line).

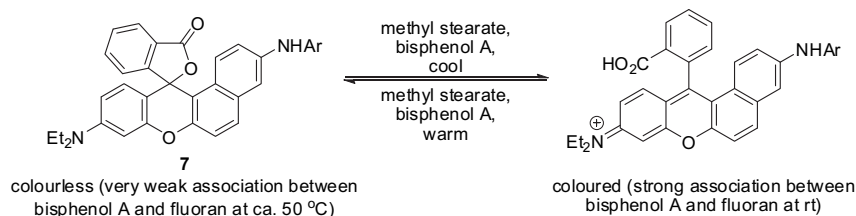

Scheme 5. Reversible colour forming process of benzo[a]fluorans **7** in methyl stearate containing bisphenol A.

black shades (Scheme 5). The interactions leading to colour development between colour forming fluorans and acidic developers such as bisphenol A are well established [26].

4. Conclusions

The amination of bromo-fluorans and benzo[a]fluorans was accomplished employing $\text{Pd}_2(\text{dba})_3$ and $\text{tris}(t\text{-Bu})_3\text{P}$ as the catalyst–ligand combination. Electronically rich and electronically deficient anilines coupled in moderate to good yield to 3'-bromo-9'-diethylaminobenzo[a]fluoran to afford a series of 3'-anilino derivatives which performed as efficient colour formers, developing near black shades on formulation with bisphenol A in methyl stearate. Using an identical method amination of 2'-bromo-6'-di(*n*-butylamino)-3'-methylfluoran with *p*-anisidine proceeded efficiently in spite of the proximal methyl substituent. Amination of 3'-bromo-9'-diethylaminobenzo[a]fluoran and 2'-bromo-6'-diethylaminofluoran with morpholine gave contrasting results with the former proceeding efficiently and the latter suffering from extensive debromination of the substrate.

This preliminary study has illustrated that a series of desirable black colouring fluorans can be readily obtained by a simple amination protocol applied to common, readily available bromo-substituted precursors thus obviating the need to access a wide variety of diarylamine intermediates which require delicate handling when preparing fluorans by the traditional acid-mediated process. Catalyst optimisation studies to enhance conversion and minimize complicating debromination reactions are ongoing.

Acknowledgement

The authors are indebted to Sun Chemical Ltd., St Mary Cray for a studentship (AJF). The Worshipful Company of Clothworkers' of the City of London are thanked for a millennium grant for the purchase of a Bruker Avance NMR instrument and the EPSRC are thanked for access to the National Mass Spectrometry Service (Swansea).

References

- [1] Bamfield P. Chromic phenomena technological applications of colour chemistry. Cambridge: Royal Society of Chemistry; 2001.
- [2] Kim S-H, editor. Functional dyes. Amsterdam: Elsevier; 2006.
- [3] Strekowski L, editor. Heterocyclic polymethine dyes. Berlin: Springer-Verlag; 2008.
- [4] Beija M, Afonso CAM, Martinho JMG. Synthesis and applications of rhodamine derivatives as fluorescent probes. *Chem Soc Rev* 2009;38:2410–33.
- [5] (a) Mishra A, Fischer MKR, Bäuerle P. Metal-free organic dyes for dye sensitized solar cells from structure property relationships to design rules. *Angew Chem Int Ed* 2009;48:2474–99; (b) Hagfeldt A, Boschloo G, Sun L, Kloo L, Pettersson H. Dye-sensitized solar cells. *Chem Rev* 2010;110:6595–663.
- [6] Wight P. In: Kirk RE, Othmer DF, editors. Xanthene dyes in 'Kirk-Othmer encyclopaedia of chemical technology'. New York: Wiley; 2000.
- [7] (a) Kolmakov K, Belov VN, Bierwagen J, Ringemann C, Müller V, Eggeling C, et al. Red-emitting rhodamine dyes for fluorescence microscopy and nanoscopy. *Chem Eur J* 2010;16:158–66; (b) Mitronova GY, Belov VN, Bossi ML, Wurm CA, Meyer L, Medda R, et al. New fluorinated rhodamines for optical microscopy and nanoscopy. *Chem Eur J* 2010;16:4477–88.
- [8] Wu L, Burgess K. Synthesis and spectroscopic properties of rosamines with cyclic amine substituents. *J Org Chem* 2008;73:8711–8.
- [9] Dahms K, Batsanov AS, Bryce MR. An unusual synthesis of a spirothioxanthene derivative. *Tetrahedron Lett* 2010;51:6605–7.
- [10] (a) Inouye M, Tsuchiya K, Kitao T. New thermo-response dyes: coloration by the Claisen rearrangement and intramolecular acid-base reaction. *Angew Chem Int Ed Engl* 1992;31:204–5; (b) Muthyala R, editor. Chemistry and applications of leuco dyes. New York: Plenum Press; 1997; (c) Burkinshaw SM, Griffiths J, Towns AD. Reversibly thermochromic systems based on pH-sensitive spiroactone-derived functional dyes. *J Mater Chem* 1998;8:2677–83; (d) Weng W, Higuchi T, Suzuki M, Fukuoka T, Shimomura T, Ono M, et al. A high-speed passive-matrix electrochromic display using a mesoporous TiO_2 electrode with vertical porosity. *Angew Chem Int Ed* 2010;49:3956–9.
- [11] (a) Kotha S, Lahiri K, Kashinath D. Recent applications of the Suzuki-Miyaura cross-coupling reaction in organic synthesis. *Tetrahedron* 2002;58:9633–95; (b) Stanforth SP. Catalytic cross-coupling reactions in biaryl synthesis. *Tetrahedron* 1998;54:263–303; (c) Suzuki A. Recent advances in the cross-coupling reactions of organoboron derivatives with organic electrophiles, 1995–1998. *J Organomet Chem* 1999;576:147–68; (d) Miyaura N, Suzuki A. Palladium-catalyzed cross-coupling reactions of organoboron compounds. *Chem Rev* 1995;95:2457–83.
- [12] (a) Hartwig JF. Transition metal-catalyzed synthesis of arylamines and aryl ethers from aryl halides and triflates: scope and mechanism. *Angew Chem Int Ed* 1998;37:2046–67; (b) Yang BH, Buchwald SL. Palladium-catalyzed amination of aryl halides and sulfonates. *J Organomet Chem* 1999;576:125–46; (c) Bedford RB, Cazin CSJ, Holder D. The development of palladium catalysts for C–C and C–heteroatom bond forming reactions of aryl chloride substrates. *Coord Chem Rev* 2004;248:2283–321.
- [13] Peng T, Yang D. Construction of a library of rhodol fluorophores for developing new fluorescent probes. *Org Lett* 2010;12:496–9.
- [14] Calitree BD, Dettly MR. Novel rhodamine dyes via Suzuki coupling of xanthone triflates with arylboroxins. *Synlett*; 2010:89–92.
- [15] Meiqin S, Yun S, Qiyu T. Synthesis of fluoran dyes with improved properties. *Dyes Pigm* 1995;29:45–55.
- [16] Fluoran colour formers for heat sensitive recording materials, Japanese patent No. JP57053561A, 1982. *Chem Abstr* 1982;97:40319.
- [17] Yamaguchi M, Kikkawa K, Gonda M, Fluoran compound and record material using the same, EU patent No. EP0356199A2, 1990. *Chem Abstr* 1990;113:193452.
- [18] (a) Liu Q-H, Liu J, Guo J-C, Yan X-L, Wang D-H, Chen L, et al. Preparation of polystyrene fluorescent microspheres based on some fluorescent labiles. *J Mater Chem* 2009;19:2018–25; (b) Kondo M, Tanaka M, Sakamoto N, Ooyoshi H. Method of producing keto acids, European patent No. EP0511019A2, 1992. *Chem Abstr* 1992;118:101655.
- [19] (a) Hatano Y. In: Muthyala R, editor. Chemistry and applications of leuco dyes. New York: Plenum Press; 1997. p. 159–205 [chapter 6]; (b) Yanagita M, Kanda S, Ito K, Shibuya R, Tokita S. The relationship between hindrance and absorption spectrum of fluoran dyes part 1. *Mol Cryst Liq Cryst* 1999;327:49–52.
- [20] Hojo M, Ueda T, Yamasaki M, Inoue A, Tokita S, Yanagita M. ^1H and ^{13}C NMR detection of the carbocations or zwitterions from rhodamine B base, a fluoran-based black colour former, trityl benzoate and methoxy-substituted trityl chlorides in the presence of alkali metal or alkaline earth metal perchlorates in acetonitrile solution. *Bull Chem Soc Jpn* 2002;75:1569–76.
- [21] (a) Paul F, Patt J, Hartwig JF. Palladium-catalyzed formation of carbon–nitrogen bonds. Reaction intermediates and catalyst improvements in the hetero cross-coupling of aryl halides and tin amides. *J Am Chem Soc* 1994;116:5969–70; (b) Guram AS, Buchwald SL. Palladium-catalyzed aromatic aminations with in situ generated aminostannanes. *J Am Chem Soc* 1994;116:7901–2.
- [22] (a) Wolfe JP, Buchwald SL. Improved functional group compatibility in the palladium-catalyzed amination of aryl bromides. *Tetrahedron Lett* 1997;38:6359–62; (b) Frost CG, Mendonça P. Iterative amination strategy in the synthesis of peptidomimetics. *Chem Lett*; 1997:1159–60; (c) Hartwig JF. Approaches to catalyst discovery. New carbon–heteroatom and carbon–carbon bond formation. *Pure Appl Chem* 1999;71:1417–23;

- (d) Charles MD, Schultz P, Buchwald SL. Efficient Pd-catalyzed amination of heteroaryl halides. *Org Lett* 2005;7:3965–8.
- [23] (a) Hayashi T, Konishi M, Kobori Y, Kumada M, Higuchi T, Hirotsu K. Dichloro [1,1'-bis(diphenylphosphino)ferrocene]palladium(II): an effective catalyst for cross-coupling of secondary and primary alkyl Grignard and alkylzinc reagents with organic halides. *J Am Chem Soc* 1984;106:158–63; (b) Hartwig JF. Palladium-catalyzed amination of aryl halides: mechanism and rational catalyst design. *Synlett*; 1997:329–40; (c) Satyanarayana G, Maier ME. Formation of spirocyclic compounds from Heck cyclizations invoking cyclic enamides. *J Org Chem* 2008;73:5410–5.
- [24] (a) Ley SV, Thomas AW. Modern synthetic methods for copper-mediated C(aryl)-O, C(aryl)-N and C(aryl)-S bond formation. *Angew Chem Int Ed* 2003;42:5400–49; (b) Beletskaya IP, Cheprakov AV. Copper in cross-coupling reactions. The post-Ullmann chemistry. *Coord Chem Rev* 2004;248:2337–64.
- [25] Kondo M, Miyake T, Iwasaki H. Pressure sensitive copying paper, Japanese patent No. JP50014572, 1975. *Chem Abstr* 1975;84:172166.
- [26] (a) Takahashi Y, Shirai A, Segawa T, Takahashi T, Sakakibara K. Why does a colour-developing phenomenon occur on thermal paper comprising of a fluoran dye and a colour developer molecule? *Bull Chem Soc Jpn* 2002;75:2225–31; (b) Sekiguchi Y, Takayama S, Gotanda T, Sano K. Importance of solvent polarity in the equilibrium reaction of leuco dye and developer. *Chem Lett* 2006;35:458–9; (c) Sekiguchi Y, Takayama S, Gotanda T, Sano K. Molecular structures of the colouring species of a leuco dye with phenolic colour developers. *Chem Lett* 2007;36:1010–1; (d) Maclaren DC, White MA. Dye-developer interactions in the crystal violet lactone-lauryl gallate binary system: implications for thermochromism. *J Mater Chem* 2003;13:1695–700; (e) Maclaren DC, White MA. Competition between dye-developer and solvent-developer interactions in a reversible thermochromic system. *J Mater Chem* 2003;13:1701–4.