



ISOMERIZATION AND HYDROGENATION OF NITROGEN-CONTAINING ORGANIC COMPOUNDS  
 CATALYZED BY HETEROGENEOUS CATALYSTS

Hideshi Hattori and Koza Tanabe \*

Department of Chemistry, Faculty of Science, Hokkaido University, Sapporo  
 060, Japan

Abstract— The double-bond isomerization of 1-N-pyrrolidino-2-propene ( $C=C-C-N$    $\longrightarrow C-C=C-N$   ) and N,N-dimethyl-2-propenylamine ( $C=C-C-N\begin{smallmatrix} C \\ \diagup \\ C \end{smallmatrix} \longrightarrow C-C=C-N\begin{smallmatrix} C \\ \diagup \\ C \end{smallmatrix}$ ) were studied at 40°C over MgO, CaO, SrO, BaO, La<sub>2</sub>O<sub>3</sub>, ThO<sub>2</sub>, ZrO<sub>2</sub>, ZnO etc. It was found that MgO and CaO which have strong basic sites on the surfaces exhibited a high catalytic activity, the selectivity for the formation of 1-N-pyrrolidino-1-propene being more than 80 %. The double-bond migration of the allylamines is suggested to proceed via anionic intermediates in which the cis form is much more stable than the trans form. For the hydrogenation of N,N-dimethyl-2-propenylamine ( $C=C-C-N\begin{smallmatrix} C \\ \diagup \\ C \end{smallmatrix} + H_2 \longrightarrow C-C-C-N\begin{smallmatrix} C \\ \diagup \\ C \end{smallmatrix}$ ), the activity as well as the selectivity of nickel catalysts supported on MgO, CaO, La<sub>2</sub>O<sub>3</sub>, ThO<sub>2</sub>, TiO<sub>2</sub>, ZrO<sub>2</sub> etc. was examined at 0°C. Nickel on MgO was found to give 100 % conversion and almost 100 % selectivity for the formation of N,N-dimethyl-propenylamine. It is suggested that nickel catalyst becomes active when supported on basic oxides. The reaction path is discussed on the basis of experiments using deuterium as a tracer.

INTRODUCTION

The potential use of enamines has expanded in organic synthesis<sup>1</sup>, because of the general ability of enamines for the acylation and alkylation of carbonyl compounds. Base-catalyzed double-bond isomerization of allylamines is one of the ways to prepare enamines. By this method, stereospecific synthesis is possible. Although

heterogeneous catalysts have several advantages compared with homogeneous catalysts, only a few solid base catalysts such as  $K/Al_2O_3$ <sup>2</sup> and  $KNH_2/Al_2O_3$ <sup>3</sup> have been examined for the isomerization of allylamine. However, there remained some problems such as requirement of high reaction temperature and activity degradation during the reaction. Thus, we have attempted to examine the catalytic actions of solid bases such as  $MgO$ <sup>4</sup>,  $CaO$ <sup>5</sup>,  $SrO$ <sup>6</sup>,  $BaO$ <sup>7</sup>,  $La_2O_3$ <sup>8</sup>,  $ThO_2$ <sup>9</sup> etc., whose basic property was studied in our laboratory for the isomerization of allylamines to enamines. Regarding the hydrogenation of unsaturated compounds containing nitrogen, not much study has been made over heterogeneous catalyst. Although NiB and borohydride-reduced Pd have been reported to be quite active and selective for such a hydrogenation<sup>10,11</sup>, poisoning by the reactant and complexities of hydrogenolysis are unavoidable for conventional metal catalysts such as Pt, Pd, and Ni<sup>12,13</sup>. A selection of materials for supports is considered to be crucial in preparation of excellent supported-metal catalysts. In the present work, we have studied the effects of supports (mainly basic oxides) on Ni catalysts for the hydrogenation of N,N-dimethyl-2-propenylamine.

#### EXPERIMENTAL

Catalysts and Reagents: The  $MgO$ ,  $CaO$ ,  $SrO$ , and  $BaO$  catalysts were prepared from  $Mg(OH)_2$ ,  $Ca(OH)_2$ ,  $SrCO_3$ , and granular  $BaO$  by thermal decomposition under a helium stream. The  $ThO_2$  catalyst was prepared from  $Th(C_2O_4)_2$  by thermal decomposition at  $500^\circ C$  in air. The  $La_2O_3$  and  $ZrO_2$  catalysts were obtained by thermal decomposition of  $La(OH)_3$  at  $700^\circ C$  under a helium stream, and  $Zr(OH)_4$  at  $700^\circ C$  in air, respectively, the hydroxides being prepared by hydrolysis of an aqueous solution of  $La(NO_3)_3$  or  $ZrOCl_2$  with aqueous ammonia, followed by washing with deionized water and drying at  $120^\circ C$ . The  $ZnO$ ,  $SiO_2$ , and  $Al_2O_3$  catalysts were prepared by hydrolysis of each aqueous solution of  $Zn(NO_3)_2$ , ethyl orthosilicate and an alcoholic solution of aluminium isopropoxide with aqueous ammonia, followed by washing and calcination at  $450^\circ C$  ( $ZnO$ ) or  $500^\circ C$  ( $SiO_2$  and  $Al_2O_3$ ) in air. The  $SiO_2-Al_2O_3$  catalyst was type SA-N of Nikki Chemical Industry Co. Prior to the reaction, all catalysts were pretreated at proper temperatures in a reactor under a helium stream for 3 h. Supported Ni catalysts were prepared by impregnating various metal oxides, which had been calcined at  $500^\circ C$  in air for 3 h, with aqueous  $Ni(NO_3)_2$  followed by drying over a water bath and decomposition by heating at  $500^\circ C$  in air for 3 h. Prior to the reaction, the catalysts were reduced under a hydrogen stream at  $500^\circ C$ . The content of Ni was 10% by weight for all catalysts.

1-N-Pyrrolidino-2-propene was prepared from allyl bromide and pyrrolidine by condensation according to the method of Sauer and Prahl.<sup>14</sup> N,N-Dimethyl-2-propenylamine was purchased from Tokyo Kasei Kogyo Co. Ltd. Amines were distilled under a reduced pressure and purified by passage through KOH column.

Reactions: A microcatalytic pulse reactor was employed to carry out the isomerization of 1-N-pyrrolidino-2-propene at 40°C and the hydrogenation of N,N-dimethyl-2-propenylamine at 0°C. The products were trapped by liquid nitrogen before being flash evaporated into a gas chromatographic column, which was directly connected to a mass spectrometer. Apiezone L on KOH-treated Chromosorb was packed in a 3-m glass column which was operated at 100°C.

Stereoselectivity in the isomerization of N,N-dimethyl-2-propenylamine over CaO was examined by NMR spectroscopic analysis. An all-glass static reactor was employed. Calcium oxide was outgassed at 500°C in a reactor and sealed. A reactant was introduced through a breakable seal. The products in the cell were kept at liquid nitrogen temperature to prevent the produced enamine from undergoing cis-trans isomerization, and melted immediately before NMR measurement. The NMR spectrum was recorded on an R 20B Hitachi spectrometer at 60 MHz.

Deuteration of N,N-dimethyl-2-propenylamine was carried out in a recirculation reactor with Ni/MgO and Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> catalyst. The numbers and location of D atoms in the product were determined by NMR, in which Eu-FOD was added to separate the NMR peaks.

## RESULTS AND DISCUSSION

### 1 Isomerization of 1-N-pyrrolidino-2-propene

The compositions of the products for each catalyst are shown in Table 1. Although a main product was 1-N-pyrrolidino-1-propene, considerable amounts of pyrrolidine and propionaldehyde were produced over all catalysts. The formation of propionaldehyde was facile especially at the first pulse. Since neither the reactant nor the carrier gas contained oxygen atoms, the oxygen atom in propionaldehyde should originate from the catalyst surface.

Magnesium oxide and CaO showed high activities when they were pretreated at proper temperatures. The activities were so high that the percentage of 1-N-pyrrolidino-1-propene was almost independent of the change in flow rate and did not decrease with increase of pulse number. The selectivity for the formation of 1-N-pyrrolidino-1-propene was more than 80 % over MgO. Activities of MgO and CaO

Table 1

Double-Bond Migration of 1-N-Pyrrolidino-2-propene at 40°C

Catalyst	Pretreatment temperature (°C)	Specific surface area (m <sup>2</sup> /g)	Weight of catalyst (mg)	Pulse No.	Flow rate (ml/min)	Percentage of each product			
						1-N-Pyrrolidino-2-propene	1-N-pyrrolidino-1-propene	Pyrrolidine	Propion-aldehyde
MgO	600	135	30	1	30	0	79.8	9.9	10.3
				3	30	0.1	85.6	11.5	2.7
				5	88	1.0	83.9	12.3	2.7
CaO	400	81	30	1	30	4.4	64.3	25.5	5.7
				3	30	28.5	49.9	18.8	2.8
				5	30	56.0	35.1	7.1	1.8
CaO	700	52	34	1	30	0.5	61.2	26.1	11.7
				3	30	0.2	81.8	15.7	2.2
				5	113	0.4	76.7	19.8	3.2
SrO	1000	10	302	1	30	0.2	77.7	11.8	10.3
				3	30	62.4	31.2	5.3	1.2
				5	30	86.3	12.9	0.6	0.1
BaO	800	0.2	313	1	30	0.4	71.9	19.1	8.7
				2	30	96.5	2.9	0.4	0.2
				1	30	16.6	50.8	17.0	15.6
ThO <sub>2</sub>	700	59	102	3	30	50.8	40.6	5.9	2.4
				5	120	72.2	19.7	5.2	2.8
				1	30	0.6	67.9	19.3	12.2
La <sub>2</sub> O <sub>3</sub>	700	27	31	3	30	71.9	20.8	5.6	1.7
				4	30	97.8	0.4	1.8	0

varied with pretreatment temperature of the catalysts and the maximum activities were obtained when pretreated in the temperature range, 400~1000°C for MgO and at 700°C for CaO. With SrO, BaO, and La<sub>2</sub>O<sub>3</sub>, the activity degradation with the pulse number was prominent. Thorium oxide gradually lost its activity with successive pulses. No activity was observed with ZrO<sub>2</sub>, ZnO, Al<sub>2</sub>O<sub>3</sub>, and SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>. Magnesium oxide, CaO, SrO, BaO, La<sub>2</sub>O<sub>3</sub>, and ThO<sub>2</sub> which showed activities at least in the first pulse are known to possess basic sites<sup>4-9</sup>. This seems to indicate that the basic sites are active sites. On the other hand, ZrO<sub>2</sub><sup>15</sup> and ZnO<sup>16</sup> which have both acidic and basic sites and Al<sub>2</sub>O<sub>3</sub><sup>17</sup> and SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub><sup>17</sup> which have strong acidic sites were inactive. Therefore, it is considered that the acidic sites on the catalysts interact with a lone pair of nitrogen atom of the reactant and become inactive or interfere the isomerization over basic sites<sup>18,19</sup>.

## 2 Isomerization of N,N-dimethyl-2-propenylamine


Stereochemistry was examined for the double-bond migration of N,N-dimethyl-2-propenylamine over CaO. Since N,N-dimethyl-2-propenylamine has a molecular structure in which a methine group of 4-methyl-1-pentene is replaced by a nitrogen atom, stereochemistry in the double-bond migration of 4-methyl-1-pentene was also studied for comparison. The cis/trans ratio of N,N-dimethyl-1-propenylamine was obtained from the intensities of quartet peaks (CH<sub>3</sub>(1)) at 0.95 ppm for the cis isomer and at 0.86 ppm for the trans isomer.

Percentages of the cis isomer in N,N-dimethyl-1-propenylamine produced are plotted

against the conversion in Fig. 1. Extrapolation to zero conversion gives 100% *cis*-*N,N*-dimethyl-1-propenylamine. Percentages of the *cis* isomer in 4-methyl-2-pentene from 4-methyl-1-pentene are also shown in Fig. 1. The percentage at zero conversion was about 50%. The percentages of *cis* isomers decreased with conversion for both reactions as the equilibria favor for the *trans* isomers.

A high *cis*-selectivity in *N,N*-dimethyl-2-propenylamine isomerization compared with *cis*-selectivity in 1-methyl-1-pentene isomerization suggests that the

energy difference between *cis* and *trans* forms of the intermediate is greater for the former reaction than the latter one. The intermediates for the double-bond migration of allylamine and of olefin are considered to be anionic.<sup>19</sup> The reaction scheme could be drawn as follows for allylamine.

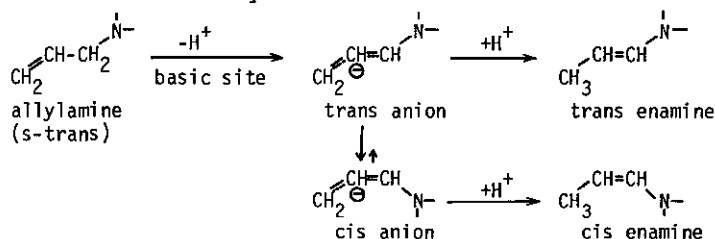

### 3 Hydrogenation of *N,N*-dimethyl-2-propenylamine

The main product over Ni supported on basic oxides was *N,N*-dimethylpropylamine. The other products such as propane and dimethylamine were negligibly small. *N,N*-Dimethyl-1-propenylamine which might result from double-bond migration was not detected in a microcatalytic pulse reactor. As shown in Fig. 2, Ni supported on MgO, CaO, La<sub>2</sub>O<sub>3</sub>, and ThO<sub>2</sub> exhibited high activities from the first pulse. Especially, Ni/MgO gave 100 % conversion and almost 100 % selectivity for the formation of *N,N*-dimethylpropylamine<sup>20</sup>. Nickel on SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> also showed a high activity after the 4th pulse. Following them, the activities were in the order of Ni/ZrO<sub>2</sub> > Ni/Al<sub>2</sub>O<sub>3</sub> > Ni/TiO<sub>2</sub> > Ni/SiO<sub>2</sub>. Since MgO, CaO, La<sub>2</sub>O<sub>3</sub>, and ThO<sub>2</sub> have basic sites on their surfaces and Ni supported on these oxides showed high activities, it is suggested that Ni catalyst becomes active when supported on basic oxides,

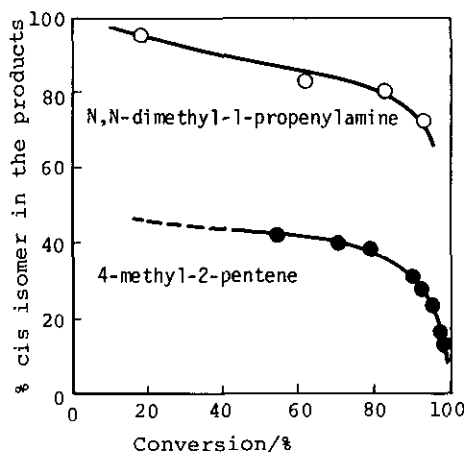


Fig. 1 Percentages of *cis* isomer in isomerized products for the double bond isomerization of *N,N*-dimethyl-2-propenylamine and 4-methyl-1-pentene. Reaction temperature; 25°C.

though there is an exception for Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>. On the other hand, the effect of supports is entirely different in the hydrogenation of 1-butene which does not contain nitrogen as shown in Fig. 3. The different effect of support was

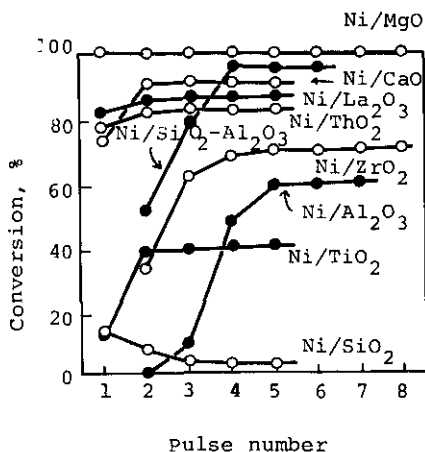


Fig. 2 Hydrogenation of N,N-dimethyl-2-propenylamine

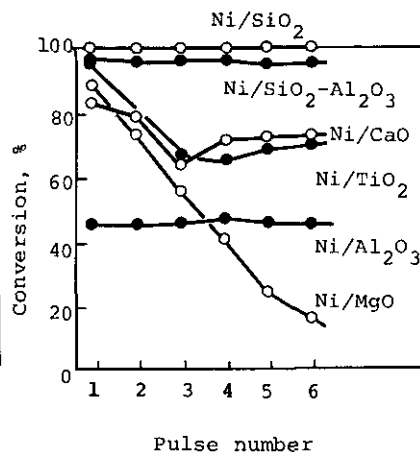


Fig. 3 Hydrogenation of 1-butene.

most prominent for Ni/SiO<sub>2</sub>, which showed the highest activity for the hydrogenation of 1-butene and the lowest activity for the hydrogenation of N,N-dimethyl-2-propenylamine. Further studies are needed to clarify the reasons. The effect of the amount of Ni supported on MgO on the conversion of N,N-dimethyl-2-propenylamine is shown in Table 2.

Table 2. Change in hydrogenation activity with Ni content in Ni/MgO

Ni wt, %	0	5	7	9	20	30	50
Conversion of N,N-dimethyl-2-propenylamine, %	0	31	70	100	100	98	94

The optimum amount of Ni was 10~30 wt. %. Over the catalysts on which 5 or 7 % of Ni was supported, the formation of N,N-dimethyl-1-propenylamine (enamine) was observed. The time course of the reaction of N,N-dimethyl-2-propenylamine over Ni(9 %)/MgO which was carried out in a closed recirculation reactor is shown in Fig. 4. The enamine forms at the initial stage of the reaction, but changes to the hydrogenated compound, as the reaction proceeds. However, no enamine was formed over Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> during the reaction. The adsorption of CO<sub>2</sub> caused to stop the reaction over Ni/MgO, but did not affect the activity of Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>. In order to examine the reactivity of enamine toward hydrogenation, MgO that is

active for the double-bond migration of allylamine to enamine and Ni/SiO<sub>2</sub> which is inactive for the hydrogenation of allylamine were put in series in a reactor and the hydrogenation of allylamine was carried out. The conversion was 95 %, indicating that Ni/SiO<sub>2</sub> is active for the hydrogenation of enamine. The high conversion is due to the fact that basic sites are unnecessary for the hydrogenation of enamine. Isotopic distributions of the products in the deuteration of N,N-dimethyl-2-propenylamine over Ni/MgO, and Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> are summarized in Table 3.

Over Ni/MgO, about two D atoms were included in the product. About one D atom was located at carbon atom 2 and the rests were equally located at carbon atoms 1 and 3. On the contrary, about two D atoms were included in the product over Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>, the positions of D atoms being limited to carbon atoms 2 and 3. These suggest that in the case of Ni/MgO, Ni/CaO, Ni/La<sub>2</sub>O<sub>3</sub>, and Ni/ThO<sub>2</sub>, allylamine isomerizes to enamine on basic sites of supports and the formed enamine is successively hydrogenated on Ni, while in the case of Ni/SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>, Ni/ZrO<sub>2</sub>, Ni/TiO<sub>2</sub>, Ni/Al<sub>2</sub>O<sub>3</sub>, and Ni/SiO<sub>2</sub>, allylamine is hydrogenated directly to alkylamine without passing through enamine.

The postulated reaction schemes are drawn as follows.

Table 3. Number of D atoms located at different carbon atoms of N,N-dimethylpropylamine in the deuteration of N,N-dimethyl-2-propenylamine.

Catalyst	Position		
	C(1)	C(2)	C(3)
Ni/MgO	0.36	1.11	0.49
Ni/SiO <sub>2</sub> -Al <sub>2</sub> O <sub>3</sub>	0.03	0.80	1.17



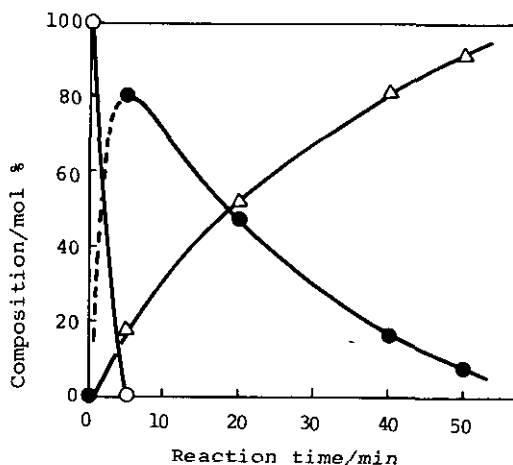


Fig. 4 Time dependence of the hydrogenation of N,N-dimethyl-2-propenylamine over Ni/MgO O; reactant, ●; N,N-dimethyl-1-propenylamine, Δ; N,N-dimethylpropylamine.



#### ACKNOWLEDGEMENTS

This paper is a summary of the works 18,19,20,21 which were supported by Grant-in-Aid for Scientific Research 311706 from the Ministry of Education, Science and Culture, Japan.

#### REFERENCES

1. A. G. Cook (Ed.), "Emanines: Synthesis, Structure and Reactions". Dekker, New York/London, 1969.
2. G. Y. Kondrat'eva and Y. S. Dol'skaya, Izv. Akad. Nauk SSSR Ser. Khim., 1967, 2045.
3. A. J. Hubert, J. Chem. Soc. C, 1968, 2048.
4. H. Hattori, N. Yoshii, and K. Tanabe, Proc. 5th Intern. Congr. Catalysis, 1973, 10 233; H. Hattori, Y. Tanaka, and K. Tanabe, J. Am. Chem. Soc., 1976, 98, 4652.
5. K. Tanabe, N. Yoshii, and H. Hattori, J. C. S. Chem. Commun., 1971, 464.
6. M. Mohri, K. Tanabe, and H. Hattori, J. Catal., 1974, 32, 144.
7. H. Hattori, K. Maruyama, and K. Tanabe, J. Catal., 1976, 44, 50.
8. Y. Fukuda, H. Hattori, and K. Tanabe, Bull. Chem. Soc. Jpn., 1978, 51, 3150.
9. Y. Imizu, T. Yamaguchi, H. Hattori, and K. Tanabe, Bull. Chem. Soc. Jpn., 1977, 50, 1040.
10. T. W. Russel, R. C. Hoy, and J. E. Cornelius, J. Org. Chem., 1972, 37, 3552.
11. T. W. Russel, and D. M. Duncan, J. Org. Chem., 1974, 39, 3050.
12. P. N. Pylander, "Catalytic Hydrogenation over Platinum Metals", Academic Press, New York, 1967.
13. W. H. Hartung, and R. Simonoff, Org. Reactions, 1953, 7, 263.
14. J. Sauer and H. Prah, Chem. Ber., 1969, 102, 1917.
15. Y. Nakano, T. Iizuka, H. Hattori, and K. Tanabe, J. Catal., 1979, 57, 1.



16. C. C. Change, W. C. Nonner, and R. J. Kokes, J. Phys. Chem., 1973, 77, 1957.
17. K. Tanabe, "Solid Acids and Bases", Academic Press, New York, London, 1970.
18. A. Hattori, K. Tanabe, and H. Hattori, Chem. Lett., 1977, 1465.
19. A. Hattori, H. Hattori, and K. Tanabe, J. Catal., 1980, 65, 245.
20. H. Imai, H. Hattori, and K. Tanabe, Chem. Lett., 1979, 1001.
21. H. Hattori, H. Imai, and K. Tanabe Shokubai (Catalyst), 1980, 22, 259.

Received, 8th June, 1981