

New Ag(I)–Iminophosphorane Coordination Polymers as Efficient Catalysts Precursors for the MW-Assisted Meyer–Schuster Rearrangement of Propargylic Alcohols in Water


Joaquín García-Álvarez,^{*,†} Josefina Díez,[†] Cristian Vidal,[†] and Cristian Vicent[‡]

[†]Laboratorio de Compuestos Organometálicos y Catálisis (Unidad Asociada al CSIC), Departamento de Química Orgánica e Inorgánica, Instituto Universitario de Química Organometálica “Enrique Moles”, Facultad de Química, Universidad de Oviedo, E-33071, Oviedo, Spain

[‡]Serveis Centrals d’Instrumentació Científica, Universitat Jaume I, Avenida Sos Baynat s/n, 12071 Castelló, Spain

Supporting Information

ABSTRACT: Treatment of the *N*-thiophosphorylated iminophosphorane ligands (PTA) =NP(=S)(OR)_2 [PTA = 1,3,5-triaza-7-phosphaadamantane, **3a** and **3b**] and (DAPTA) =NP(=S)(OR)_2 [DAPTA = 3,7-diacetyl-1,3,7-triaza-5-bicyclo[3.3.1]nonane, **4a** and **4b**] with an equimolar amount of AgSbF_6 leads to high-yield formation of the new one-dimensional coordination polymers $[\text{Ag}\{\mu^2\text{-N,S-(PTA)=NP(=S)(OR)}_2\}]_x[\text{SbF}_6]_x$ (**5a** and **5b**) and $[\text{Ag}\{\mu^2\text{-O,S-(DAPTA)=NP(=S)(OR)}_2\}]_x[\text{SbF}_6]_x$ (**6a** and **6b**), respectively. These new (iminophosphorane)silver(I) coordination polymers are efficient catalyst precursors for the Meyer–Schuster isomerization of both terminal and internal alkynols. Reactions proceeded in water, under aerobic conditions and using microwave irradiation as heating source, to afford the corresponding α,β -unsaturated carbonyl compounds in excellent yields, without the addition of any cocatalyst. Remarkably, it should be noted that this catalytic system can be recycled up to 10 consecutive runs (1st cycle 45 min, 99%; 10th cycle 6 h, 97%). ESI-MS analysis of **5a** in water has been carried out providing valuable insight into the monomeric active species responsible for catalytic activity in water.

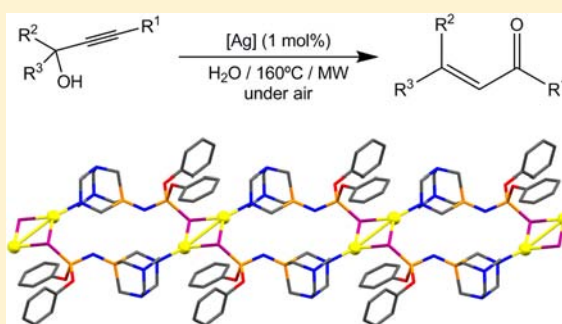

INTRODUCTION

During the past decade, construction of new coordination polymers has emerged as one of the most important research topics due to their wide application in many fields such as crystal engineering and coordination and materials chemistry,¹ to name a few. In this sense, the water-soluble phosphine PTA [1,3,5-triaza-7-phosphaadamantane (**1**), Figure 1] and its

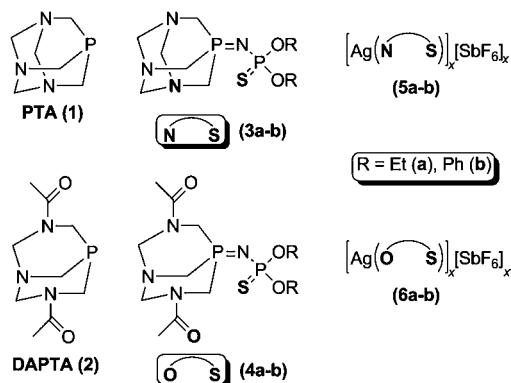


Figure 1. Structure of ligands **3**, **4a**, and **4b** and their Ag(I)-coordination polymers **5a**, **5b**, **6a**, and **6b**.

derivatives [i.e., DAPTA, 3,7-diacetyl-1,3,7-triaza-5-bicyclo[3.3.1]nonane (**2**), Figure 1] have been previously used as versatile building blocks for design of both one- and two-dimensional coordination polymers.² However, to our knowledge, the ability of their iminophosphorane derivatives [general formula (PTA) =NR and (DAPTA) =NR , respectively] to act as the cornerstone piece for easy synthesis of new coordination polymers has been totally neglected. In this sense, we recently reported the synthesis of the first water-stable iminophosphorane ligands based on the water-soluble phosphines PTA and DAPTA [(PTA) =NP(=S)(OR)_2 (R = Et (**3a**), Ph (**3b**); (DAPTA) =NP(=S)(OR)_2 (R = Et (**4a**), Ph (**4b**), see Figure 1] as well as studying their coordination in a Cu(I) precursor, yielding the corresponding one-dimensional coordination polymers $[\text{Cu}\{\mu^2\text{-N,S-(PTA)=NP(=S)(OR)}_2\}]_x[\text{PF}_6]_x$.³ These compounds have proved to be efficient catalysts for copper-catalyzed cycloaddition of azides and alkynes (both terminal and internal) in water and under aerobic reaction conditions.³


On the other hand, the search for novel efficient organic methodologies which proceed with high levels of selectivity and

Received: February 27, 2013

Published: May 15, 2013

atom economy (i.e., all atoms of the reaction end up in the final product) constitutes one of the major challenges in modern synthesis.⁴ In this sense, isomerization reactions are typical examples of atom economic processes as no byproducts are generated. In this regard, isomerization reactions of propargylic alcohols provide straightforward synthetic routes to α,β -unsaturated carbonyl compounds which are (i) useful building blocks in organic synthesis, (ii) advanced intermediates in the manufacture of aromes and fragrances, and (iii) key structural units in a large number of biologically active natural products.⁵ The isomerization process of these propargylic alcohols proceeds through a formal 1,3-shift of the hydroxyl moiety, known as the Meyer–Schuster rearrangement (Scheme 1).⁶

Scheme 1. Meyer–Schuster and Rupe Rearrangements of Propargylic Alcohols

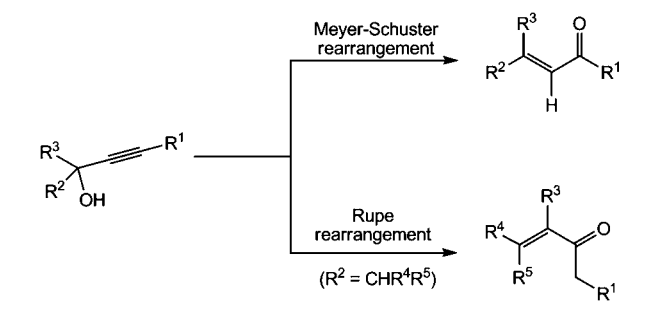

This method represents a significant upgrade to more traditional protocols for synthesis of α,β -unsaturated carbonyl compounds,⁷ which required the use of Brønsted acids under harsh reaction conditions, leading usually to nonregioselective transformations and poor functional group tolerance. In particular, starting from substrates able to undergo a competitive Rupe-type rearrangement (Scheme 1),⁸ nonregioselective transformations are usually observed.⁹ In this sense and with the gradual emergence of new catalysts, both the Meyer–Schuster and the Rupe rearrangements have gained a prominent role in organic synthesis,¹⁰ as clearly exemplified by their implication in (i) synthetic protocols for total synthesis of several natural organic products¹¹ and (ii) tandem processes


involving combination of these isomerization processes with other well-established synthetic organic reactions.^{12–15}

Despite the growing interest in this metal-catalyzed isomerization reaction, efforts devoted to develop catalytic systems able to operate in environmentally friendly solvents (i.e., water) have been scarce. In fact, only a very limited number of active catalysts in the Meyer–Schuster¹⁶ or Rupe¹⁷ rearrangement of propargylic alcohols in water have been described to date in the literature.¹⁸ This is particularly surprising considering (i) water is a safe, a nontoxic, an eco-friendly, and a cheap solvent,¹⁹ (ii) it may give rise to a completely new reactivity, and (iii) the strong acceleration effect and regioselectivity of many organic reactions in aqueous media have been previously reported.²⁰ With these precedents in mind and continuing with our studies aimed at exploiting the utility of new organometallic complexes containing the iminophosphorane ligands **3a**, **3b**, **4a**, and **4b** in metal-catalyzed organic reactions in water,^{3,21} herein we describe (i) the synthesis and characterization of the new one-dimensional Ag(I) coordination polymers $[\text{Ag}\{\mu^2\text{-}N,S\text{-}(\text{PTA})=\text{NP}(=\text{S})(\text{OR})_2\}_x][\text{SbF}_6]_x$ (**5a** and **5b**) and $[\text{Ag}\{\mu^2\text{-}O,S\text{-}(\text{DAPTA})=\text{NP}(=\text{S})(\text{OR})_2\}_x][\text{SbF}_6]_x$ (**6a** and **6b**), (ii) the high catalytic activity of complex **5a** for the regioselective isomerization of propargylic alcohols into α,β -unsaturated compounds with both terminal and internal alkynols, without addition of any cocatalyst, in water, under microwave irradiation and under air, and (iii) the recyclability of the catalytic system in water (up to 10 consecutive runs).

RESULTS AND DISCUSSION

Synthesis and Characterization of the New Silver(I) Coordination Polymers $[\text{Ag}\{\mu^2\text{-}N,S\text{-}(\text{PTA})=\text{NP}(=\text{S})(\text{OR})_2\}_x][\text{SbF}_6]_x$ (R = Et (5a**), Ph (**5b**)) and $[\text{Ag}\{\mu^2\text{-}O,S\text{-}(\text{DAPTA})=\text{NP}(=\text{S})(\text{OR})_2\}_x][\text{SbF}_6]_x$ (R = Et (**6a**), Ph (**6b**)).** Following our previous interest on the design of Ag(I) coordination polymers containing iminophosphorane ligands $[\text{Ag}\{\mu^2\text{-}S,S\text{-}(\text{CH}_2)_n[\text{P}\{\text{=NP}(=\text{S})(\text{OR})_2\}\text{Ph}_2]_2\}_x][\text{SbF}_6]_x$ ($n = 4, 6$)²² and our recent studies on coordination of the PTA–iminophosphorane ligands,^{3,21} we decided to investigate reaction of the iminophosphorane ligands **3a**, **3b**, **4a**, and **4b** with a silver(I) precursor.^{23,24} In this sense, we found that treatment of the silver(I) precursor AgSbF_6 with a stoichiometric

Scheme 2. Synthesis of the Silver(I) Complexes **5a, **5b**, **6a**, and **6b****

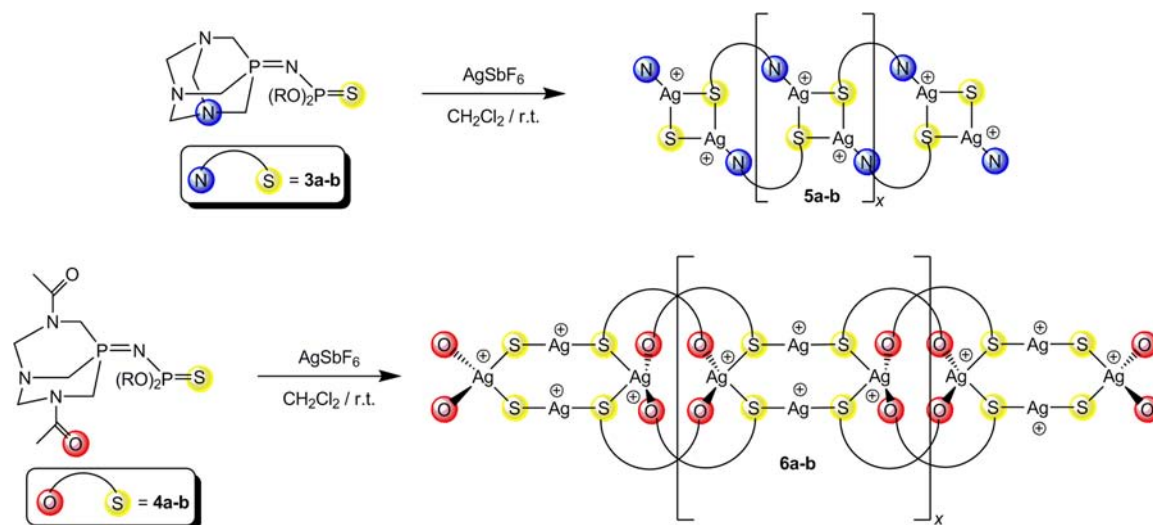

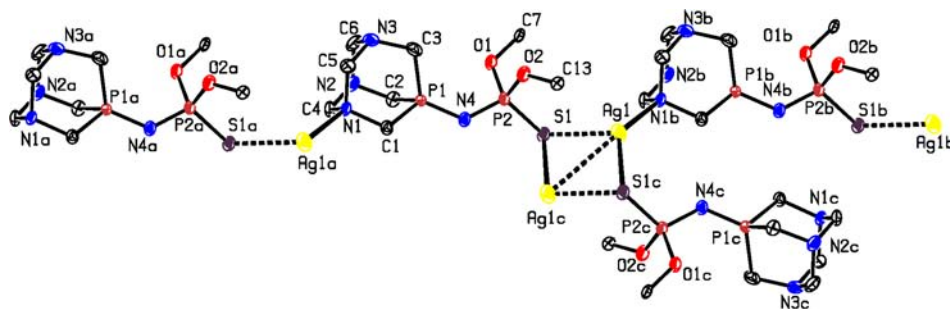


Figure 2. ORTEP-type view of the unit cell of compound **5b** showing the crystallographic labeling scheme. Hydrogen atoms, aryl groups (except the ipso carbons), and SbF_6^- anions have been omitted for clarity. Thermal ellipsoids are drawn at 10% probability level. Selected bond lengths (Angstroms): $\text{Ag}(1)\text{--S}(1) = 2.517(1)$; $\text{Ag}(1)\text{--S}(1c) = 2.680(1)$; $\text{Ag}(1)\text{--Ag}(1c) = 3.1548(8)$; $\text{Ag}(1)\text{--N}(1b) = 2.301(4)$; $\text{P}(1)\text{--N}(4) = 1.587(4)$; $\text{N}(4)\text{--P}(2) = 1.564(4)$; $\text{P}(2)\text{--S}(1) = 1.990(2)$. Selected bond angles (degrees): $\text{S}(1)\text{--Ag}(1)\text{--S}(1c) = 105.32(4)$; $\text{S}(1)\text{--Ag}(1)\text{--Ag}(1c) = 50.31(3)$; $\text{S}(1)\text{--Ag}(1c)\text{--Ag}(1) = 55.01(3)$; $\text{Ag}(1)\text{--S}(1)\text{--Ag}(1c) = 74.68(4)$; $\text{P}(1)\text{--N}(4)\text{--P}(2) = 127.0(3)$; $\text{N}(4)\text{--P}(2)\text{--S}(1) = 115.1(2)$; $\text{P}(2)\text{--S}(1)\text{--Ag}(1) = 102.33(6)$; $\text{P}(2)\text{--S}(1)\text{--Ag}(1c) = 115.56(7)$.

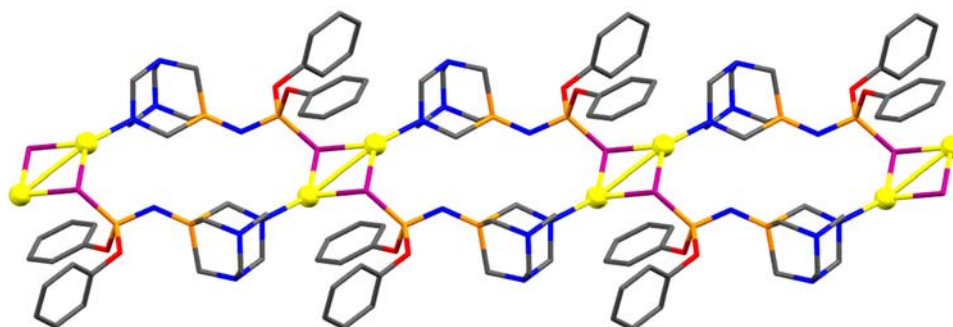


Figure 3. Part of the polymeric chain of complex **5b** showing formation of alternated fused 4- and 14-membered rings (yellow = silver; pink = sulfur; blue = nitrogen; orange = phosphorus; red = oxygen; gray = carbon).

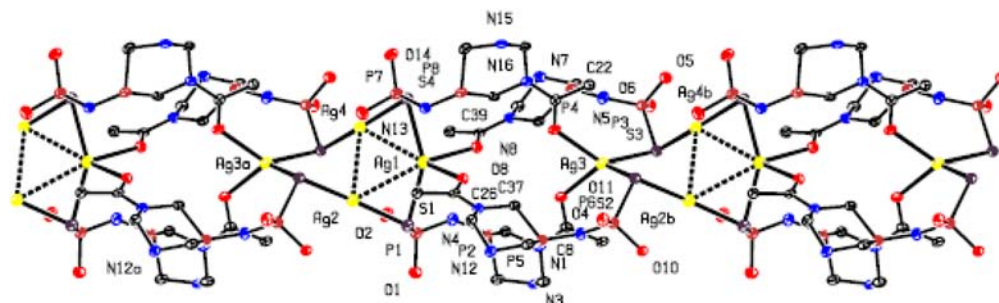


Figure 4. ORTEP-type view of the unit cell of compound **6a** showing the crystallographic labeling scheme. Hydrogen atoms, ethyl groups, the $\text{--}(\text{CH}_2)_2\text{N}(\text{C}(\text{=O})\text{CH}_3)_2\text{--}$ arm of the ligand **4a** that does coordinate to the silver atoms, and the SbF_6^- anions have been omitted for clarity. Thermal ellipsoids are drawn at 10% probability level. Selected bond lengths (Angstroms): $\text{Ag}(1)\text{--S}(1) = 2.515(3)$; $\text{Ag}(1)\text{--S}(4) = 2.531(3)$; $\text{Ag}(2)\text{--S}(1) = 2.371(3)$; $\text{Ag}(2)\text{--S}(2) = 2.391(3)$; $\text{Ag}(3)\text{--S}(2) = 2.607(3)$; $\text{Ag}(3)\text{--S}(3) = 2.606(3)$; $\text{Ag}(4)\text{--S}(3) = 2.405(3)$; $\text{Ag}(4)\text{--S}(4) = 2.389(3)$; $\text{Ag}(1)\text{--O}(8) = 2.384(7)$; $\text{Ag}(1)\text{--O}(9) = 2.394(8)$; $\text{Ag}(3)\text{--O}(4) = 2.346(8)$; $\text{Ag}(3)\text{--O}(16) = 2.339(8)$; $\text{Ag}(1)\text{--Ag}(2) = 3.124(1)$; $\text{Ag}(1)\text{--Ag}(4) = 3.015(1)$; $\text{Ag}(2)\text{--Ag}(4) = 3.074(2)$; $\text{P}(1)\text{--N}(4) = 1.58(1)$; $\text{P}(2)\text{--N}(4) = 1.57(1)$; $\text{P}(3)\text{--N}(5) = 1.56(1)$; $\text{P}(4)\text{--N}(5) = 1.576(9)$; $\text{P}(5)\text{--N}(10) = 1.589(9)$; $\text{P}(6)\text{--N}(10) = 1.555(9)$; $\text{P}(7)\text{--N}(13) = 1.575(9)$; $\text{P}(8)\text{--N}(13) = 1.58(1)$; $\text{C}(8)\text{--O}(4) = 1.25(1)$; $\text{C}(25)\text{--O}(8) = 1.24(1)$; $\text{C}(26)\text{--O}(9) = 1.24(1)$; $\text{C}(51)\text{--O}(16) = 1.23(1)$. Selected bond angles (degrees): $\text{S}(1)\text{--Ag}(1)\text{--S}(4) = 150.5(1)$; $\text{Ag}(1)\text{--S}(4)\text{--Ag}(4) = 75.54(9)$; $\text{S}(4)\text{--Ag}(4)\text{--S}(3) = 164.9(1)$; $\text{Ag}(4)\text{--S}(3)\text{--Ag}(3) = 102.3(1)$; $\text{S}(3)\text{--Ag}(3)\text{--S}(2) = 96.71(9)$; $\text{Ag}(3)\text{--S}(2)\text{--Ag}(2) = 102.8(2)$; $\text{S}(2)\text{--Ag}(2)\text{--S}(1) = 167.6(1)$; $\text{S}(1)\text{--Ag}(1)\text{--O}(8) = 114.3(2)$; $\text{S}(1)\text{--Ag}(1)\text{--O}(9) = 87.0(2)$; $\text{S}(4)\text{--Ag}(1)\text{--O}(8) = 89.0(2)$; $\text{S}(4)\text{--Ag}(1)\text{--O}(9) = 115.5(2)$; $\text{O}(8)\text{--Ag}(1)\text{--O}(9) = 81.2(3)$; $\text{S}(2)\text{--Ag}(3)\text{--O}(4) = 129.0(2)$; $\text{S}(2)\text{--Ag}(3)\text{--O}(16) = 108.0(2)$; $\text{S}(3)\text{--Ag}(3)\text{--O}(4) = 112.3(2)$; $\text{S}(3)\text{--Ag}(3)\text{--O}(16) = 132.6(2)$; $\text{O}(4)\text{--Ag}(3)\text{--O}(16) = 82.6(3)$.

metric amount of the PTA-based iminophosphorane ligands **3a** and **3b**, in dichloromethane at room temperature, leads to selective formation of polymeric complexes $[\text{Ag}\{\mu^2\text{-N,S-}(\text{PTA})\text{=NP(=S)(OR)}_2\}]_x[\text{SbF}_6]_x$ ($\text{R} = \text{Et}$ (**5a**), Ph (**5b**); 76–79%, Scheme 2). Both **5a** and **5b** are formed via selective bidentate (i) S-coordination of the N-thiophosphoryl fragment and (ii) N-coordination of one nitrogen atom from the

adamantane ring. In contrast, the DAPTA-base iminophosphorane ligands **4a** and **4b** containing carbonyl groups ($\text{C}(\text{=O})\text{CH}_3$) generate, under the same reaction conditions, new polymeric derivatives $[\text{Ag}\{\mu^2\text{-O,S-}(\text{DAPTA})\text{=NP(=S)-}(\text{OR)}_2\}]_x[\text{SbF}_6]_x$ ($\text{R} = \text{Et}$ (**6a**), Ph (**6b**); 87–91%, Scheme 2) via selective bidentate (i) S-coordination of the N-

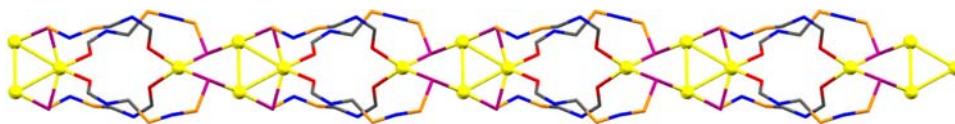


Figure 5. Core of the polymeric double chain of complex **6a** showing only the atoms involved in the chain (yellow = silver; pink = sulfur; blue = nitrogen; orange = phosphorus; red = oxygen; gray = carbon).

thiophosphoryl fragment and in this case (ii) *O*-coordination of the oxygen atom of the C(=O)CH₃ unit.

Compounds **5a**, **5b**, **6a**, and **6b** have been isolated in high yields as air- and light-stable white solids that behave as 1:1 electrolytes in acetone solutions ($\Lambda_M = 105\text{--}115 \text{ } \Omega^{-1}\cdot\text{cm}^{-2}\cdot\text{mol}^{-1}$). As we previously described for the iminophosphorane Cu(I) coordination polymers [Cu{ μ^2 -*N,S*-(PTA)=NP(=S)(OR)₂}₂]_x[PF₆]_x,³ we found that only complexes **5** and **6a**, which contain ethyl groups in the *N*-thiophosphorylated units –P(=S)(OEt)₂, were soluble in water (*S*_{25 °C} values of 5.0 and 7.0 mg mL⁻¹, respectively), while complexes **5** and **6b** were scarcely soluble in water. Complexes **5a**, **5b**, **6a**, and **6b** have been characterized by means of standard spectroscopic techniques [IR and ³¹P{¹H}, ¹H, and ¹³C{¹H} NMR] and elemental analysis, which support the proposed formulations. Complexation of ligands **3a**, **3b**, **4a**, and **4b** to silver is reflected in the ³¹P{¹H} NMR spectra of **5a**, **5b**, **6a**, and **6b** (see Experimental Section) by slight variations in the P=N [$\Delta\delta = 3\text{--}9$ ppm; $\delta_p = -31.94$ to -10.92 ppm] and (RO)₂P=S [$\Delta\delta = 2\text{--}5$ ppm; $\delta_p = 49.90\text{--}55.46$ ppm] resonances. As expected, ¹H and ¹³C{¹H} NMR spectra display the corresponding phosphine backbone signals of PTA and DAPTA. The observed preference for *S*- vs *N*-coordination of the iminophosphoranyl units P=N–P(=S)(OR)₂ in complexes **5a**, **5b**, **6a**, and **6b** is in complete accord with the well-known coordination chemistry of *N*-thiophosphorylated iminophosphoranes R₃P=N–P(=S)(OR)₂, which is almost entirely dominated by coordination of the sulfur atom.²⁵ Although formation of formally 1:1 adducts of the starting reagents [AgSbF₆·ligand] is readily deduced from their elemental analysis (details are given in Experimental Section), the real nature of these complexes could only be determined by single-crystal X-ray diffraction methods. Drawings of the unit cell and polymeric chains of complexes **5b** and **6a** are shown in Figures 2–4; selected bonding parameters for **5b** and **6a** are listed in the captions of Figures 2 and 4, respectively.

Concerning the structure of complex **5b** (see Figure 2), the unit cell corresponds to the fragment [Ag{ μ^2 -*N,S*-(PTA)=NP(=S)(OR)₂}₄][SbF₆]₄ containing four silver atoms and four ligands (PTA)=NP(=S)(OPh)₂ (**3b**), which gives rise to a polymeric double chain along the *z* axis. Thus, this X-ray analysis unambiguously confirms formation of a 14-membered dimetalla ring formed by two silver atoms bridged by two iminophosphorane ligands in a head-to-tail conformation. The coordination sphere around silver consists of (i) one *S*-coordinated (PhO)₂P=S unit, as suggested by the ³¹P{¹H} NMR data, and (ii) one *N*-coordinated amino group from the aminophosphine ring. The Ag(1)–S(1) (2.517(1) Å) bond length inside the 14-membered dimetalla ring is longer than those previously described for Ag(I) complexes containing *S*-coordinated *N*-thiophosphorylated bis(iminophosphorane) ligands²² (Ag–S = 2.324(3)–2.449(2) Å) but compare well with those shown by Ag(I) complexes containing *S*-coordinated phosphine–sulfides.²⁶ In contrast, the Ag(1)–N(1b) (2.301(4) Å) bond length is smaller than those previously described for

(i) the silver(I) complex [Ag(PTA)(H₂O)][NO₃] (Ag–N = 2.441(4) and 2.468(4) Å) with tridentate *P,N,N'*-coordinated PTA in a polymeric net structure^{2b} and (ii) the mixed-metal Ag(I)/Ru(II) water-soluble organometallic polymer [CpRu(H₂O)(μ^2 -*P,N*-PTA)₂AgCl₂]_x (Ag–N = 2.423(6) Å).^{2a}

Remarkably, intermolecular silver–sulfur interactions take place leading to a polymeric chain with alternating 14-membered (Ag–S–P–N–P–C–N–Ag–S–P–N–P–C–N) and 4-membered (Ag–S–Ag–S) dimetalla fused rings (see Figure 3). The Ag(1)–S(1c) (2.680(1) Å) bond length can be reasonably regarded as a real bonding interaction since it falls within the accepted range for single Ag–S bonds (ca. 2.2–3.0 Å).^{22,26} A weak silver–silver contact is also present in the polymer (Ag(1)–Ag(1a) = 3.1548(8) Å).²⁷ The existence of all these intermolecular bonding interactions is clearly reflected in the S(1)–Ag(1)–S(1c) angle, which deviates considerably from the expected linearity (105.32(4)°). It is also interesting to note that bond distances within the P=N–P=S framework are almost identical (ca. ±0.02 Å) to those found in the structure of the free ligand **3b**,³ indicating that electronic delocalization of the nitrogen lone pair is maintained upon coordination of the thiophosphoryl unit to the metal.


In contrast to **5b**, the unit cell of complex **6a** corresponds to the fragment [Ag{ μ^2 -*S,O*-(DAPTA)=NP(=S)(OEt)₂}₁₂][SbF₆]₁₂ (see Figure 4), which contains 12 silver atoms and 12 ligands (DAPTA)=NP(=S)(OEt)₂ (**4a**). Selective μ^2 -*S,O* coordination of the *N*-thiophosphoryl ((EtO)₂P=S) and carbonylic (C(=O)CH₃) units of the iminophosphorane ligand **4a** is observed, which acts as a bridge between the silver atoms, while the nitrogen atoms of the aminophosphine remain uncoordinated. To our knowledge, **6a** represents the first example of an organometallic complex that shows *O*-coordination of DAPTA to a metal.²⁸ X-ray crystallographic analysis revealed formation of an eight-membered ring (Ag–S–Ag–S–Ag–S–Ag–S)²⁹ in which three of the silver atoms (Ag(1), Ag(2), and Ag(4)) are closer [with small Ag–S interactions; Ag(1)–S(1) = 2.514(3) Å, Ag(1)–S(4) = 2.531(3) Å, Ag(2)–S(1) = 2.371(3) Å, Ag(4)–S(4) = 2.389(3) Å], adopting a triangle-like disposition,³⁰ while the fourth silver atom (Ag(3)) is located further away, bridged to the Ag(2) and Ag(4) atoms by a longer Ag–S interaction (Ag(3)–S(2) = 2.607(3) Å, Ag(3)–S(3) = 2.606(3) Å). All these Ag–S contacts compare well with those previously described for the polymeric structure of the Ag(I) complex **5b** (see caption of Figure 2). The three Ag–Ag bond lengths [Ag(1)–Ag(2) = 3.124(1) Å, Ag(2)–Ag(4) = 3.074(1) Å, Ag(4)–Ag(1) = 3.015(1) Å] are consistent with the presence of weak silver–silver contacts as in polymer **5b**.²⁷ It should be noticed that the central silver atoms (Ag(2) and Ag(4)) of the eight-membered ring adopt a pseudolinear arrangement [S(1)–Ag(2)–S(2) = 167.6(1)° and S(3)–Ag(4)–S(4) = 164.9(1)°], while the terminal silver atoms display a distorted tetrahedral geometry [subtending bond angles from 82.6(3)° (O(4)–Ag(3)–O(16)) to 132.6(2)° (O(16)–Ag(3)–S(3)) (mean 110.2°) for Ag(3) and from 81.2(3)° (O(8)–Ag(1)–O(9)) to

150.5(1)° (S(1)–Ag(1)–S(4)) (mean 106.3° for Ag(1)). These tetracoordinated silver(I) atoms (Ag(3) and Ag(1)) allow the connection of two eight-membered rings (Ag₄S₄) through the O-coordination of the carbonylic unit (C(=O)CH₃) of the iminophosphorane ligand **4a**, giving rise to a polymeric double chain (see Figure 5) along the *y* axis. The Ag–O bond lengths [from 2.339(8) Å for Ag(3)–O(16) to 2.394(8) Å for Ag(1)–O(9)] fall within the previously reported values for silver(I) complexes containing O-coordinated carbonylic (NC(=O)R) fragments.³¹ As we have previously seen in the case of the free iminophosphorane ligands³ and in the aforementioned polymeric Ag(I) complex **5b** (see Figure 2), the bond distances within the P=N–P=S framework are again almost identical (ca. ±0.02 Å, see caption to Figure 4), indicating that electronic delocalization of the nitrogen lone pair is maintained upon coordination of the thiophosphoryl unit to the metal. As expected, the C=O bond distances in **6b** [from 1.23(1) (C(51)–O(16)) to 1.24(1) Å (C(8)–O(4))] are slightly longer than those previously observed in the free ligand **4b** (ca. 1.222 Å).³

In order to gain more information about the integrity and nature of the species present in aqueous solution, electrospray ionization (ESI) mass spectrometric measurements of a solution of **5a** in water were performed.³² Positive ESI mass spectra recorded upon gentle ionization conditions (cone voltage *U_c* = 10 V) revealed the presence of a variety of Ag-containing species readily identified on the basis of their characteristic isotopic pattern. The base peak corresponds to the [Ag{(PTA)=NP(=S)(OEt)₂}]⁺ cation at *m/z* 755.0, and additional (i) monomeric species formulated as [Ag{(PTA)=NP(=S)(OEt)₂}]⁺ (*m/z* 431.0) and [Ag{(PTA)=NP(=S)(OEt)₂}(H₂O)]⁺ (*m/z* = 449.0) (ii) and dimeric [Ag₂{(PTA)=NP(=S)(OEt)₂}]²⁺ (*m/z* 593.0) were also observed. Assignments were based on accurate *m/z* determinations as well as comparison of simulated an experimental isotopic pattern (see Figures ESI-1 and ESI-2 in the Supporting Information). Interestingly, mononuclear complexes were observed as dominant species in solution, suggesting that unlike in the solid state complex **5a** is dismantled in aqueous solution to give predominantly monomeric species. It is apparent that these monomeric species are readily formed and therefore can be proposed as the active catalytic species in aqueous medium (see below).

Isomerization of Propargylic Alcohols into α,β -Unsaturated Carbonyl Compounds Catalyzed by the Cationic Ag(I) Compound [Ag{ μ^2 -*N,S*-(PTA)=NP(=S)(OEt)₂}]_x[SbF₆]_x (5a**).** Although in recent years Ag(I) complexes containing water-soluble PTA ligands have been screened for their potential antimicrobial activity^{21,24} and luminescent properties,²¹ their applications as catalysts for organic transformations in water are virtually unknown.³³ With this precedent in mind, we decided to test the silver(I) coordination polymers **5a**, **5b**, **6a**, and **6b** as potential catalyst precursors in the Meyer–Schuster rearrangement of propargylic alcohols in aqueous media^{34,35} using the isomerization of the commercially available 1,1-diphenyl-2-propyn-1-ol (**7a**) into 3,3-diphenylpropenal (**8a**) as a model reaction (see Scheme 3). Thus, in a typical experiment, the corresponding Ag(I) precursor (1 mol % of Ag) and the propargylic alcohol **7a** were added to 1 mL of water under air using as the heating source microwave irradiation at 160 °C,³⁶ the course of the reaction being monitored by gas chromatography. Pleasingly, all Ag(I) complexes tested were found to be active and selective

Scheme 3. Ag(I)-Catalyzed Isomerization of 1,1-Diphenyl-2-propyn-1-ol (**7a**) to 3,3-Diphenylpropenal (**8a**) Catalyzed by Complexes **5a**, **5b**, **6a**, and **6b**^a




^aReactions were performed under air with microwave irradiation at 160 °C in water and using 1 mmol of the alkynol **7a**. [Substrate]/[Ag] ratio = 100:1.

catalysts in water, affording 3,3-diphenylpropenal (**8a**) as the unique reaction product. Interestingly, the catalytic activity of complex **5a** (containing the ligand PTA–iminophosphorane) is higher than that of complex **6a** (containing the ligand DAPTA–iminophosphorane) [45 min (99%) vs 1.5 h (97%)]. A similar catalytic trend has also been found in their water-insoluble counterpart catalysts **5b** and **6b** [1 h (98%) vs 3 h (96%)], demonstrating the influence of the iminophosphorane ligand on the reaction rate. The presence of catalytic amounts of silver(I) complexes **5a**, **5b**, **6a**, and **6b** was found to be essential as no isomerization reaction was observed in their absence. Use of other reaction conditions (like, for example, conventional heating, lower temperatures, and/or lower catalyst loadings) slowed down the reaction considerably; as an example, using 1 mol % of complex **5a** in refluxing water, 20% conversion of 1,1-diphenyl-2-propyn-1-ol into 3,3-diphenylpropenal was only achieved after 24 h. At this point it should be noticed that under similar reactions conditions (1 mol % of catalyst loading, in water, at 160 °C, and under microwave irradiation) InCl₃ is able to catalyze the isomerization reaction of the alkynol **7a** into the corresponding enal **8a** in a shorter reaction time (5 min).^{16h}

Under these optimized reaction conditions, the most active Ag(I) complex [Ag{ μ^2 -*N,S*-(PTA)=NP(=S)(OEt)₂}]_x[SbF₆]_x (**5a**) was found to be an efficient catalyst precursor for selective isomerization of a large number of other terminal propargylic alcohols, highlighting the wide substrate scope and synthetic utility of this catalytic transformation. Thus, as observed for 1,1-diphenyl-2-propyn-1-ol (entry 1 in Table 1), other tertiary alkynols **7b–f** underwent selective isomerization into the corresponding enals **8b–f**, which could be isolated after appropriate chromatographic workup in excellent yields (91–95%; entries 1–5 in Table 1). An influence of the electronic properties of the aryl rings on the reaction rates was observed. Thus, alkynols with electron-withdrawing groups showed less reactivity (entry 4) as compared to substrates with electron-donating substituents (entry 5). It is important to note that for the propargylic alcohol 2-phenyl-3-butyn-2-ol (**7f**, entry 6), in which the isomerization process can proceed through the competitive Rupe-type rearrangement to generate the corresponding α,β -unsaturated enone (see Scheme 1), exclusive formation of the α,β -unsaturated enal **8f** as a mixture of the corresponding *E* and *Z* stereoisomers in a ca. 3:2 ratio was observed.³⁷ Secondary terminal alkynols (entries 7 and 8, Table 1) can also be efficiently and selectively isomerized into the corresponding enals using complex [Ag{ μ^2 -*N,S*-(PTA)=NP(=S)(OEt)₂}]_x[SbF₆]_x (**5a**) as catalyst in water. Again, reactions proceeded to completion in the absence of any cocatalyst. Interestingly, resulting enals **7g–h** were exclusively obtained as the thermodynamically more stable *E* isomers.³⁸

Table 1. Isomerization of Terminal Propargylic Alcohols 7a–h into Enals 8a–h Catalyzed by Complex [Ag(μ^2 -N,S-(PTA)=NP(=S)(OEt)₂)_x][SbF₆]_x (5a) in Water^a




entry	substrate 7	T [min]	yield of 8 ^b
1	R ¹ = R ² = Ph (7a)	45	8a; 99 (95)
2	R ¹ R ² = 2,2'-C ₆ H ₄ -C ₆ H ₄ (7b)	30	8b; 95 (91)
3	R ¹ R ² = 2,2'-C ₆ H ₄ -CH=CH-C ₆ H ₄ (7c)	30	8c; 97 (92)
4	R ¹ = R ² = 4-C ₆ H ₄ F (7d)	300	8d; 99 (95)
5	R ¹ = R ² = 4-C ₆ H ₄ Me (7e)	15	8e; 98 (93)
6	R ¹ = Ph, R ² = Me (7f)	90	8f; 97 (91) ^c
7	R ¹ = Ph, R ² = H (7g)	300	8g; 99 (91)
8	R ¹ = 2-naphthyl, R ² = H (7h)	240	8h; 97 (93)

^aReactions were performed under air in a CEM Discover S-Class microwave synthesizer at 160 °C through moderation of the initial power (300 W). A 1 mmol amount of the corresponding alkynol was used (1 mL of water). [Substrate]/[Ag] ratio = 100:1. ^bDetermined by GC. Isolated yields after chromatographic workup are given in brackets. ^cA mixture of *E* and *Z* isomers in ca. 3:2 ratio is formed.

Use of MW heating has received considerable attention as a new method for one-pot synthesis of silver nanostructures in solution.³⁹ In all the catalytic reactions listed in Table 1, formation of silver nanoparticles was studied by means of TEM (transmission electron microscopy) or SEM/EDX (scanning electron microscopy/energy-dispersive X-ray spectroscopy) techniques (see Supporting Information), and silver nanoparticles were detected in the reaction (see Supplementary Information). Thus and in order to determine whether the process is really homogeneous, isomerization of the propargylic alcohol 7a into the enal 8a promoted by the silver(I) complex 5a, in the presence of Hg, was studied. The Hg-poisoned catalytic reactions proceed with the same conversion (99%, 45 min), thus suggesting that the formed silver nanoparticles do not play a role in this catalytic transformation. This Hg(0)-poisoning test is the most direct method to distinguishing homogeneous from heterogeneous catalysis when transition metals able to form an amalgam are employed.⁴⁰ In line with this, the isolated silver nanoparticles generated from complex 5a showed no catalytic activity toward formation of the desired enal 8a. These experimental facts seem to indicate that possible catalysis by silver nanoparticles is not involved in this isomerization process.

Finally, and as shown in Table 2, it is also worth noting that the activity of complex 5a is not restricted to terminal alkynols, as the internal propargylic alcohols 9a–d can be also efficiently transformed into the corresponding enones 10a–d. As previously observed, complete *E* stereoselectivity was once again reached starting from secondary alcohols. The limitation of this methodology concerns the use of primary propargylic alcohols RC≡CCH₂OH, which under standard reaction conditions give rise to intractable polymeric materials.⁴¹ The observed catalytic activity of complex 5a with internal alkynols seems to indicate that silver(I) hydroxyvinylidene derivatives are not involved as key intermediate complexes in this isomerization reaction.⁴² In this sense, a possible dehydration/hydration sequence through a carbocation intermediate is in accord with the experimental fact that electron-rich aryl

Table 2. Isomerization of Internal Propargylic Alcohols 9a–d into Enones 10a–d Catalyzed by Complex [Ag(μ^2 -N,S-(PTA)=NP(=S)(OEt)₂)_x][SbF₆]_x (5a) in Water^a




entry	substrate 9	T [min]	yield of 10 ^b
1	R ¹ = R ² = R ³ = Ph (9a)	15	10a; 99 (92)
2	R ¹ = Me; R ² = Ph; R ³ = H (9b)	60	10b; 96 (90)
3	R ¹ = Me; R ² = 4-C ₆ H ₄ OMe; R ³ = H (9c)	90	10c; 96 (91)
4	R ¹ = Ph; R ² = Ph; R ³ = H (9d)	30	10d; 99 (94)

^aReactions were performed under air in a CEM Discover S-Class microwave synthesizer at 160 °C through moderation of the initial power (300 W). A 1 mmol amount of the corresponding alkynol was used (1 mL of water). [Substrate]/[Ag] ratio = 100:1. ^bDetermined by GC. Isolated yields after chromatographic workup are given in brackets.

groups on the propargylic alcohol were more reactive than propargylic alcohols with electron-poor aryl groups (see Table 1).¹⁰

It is well known that one of the major advantages associated with the use of water as reaction media in metal-catalyzed organic reactions is the possibility of recycling the catalyst previous separation of the organic product formed by simple extraction with organic solvents (without the need of recovering the catalyst; see the general procedure for catalyst recycling in the Supporting Information).²⁰ In addition, the lifetime of a catalytic system and its level of reusability are very important factors.⁴³ Thus, under the aforementioned reaction conditions (Tables 1 and 2) and using as a model reaction isomerization of the propargylic alcohol 7a, we found that the catalytic system remains active (97–99% yield) after recycling up to 10 consecutive times (see Table 3) with a gradual decrease of the activity after each recycling. Thus, for the first five cycles less than 2 h was needed to achieve quantitative conversion, while more than 3 h was required after the fifth cycle, probably due to both leaching during workup and decomposition of the catalyst.

Table 3. Ag(I)-Catalyzed Isomerization of the Propargylic Alcohol 7a into Enal 8a in Water: Catalyst Recycling^a



cycle	T [min]	yield ^b	TON ^c	cycle	T [min]	yield	TON ^c
1	45	99	99	6	180	99	592
2	60	99	198	7	180	98	690
3	60	99	297	8	240	99	789
4	90	99	396	9	300	99	1089
5	90	97	493	10	360	97	1189

^aReactions were performed under air in a CEM Discover S-Class microwave synthesizer at 160 °C through moderation of the initial power (300 W). A 1 mmol amount of the corresponding alkynol was used (1 mL of water). [Substrate]/[Ag] ratio = 100:1. ^bDetermined by GC. ^cCumulative TON values (turnover number = (mol of product/mol of Ag)).

CONCLUSION

In summary, in the present work we described the use, for the first time, of PTA- or DAPTA-base iminophosphorane ligands as versatile building blocks for high-yield synthesis of a series of new Ag(I) coordination polymers $[Ag\{\mu^2-N,S-(PTA)=NP(=S)(OR)_2\}_x[SbF_6]_x$ (R = Et (**5a**), Ph (**5b**)) and $[Ag\{\mu^2-O,S-(DAPTA)=NP(=S)(OR)_2\}_x[SbF_6]_x$ (R = Et (**6a**), Ph (**6b**)). To our knowledge, complexes **6a** and **6b** represent the first examples in which coordination of the acetyl group of DAPTA is achieved. In addition, we have also shown that the complex $[Ag\{\mu^2-N,S-(PTA)=NP(=S)(OEt)_2\}_x[SbF_6]_x$ (**5a**), always in neutral conditions, is a highly efficient catalyst precursor for isomerization of both terminal and internal propargylic alcohols into α,β -unsaturated carbonyl compounds, which can be obtained in excellent yields in water. This catalytic system has also proven to promote chemoselective transformations producing enals (terminal alkynols) or enones (internal alkynols) depending on the nature of the propargylic alcohol. Finally, we must also note that (i) the highly effective catalyst recycling observed using water as solvent and (ii) the total atom economy of this process are in good agreement with the principles of so-called "Green Chemistry".¹⁹

EXPERIMENTAL SECTION

General Comments. All reagents were obtained from commercial suppliers and used without further purification with the exception of compounds $(PTA)=NP(=S)(OR)_2$ (R = Et (**3a**), Ph (**3b**)) and $(DAPTA)=NP(=S)(OR)_2$ (R = Et (**4a**), Ph (**4b**)), which were prepared by the following methods reported in the literature.³ Propargylic alcohols **7a–h** and **9a–d** were obtained from commercial suppliers or synthesized following the classical Midlands procedure.⁴⁴ Infrared spectra were recorded on a Perkin-Elmer 1720-XFT spectrometer. For electrospray ionization mass spectrometry (ESI-MS) studies, a QTOF Premier instrument with an orthogonal Z-spray-electrospray interface (Waters, Manchester, U.K.) was used operating in the W mode at a resolution of ca. 15 000 (fwhm). The drying and cone gas was nitrogen set to flow rates of 300 and 30 L/h, respectively. A capillary voltage of 3.5 kV was used in the positive scan mode, and the cone voltage was set to $U_c = 10$ V. For accurate mass measurements, a 2 mg/L standard solution of leucine enkephalin was introduced via the lock spray needle at a cone voltage set to 45 V and a flow rate of 30 μ L/min. C, H, and N analyses were carried out with a Perkin-Elmer 2400 microanalyzer. NMR spectra were recorded on a Bruker DPX300 instrument at 300 (¹H), 121.5 (³¹P), and 75.4 MHz (¹³C) using SiMe₄ or 85% H₃PO₄ as standards. DEPT experiments have been carried out for all compounds reported in this paper.

Preparations. *Synthesis of Ag(I) Coordination Polymers* ($[Ag\{\mu^2-N,S-(PTA)=NP(=S)(OR)_2\}_x[SbF_6]_x$ (R = Et (**5a**), Ph (**5b**)) and $[Ag\{\mu^2-O,S-(DAPTA)=NP(=S)(OR)_2\}_x[SbF_6]_x$ (R = Et (**6a**), Ph (**6b**)). A solution of the corresponding iminophosphorane ligands **3a**, **3b**, **4a**, and **4b** (1 mmol) in 30 mL of CH₂Cl₂ was treated with AgSbF₆ (0.343 g, 1 mmol) and stirred for 1 h to yield a pale-yellow clear solution. The solvent was then concentrated (ca. 1 mL) in vacuo, and addition of diethyl ether (ca. 50 mL) precipitated a white solid, which was washed with diethyl ether (3 \times 10 mL) and dried in vacuo. **5a**: Yield 76% (0.508 g). Anal. Calcd for AgC₁₀H₂₂F₆N₄O₂P₂SbS: C, 17.98; H, 3.32; N, 8.39. Found: C, 18.04; H, 3.29; N 8.45. Conductivity (acetone, 20 °C): 105 $\Omega^{-1}\cdot\text{cm}^2\cdot\text{mol}^{-1}$. IR (KBr, cm⁻¹): ν 542 (w), 594 (s), 660 (vs), 744 (m), 783 (m), 818 (m), 834 (m), 907 (m), 942 (s), 972 (s), 1010 (vs), 1096 (m), 1161 (m), 1238 (s), 1299 (s), 1369 (m), 1391 (m), 1412 (m), 1447 (m), 1473 (w), 1521 (m), 1635 (w), 1700 (w), 2090 (w), 2984 (m). ³¹P{¹H} NMR ((CD₃)₂C=O): δ -31.94 (d, ²J_{PP} = 2.4 Hz, Ph₂P=N), 53.62 (d, ²J_{PP} = 2.4 Hz, (RO)₂P=S) ppm. ¹H NMR ((CD₃)₂C=O): δ 1.39 (t, 6H, ³J_{HH} = 6.9 Hz, OCH₂CH₃), 4.18 (m, 4H, OCH₂CH₃), 4.47 (d, 6H, ²J_{HP} = 9.4 Hz, PCH₂N), 4.52 and 4.63 (AB spin system, 3H each, ¹J_{HA,HB} = 15.5 Hz, NCH₂N) ppm.

¹³C{¹H} NMR ((CD₃)₂C=O): δ 15.63 (d, ³J_{CP} = 9.7 Hz, OCH₂CH₃), 53.49 (dd, ¹J_{CP} = 50.6 Hz, ³J_{CP} = 2.8 Hz, PCH₂N), 64.60 (d, ²J_{CP} = 7.4 Hz, OCH₂CH₃), 71.98 (d, ³J_{CP} = 9.9 Hz, NCH₂N) ppm. **5b**: Yield 79% (0.603 g). Anal. Calcd for AgC₁₈H₂₂F₆N₄O₂P₂SbS: C, 28.30; H, 2.90; N, 7.33. Found: C, 28.22; H, 2.96; N 7.40. Conductivity (acetone, 20 °C): 110 $\Omega^{-1}\cdot\text{cm}^2\cdot\text{mol}^{-1}$. IR (KBr, cm⁻¹): ν 584 (w), 605 (s), 639 (s), 714 (m), 760 (m), 797 (m), 827 (m), 903 (m), 939 (m), 991 (s), 1073 (s), 1087 (w), 1127 (m), 1205 (s), 1297 (s), 1363 (m), 1412 (w), 1507 (w), 1538 (m), 1583 (w), 1669 (w), 1739 (m), 2096 (m), 2974 (m), 3041 (w). ³¹P{¹H} NMR ((CD₃)₂C=O): δ -28.90 (bs, Ph₂P=N), 49.99 (bs, (RO)₂P=S) ppm. ¹H NMR ((CD₃)₂C=O): δ 4.35 (d, 6H, ²J_{HP} = 9.7 Hz, PCH₂N), 4.52 and 4.61 (AB spin system, 3H each, ¹J_{HA,HB} = 13.3 Hz, NCH₂N), 7.30–7.51 (m, 10H, CH_{arom}) ppm. ¹³C{¹H} NMR ((CD₃)₂C=O): δ 53.58 (d, ¹J_{CP} = 51.5 Hz, PCH₂N), 72.59 (d, ³J_{CP} = 9.5 Hz, NCH₂N), 121.88–131.18 (m, CH_{arom}), 151.74 (d, ²J_{CP} = 8.5 Hz, C_{ipso} of OPh) ppm. **6a**: Yield 87% (0.644 g). Anal. Calcd for AgC₁₃H₂₆F₆N₄O₄P₂SbS: C, 21.10; H, 3.54; N, 7.57. Found: C, 21.17; H, 3.56; N 7.61. Conductivity (acetone, 20 °C): 110 $\Omega^{-1}\cdot\text{cm}^2\cdot\text{mol}^{-1}$. IR (KBr, cm⁻¹): ν 483 (w), 591 (m), 623 (m), 659 (s), 702 (w), 753 (s), 781 (s), 839 (w), 894 (s), 956 (s), 989 (s), 1042 (vs), 1095 (w), 1123 (w), 1161 (m), 1223 (vs), 1261 (s), 1303 (s), 1333 (s), 1355 (m), 1428 (s), 1651 (vs), 2929 (w), 2981 (w). ³¹P{¹H} NMR ((CD₃)₂C=O): δ -10.92 (d, ²J_{PP} = 13.7 Hz, Ph₂P=N), 53.30 (d, ²J_{PP} = 13.7 Hz, (RO)₂P=S) ppm. ¹H NMR ((CD₃)₂C=O): δ 1.33 (t, 6H, ³J_{HH} = 6.9 Hz, OCH₂CH₃), 2.09 and 2.12 (s, 3H each, COCH₃), 3.78 (m, 1H, NCH₂N), 4.18 (m, 8H, 4H for OCH₂CH₃ and 4H for PCH₂NCO), 4.71 and 5.10 (d, 1H each, ¹J_{HH} = 14.0 Hz, NCH₂N), 4.88 (m, 1H, PCH₂N), 5.66 (m, 2H, 1H for NCH₂N and 1H for PCH₂N). ¹³C{¹H} NMR ((CD₃)₂C=O): δ 21.27 (d, ³J_{CP} = 8.5 Hz, OCH₂CH₃), 26.33 and 26.74 (s, COCH₃), 45.73 (dd, ¹J_{CP} = 70.2 Hz, ³J_{CP} = 4.0 Hz, PCH₂N), 50.94 (dd, ¹J_{CP} = 69.4 Hz, ³J_{CP} = 4.8 Hz, PCH₂N), 56.05 (dd, ¹J_{CP} = 59.9 Hz, ³J_{CP} = 2.1 Hz, PCH₂N), 66.79 and 72.02 (d, ³J_{CP} = 6.9 Hz, NCH₂N), 68.48 (d, ²J_{CP} = 6.9 Hz, OCH₂CH₃), 174.51 and 174.95 (s, COCH₃) ppm. **6b**: Yield 91% (0.761 g). Anal. Calcd for AgC₂₁H₂₆F₆N₄O₄P₂SbS: C, 30.17; H, 3.13; N, 6.70. Found: C, 30.10; H, 3.09; N, 6.65. Conductivity (acetone, 20 °C): 115 $\Omega^{-1}\cdot\text{cm}^2\cdot\text{mol}^{-1}$. IR (KBr, cm⁻¹): ν 474 (w), 537 (m), 585 (m), 599 (m), 658 (m), 690 (m), 743 (s), 782 (s), 839 (m), 898 (s), 931 (s), 945 (s), 1022 (s), 1081 (m), 1170 (w), 1153 (w), 1162 (m), 1195 (w), 1212 (s), 1267 (s), 1306 (s), 1320 (s), 1359 (w), 1425 (s), 1460 (w), 1657 (vs), 1891 (w), 1965 (w), 2933 (w), 2988 (w). ³¹P{¹H} NMR ((CD₃)₂C=O): δ -14.64 (d, ²J_{PP} = 21.4 Hz, Ph₂P=N), 55.46 (d, ²J_{PP} = 21.4 Hz, (RO)₂P=S) ppm. ¹H NMR ((CD₃)₂C=O): δ 1.99 and 2.01 (s, 3H each, COCH₃), 3.50 (m, 1H, NCH₂N), 4.04 (m, 4H, PCH₂NCO), 4.58 and 5.51 (m, 2H each, 1H for NCH₂N and 1H for PCH₂N), 5.00 (d, 1H, ¹J_{HH} = 14.3 Hz, NCH₂N), 7.17–7.40 (m, 10H, CH_{arom}) ppm. ¹³C{¹H} NMR ((CD₃)₂C=O): δ 21.01 and 21.40 (s, COCH₃), 39.99 (dd, ¹J_{CP} = 71.0 Hz, ³J_{CP} = 4.8 Hz, PCH₂N), 45.20 (dd, ¹J_{CP} = 69.4 Hz, ³J_{CP} = 4.2 Hz, PCH₂N), 50.42 (dd, ¹J_{CP} = 59.9 Hz, ³J_{CP} = 2.7 Hz, PCH₂N), 61.52 and 66.75 (d, ³J_{CP} = 6.9 Hz, NCH₂N), 122.05–129.73 (m, CH_{arom}), 152.39 (d, ²J_{CP} = 7.4 Hz, C_{ipso} of OPh), 152.44 (d, ²J_{CP} = 8.0 Hz, C_{ipso} of OPh), 169.13 (s, COCH₃), 169.61 (d, ³J_{CP} = 2.1 Hz, COCH₃) ppm.

General Procedure for Catalytic Propargylic Isomerization in Water. Under air, a pressure-resistant septum-sealed glass microwave reactor vial was charged with the corresponding alkynol (1 mmol), silver catalyst **5a** (0.0067 g, 1 mol % of Ag), a magnetic stirring bar, and distilled water (1 mL). The vial was then placed inside the cavity of a CEM Discover S-Class microwave synthesizer, and power was held at 300 W until the desired temperature (160 °C) was reached. Microwave power was automatically regulated for the remainder of the experiment to maintain the temperature monitored by a built-in infrared sensor (the course of the reaction was monitored by regular sampling and analysis by GC). The internal pressure during the reaction ranged between 5 and 95 psi. After completion of the reaction, the organic product was extracted with diethyl ether (3 \times 5 mL). The organic crude reaction was purified by flash chromatography over silica gel using EtOAc/hexane (1:10) as eluent. The identity of the resulting α,β -unsaturated carbonyl compounds was assessed by

comparison of their ^1H and $^{13}\text{C}\{^1\text{H}\}$ NMR spectroscopic data with those reported in the literature and by their fragmentation in GC/MS.

General Procedure for Catalyst Recycling. The recyclability of the Ag(I) complex **5a** was investigated using isomerization of the commercially available alkynol 1,1-diphenyl-2-propyn-1-ol (**7a**) to 3,3-diphenylpropenal (**8a**) as a model reaction. Under air, a pressure-resistant septum-sealed glass microwave reactor vial was charged with the alkynol **7a** (0.208 g, mmol), silver catalyst **5a** (0.0067 g, 1 mol % of Ag), a magnetic stirring bar, and distilled water (1 mL). The vial was then placed inside the cavity of a CEM Discover S-Class microwave synthesizer, and power was held at 300 W until the desired temperature (160 °C) was reached. Microwave power was automatically regulated for the remainder of the experiment to maintain the temperature monitored by a built-in infrared sensor (the course of the reaction was monitored by regular sampling and analysis by GC). The internal pressure during the reaction ranged between 5 and 95 psi. Complete consumption of **7a** was observed after 45 min. Aqueous phase was extracted with diethyl ether (3 × 5 mL). To the aqueous layer, 0.208 g (1 mmol) of alkynol **7a** was again added, and the mixture was stirred again under the same conditions for the required time. This procedure was repeated up to 10 consecutive times.

■ ASSOCIATED CONTENT

■ Supporting Information

Crystallographic data for **5b** and **6a**, ESI-MS spectrum of an aqueous solution of complex **5a**, and micrographs of the silver nanoparticles (TEM and SEM images). This material is available free of charge via the Internet at <http://pubs.acs.org>.

■ AUTHOR INFORMATION

Corresponding Author

*E-mail: garciajoaquin@uniovi.es.

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

We are indebted to the Ministerio de Ciencia e Innovación (MICINN) of Spain (Projects CTQ2008-00506, CTQ2010-14796, and RYC-2011-08451) and Consolider Ingenio 2010 (CSD2007-00006) for financial support. J.G.-A. thanks the MICINN and the European Social Fund for the award of a “Juan de la Cierva” and a “Ramón y Cajal” contracts. We are thankful for the support of the Scientific and Technical Services (Uniovi) X Ray Single Crystal Diffraction. The authors are also grateful to the Serveis Centrals d'Instrumentació Científica (SCIC) of the Universitat Jaume I for providing the mass spectrometry facilities.

■ REFERENCES

(1) For examples of the state of the art books and reviews on coordination polymers, see: (a) Moulton, B.; Zaworotko, M. J. *Chem. Rev.* **2001**, *101*, 1629. (b) Janiak, C. *Dalton Trans.* **2003**, 2781. (c) Kitagawa, S.; Kitaura, R.; Noro, S. *Angew. Chem., Int. Ed.* **2004**, *43*, 2334. (d) Kitagawa, S.; Uemura, K. *Chem. Soc. Rev.* **2005**, *34*, 109. (e) In *Macromolecules Containing Metal and Metal-Like Elements in Metal-Coordination Polymers*; Abd-El-Aziz, A. S., Carraher, C. E., Jr., Pittman, C. U., Jr., Zeldin, M., Eds.; Wiley: New York, 2005; Vol. 5. (f) Robin, A. Y.; Fromm, K. M. *Coord. Chem. Rev.* **2006**, *250*, 2127. (g) In *Design and Construction of Coordination Polymers*; Hong, M.-C., Chen, L., Eds.; Wiley: New York, 2009. (h) Batten, S. R.; Turner, D. R.; Neville, S. M. *Coordination Polymers: Design, Analysis and Application*; Royal Society of Chemistry: London, 2009. (i) Fromm, K. M.; Sagué, J. L.; Mirolo, L. *Macromol. Symp.* **2010**, *291–292*, 75. (j) Ardash, N. N.; Dastidar, P. *Chem. Soc. Rev.* **2012**, *41*, 3039. (k) Vukotic, V. N.; Loeb, S. J. *Chem. Soc. Rev.* **2012**, *41*, 5896.

(l) Kirillov, A. M.; Kirillova, M. V.; Pombeiro, A. J. L. *Coord. Chem. Rev.* **2012**, 2741.

(2) (a) Lidrissi, C.; Romerosa, A.; Saoud, M.; Serrano-Ruiz, M.; Gonsalvi, L.; Peruzzini, M. *Angew. Chem., Int. Ed.* **2005**, *44*, 2568. (b) Mohr, F.; Falvello, L. R.; Laguna, M. *Eur. J. Inorg. Chem.* **2006**, 3152. (c) Serrano-Ruiz, M.; Romerosa, A.; Sierra-Martín, B.; Fernández-Barbero, A. *Angew. Chem., Int. Ed.* **2008**, *47*, 8665. (d) Kirillov, A. M.; Smoleński, P.; Haukka, M.; Guedes da Silva, M. F. C.; Pombeiro, A. J. L. *Organometallics* **2009**, *28*, 1683. (e) Jaremko, E.; Kirillov, A. M.; Smoleński, P.; Pombeiro, A. J. L. *Cryst. Growth Des.* **2009**, *9*, 3006. (f) Lis, A.; Guedes da Silva, M. F. C.; Kirillov, A. M.; Smoleński, P.; Pombeiro, A. J. L. *Cryst. Growth Des.* **2010**, *10*, 5244. (g) Tu, H. X.; Truong, W.-C.; Nichol, G. S.; Zheng, Z. *Inorg. Chim. Acta* **2010**, *363*, 4189. (h) Frost, B. J.; Lee, W.-C.; Pal, K.; Kim, T. H.; VanDerveer, D.; Rabinovich, D. *Polyhedron* **2010**, *29*, 2239. (i) Kirillov, A. M.; Wiczorek, S. W.; Guedes da Silva, M. F. C.; Sokolnicki, J.; Smoleński, P.; Pombeiro, A. J. L. *CrystEngComm* **2011**, *3*, 6329. (j) Kirillov, A. M.; Wiczorek, S. W.; Lis, A.; Guedes da Silva, M. F. C.; Florek, M.; Król, J.; Staroniewicz, Z.; Smoleński, P.; Pombeiro, A. J. L. *Cryst. Growth Des.* **2011**, *11*, 2711.

(3) (a) García-Álvarez, J.; Díez, J.; Gimeno, J. *Green Chem.* **2010**, *12*, 2127. (b) García-Álvarez, J.; Díez, J.; Gimeno, J.; Suárez, F. J.; Vincent, C. *Eur. J. Inorg. Chem.* **2012**, 5854.

(4) See, for example: (a) Trost, B. M. *Science* **1991**, *254*, 1471. (b) Trost, B. M. *Angew. Chem., Int. Ed. Engl.* **1995**, *34*, 259. (c) Sheldon, R. A. *Pure Appl. Chem.* **2000**, *72*, 1233. (d) Trost, B. M. *Acc. Chem. Res.* **2002**, *35*, 695. (e) Trost, B. M.; Frederiksen, M. U.; Rudd, M. T. *Angew. Chem., Int. Ed.* **2005**, *44*, 6630. (f) Sheldon, R. A. *Green Chem.* **2007**, *9*, 1273.

(5) See, for example: (a) Jung, M. E. In *Comprehensive Organic Synthesis*; Trost, B. M., Fleming, I., Semmelhack, M. F., Eds.; Pergamon Press: Oxford, 1991; Vol. 4, pp 1–67. (b) Lee, V. J. In *Comprehensive Organic Synthesis*; Trost, B. M., Fleming, I., Semmelhack, M. F., Eds.; Pergamon Press: Oxford, 1991; Vol. 4, pp 69–137. (c) Lee, V. J. In *Comprehensive Organic Synthesis*; Trost, B. M., Fleming, I., Semmelhack, M. F., Eds.; Pergamon Press: Oxford, 1991; Vol. 4, pp 139–168. (d) Kozłowski, J. A. In *Comprehensive Organic Synthesis*; Trost, B. M., Fleming, I., Semmelhack, M. F., Eds.; Pergamon Press: Oxford, 1991; Vol. 4, pp 169–198. (e) Bauer, K.; Garbe, D.; Surburg, H. *Common Fragrance and Flavor Materials*; Wiley-VCH: Weinheim, 2001. (f) Marsden, S. P. In *Science of Synthesis*; Cossy, J., Ed.; Thieme Verlag: Stuttgart, 2004; Vol. 26, pp 1045–1121. (g) Takeda, T. *Modern Carbonyl Olefination*; Wiley-VCH: Weinheim, 2004. (h) Escher, I.; Glorius, F. In *Science of Synthesis*; Brückner, R., Schaumann, E., Eds.; Thieme Verlag: Stuttgart, 2006; Vol. 25, pp 733–777.

(6) Meyer, K. H.; Schuster, K. *Ber. Dtsch. Chem. Gess.* **1922**, *55*, 819.

(7) For example see: Clayden, J.; Greeves, N.; Warren, S.; Wothers, P. *Organic Chemistry*; Oxford University Press: Oxford, 2001.

(8) Rupe, H.; Kambli, E. *Helv. Chim. Acta* **1926**, *9*, 672.

(9) For early reviews, see: (a) Vartanyan, S. A.; Babanyan, S. O. *Russ. Chem. Rev.* **1967**, *36*, 670. (b) Swaminathan, S.; Narayanan, K. V. *Chem. Rev.* **1971**, *71*, 529.

(10) Three review articles have appeared giving complete overviews of the different catalysts presently available, their mechanisms of action, as well as relevant synthetic applications, see: (a) Engel, D. A.; Dudley, G. B. *Org. Biomol. Chem.* **2009**, *7*, 4149. (b) Cadierno, V.; Crochet, P.; García-Garrido, S. E.; Gimeno, J. *Dalton Trans.* **2010**, *39*, 4015. (c) Bauer, E. B. *Synthesis* **2012**, *44*, 1131.

(11) For example, see: (a) Yamano, Y.; Tode, C.; Ito, M. *J. Chem. Soc., Perkin Trans. 1* **1995**, 1895. (b) Trost, B. M.; Lee, C. *J. Am. Chem. Soc.* **2001**, *123*, 12191. (c) Trost, B. M.; Livingston, R. C. *J. Am. Chem. Soc.* **2008**, *130*, 11970. (d) Stefanoni, M.; Luparia, M.; Porta, A.; Zanon, G.; Vidari, G. *Chem.—Eur. J.* **2009**, *15*, 3940. (e) Ramón, R. S.; Gaillard, S.; Slawin, A. M. Z.; Porta, A.; D'Alfonso, A.; Zanon, G.; Nolan, S. P. *Organometallics* **2010**, *29*, 3665. (f) Zanon, G.; D'Alfonso, A.; Porta, A.; Feliciani, L.; Nolan, S. P.; Vidari, G. *Tetrahedron* **2010**, *66*, 7472. (g) Hodgson, D. M.; Talbot, E. P. A.;

Clark, B. P. *Org. Lett.* **2011**, *13*, 5751. (h) Fresneda, M. A.; Alibés, R.; Font, J.; Bayón, P.; Figueredo, M. J. *Org. Chem.* **2012**, *77*, 5030.

(12) For tandem isomerization rearrangement and addition or condensation reactions, see: (a) Onodera, G.; Matsumoto, H.; Nishibayashi, Y.; Uemura, S. *Organometallics* **2005**, *24*, 5799. (b) Cadierno, V.; Díez, J.; García-Garrido, S. E.; Gimeno, J.; Nebra, N. *Adv. Synth. Catal.* **2006**, *348*, 2125. (c) Sarma, R.; Prajapati, D. *Synlett* **2008**, 3001. (d) Bhuvanawari, S.; Jegannathan, M.; Cheng, C.-H. *Chem. Asian J.* **2010**, *5*, 141. (e) Borge, J.; Cadierno, V.; Díez, J.; García-Garrido, S. E.; Gimeno, J. *Dyes Pigm.* **2010**, *87*, 209. (f) Cadierno, V.; Gimeno, J.; Nebra, N. *ChemCatChem* **2010**, *2*, 519. (g) Rieder, C. J.; Winberg, K. J.; West, F. G. *J. Org. Chem.* **2011**, *76*, 50. (h) Alcaide, B.; Almendros, P.; Quirós, M. T. *Adv. Synth. Catal.* **2011**, *353*, 585. (i) Trost, B. M.; Breder, A. *Org. Lett.* **2011**, *13*, 398.

(13) For tandem Meyer–Schuster rearrangement and reduction sequence, see: Nolin, K. A.; Ahn, R. W.; Kobayashi, Y.; Kennedy-Smith, J. J.; Toste, F. D. *Chem.—Eur. J.* **2010**, *16*, 9555.

(14) For tandem Meyer–Schuster rearrangement and oxirane ring-opening reaction, see: Dai, L.-Z.; Shi, M. *Chem.—Eur. J.* **2008**, *14*, 5538.

(15) For tandem Meyer–Schuster and alkylation or arylation reactions, see: (a) Trost, B. M.; Luan, X.; Miller, Y. *J. Am. Chem. Soc.* **2011**, *133*, 12884. (b) Pennell, M. N.; Unthank, M. G.; Turner, P.; Sheppard, T. D. *J. Org. Chem.* **2011**, *76*, 1479.

(16) For Hg(II) catalyst active in water, see: (a) Yadav, J. S.; Prahlad, V.; Muralidhar, B. *Synth. Commun.* **1997**, *27*, 3415. For Ru(II) catalysts active in water, see: (b) Suzuki, T.; Tokunaga, M.; Wakatsuki, Y. *Tetrahedron Lett.* **2002**, *43*, 7531. (c) Hintermann, L.; Kribber, T.; Labonne, A.; Paciok, E. *Synlett* **2009**, 2412. (d) d'Alessandro, N.; Di Deo, M.; Bonetti, M.; Tonucci, L.; Morvillo, A.; Bressan, M. *Eur. J. Inorg. Chem.* **2004**, 810. For Au(I) catalyst active in water, see: (e) Ramón, R. S.; Marion, N.; Nolan, S. P. *Tetrahedron* **2009**, *65*, 1767. (f) Gaillard, S.; Bosson, J.; Ramón, R. S.; Nun, P.; Nolan, S. P. *Chem.—Eur. J.* **2010**, *16*, 13729. (g) Nolan, S. P. PCT Int. Appl. WO2011/107736, 2011. (h) Merlini, V.; Gaillard, S.; Porta, A.; Zaroni, G.; Vidari, G.; Nolan, S. P. *Tetrahedron Lett.* **2011**, *52*, 1124. See also ref 11e. For In(III) catalyst active in water, see: (i) Cadierno, V.; Francos, J.; Gimeno, J. *Tetrahedron Lett.* **2009**, *50*, 4773. For a recent review covering isomerization of propargylic alcohols in water, see: (j) García-Álvarez, J.; García-Garrido, S. E.; Crochet, P.; Cadierno, V. *Curr. Top. Catal.* **2012**, *10*, 35. (k) For a recent chapter of a book, see: Cadierno, V.; García-Álvarez, J.; García-Garrido, S. E. In *Metal Catalyzed Reactions in Water*; Dixneuf, P. H., Cadierno, V., Eds.; Wiley-VCH Verlag GmbH & Co.: Weinheim, Germany, 2013.

(17) We must note that some Rupe and Meyer–Schuster rearrangements have been performed in water, under supercritical conditions, without the aid of metal complexes: An, J.; Bagnell, L.; Cablewski, T.; Strauss, C. R.; Trainor, R. W. *J. Org. Chem.* **1997**, *62*, 2505.

(18) Other nonconventional solvents, like ionic liquids, have been successfully applied as reaction media in the isomerization of a variety of propargylic alcohols, see: (a) García-Álvarez, J.; Díez, J.; Gimeno, J.; Seifried, C. M. *Chem. Commun.* **2011**, *47*, 6470. (b) García-Álvarez, J.; Díez, J.; Gimeno, J.; Seifried, C. M.; Vidal, C. *Inorg. Chem.* **2013**, *52*, DOI: 10.1021/ic4003687. See also ref 12c.

(19) Catalytic processes in water are genuine examples of Green Chemistry. For fundamental principles see, for example: (a) Anastas, P. T.; Warner, J. C. *Green Chemistry: Theory and Practice*; Oxford University Press: Oxford, 1998. (b) Matlack, A. S. *Introduction to Green Chemistry*; Marcel Dekker: New York, 2001. (c) Lancaster, M. *Green Chemistry: An Introductory Text*; RSC: London, 2002.

(20) (a) Joó, F. *Aqueous Organometallic Catalysts*; Kluwer: Dordrecht, 2001. (b) In *Aqueous-Phase Organometallic Catalysis*; Cornils, B.; Hermann, W. A., Eds.; Wiley-VCH: Weinheim, 2004. (c) Wang, M.; Li, C.-J. *Top. Organomet. Chem.* **2004**, *11*, 312. (d) In *Multiphase Homogeneous Catalysis*; Cornils, B.; Hermann, W. A.; Horváth, I. T.; Leitner, W.; Mecking, S.; Olivier-Bourbigou, H.; Vogt, D., Eds.; Wiley-VCH: Weinheim, 2005. (e) Li, C.-J. *Chem. Rev.* **2005**, *105*, 3095. (f) Li, C.-J.; Chen, L. *Chem. Soc. Rev.* **2006**, *35*, 68. (g) Chen, L.; Li, C.-

J. *Adv. Synth. Catal.* **2006**, *348*, 1459. (h) In *Comprehensive Organic Reactions in Aqueous Media*, 2nd ed.; Li, C.-J., Chan, T.-H., Eds.; Wiley: Hoboken, NJ, 2007. (i) In *Organic Reactions in Water*; Lindström, U. M., Ed.; Blackwell Publishing: Oxford, 2007. (j) In *Organic Reactions in Water—Principles, Strategies and Applications*; Lindström, V. M., Ed.; Wiley-Blackwell: Chichester, West Sussex, UK, 2007. (k) In *Handbook of Green Chemistry, Green Solvents*; Li, C.-J., Anastas, P. T., Eds.; Wiley-VCH: Weinheim, Germany, 2011; Vol. 5 (Reactions in Water).

(21) García-Álvarez, J.; Díez, J.; Vidal, C. *Green Chem.* **2012**, *14*, 3190.

(22) Cadierno, V.; Díez, J.; García-Álvarez, J.; Gimeno, J. *Dalton Trans.* **2007**, 2706.

(23) We synthesized iminophosphorane **3a**, **3b**, **4a**, and **4b** applying the procedure previously described by Majoral and co-workers, see: Benhammou, M.; Kraemer, R.; Germa, H.; Majoral, J.-P.; Navech, J. *Phosphorus Sulfur Relat. Elem.* **1982**, *14*, 105.

(24) For Ag(I) complexes containing PTA ligand, see: (a) Santini, C.; Pellei, M.; Papini, G.; Morresi, B.; Galassi, R.; Ricci, S.; Tisato, F.; Porchia, M.; Rigobello, M. P.; Gandin, V.; Marzano, C. J. *Inorg. Biochem.* **2011**, *105*, 232. (b) Pettinari, C.; Marchetti, F.; Lupidi, G.; Quassinti, L.; Bramucci, M.; Petrelli, D.; Vitali, L. A.; Guedes da Silva, M. F. C.; Martins, L. M. D. R. S.; Smoleński, P.; Pombeiro, A. J. L. *Inorg. Chem.* **2011**, 11173 and refs 2a, 2b, 2f, and 2i.

(25) (a) Larré, C.; Donnadiou, B.; Caminade, A.-M.; Majoral, J. P. *Chem.—Eur. J.* **1998**, *4*, 2031. (b) Rossell, O.; Seco, M.; Caminade, A.-M.; Majoral, J. P. *Gold Bull.* **2001**, *34*, 88. (c) Turrin, B.; Donnadiou, B.; Caminade, A.-M.; Majoral, J. P. *Z. Anorg. Allg. Chem.* **2005**, *631*, 2881. (d) Maraval, A.; Magro, G.; Maraval, V.; Vendier, L.; Caminade, A.-M.; Majoral, J. P. *J. Organomet. Chem.* **2006**, *691*, 1333. Iminophosphorane ligands **3a**, **3b**, **4a**, and **4b** also showed preferential S-coordination of the P=N—P=S framework in Cu(I) (ref 3) and Pd(II) fragments (ref 21).

(26) See, for example: (a) Wang, S.; Fackler, J. P., Jr.; Carlson, T. F. *Organometallics* **1990**, *9*, 1973. (b) Bembenek, E.; Crespo, O.; Gimeno, M. C.; Jones, P. G.; Laguna, A. *Chem. Ber.* **1994**, *127*, 835. (c) Gimeno, M. C.; Jones, P. G.; Laguna, A.; Sarroca, C. J. *Chem. Soc., Dalton Trans.* **1995**, 3563. (d) Gimeno, M. C.; Jones, P. G.; Laguna, A.; Sarroca, C. J. *Chem. Soc., Dalton Trans.* **1998**, 1277. (e) Canales, S.; Crespo, O.; Gimeno, M. C.; Jones, P. G.; Laguna, A. *J. Organomet. Chem.* **2000**, *613*, 50. (f) Wilton-Ely, J. D. E. T.; Schier, L. A.; Schmidbaur, H. *J. Chem. Soc., Dalton Trans.* **2001**, 3647. (g) Liu, H.; Bandeira, N. A. G.; Calhorda, M. J.; Drew, M. G. B.; Félix, V.; Novosad, J.; de Biani, F. F.; Zanello, P. *J. Organomet. Chem.* **2004**, *689*, 2808. (h) Crespo, O.; Brusko, V. V.; Gimeno, M. C.; Tornil, M. L.; Laguna, A.; Zabirow, N. G. *Eur. J. Inorg. Chem.* **2004**, 423.

(27) Metal–metal interactions in d¹⁰ metal complexes is a well-known phenomena. For reviews covering this topic, see: (a) Pyykkö, P. *Chem. Rev.* **1997**, *97*, 597. (b) Bardají, M.; Laguna, A. *Eur. J. Inorg. Chem.* **2003**, 3069. (c) Che, C.-M.; Lai, S.-W. *Coord. Chem. Rev.* **2005**, *249*, 1296. (d) Phillips, D. L.; Che, C.-M.; Leung, K. H.; Mao, Z.; Tse, M.-C. *Coord. Chem. Rev.* **2005**, *249*, 1476.

(28) A search of the Cambridge Structural Database scored no hits for other structures containing O-coordinated DAPTA. (a) Allen, F. H. *Acta Crystallogr., Sect. B: Struct. Sci.* **2002**, *58*, 380. (b) Cambridge Structural Database, version 5.33 with updates to Nov 2011.

(29) Formation of eight-membered rings Ag₄S₄ is well known in organometallic chemistry; for recent examples, see: (a) Castineiras, A.; Pedrido, R. *Inorg. Chem.* **2008**, *47*, 5534. (b) Pedrido, R.; González-Noya, A. M.; Romero, M. J.; Martínez-Calvo, M.; Vázquez-López, M.; Gómez-Forneas, E.; Zaragoza, G.; Bermejo, M. R. *Dalton Trans.* **2008**, 6776. (c) MacDonald, D. G.; Corrigan, J. F. *Dalton Trans.* **2008**, 5048. (d) Vicente, J.; González-Herrero, P.; García-Sánchez, Y.; Jones, P. G. *Inorg. Chem.* **2009**, *48*, 2060.

(30) Similar homometallic three-membered rings Ag₃ that belong to a bigger (Ag_nS_n) (n ≥ 4) rings have been previously reported, for example, see: (a) Henkel, G.; Betz, P.; Krebs, B. *Angew. Chem., Int. Ed.* **1987**, *26*, 145. (b) Falckler, J. P., Jr.; Lopez, C. A.; Staples, R. J.; Wang, S.; Wunpenny, R. E. P.; Lattimer, R. P. *Chem. Commun.* **1992**, 146. (c) Wang, X.-J.; Langetepe, T.; Persau, C.; Kang, B.-S.; Sheldrick, G.

M.; Fenske, D. *Angew. Chem., Int. Ed.* **2002**, *41*, 3818. (d) Tang, K.; Xie, X.; Zhao, L.; Zhang, Y.; Jin, X. *Eur. J. Inorg. Chem.* **2004**, 78. (e) Bermejo, M. R.; González-Noya, A. M.; Pedrido, R. M.; Romero, M. J.; Vázquez, M. *Angew. Chem., Int. Ed.* **2005**, *44*, 4182.

(31) (a) Zheng, S.-L.; Zhang, J.-P.; Wong, W.-T.; Chen, X.-M. *J. Am. Chem. Soc.* **2003**, *125*, 6882. (b) Zhang, J.-P.; Wang, Y.-B.; Hueng, X.-C.; Lin, Y.-Y.; Chen, X.-M. *Chem.—Eur. J.* **2005**, *11*, 552. (c) Zhang, J.-P.; Lin, Y.-Y.; Huang, X.-C.; Chen, X.-M. *Inorg. Chem.* **2005**, *44*, 3146.

(32) ESI-MS has become an important technique in solution speciation studies related analysis of catalytic processes. See, for example: (a) Chen, P. *Angew. Chem.* **2003**, *115*, 2938. *Angew. Chem., Int. Ed.*, **2003**, *42*, 2832. (b) Santos, L. S.; Knaack, L.; Metzger, J. O. *Int. J. Mass Spectrom.* **2005**, *246*, 84. (c) Eberlin, M. N. *Eur. J. Mass Spectrom.* **2007**, *13*, 19. (d) Santos, L. S. *Eur. J. Org. Chem.* **2008**, 235. (e) Jirasko, R.; Holcapek, M. *Mass Spectrom. Rev.* **2011**, *30*, 1013. (f) Bellarosa, L.; Díez, J.; Gimeno, J.; Lledós, A.; Suárez, F. J.; Ujaque, G.; Vicent, C. *Chem.—Eur. J.* **2012**, *18*, 7749.

(33) Among other transition metal catalysts, Ag(I) salts have generally been considered to have a low catalytic efficiency and only serve as either cocatalysts or Lewis acids. However, in recent years, Ag(I) salts have been demonstrated to be important and versatile catalysts for some organic transformations in water: (a) Wei, C.; Li, Z.; Li, C.-J. *Org. Lett.* **2003**, *5*, 4473. (b) Yao, X.; Li, C.-J. *Org. Lett.* **2005**, *7*, 4395. (c) Zhang, X.; Zhou, Y.; Wang, H.; Guo, D.; Ye, D.; Xu, Y.; Jiang, H.; Liu, H. *Green Chem.* **2011**, *13*, 397. (d) Fu, X.-P.; Liu, L.; Wang, D.; Chen, Y.-J.; Li, C.-J. *Green Chem.* **2011**, *13*, 549. (e) Rustagi, V.; Aggarwal, T.; Verma, A. K. *Green Chem.* **2011**, *13*, 1640. (f) Lockner, J. W.; Dixon, D. D.; Risgaard, R.; Baran, P. S. *Org. Lett.* **2011**, *13*, 5628. (g) Liu, X.; Wang, Z.; Cheng, X.; Li, C.-J. *J. Am. Chem. Soc.* **2012**, *134*, 14330.

(34) For recent examples of Ag(I)-catalyzed isomerization of propargylic alcohols in conventional organic solvents, see: (a) Egi, M.; Umemura, M.; Kawai, T.; Akai, S. *Angew. Chem., Int. Ed.* **2011**, *50*, 12197. (b) Kikuchi, S.; Yoshida, S.; Sugawara, Y.; Yamada, W.; Cheng, H.-M.; Fukui, K.; Sekine, K.; Iwakura, I.; Ikeno, T.; Yamada, T. *Bull. Chem. Soc. Jpn.* **2011**, *84*, 698. (c) Pennell, M. N.; Turner, P. G.; Sheppard, T. D. *Chem.—Eur. J.* **2012**, *18*, 4748.

(35) Gold complexes have been also reported as efficient catalysts for Meyer–Schuster rearrangements. For a recent review, see: Corma, A.; Leyva-Pérez, A.; Sabater, M. J. *Chem. Rev.* **2011**, *111*, 1657.

(36) It is nowadays well recognized that use of microwave (MW) irradiation represents a convenient alternative to conventional thermal heating in organic synthesis since a more effective energy transfer to the system takes place, thus shortening considerably the reaction times and improving in many cases the product yields. See, for example: (a) In *Microwaves in Organic Synthesis*; Loupy, A., Ed.; Wiley-VCH: Weinheim, 2006. (b) Kappe, C. O.; Dallinger, D.; Murphee, S. S. *Practical Microwave Synthesis for Organic Chemists*; Wiley-VCH: Weinheim, 2009. (c) In *Microwave Heating as a Tool for Sustainable Chemistry*; Leadbeater, N. E., Ed.; CRC Press: Boca Raton, 2011.

(37) This total Meyer–Schuster vs Rupe selectivity was also previously observed for other catalysts in water. See, for example, ref 16h.

(38) Such an *E* selectivity with secondary alkynols has been also observed using other catalysts. See, for example, refs 11d, e, 16h, and 18, and (a) Cadierno, V.; García-Garrido, S. E.; Gimeno, J. *Adv. Synth. Catal.* **2006**, *348*, 101. (b) Antiñolo, A.; Carrillo-Hermosilla, F.; Cadierno, V.; García-Álvarez, J.; Otero, A. *ChemCatChem* **2012**, *4*, 123.

(39) For a recent account see: Nadagouda, M. N.; Speth, T. F.; Varma, R. S. *Acc. Chem. Rev.* **2011**, *7*, 469.

(40) See, for example: Wildegren, J. A.; Finke, R. G. *J. Mol. Catal. A: Chem.* **2003**, *198*, 317 and references therein.

(41) Primary propargylic alcohols have proven to be very difficult substrates for the Meyer–Schuster reaction. To our knowledge, only one successful methodology has been described to date in the literature, see: Egi, M.; Yamaguchi, Y.; Fujiwara, N.; Akai, S. *Org. Lett.* **2008**, *10*, 1867.

(42) For a recent book covering the synthesis, reactivity, and catalytic applications of transition-metal vinylidenes and allenylidene com-

plexes, see: In *Metal Vinylidenes and Allenylidenes in Catalysis: From Reactivity to Applications in Synthesis*; Bruneau, C., Dixneuf, P. H., Eds.; Wiley-VCH: Weinheim, 2008.

(43) In *Recoverable and Recyclable Catalyst*; Benaglia, M., Ed.; John Wiley & Sons: Chichester, 2009.

(44) Midland, M. M. *J. Org. Chem.* **1975**, *40*, 2250.