

## Two-Photon Oxygen Sensing with Quantum Dot-Porphyrin Conjugates


Christopher M. Lemon,<sup>†,‡</sup> Elizabeth Karnas,<sup>†</sup> Mounji G. Bawendi,<sup>\*,†</sup> and Daniel G. Nocera<sup>\*,‡</sup>

<sup>†</sup>Department of Chemistry, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, Massachusetts 02139, United States

<sup>‡</sup>Department of Chemistry and Chemical Biology, Harvard University, 12 Oxford Street, Cambridge, Massachusetts 02138, United States

### Supporting Information

**ABSTRACT:** Supramolecular assemblies of a quantum dot (QD) associated to palladium(II) porphyrins have been developed to detect oxygen ( $pO_2$ ) in organic solvents. Palladium porphyrins are sensitive in the 0–160 Torr range, making them ideal phosphors for in vivo biological oxygen quantification. Porphyrins with *meso* pyridyl substituents bind to the surface of the QD to produce self-assembled nanosensors. Appreciable overlap between QD emission and porphyrin absorption features results in efficient Förster resonance energy transfer (FRET) for signal transduction in these sensors. The QD serves as a photon antenna, enhancing porphyrin emission under both one- and two-photon excitation, demonstrating that QD-palladium porphyrin conjugates may be used for oxygen sensing over physiological oxygen ranges.

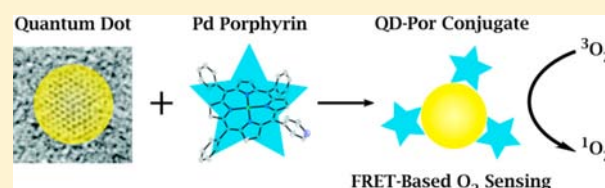

### INTRODUCTION

Generating metabolic profiles of tumors provides a spatiotemporal map of the concentration of key species to assess and quantify tumor growth, metabolism, and response to therapy. Because the tumor microenvironment is characterized by acidity and hypoxia,<sup>1</sup> the concentration of protons and oxygen are important indicators of tumor health.<sup>2</sup> Understanding how these two parameters change as a function of disease progression is critical to develop novel targeted therapeutics such as antiangiogenic agents, which can engender normalization of the leaky, distended, and tortuous tumor vasculature.<sup>3</sup> Upon normalization, blood flow, oxygen levels, and drug distribution are increased; this represents an opportunity to treat the tumor with a substantial dose of chemotherapeutics to have a superior impact on tumor progression.<sup>4</sup> However, the normalization process must be efficiently monitored so that doses of chemotherapeutics can be timed appropriately to have a maximal effect on tumor viability. To address this challenge, new non-invasive sensors must be developed that are small enough to penetrate into the tumor and monitor dynamic changes with high resolution.<sup>5</sup> To this end, we have developed self-referencing pH sensors<sup>6–8</sup> and a high-pressure (160–760 Torr) oxygen sensor<sup>9</sup> to probe biological microenvironments. Herein, we report a low-pressure (0–160 Torr) oxygen sensor that covers the oxygen concentration range of the hypoxic tumor environment.

Fluorescent semiconductor quantum dots (QDs) have high quantum yields, photostability, narrow emission bands, and broad excitation profiles,<sup>10</sup> rendering them ideal scaffolds for constructing optical biosensors.<sup>11–13</sup> By attaching an analyte-sensitive fluorophore to the QD, Förster resonance energy transfer (FRET) may be exploited as a means of signal


transduction.<sup>14–16</sup> Additionally, QDs exhibit high two-photon absorption cross-sections ( $\sigma_2 \sim 10^4$  Göppert–Mayer, 1 GM =  $10^{-50}$  cm<sup>4</sup>·s/photon),<sup>17–19</sup> making them attractive fluorophores for multiphoton imaging. Near-IR excitation and detection (600–1000 nm) in the so-called therapeutic window allows for imaging with minimal background signal from cellular autofluorescence.<sup>20</sup> This spectral window is readily accessed using two-photon excitation. This imaging technique is nondestructive to tissue and provides high-resolution images of live tissue at depths of several hundred micrometers with submicrometer spatial resolution.<sup>21,22</sup> Thus, QDs offer a versatile platform on which to build supramolecular oxygen sensing assemblies.

Many oxygen sensitive phosphors have been reported in the literature using osmium,<sup>9</sup> iridium,<sup>23</sup> and ruthenium<sup>24</sup> polypyridine complexes as well as pyrene.<sup>25</sup> Platinum and palladium porphyrins are especially well-suited for O<sub>2</sub> sensing applications because of their strong room temperature phosphorescence in the 650–800 nm range and long ( $\sim 10^2$   $\mu$ s) phosphorescence lifetime.<sup>26</sup> Most oxygen chemosensors heretofore have relied on the immobilization of these porphyrins in polymer matrices,<sup>26–28</sup> on solid surfaces,<sup>26,29</sup> or in mesoporous silica.<sup>26,30</sup> Commercial palladium porphyrins (Oxyphor R2) and benzoporphyrins (Oxyphor G2), which are available as water-soluble glutamate dendrimers, have also been used for oxygen sensing in solution.<sup>31</sup>

The exceptionally long phosphorescence lifetimes of palladium porphyrins make them ideal for oxygen sensing in the biologically relevant 0–160 Torr range. The heavy metal Pd

Received: May 4, 2013

Published: August 26, 2013

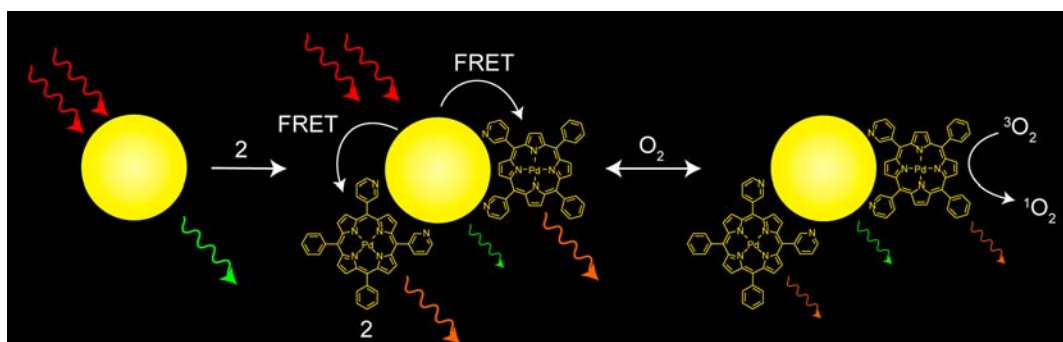


**Figure 1.** Schematic representation of the O<sub>2</sub> sensing transduction mechanism of a self-assembled Pd porphyrin (2)-QD construct. The QD acts as the two-photon antenna of NIR (700–1000 nm) excitation. The QD emission is quenched in the presence of a surface-bound Pd porphyrin (2) via a FRET mechanism. The insensitivity of the QD emission to O<sub>2</sub> affords an internal reference to establish a ratiometric O<sub>2</sub> response.

promotes rapid intersystem crossing to produce the long-lived triplet state. Molecular oxygen (a ground state triplet) deactivates this excited state efficiently through collisional quenching, as dictated by Stern–Volmer kinetics. By monitoring the intensity or lifetime of the triplet excited state of the Pd porphyrin, the amount of oxygen may be quantified.<sup>32</sup> However, porphyrins alone have prohibitively low two-photon absorption cross-sections ( $\sigma_2 = 1\text{--}25$  GM for free-base tetraphenylporphyrin),<sup>33</sup> and thus an ideal oxygen sensor using Pd porphyrins combines the oxygen-sensitive properties of porphyrins with an efficient two-photon antenna. In this regard, coumarin dyes have served as two-photon antennae for covalently attached Pd or Pt porphyrins.<sup>34–37</sup> Herein, we expand this approach by using a QD as the two-photon antenna.

The porphyrin-QD construct shown in Figure 1 is prepared by self-assembly, promoted by binding of Pd porphyrins with *meso*-pyridyl substituents (compounds 1–3, Chart 1) to the

**Chart 1**

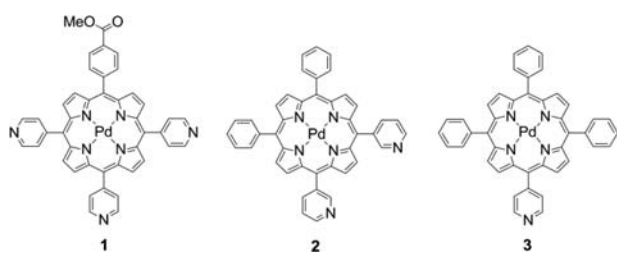

surface of a QD. In this sensing scheme, the QD is irradiated with two-photon excitation and energy is transferred via FRET to excite the Pd porphyrin, which is quenched by molecular oxygen; the extent of quenching is proportional to the amount of oxygen. Since the QD is unaffected by oxygen, its emission may serve as an internal standard to afford a ratiometric oxygen sensor by monitoring the QD:porphyrin emission intensity.

The system shown in Figure 1 offers several new advantages for O<sub>2</sub> sensing. First, the self-assembling process allows for facile construction of a nanosensing construct. Second, QDs are among the most efficient two-photon chromophores, exhibiting absorption cross-sections that are 1000-fold greater than common organic dyes ( $\sigma_2 \sim 10^4$  GM for QDs versus  $\sigma_2 = 20$  GM for Coumarin-343).<sup>35</sup> Third, the photophysical properties, namely, the emission wavelength, of QDs are tunable,<sup>10</sup> enabling optimized spectral overlap between Pd porphyrin and QD, thus maximizing FRET efficiency. Fourth, several

porphyrins are associated to a single two-photon QD antenna, giving a sizable porphyrin response on a per sensor basis. Fifth, the insensitivity of QD emission to O<sub>2</sub> establishes a ratiometric signal response. Finally, the construct exhibits greatest response over the biologically important 0–160 Torr O<sub>2</sub> pressure range.

## EXPERIMENTAL SECTION

**Materials.** The following chemicals were used as received: hexanes, diethylether (Et<sub>2</sub>O), anhydrous inhibitor-free tetrahydrofuran (THF), dichloromethane (CH<sub>2</sub>Cl<sub>2</sub>), toluene, acetonitrile (MeCN), methanol (MeOH), anhydrous methanol (MeOH), ethanol (EtOH), ethyl acetate (EtOAc), 2-mercaptopyridine, isonicotinoyl chloride hydrochloride, nicotinoyl chloride hydrochloride, pyrrole, 4-pyridinecarboxaldehyde, 3-pyridinecarboxaldehyde, benzaldehyde, methyl 4-formylbenzoate, indium(III) chloride (InCl<sub>3</sub>), sodium hydroxide (NaOH) beads, ethyl magnesium bromide 1 M solution in THF (EtMgBr), bromine (Br<sub>2</sub>), 1,8-diazabicyclo[5.4.0]undec-7-ene (DBU), magnesium bromide (MgBr<sub>2</sub>), tris(2,2'-bipyridyl)dichlororuthenium(II) hexahydrate ([Ru(bpy)<sub>3</sub>]Cl<sub>2</sub>), 2',7'-dichlorofluorescein (fluorescein 27), trifluoroacetic acid (TFA), triethylamine (NEt<sub>3</sub>), 2,3-dichloro-5,6-dicyano-1,4-benzoquinone (DDQ), and sodium borohydride (NaBH<sub>4</sub>) from Sigma-Aldrich; sodium bicarbonate (NaHCO<sub>3</sub>), sodium sulfate (Na<sub>2</sub>SO<sub>4</sub>), ammonium chloride (NH<sub>4</sub>Cl), ammonium sulfate ((NH<sub>4</sub>)<sub>2</sub>SO<sub>4</sub>), and sodium chloride (NaCl) from Mallinckrodt; potassium carbonate (K<sub>2</sub>CO<sub>3</sub>) and Celite 512 from Fluka; palladium(II) acetylacetonate (Pd(acac)<sub>2</sub>) and ytterbium(III) triflate (Yb(OTf)<sub>3</sub>) from Strem; benzoyl chloride from J. T. Baker; pyridine from EMD; silica gel 60 Å 230–400 mesh ASTM from Whatman; and chloroform-*d* (CDCl<sub>3</sub>) from Cambridge Isotope Laboratories. Nitrogen and argon gases (Airgas) were passed over a Drierite column prior to use. Cadmium selenide core/shell QDs (518 nm emission, QD Vision) were twice precipitated from toluene using EtOH and redissolved in toluene prior to use. The following compounds were prepared according to literature procedures or slight modifications thereof: 5-(3-pyridyl)dipyrromethane (S1),<sup>38</sup> 5-2-pyridyl nicotinoylthioate (S2),<sup>39,40</sup> 5-phenyldipyrromethane (S3),<sup>41,42</sup> 5-2-pyridyl benzoylthioate (S4),<sup>39,43</sup> 5-(4-methoxycarbonylphenyl) dipyrromethane (4),<sup>41,42</sup> 5-2-pyridyl isonicotinoylthioate (5),<sup>39,40</sup> 1-isonicotinoyl-5-(4-pyridyl) dipyrromethane (7),<sup>39,40</sup> 1-nicotinoyl-5-(3-pyridyl)-dipyrromethane (8),<sup>39,40</sup> 1-benzoyl-5-phenyldipyrromethane (9),<sup>39,40</sup> 1,9-dibenzoyl-5-phenyldipyrromethane (10),<sup>38</sup> and 5-(4-pyridyl)-dipyrromethane (12).<sup>38</sup> Exact procedures for the preparation of these compounds and <sup>1</sup>H NMR are provided in the Supporting Information.

**1-Isonicotinoyl-5-(4-methoxycarbonylphenyl)-dipyrromethane (6).** This compound was prepared using a procedure similar to that used for other 1-acyl dipyrromethanes,<sup>39,40</sup> with minor modifications including the addition of acylating reagent as a solid in one portion rather than a homogeneous solution. In an oven-dried flask, 1.89 g of 5-(4-methoxycarbonylphenyl)dipyrromethane (4)<sup>41,42</sup> (6.74 mmol) was dissolved in 15 mL of anhydrous

tetrahydrofuran (THF) under an argon atmosphere to afford a tan solution. Seventeen milliliters of EtMgBr (1 M solution in THF) was then slowly added, and the resultant dark brown solution was stirred at room temperature for 10 min. The solution was cooled to  $-78\text{ }^{\circ}\text{C}$  in a dry ice/acetone bath, and 1.50 g (6.94 mmol) of 5-2-pyridyl isonicotinothioate (**5**)<sup>39,40</sup> was added in one portion; the resultant mixture was stirred at  $-78\text{ }^{\circ}\text{C}$  for 1 h. The solution was warmed to room temperature and stirred for an additional 3 h. Saturated  $\text{NH}_4\text{Cl}$  was added, and the product was extracted with EtOAc. The combined organics were washed with water and brine, then dried over  $\text{Na}_2\text{SO}_4$ . Solvent was removed by rotary evaporation to afford a brown oil. The crude reaction mixture was loaded onto a silica gel column packed with ethyl acetate. The product (second band, which turns yellow-orange upon  $\text{Br}_2$  staining on TLC) was eluted with 100% EtOAc. After solvent removal, the oily brown residue was dissolved in a minimal amount of EtOAc and subsequently precipitated with a large excess of hexanes, and the resultant solid was collected on a frit and washed with hexanes to afford 1.67 g (64.2% yield) of the title compound as a tan solid.  $^1\text{H NMR}$  (500 MHz,  $\text{CDCl}_3$ )  $\delta$  = 3.92 (s, 3H), 5.61 (s, 1H), 5.97 (m, 1H), 6.08 (m, 1H), 6.19 (m, 1H), 6.76 (m, 1H), 6.81 (m, 1H), 7.30 (m, 2H), 7.63 (m, 2H), 8.01 (m, 2H), 8.04 (bs, 1H), 8.77 (m, 2H), 9.56 (bs, 1H).

**5-(4-Methoxycarbonylphenyl)-10,15,20-tris(4-pyridyl)porphyrin (1-H<sub>2</sub>).** This compound was prepared using a microwave-mediated [2 + 2] condensation.<sup>40</sup> In a 10 mL microwave tube, 69 mg (0.21 mmol) of 1-isonicotinoyl-5-(4-pyridyl)dipyrromethane (**7**)<sup>39,40</sup> and 76 mg (0.20 mmol) of 1-isonicotinoyl-5-(4-methoxycarbonylphenyl)dipyrromethane (**6**) were dissolved in 4 mL of toluene to afford a dark brown-black suspension. The suspension turned red after the addition of 0.6 mL of DBU (0.6 g, 4 mmol), and was stirred for 5 min at room temperature.  $\text{MgBr}_2$  (420 mg, 2.3 mmol) was added, and an additional 1 mL of toluene was added to rinse the walls of the tube. The resultant orange-brown suspension was placed in a microwave reactor (CEM Discover) and irradiated at  $115\text{ }^{\circ}\text{C}$  for 2 h. The reaction mixture was transferred to a flask, dissolved in THF, and the solvent was removed by rotary evaporation. The residue was dissolved in EtOAc, washed with water, and brought to dryness under rotary evaporation. The magnesium porphyrins of the crude reaction mixture were demetallated by dissolving the residue in 10 mL of  $\text{CH}_2\text{Cl}_2$  and adding 0.2 mL of TFA (0.3 g, 2.6 mmol); the resulting green solution was stirred at room temperature for 30 min. Then 0.4 mL of  $\text{NEt}_3$  (0.3 g, 2.9 mmol) was added, and the reaction mixture was washed with water and brine, dried over  $\text{Na}_2\text{SO}_4$ , and brought to dryness. The residue was loaded onto a silica gel column and eluted with EtOAc. After removal of the *trans*- $\text{A}_2\text{B}_2$  product, the solvent was changed to 4% MeOH in EtOAc to give 15 mg (11% yield) of the title compound.  $^1\text{H NMR}$  (500 MHz,  $\text{CDCl}_3$ )  $\delta$  =  $-2.90$  (bs, 2H), 4.12 (s, 3H), 8.16 (m, 6H), 8.30 (m, 2H), 8.47 (m, 2H), 8.82–8.89 (bm, 8H), 9.06 (m, 6H).

**5,10-Diphenyl-15,20-bis(3-pyridyl)porphyrin (2-H<sub>2</sub>).** This compound was prepared using a microwave-mediated [2 + 2] condensation.<sup>40</sup> In a 10 mL microwave tube, 60 mg (0.18 mmol) of 1-nicotinoyl-5-(3-pyridyl)dipyrromethane (**8**)<sup>39,40</sup> and 60 mg (0.18 mmol) of 1-benzoyl-5-phenyldipyrromethane (**9**)<sup>39,40</sup> were dissolved in 4 mL of toluene to afford a dark brown-black suspension. After the addition of 0.6 mL of DBU (0.6 g, 4.0 mmol), the suspension became red and was subsequently stirred for 5 min.  $\text{MgBr}_2$  (453 mg, 2.46 mmol) was added, and 1 mL of toluene was added to rinse the solids down the tube. The resultant orange-brown suspension was placed in a microwave reactor (CEM Discover) and irradiated at  $115\text{ }^{\circ}\text{C}$  for 2 h. The reaction mixture was transferred to a flask, dissolved in THF, and the solvent was removed by rotary evaporation. The residue was dissolved in ethyl acetate, washed with water and brine, dried over  $\text{Na}_2\text{SO}_4$ , and brought to dryness. The crude reaction mixture was purified on a silica gel column using ethyl acetate as the eluent to remove the first major band,  $\text{Mg}(\text{TPP})$ . The solvent was then switched to 5% MeOH in EtOAc to elute the desired product, which moved as the second fluorescent band on the column. The  $\text{A}_4$  complex with four 3-pyridyl groups remained at the top of the column and was not isolated. The  $\text{Mg}$  complex was demetallated by dissolving the solid in

10 mL of  $\text{CH}_2\text{Cl}_2$  and adding 0.2 mL of TFA (0.3 g, 2.6 mmol); the resulting green solution was stirred at room temperature for 30 min after which 0.4 mL of  $\text{NEt}_3$  (0.3 g, 2.9 mmol) was added. The reaction mixture was washed with water and brine, dried over  $\text{Na}_2\text{SO}_4$ , and brought to dryness. The free-base porphyrin (27 mg, 24% yield) was used without further purification.  $^1\text{H NMR}$  (500 MHz,  $\text{CDCl}_3$ )  $\delta$  =  $-2.81$  (bs, 2H), 7.75–7.81 (overlapping m, 6H), 7.79 (overlapping m, 2H), 8.22 (d,  $J$  = 6.1 Hz, 4H), 8.53 (d,  $J$  = 6.8 Hz, 2H), 8.80 (d,  $J$  = 4.7 Hz, 2H), 8.84 (s, 2H), 8.87 (s, 2H), 8.91 (d,  $J$  = 4.7 Hz, 2H), 9.06 (m, 2H), 9.46 (s, 2H).

**5,10,15-Triphenyl-20-(4-pyridyl)porphyrin (3-H<sub>2</sub>).** In an oven-dried flask, 90 mg of 1,9-dibenzoyl-5-phenyldipyrromethane (**10**)<sup>38</sup> (0.21 mmol) was dissolved in 12 mL of anhydrous THF and 4 mL of anhydrous MeOH under a nitrogen atmosphere to give a brown solution. To this solution, 0.42 g of  $\text{NaBH}_4$  (11 mmol) was added, and the resultant tan-orange mixture was stirred at room temperature for 1 h. Water was added to quench excess  $\text{NaBH}_4$ , and the product was extracted with  $\text{CH}_2\text{Cl}_2$  and dried over  $\text{K}_2\text{CO}_3$  to afford a solution of the corresponding dicarbinol (**11**). Since the dicarbinol is prone to decomposition, the solution was concentrated to near-dryness without heating. The residue was dissolved in 50 mL of MeCN, and 45 mg of 5-(4-pyridyl)dipyrromethane (**12**)<sup>38</sup> (0.20 mmol) and 1.22 g of  $\text{Yb}(\text{OTf})_3$  (2.0 mmol) were added; the resulting red solution was stirred at room temperature for 1 h all the while protected from light. DDQ (183 mg, 0.806 mmol) was added, and the solution was stirred at room temperature for an additional 1 h.  $\text{NEt}_3$  (2 mL, 1.6 g, 16 mmol) was added to the solution and stirred for an additional 30 min. Ethyl acetate was added, and the reaction mixture was washed with water and brine, dried over  $\text{Na}_2\text{SO}_4$ , and brought to dryness. The product was purified on a silica gel column using EtOAc as the eluent to obtain 30 mg (24% yield) of the title compound.  $^1\text{H NMR}$  (400 MHz,  $\text{CDCl}_3$ )  $\delta$  =  $-2.80$  (bs, 2H), 7.75–7.80 (m, 9H), 8.17 (m, 2H), 8.22 (m, 6H), 8.80 (d,  $J$  = 4.5 Hz, 2H), 8.86 (s, 4H), 8.90 (d,  $J$  = 4.7 Hz, 2H), 9.03 (m, 2H).

**General Procedure for Palladium(II) Metalation.** In a 10 mL microwave tube, free-base porphyrin was dissolved in 3 mL of pyridine, and  $\text{Pd}(\text{acac})_2$  was added. An additional 1 mL of pyridine was added to rinse solids down the tube. The resultant solution was placed in a microwave reactor (CEM Discover) and irradiated at  $180\text{ }^{\circ}\text{C}$  for 20 min. The crude reaction mixture was filtered through a plug of Celite and rinsed with  $\text{CH}_2\text{Cl}_2$ ; the collected orange filtrate was brought to dryness. The palladium complex was purified on a silica gel column to afford the product.

**5-(4-Methoxycarbonylphenyl)-10,15,20-tris(4-pyridyl)porphyrinopalladium(II) (1).** Following the aforementioned general procedure, 65 mg (0.10 mmol) of the free-base porphyrin **1-H<sub>2</sub>** was treated with 175 mg (0.574 mmol) of  $\text{Pd}(\text{acac})_2$ . The compound was purified using a gradient of 0–10% MeOH in EtOAc as the eluent to give 39 mg (50% yield) of the title product.  $^1\text{H NMR}$  (400 MHz,  $\text{CDCl}_3$ )  $\delta$  4.12 (s, 3H), 8.12 (m, 6H), 8.25 (m, 2H), 8.45 (m, 2H), 8.80 (d,  $J$  = 5.1 Hz, 2H), 8.82 (s, 4H), 8.83 (d,  $J$  = 5.0 Hz, 2H), 9.05 (m, 6H). Anal. Calcd. for  $(\text{M}+\text{H})^+$ ,  $\text{M} = \text{C}_{43}\text{H}_{27}\text{N}_7\text{O}_2\text{Pd}$ : 780.1339. Found: 780.1507. Elem. Anal. Calcd.: 66.20% C, 3.49% H, 12.57% N. Found: 66.14% C, 3.47% H, 12.53% N.

**5,10-Diphenyl-15,20-bis(3-pyridyl)porphyrinatopalladium(II) (2).** Following the aforementioned general procedure, 16 mg of the free-base porphyrin **2-H<sub>2</sub>** (0.03 mmol) was treated with 55 mg (0.18 mmol) of  $\text{Pd}(\text{acac})_2$  then purified using EtOAc as the eluent to give 7 mg (32% yield) of the title product.  $^1\text{H NMR}$  (500 MHz,  $\text{CDCl}_3$ )  $\delta$  7.72–7.80 (m, 8H), 8.16 (m, 4H), 8.48 (m, 2H), 8.76 (d,  $J$  = 5.1 Hz, 2H), 8.80 (d,  $J$  = 2.2 Hz, 2H), 8.84 (s, 2H), 8.87 (d,  $J$  = 5.1 Hz, 2H), 9.04 (m, 2H), 9.42 (m, 2H). Anal. Calcd. for  $(\text{M}+\text{H})^+$ ,  $\text{M} = \text{C}_{42}\text{H}_{26}\text{N}_6\text{Pd}$ : 721.1332. Found: 721.1335.

**5,10,15-Triphenyl-20-(4-pyridyl)porphyrinatopalladium(II) (3).** Following the aforementioned general procedure, 30 mg (0.05 mmol) of the free-base porphyrin **3-H<sub>2</sub>** was treated with 136 mg (0.446 mmol) of  $\text{Pd}(\text{acac})_2$  then purified using  $\text{CH}_2\text{Cl}_2$  as the eluent to give 6 mg (17% yield) of the title product.  $^1\text{H NMR}$  (500 MHz,  $\text{CDCl}_3$ )  $\delta$  7.72–7.80 (m, 9H), 8.13 (m, 2H), 8.16 (m, 6H), 8.75 (d,  $J$  = 5.1 Hz, 2H), 8.82 (s, 4H), 8.85 (d,  $J$  = 5.1 Hz, 2H), 9.02 (m, 2H).

Anal. Calcd. for (M+H)<sup>+</sup>, M = C<sub>43</sub>H<sub>27</sub>N<sub>5</sub>Pd: 720.1380. Found: 720.1430.

**Preparation of QD/Porphyrin Conjugates.** Toluene stock solutions of each palladium porphyrin 1–3 (~100 μM) and QD (~10 μM) were prepared. The concentration of the QD stock solution was calculated using  $\epsilon_{350} = 4.34 \times 10^5 \text{ M}^{-1} \text{ cm}^{-1}$ , as estimated using an empirical formula based on the first absorbance feature at 501 nm.<sup>44</sup> An aliquot of the QD stock (typically containing ~1 nmol of QDs) was dissolved in 4 mL of toluene; an appropriate volume of the porphyrin stock was then added to give 10 mol equiv of porphyrin per QD. The resultant mixture was stirred overnight at room temperature to allow equilibration of the porphyrin to the QD surface, to furnish conjugates **QD1–QD3**.

**Physical Measurements.** <sup>1</sup>H NMR spectra were recorded at room temperature on a Varian Inova-500 or Bruker Avance-400 NMR spectrometer at the MIT Department of Chemistry Instrumentation Facility (DCIF) and internally referenced to the residual solvent signal ( $\delta = 7.26$  for CHCl<sub>3</sub> in CDCl<sub>3</sub>).<sup>45</sup> Mass spectra were recorded on a Bruker micrO-TOF-QII LCMS/ESI-TOF mass spectrometer in positive ion mode. All spectra were externally calibrated with sodium formate. Elemental analysis was performed by Complete Analysis Laboratories, Inc. (Parsippany, NJ). UV–vis absorption spectra were acquired using a Cary 5000 spectrometer (Agilent). Steady-state emission and excitation spectra were recorded on a SPEX FluoroMax-3 spectrofluorimeter (Jobin Yvon Horiba). Relative quantum yields of porphyrins ( $\Phi_{\text{sam}}$ ) were calculated using [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> in MeCN as the reference according to the following equation,

$$\Phi_{\text{sam}} = \Phi_{\text{ref}} \left( \frac{A_{\text{ref}}}{A_{\text{sam}}} \right) \left( \frac{I_{\text{sam}}}{I_{\text{ref}}} \right) \left( \frac{\eta_{\text{sam}}}{\eta_{\text{ref}}} \right)^2 \quad (1)$$

where  $A$  is the measured absorbance,  $\eta$  is the refractive index of the solvent,  $I$  is the integrated emission intensity, and  $\Phi_{\text{ref}}$  is the emission quantum yield of the reference.  $\Phi_{\text{ref}}$  was taken to be 0.094 for a freeze–pump–thawed (FPT) sample of [Ru(bpy)<sub>3</sub>]Cl<sub>2</sub> in MeCN.<sup>46</sup> The quantum yield of **QD** was similarly determined using fluorescein 27 in 0.1 M NaOH ( $\Phi_{\text{ref}} = 0.87$ ,  $\eta = 1.335$ )<sup>47</sup> as the standard. Porphyrin samples for quantum yield measurements, vacuum lifetime ( $\tau_v$ ) measurements, and evacuated steady-state emission spectra were prepared using three cycles of FPT to pressures below 10<sup>−5</sup> Torr.

Nanosecond time-resolved emission measurements of porphyrin lifetimes were acquired using a previously reported system.<sup>48,49</sup> Pump light was provided by the third harmonic (355 nm) of a Quanta-Ray Nd:YAG laser (Spectra Physics) operating at 10 Hz. The pump light was passed through a BBO crystal in an optical parametric oscillator (OPO), yielding a visible frequency that was tuned to 525 nm to excite 1–3 or 450 nm to excite the assemblies **QD1–QD3**. Excitation light was attenuated to 1–4 mJ per pulse for all experiments using neutral density filters. Emitted light was first passed through a series of long pass filters to remove excitation light and then entered a Triax 320 monochromator (Jobin Yvon Horiba) and was dispersed by a blazed grating (500 nm, 300 grooves/mm) centered at 685 nm. The entrance and exit slits of the monochromator were set to 0.36 mm in all experiments herein, corresponding to a spectral resolution of 4.5 nm. The signal was amplified by a photomultiplier tube (R928, Hamamatsu) and collected on a 1 GHz digital oscilloscope (9384CM, LeCroy); acquisition was triggered using a photodiode to collect scattered laser excitation light.

Femtosecond emission lifetime measurements were acquired using a Libra-F-HE (Coherent) chirped-pulse amplified Ti:sapphire laser system. Sub-100 fs laser pulses were generated in a mode-locked Ti:sapphire oscillator (Coherent Vitesse) which was pumped by a 5 W cw Coherent Verdi solid-state, frequency-doubled Nd:YVO<sub>4</sub> laser. The 80-MHz output was amplified in a regenerative amplifier cavity, pumped by a diode-pumped, frequency-doubled Nd:YLF laser (Coherent Evolution-30) to generate a 1 kHz pulse train with a wavelength of 800 nm. This was then used to pump an Opera Solo (Coherent) optical parametric amplifier (OPA), which is able to generate frequencies between 285 and 2600 nm. Excitation pulses of 450 nm were produced via fourth harmonic generation of the idler

using a BBO crystal; the pulse power was attenuated to 2.5 mW at the sample. Emission lifetimes were measured on a Hamamatsu C4334 Streak Scope streak camera, which has been described elsewhere.<sup>50</sup> The emission signal was collected over a 140 nm window centered at 475 nm using 100, 50, 20, 10, or 5 ns time windows. Delays in the 100 ns time window were generated using a Hamamatsu C1097-04 delay unit, whereas a Stanford Research Systems DG535 delay generator was used to generate delays for the other time windows.

Two-photon emission spectra were generated using the aforementioned Libra-F-HE (Coherent) chirped-pulse amplified Ti:sapphire laser system. Excitation pulses of 800 nm were used directly from the Libra output; the pulse power was attenuated to 6 mW using neutral density filters, and the beam was focused onto the sample using a 500 mm focal length lens. The emission spectrum was collected using a Hamamatsu C4334 Streak Scope streak camera in 140 nm windows centered at 500, 550, and 650 nm.

Two-photon lifetime measurements were performed using a previously described custom-built multiphoton laser-scanning microscope (MPLSM) in the Edwin L. Steele Laboratory at the Department of Radiation Oncology at Massachusetts General Hospital.<sup>51</sup> The MPLSM system was modified to enable lifetime measurements to be performed.<sup>52</sup> Sub-100 fs laser pulses were generated at a repetition rate of 80 MHz in a mode-locked Ti:sapphire oscillator (Spectra Physics Mai Tai HP), which was pumped by a 14 W cw Spectra Physics Millennia diode-pumped solid-state (DPSS) laser operating at 532 nm; the output of the Mai Tai laser was tunable over the 690–1040 nm range. The 850 nm laser output was adjusted using a 10RP52-2 zero-order half-wave plate (Newport) and a 10GL08AR.16 Glan-Laser polarizer (Newport) to attenuate the power to 700–800 mW for aerated samples and 400 mW for FPT samples. The beam was passed through a 350–50 KD\*P Pockels cell (Conoptics) that amplified and switched the triggering pulses from a DG535 digital delay generator (Stanford Research Systems). The experimental square wave trigger pulse from the delay generator defined the repetition rate while a second delayed pulse defined the excitation pulse, which was 1.6 μs in duration for aerated samples and 15.36, 30.72, or 51.20 μs in duration for FPT samples. At the rejection site of the Pockels cell, a TDS-3052 oscilloscope (Tektronix) and photodiode were used to monitor the applied voltage and the optical response; the Pockels cell attenuated the beam to 10% of the incident power. The laser beam was directed into a custom-modified multiphoton microscope based on the Olympus Fluoview 300 laser scanner. The output beam from the scanner was collimated through a scan lens into the back of an Olympus BX61WI microscope. An Olympus LUMPlanFL 20×, 0.95 NA water immersion objective lens was used to focus the excitation light and collect the emission light. NIR laser excitation light and visible emission light were separated using a 750SP-2P AR-coated dichroic mirror (Chroma Technology). A 690/90 bandpass filter (Chroma Technology) and a focusing lens were used in front of the GaAs H7421-50 photomultiplier tube (Hamamatsu) to collect phosphorescent emission. Photon counting was performed using a SR430 multichannel scaler (Stanford Research Systems) to histogram the counts in 1024 or 2048 bins of 40 ns for aerated samples or 2.56 or 5.12 μs for FPT samples.

**Energy Transfer Analysis.** The efficiency of energy transfer ( $E$ ) from the QD to the porphyrin was evaluated using Förster analysis,<sup>32,53</sup>

$$E = \frac{mk_{D-A}}{mk_{D-A} + \tau_D^{-1}} = \frac{mR_0^6}{mR_0^6 + r^6} \quad (2)$$

where  $k_{D-A}$  is the rate of energy transfer,  $r$  is the distance between the donor and acceptor,  $R_0$  is the Förster distance or the distance at which the energy transfer efficiency is 50%, and  $m$  is the number of acceptor molecules per donor. This quantity can be measured experimentally:

$$E = 1 - \frac{\tau_{D-A}}{\tau_D} \quad (3)$$

where  $\tau_D$  is the lifetime of the QD alone and  $\tau_{D-A}$  is the lifetime of the QD with surface-bound porphyrin (**QD1–QD3**). Although the

efficiency can be experimentally determined from the excited-state lifetime quenching, additional information is needed to quantify the parameters  $R_0$ ,  $r$ , and  $m$ . The Förster distance is calculated using the following equation

$$R_0^6 = \frac{9000(\ln 10)\kappa^2\Phi_D}{128\pi^5N_A^4} \int_0^\infty F_D(\lambda) \epsilon_A(\lambda)\lambda^4 d\lambda \quad (4)$$

where  $\kappa^2$  is the relative orientation factor of the dipoles, taken to be 0.476 for static donor-acceptor orientations,<sup>32,54</sup>  $\Phi_D$  is the quantum efficiency of the donor (determined to be 0.72 for QD in toluene),  $N_A$  is Avogadro's number, and  $n$  is the index of refraction of the medium, which is taken to be 1.4961 for toluene.<sup>55</sup> The latter half of the equation represents the spectral overlap integral, often represented as  $J$ , where  $F_D(\lambda)$  is the normalized intensity of the donor and  $\epsilon_A(\lambda)$  is the extinction coefficient of the acceptor at wavelength  $\lambda$ . Thus,  $R_0$  may be calculated from the experimentally determined emission spectrum of the donor and the absorption spectrum of the acceptor.


**X-ray Crystallographic Details.** Diffraction quality crystals of **3** were obtained via slow vapor diffusion of heptane into a toluene solution of the compound, affording the crystals as orange blocks. Low-temperature (100 K) X-ray diffraction data was collected on a Siemens Platform three-circle diffractometer coupled to a Bruker-AXS Smart Apex CCD detector with graphite-monochromated Mo  $K\alpha$  radiation ( $\lambda = 0.71073 \text{ \AA}$ ), performing  $\varphi$ - and  $\omega$ -scans. The data were processed and refined using the program SAINT supplied by Siemens Industrial Automation. The structure was solved by direct methods using SHELXS and refined by standard difference Fourier techniques in the SHELXL program suite.<sup>56</sup> All hydrogen atoms were included in the model at geometrically calculated positions using a riding model and refined isotropically; all non-hydrogen atoms were refined anisotropically. Unit cell parameters, morphology, and solution statistics for the structure are summarized in Supporting Information, Table S1. Thermal ellipsoid plots are drawn at the 50% probability level with hydrogen atoms omitted for clarity.

## RESULTS AND DISCUSSION

**Porphyrin Synthesis.** The methodology to synthesize the free-base pyridyl porphyrins **1-H<sub>2</sub>**–**3-H<sub>2</sub>** was optimized by comparing the merits of various synthetic protocols for **1-H<sub>2</sub>**. Initially, a mixed aldehyde condensation under standard Lindsey conditions<sup>57</sup> was attempted, as this synthesis is well-known and works for a wide variety of *meso*-substituted porphyrins. However, only an insoluble black material was obtained in the attempted synthesis of **1-H<sub>2</sub>**, likely because of the formation of polypyrrolic species. To circumvent these side reactions, a mixed aldehyde/dipyrromethane condensation<sup>58</sup> of 5-(4-pyridyl)dipyrromethane (**12**), 4-pyridinecarboxaldehyde, and methyl 4-formylbenzoate was performed under Lindsey conditions; no macrocyclic products were identified from this reaction. The failure of these reactions is presumably because of coordination of  $\text{BF}_3 \cdot \text{OEt}_2$  to a pyridyl nitrogen, thereby sequestering the Lewis acid catalyst. While compound **1-H<sub>2</sub>** has been prepared using Adler–Longo<sup>59,60</sup> porphyrin synthesis (Supporting Information, Scheme S1),<sup>61–64</sup> this protocol suffers from difficult and repetitive chromatographic separations as all six possible porphyrin isomers ( $A_4$ ,  $A_3B$ , *cis*- $A_2B_2$ , *trans*- $A_2B_2$ ,  $AB_3$ , and  $B_4$ ) are formed in addition to other tetrapyrrolic products, thus resulting in a low yield (4.3–5.9%)<sup>61–64</sup> of the desired  $A_3B$  product. Indeed, we could only obtain **1-H<sub>2</sub>** under Adler–Longo conditions at 3.9% yield (see Supporting Information). An alternative to statistical methods, which involve the construction of a linear tetrapyrrole (i.e., bilane) that is cyclized and subsequently oxidized to afford the corresponding porphyrin.<sup>65,66</sup> This method has the advantage of forming a single porphyrin product, thereby circumventing difficult chromato-

graphic separations. It also allows for the synthesis of porphyrin isomers that are difficult to isolate under statistical conditions (e.g., *cis*- $A_2B_2$  versus *trans*- $A_2B_2$ ). Additionally, up to four different *meso* substituents can be incorporated, thus enabling the formation of precise porphyrin isomers that are inaccessible with statistical methods (e.g., *cis*- $A_2BC$  and  $ABCD$ ). However, the rational synthesis (Supporting Information, Scheme S2) of **1-H<sub>2</sub>** entails a series of nine synthetic steps, with a yield of 15% (based on bilane precursor) for the combined bilane synthesis and subsequent porphyrin-forming steps.

A more facile synthesis of **1–3** is outlined in Figure 2. The method relies on the use of bilane precursors (1-acyl

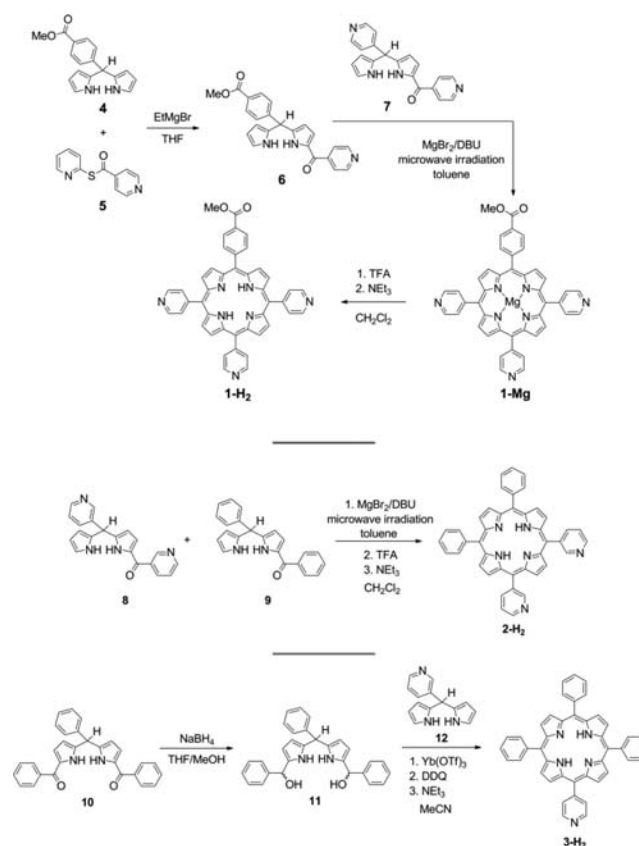


**Figure 2.** Synthesis of **1–3** from metal-catalyzed [2 + 2] cycloadditions of appropriate bilane precursors.

dipyrromethanes) in a  $\text{MgBr}_2$ -catalyzed [2 + 2] cycloaddition under microwave irradiation.<sup>40</sup> While this is a statistical method of synthesis for **1**, the formation of only three porphyrin isomers (*trans*- $A_2B_2$ ,  $A_3B$ , and  $A_4$ ) is possible. Using this method, porphyrin **1-H<sub>2</sub>** was isolated in 11% yield. This nominal decrease in yield relative to the aforementioned bilane route is more than compensated by the elimination of three synthetic steps. This route is particularly amenable to the synthesis of *cis*- $A_2B_2$  porphyrins such as **2-H<sub>2</sub>** for which the separation of the three porphyrins is facile. Similarly, **3-H<sub>2</sub>** was synthesized in a [2 + 2] cycloaddition of a 1,9-diacetyldipyrromethane and a dipyrromethane. By replacing the typical TFA acid catalyst<sup>38</sup> with  $\text{Yb}(\text{OTf})_3$ , the yield of **3-H<sub>2</sub>** was increased dramatically from 3.9% to 24%. In this case, the formation of only one porphyrin isomer is possible. Given the simplicity of this route and its advantages over both completely statistical and rational methods, the [2 + 2] route was preferred in the synthesis of **1-H<sub>2</sub>**–**3-H<sub>2</sub>**.

Palladium was introduced into the porphyrin macrocycle by using Pd(acac)<sub>2</sub> in pyridine under microwave irradiation.<sup>67</sup> This dramatically reduces the reaction time from as long as 4 d under conventional heating<sup>68</sup> to 20 min with microwave irradiation. Although the metalation reaction using this method is typically quantitative,<sup>67</sup> the observed yields here are low (17–50%). This is attributed to the formation of insoluble coordination oligomers in which Pd<sup>2+</sup> coordinates to pyridyl groups of two different porphyrins, as has previously been observed.<sup>69–72</sup>


Diffraction quality crystals of **3** were obtained as orange blocks by slow vapor diffusion of heptane into a toluene solution of the compound. The thermal ellipsoid plot of the refined structure is shown in Figure 3, and a summary of the

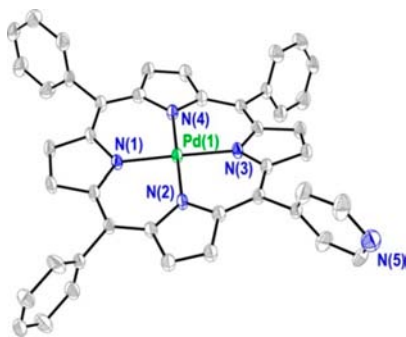

**Figure 3.** Solid-state crystal structure of compound **3**. Thermal ellipsoids are drawn at the 50% probability level and hydrogen atoms have been removed for clarity.

crystallographic data is presented in Supporting Information, Table S1. To identify the unique 4-pyridyl group of the structure, the 4 position of each *meso* substituent was refined as a carbon atom, and the resultant electronic density difference map was examined. The 10 largest residual density peaks (Q peaks) of this refinement cycle are shown in Supporting Information, Figure S1. Three of the four *meso* substituents show a Q peak adjacent to the 4 position of the ring, indicating the presence of a hydrogen atom, while the fourth does not, thereby differentiating the 4-pyridyl ring from the phenyl rings. Qualitatively, the structure is very similar to other Pd porphyrin complexes, such as 5,10,15,20-tetrakis(4-carboxyphenyl)porphyrinatopalladium(II).<sup>73</sup> The palladium atom resides in the center of the 24 atom macrocycle plane with an average Pd–N distance of 2.011 Å (as compared to 2.009 Å for 5,10,15,20-tetraphenylporphyrinatopalladium(II), PdTPP).<sup>74</sup> The porphyrin plane exhibits an S<sub>4</sub> ruffle with an average deviation of 0.196 Å from the mean 24 atom plane. Such nonplanarity is also observed in the solid state structure of PdTPP. Each of the pyrrole nitrogen atoms deviates from the mean N<sub>4</sub> plane by 0.030 Å, a displacement that is identical to that observed for PdTPP.<sup>74</sup>

**Electronic Properties of Porphyrins.** Porphyrins **1–3** display absorption spectra (Figure 4) that are typical of hypsoporphyrins.<sup>75,76</sup> Table 1 summarizes the spectroscopic data for these porphyrins. The B band (Soret), centered at 415 nm, is intense and flanked by the weaker Q(1,0) and Q(0,0) bands at 523 and 554 nm, respectively. This absorption profile is similar to other *meso*-substituted Pd porphyrins. For comparison, PdTPP exhibits analogous absorbance features at 416, 522, and 551 nm.<sup>77</sup> The porphyrin emission spectra (Figure 4) ( $\lambda_{\text{exc}} = 525$  nm) exhibits two broad emission bands

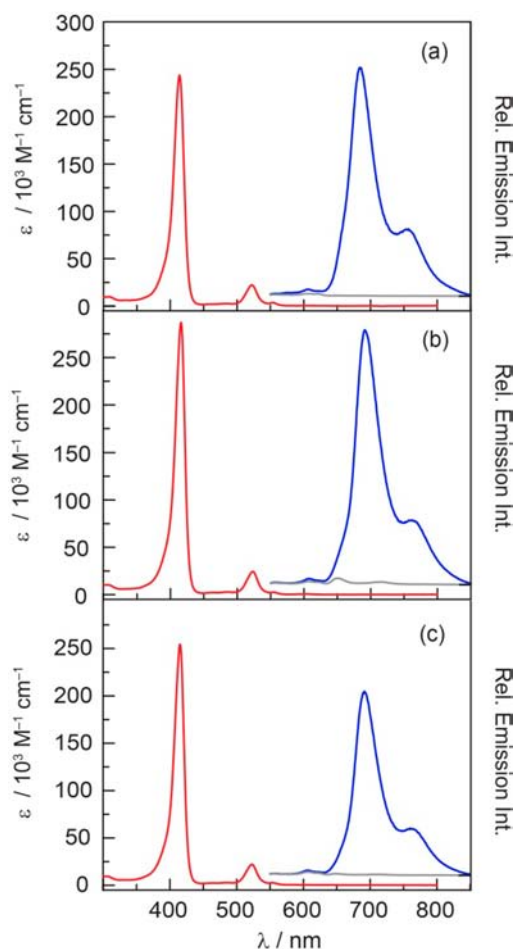

**Figure 4.** Comparison of the steady state absorption (red lines) and emission spectra ( $\lambda_{\text{exc}} = 525$  nm) of (a) **1**, (b) **2**, and (c) **3** in the presence of air ( $\sim 160$  Torr O<sub>2</sub>) (gray lines) and under vacuum (blue lines) in toluene.

with maxima observed at 690 nm for T(0,0) and 760 nm for T(0,1); these spectral features are similar to those observed for PdTPP (688 and  $\sim 760$  nm).<sup>77</sup> Each porphyrin also exhibits a small emission feature at about 606 nm that is attributed to the Q(0,1) fluorescence transition. This assignment is consistent with the insensitivity of the intensity of this band to oxygen; such a transition has been observed at 606 nm for PdTPP.<sup>78</sup>

The additional feature observed in the emission spectrum of **2** centered at 650 nm is assigned to the Q(0,0) transition of 2-H<sub>2</sub>. Based on the size of the emission band and the ten-fold higher emission quantum yield for H<sub>2</sub>TPP ( $\phi_f = 0.13$ )<sup>79</sup> as compared to that of the Pd complex ( $\phi_p = 0.011$  for **2**), it is estimated that 2-H<sub>2</sub> is present at most as a 1% impurity. In accordance with this contention, no trace of 2-H<sub>2</sub> was visible by NMR or TLC. Since the 2-H<sub>2</sub> fluorescence band is eclipsed by the phosphorescence bands of **2** in the absence of oxygen (Figure 4b) and the fluorescence lifetime of 2-H<sub>2</sub> ( $\tau_{\text{air}} \sim 9$  ns for free-base pyridyl porphyrins)<sup>80</sup> is much shorter than **2** ( $\tau_{\text{air}} \sim 300$  ns), the trace presence of this species has little impact on the results presented herein.

The phosphorescence quantum yields of **1–3** are between 1–2% and are comparable to other Pd porphyrins ( $\phi_p = 0.02$  for PdTPP).<sup>81</sup> As shown in Figure 4, the phosphorescence is quenched significantly by air, establishing that these compounds are responsive to oxygen in the 0–160 Torr range.

Table 1. Summary of Linear Spectroscopic Data for Pd Porphyrins and QD Conjugates

compound <sup>a</sup>	B(0,0), $\epsilon^b$	Q(1,0), $\epsilon^b$	Q(0,0), $\epsilon^b$	QD <sub>Em</sub>	T(0,0) <sup>c</sup>	T(0,1) <sup>c</sup>	$\phi_p^d$
1	414, 240	522, 22	554, 3.6		684	753	0.014
2	416, 290	523, 24	554, 2.6		691	760	0.011
3	415, 250	523, 22	554, 2.8		691	760	0.014
QD1	416	523	554	517	684	754	0.040
QD2	418	524	555	518	692	763	0.027
QD3	417	523	553	516	691	761	0.018

<sup>a</sup>Toluene solution, transition wavelengths are in units of nm. <sup>b</sup> $\epsilon$  in  $10^3 \text{ M}^{-1} \text{ cm}^{-1}$ , as determined in  $\text{CH}_2\text{Cl}_2$ . <sup>c</sup>Triplet transitions for evacuated samples ( $<10^{-5}$  Torr). <sup>d</sup>Phosphorescence quantum yield of freeze–pump–thawed samples.

Indeed, the phosphorescence emission intensity from a freeze–pumped–thawed (FPT) sample of **1** is 500-fold that observed for the sample in air; a 100-fold to 200-fold enhancement was observed for **2** and **3**.

The triplet lifetime ( $\lambda_{\text{exc}} = 525 \text{ nm}$ ) data of **1–3** in toluene at room temperature in the presence and absence of air is summarized in Table 2. Decay traces were fit at  $t > 100 \text{ ns}$  to a

Table 2. Summary of Lifetime Data for Pd Porphyrins

compound <sup>a</sup>	$\tau_{\text{air}}$ (ns) 1-photon <sup>c</sup>	$\tau_o$ ( $\mu\text{s}$ ) <sup>b</sup> 1-photon <sup>c</sup>	$\tau_{\text{air}}$ (ns) 2-photon <sup>d</sup>	$\tau_o$ ( $\mu\text{s}$ ) <sup>b</sup> 2-photon <sup>d</sup>
1	$332 \pm 3^e$	$154 \pm 12$	$556 \pm 40$	$157 \pm 3$
2	$289 \pm 7$	$133 \pm 5$	$354 \pm 14$	$77 \pm 5$
3	$305 \pm 6$	$144 \pm 6$	$365 \pm 12$	$80 \pm 3$

<sup>a</sup>Toluene solution. <sup>b</sup>Freeze–pump–thawed samples ( $<10^{-5}$  Torr). <sup>c</sup> $\lambda_{\text{exc}} = 525 \text{ nm}$ . <sup>d</sup> $\lambda_{\text{exc}} = 850 \text{ nm}$ . <sup>e</sup>95% confidence interval.

monoexponential decay curve ( $R_{\text{adj}}^2 > 0.96$ ). The significant difference in the lifetimes of **1–3** in the presence ( $\sim 300 \text{ ns}$ ) and absence of air ( $\sim 150 \mu\text{s}$ ) suggests that these phosphors have a sufficient dynamic range to accurately quantify oxygen over a 0–160 Torr range. Although porphyrins have low two-photon cross sections, sufficient signal was acquired to measure the lifetimes of **1–3** under two-photon ( $\lambda_{\text{exc}} = 850 \text{ nm}$ ) excitation (Table 2). To the best of our knowledge, this is the first study that compares porphyrin lifetimes under one- and two-photon excitation. Because of differences in selection rules for one- and two-photon transitions, different states are accessed with different vibronic coupling.<sup>82</sup> It has been shown for linear polyenes that these differences lead to different one- and two-photon lifetimes.<sup>83</sup> Accordingly, the differences in lifetimes of **1–3** under one- and two-excitation are not unexpected.

**QD Quenching Titrations with 1–3.** Titration experiments were performed to assess surface binding of pyridyl porphyrins **1–3** to the surface of QD. In these titrations, there exists the following equilibrium,



with an equilibrium constant  $K_A$ . Upon increasing the amount of porphyrin, the equilibrium is driven to conjugate formation. The QD emission provides a convenient probe of the equilibrium. For these experiments, the QD was judiciously chosen such that its emission overlapped with the absorbance of Q(1,0) of **1–3**, thereby maximizing the spectral overlap integral  $J$  (eq 4) and accordingly enabling quenching of QD emission by energy transfer. Specifically, we selected a QD with a first absorbance feature at 501 nm and emission band ( $\lambda_{\text{exc}} =$

450 nm) centered at 519 nm (Supporting Information, Figure S2).


The quenching of QD luminescence via energy transfer was examined as a function of the disposition of pyridyl rings at the *meso* positions: two *cis* 4-pyridyl rings (**1**), two *cis* 3-pyridyl rings (**2**), and a single 4-pyridyl ring (**3**). Titrations were performed in which the same amount of QD ( $\sim 400$  picomoles or  $\sim 100 \text{ nM}$ ) was treated with 1, 2, 5, or 10 equiv of **1–3**. Each sample point in the titration was prepared independently and incubated overnight at room temperature to ensure porphyrin binding on the QD surface. Figure 5 shows the absorption, steady-state emission and time-resolved emission profiles for the titration of QD with **1**; similar data for compounds **2** and **3** are presented in Supporting Information, Figures S3 and S4, respectively. The excitation wavelength of 450 nm was chosen for these experiments because the absorbance of the porphyrin is minimal whereas that of the QD is relatively high.

The absorption profile (Figure 5a) is effectively the sum of the QD and compound profiles. Figures 5b and 5c establish significant quenching of the QD emission with increasing concentration of the porphyrin. The quenching lifetimes obtained from the decay profiles in Figure 5c are provided in Supporting Information, Table S2. We note that the emission decay of QD in the absence of porphyrin is biexponential ( $R_{\text{adj}}^2 > 0.99$ ) with components that reflect surface trapped states (17 ns) and exciton emission (5 ns).<sup>84,85</sup> While QD lifetimes have been fit to triexponential functions<sup>86,87</sup> to include Auger recombination,<sup>88</sup> the inclusion of a third term is an over-parameterization of our data. Biexponential behavior is preserved upon titration with porphyrin. Of the three compounds, **2**, with its *cis* disposition of pyridyl rings, quenches QD emission most effectively whereas **3**, with its single pyridyl ring is the least effective quencher. These results clearly suggest that two *cis* pyridyl rings facilitate porphyrin binding to the QD surface.

Since the formation of the QD/porphyrin conjugate occurs under dynamic self-assembly, there exists a discrete distribution of the number of porphyrins attached to the QD; hence there is a distribution of QD:porphyrin ratios at any point in the titration. Such a distribution is best described with Poisson statistics.<sup>80</sup> The Poisson probability distribution provides a model for the probability,  $p(Y)$ , that the number of events  $Y$  (i.e., a given QD:porphyrin ratio) occur, where  $\lambda$  is the average value of  $Y$ .<sup>89</sup>

$$p(Y) = \frac{\lambda^Y}{Y!} e^{-\lambda} \quad (6)$$

where  $Y = 0, 1, 2, \dots$ , and  $\lambda > 0$ . For example, after the addition of 1 equiv of porphyrin per equiv of QD ( $\lambda = 1$ ), the probability  $p(Y)$  that there are 0, 1, 2, or  $\geq 3$  porphyrins per QD is 0.368, 0.368, 0.184, and 0.080, respectively.

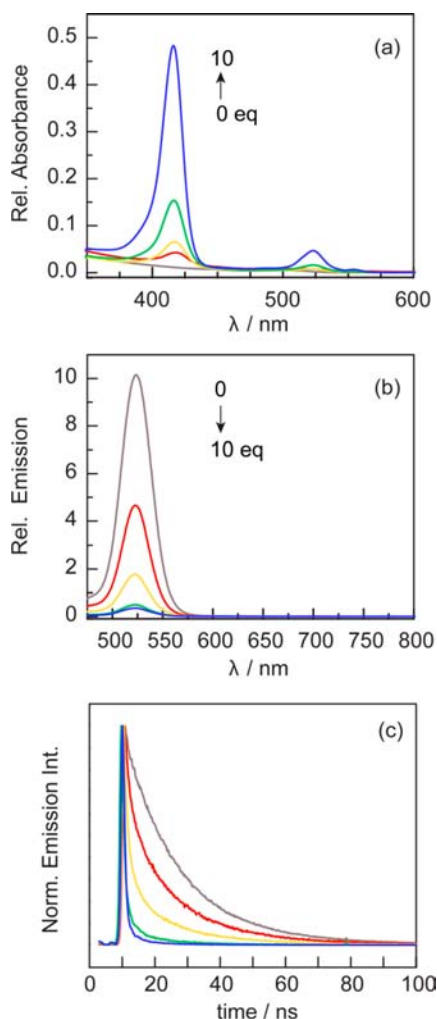

**Figure 5.** Spectral changes associated with titration of a toluene solution of QD (gray lines) with **1** (red lines), **2** (yellow lines), **5** (green lines), and **10** (blue lines) equiv of **1**. Similar data for **2** and **3** are shown in Supporting Information, Figures S3 and S4. (a) The intensity of the Soret and Q-band absorption profiles increases. (b) The QD emission ( $\lambda_{\text{exc}} = 450$  nm) intensity is quenched, and (c) the decay profiles of the QD emission ( $\lambda_{\text{exc}} = 450$  nm) decrease with increasing equiv of **1**.

As with the QD alone, the presence of porphyrin gives rise to a biexponential decay. Both the exciton emission (short lifetime component) and surface trapped state (long lifetime component) are affected by the presence of porphyrin. Because the surface state is most perturbed by porphyrin binding, the amplitude of the long lifetime component was used as a metric for determining the amount of free QD in solution. To this end, the long component of each decay was fixed at 16.93 ns, which is the calculated lifetime of the surface-trapped states for the QD alone. The relative reduction in the amplitude of this component serves as a measure of free QD at various points in the titration. The lifetime data is summarized in Supporting Information, Table S2. Over the course of the titration, the surface trapped state is quenched, resulting in the formation of a non-fluorescent QD-porphyrin complex (i.e., static quenching). Based on the data, 10 equiv of **1** and **2** reduce the QD lifetime to  $\sim 300$  ps with a similar emission intensity (vide supra), indicating that the *cis* pyridyl groups enhance QD surface binding and result in efficient luminescence quenching.

For 1 equiv of **1**, the long component (surface trapped states) is reduced to 12% of the overall fit (compared to 53% for free QD), suggesting that  $\sim 20\%$  of the QDs in solution lack a surface bound porphyrin. If the distribution of species in solution were purely statistical (i.e., non-specific interactions or encounter complexes), one would expect that  $\sim 37\%$  of QDs would lack a surface bound porphyrin based on the Poisson distribution. Since we observe fewer free QDs in solution, it is clear that **1** is binding to the QD surface in a directed manner. This is more clearly illustrated with **2**, which shows virtually no free QDs in solution after the addition of 1 equiv of porphyrin. The fact that these two compounds do not follow the expected Poisson distribution indicates that the QD-porphyrin interaction is specific (i.e., directed bidentate surface binding) and not just a statistical non-specific interaction. These observations are in stark contrast to compound **3**. After the addition of 1 equiv of **3**, the amplitude of the long component is reduced to 25%, suggestive of 47% free QDs in solution. This is consistent with the expected value of 37% base distribution. The binding of **3** is so inefficient that  $\sim 34\%$  of QDs are free in solution after the addition of 2 equiv (compare to an expected 13% based on the Poisson distribution). Since the titration with **3** matches the expected Poisson distribution, the interaction between this molecule and the QD is nonspecific, suggesting that the interaction is statistical rather than directed. These results are consistent with the proposal that **1** and **2** are immobilized via a two point attachment, while porphyrin **3**, with a single 4-pyridyl group, results in less efficient luminescence quenching.

Whereas the distribution of species at low porphyrin concentration can be probed using QD lifetime data as a measure of free QD in solution, the lack of a suitable spectroscopic signature at high porphyrin concentrations renders the experimental determination of QD-porphyrin ratios intractable. At low porphyrin concentrations, the distribution of species in solution is dictated by the porphyrin's affinity for the surface (i.e., equilibrium constants as described below). At high porphyrin concentrations, geometric and steric factors control the distribution of QD-porphyrin species. Therefore, it is expected that this phenomenon is stochastic and follows a Poisson distribution.<sup>80</sup>

**Determination of Equilibrium Constants.** Using both the QD emission intensity and the lifetime titration data, the equilibrium constant ( $K_A$ ) for the formation of the QD-porphyrin conjugate (eq 5) was determined. The association constant can be determined using the Stern–Volmer equation:

$$\frac{I_0}{I} = \frac{\tau_0}{\tau} = 1 + K_A[\text{Por}] \quad (7)$$

where  $I_0$  and  $\tau_0$  are the emission intensity and lifetime, respectively, in the absence of added porphyrin,  $I$  and  $\tau$  are the emission intensity and lifetime, respectively, in the presence of a given concentration of porphyrin, [Por]. For all three porphyrins, both the lifetime (short component of Supporting Information, Table S2) and intensity data are consistent, giving qualitatively similar plots (Supporting Information, Figure S5). Downward curvature in the plots of the stronger ligands **1** and **2** at high porphyrin concentrations suggests a binding saturation event while **3** exhibits a linear plot. The linear regions of the data (Supporting Information, Table S3) were fit to eq 7 to give average values of  $K_A = 2.50 \times 10^7 \text{ M}^{-1}$  (**1**),  $2.83 \times 10^7 \text{ M}^{-1}$  (**2**), and  $1.36 \times 10^6 \text{ M}^{-1}$  (**3**). These results are consistent with the data of Figure 5, Supporting Information, Figures S3 and S4, indicating that **1** and **2** bind to the QD




surface with similar efficacy whereas **3** binds more weakly. At high porphyrin concentrations, the curvature of **1** and **2** may be modeled with the Hill equation, which accounts for binding cooperativity:

$$y = y_{\max} \frac{[\text{Por}]^n}{K_D^n + [\text{Por}]^n} \quad (8)$$


where  $y_{\max}$  is the theoretical maximum value of  $y$  ( $I_0/I$  or  $\tau_0/\tau$ ) at infinite substrate concentration and is a measure of the maximum extent of quenching of lifetime or emission intensity.  $K_D$  is the dissociation constant ( $K_D = 1/K_A$ ), and  $n$  is the Hill coefficient, which is a measure of the degree of binding cooperativity. Positive cooperativity, that is, the binding of one molecule facilitates the subsequent binding event, is indicated for  $n > 1$ . For  $n < 1$ , there is negative cooperativity such that the binding of one molecule impedes the binding of additional molecules. If  $n = 1$ , binding is not cooperative, and each binding event is independent. The fits of the data for **1** and **2** to eq 8 are presented in Supporting Information, Table S4. For both intensity and lifetime data, the calculated  $y_{\max}$  is very close to the observed  $y$  values at 10 equiv, suggesting that binding saturation to a QD is reached at a limiting value of 10 equiv of **1** and **2**. The different values of  $n = 1.8$  for **1** and  $n = 0.8$  for **2**, may reflect the different coordination modes of the porphyrins on the QD surface. The  $\pi$ -stacking of **1** between porphyrin rings could lead to a positive cooperativity through  $\pi$ - $\pi$  stacking interactions that facilitate the binding of subsequent porphyrin molecules. Conversely, an angled conformation in which the porphyrin covers the surface of the QD, would inhibit the binding of neighboring porphyrin molecules. This binding model is supported by titration experiments in which 1 equiv of **2** dramatically quenches QD (Supporting Information, Figure S3 and Table S2); we suspect this is because of the proximity of the porphyrin macrocycle to the QD surface.

**Characterization of QD–Porphyrin Conjugates.** Given the results of the titration experiments, 10 equiv of porphyrin drives the equilibrium in eq 5 far to the right and ensures that each QD is associated to porphyrin. From eq 6, the probability of having a free QD at 10 equiv of porphyrin in solution is essentially 0 (0.0045%). Conjugates prepared from 10 equiv of porphyrin are designated **QD1–QD3**.

Table 1 lists selected steady-state absorption and emission spectroscopic data for the self-assembled **QD1–QD3** conjugates. The absorption spectrum of the conjugates is a composite sum of the porphyrin and QD spectra, as illustrated in Figure 6 for **QD1**. The emission spectra ( $\lambda_{\text{exc}} = 450$  nm) also exhibit features characteristic of both the porphyrin and the QD. As shown in Figure 7, a slight 1–2 nm ( $\sim 100$   $\text{cm}^{-1}$  for B bands and  $\sim 40$   $\text{cm}^{-1}$  for Q bands) red shift was observed in the porphyrin absorption and emission bands of **QD1–QD3** as compared to **1–3**. This phenomenon, which has been observed for free-base porphyrins<sup>90</sup> and pyrene<sup>25</sup> bound to a QD surface, has been attributed to differences between the average dielectric constant of the lumophore in solution as compared to that near the surface of the QD. The QD emission from the conjugate is slightly blue-shifted (1–3 nm, 40–100  $\text{cm}^{-1}$ ) relative to free QD, which has previously been ascribed to modulation of the QD surface states<sup>91,92</sup> upon ligand binding.<sup>93</sup> More pronounced than these slight wavelength shifts is the increase in porphyrin phosphorescence quantum yield when bound to the QD (Table 1); **QD1** and **QD2** show the greatest enhancement (nearly a three-fold increase) in quantum yield upon surface binding as

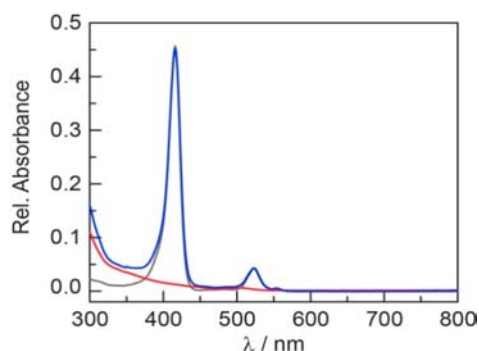

**Figure 6.** Comparison of the absorption spectra of **1** (gray lines), **QD** (red lines) and **QD1** (blue lines) in toluene. The spectrum of **QD1** represents a composite of the two constituent spectra.

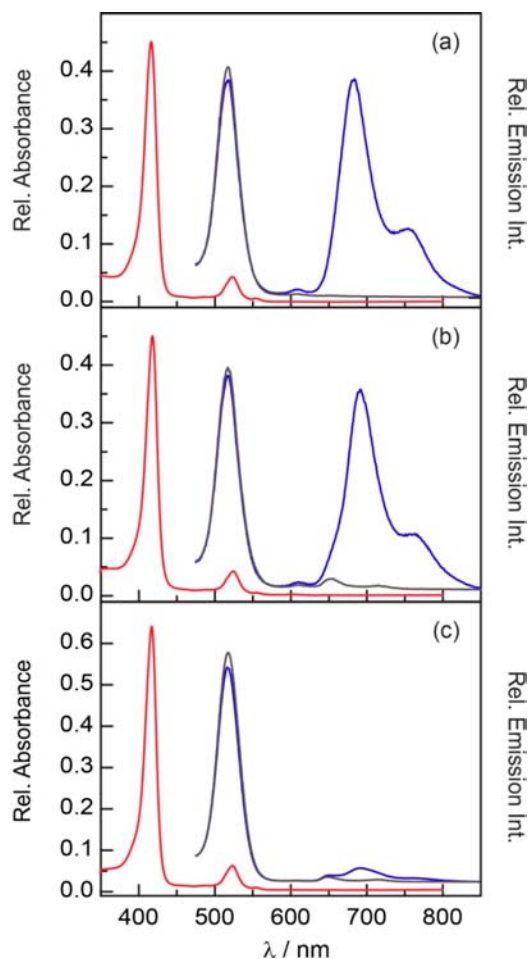

**Figure 7.** Comparison of the steady state absorption (red lines) and emission spectra ( $\lambda_{\text{exc}} = 525$  nm) of (a) **QD1**, (b) **QD2**, and (c) **QD3** in the presence of air ( $\sim 160$  Torr  $\text{O}_2$ ) (gray lines) and under vacuum (blue lines) in toluene.


compared to **QD3**. This phenomenon has been attributed to a decrease in  $k_{\text{nr}}$  when the porphyrin is intercalating within the capping ligand environment.<sup>9</sup> These observations are concordant with stronger association of **1** and **2** to the QD surface than as compared to **3** owing to the *cis*-disposition of pyridyl ligands at the *meso* sites of the porphyrin framework of the former. Because the intensity of the T(0,0) porphyrin and QD emissions of **QD1** and **QD2** are comparable, a self-referencing scheme is easily established with these conjugates. This is not

the case of **QD3**, which displays weak porphyrin emission as compared to the **QD** emission. The  $O_2$  response is reversible, as the phosphorescence intensity is recovered upon subjecting an aerated sample to a freeze–pump–thaw cycle. This process may be repeated with no change in intensity.

The enhancement of porphyrin emission upon association of the **QD** is a result of FRET. In these assemblies, the **QD** serves as the antenna for photon absorption. Energy is passed from the **QD** donor to the porphyrin acceptor by the FRET mechanism. Under linear excitation ( $\lambda_{exc} = 450$  nm), a nearly four-fold enhancement in emission is observed when **QD** is present (Supporting Information, Figure S6) owing to the greater absorbance of the **QD** at 450 nm relative to **1**.

The FRET parameters for **QD1–QD3** are summarized in Supporting Information, Table S5, and the spectral overlap of **QD** donor and porphyrin acceptor is illustrated in Supporting Information, Figure S7.  $J$  is similar for all three assemblies and thus Förster distances ( $R_0$ ) for the **QD**–porphyrin conjugates are also similar. Nevertheless, the FRET efficiencies, as calculated from the short component of the **QD** lifetimes at 10 equiv (Supporting Information, Table S2) and eq 3, vary significantly owing to differences in the interaction of the porphyrin with **QD**. The efficiency is 94% for **1** and **2**, but only 67% for **3**. The disparate conjugate interactions are unveiled in the donor–acceptor distances calculated from eq 2.  $r$  is significantly ( $\sim 1.5$  nm) longer in **QD3** as compared to **QD1** and **QD2**. These data again indicate that the *cis* disposition of the *meso* pyridyl substituents results in a tighter and more compact **QD**:porphyrin conjugate. The similarity of  $r$  for **QD1** and **QD2** indicate that the substitution motif (4-pyridyl versus 3-pyridyl) is not crucial to the FRET efficiency.

The consequences of the FRET efficiency calculations are revealed in the excitation spectra of **QD1–QD3** in Figure 8,

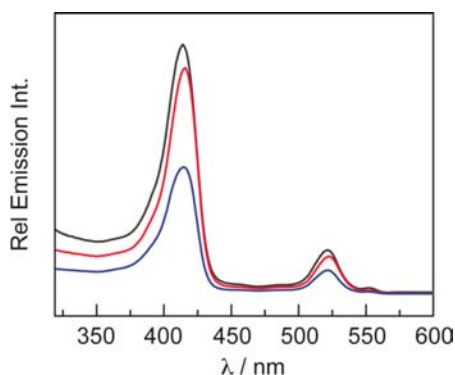


**Figure 8.** Excitation spectra ( $\lambda_{em} = 685$  nm) of concentration-matched toluene solutions of **QD1** (black lines), **QD2** (red lines), and **QD3** (blue lines).

which were recorded by monitoring the porphyrin emission at 685 nm with a 5 nm bandwidth. All of the collected emission is attributed to the porphyrin, as **QD** emission is spectrally separated by over 150 nm. At wavelengths where the porphyrins do not readily absorb ( $<375$  nm), a substantial emission signal is observed. This cannot be attributed to porphyrin absorption and subsequent emission. Instead, the **QD** absorbs the incident photons and transfers energy to the porphyrin which then emits. These excitation spectra correspond to the absorption profile of the conjugates (Figure 6), reflecting both porphyrin and **QD** absorption profiles. If the **QD** were not acting as a FRET donor, the excitation spectra

would look like the absorption profiles of **1–3**. Because of the similar extinction coefficients of **1–3**, the excitation spectra of these compounds should be the same in the absence of other effects. However, this is not the case because the FRET is modulated by the association of porphyrin to the **QD**. Accordingly, concentration-matched solutions of **QD1–QD3** show that **QD3** produces the least emission signal (since **3** is the weakest binder), having an intensity that is approximately 50% of **QD1**.

The FRET enhancement of porphyrin emission via the **QD** donor is more dramatic under two-photon excitation ( $\lambda_{exc} = 800$  nm), as the two-photon absorption cross-section for **QD** is  $\sim 10^4$  times greater than for the porphyrin itself. Figure 9 shows

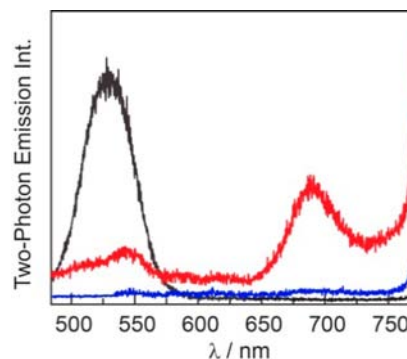

**Figure 9.** Two-photon emission spectra ( $\lambda_{exc} = 800$  nm) of concentration-matched toluene solutions of **QD** (black lines) and freeze–pump–thawed solutions of **1** (blue lines) and **QD1** (red lines). **1** does not emit under two-photon excitation, and emission is only observable in the presence of **QD**.

the two-photon emission spectrum for concentration-matched solutions of **QD**, **1**, and **QD1**. The porphyrin emission in **QD1** relative to **1** is enhanced by 10-fold and at the same time, the **QD** emission is reduced by  $\sim 70\%$  in **QD1** relative to **QD**. These results indicate that the **QD** serves as a photon antenna and FRET donor, resulting in enhanced porphyrin emission under both one- and two-photon excitation.

Although **QD1–QD3** show a qualitatively similar response to oxygen as do **1–3**, evidenced by the difference in the emission intensity (Figure 7) in the presence and absence of air, the relative extent of quenching is not as great as the free porphyrin in solution. This observation is attributed to the overall lower amount of signal due to the FRET excitation of the porphyrin in **QD1–QD3** relative to direct excitation of  $Q(1,0)$  in **1–3**. Air quenches the  $T(0,0)$  emission of **QD1** by 100- and by 50-fold for  $T(0,1)$ . **QD2** is somewhat less sensitive with approximately a 50-fold effect for both transitions whereas only a 10-fold effect is observed for **QD3**, presumably because of the lower FRET efficiency and thus lower amount of total signal.

Triplet lifetimes ( $\lambda_{exc} = 450$  nm) of **QD1–QD3** were determined in toluene at room temperature under air and for FPT solutions (Table 3). Decay traces at  $t > 100$  ns were fit to a biexponential decay curve ( $R_{adj}^2 > 0.96$ ). With an increase in quantum yield of the porphyrin within the **QD** construct, a similar increase in lifetime is expected based on

$$\Phi = \frac{k_r}{k_r + k_{nr}} = k_r \tau_0 \quad (9)$$

Table 3. Summary of Porphyrin Triplet State Lifetime Data for Assemblies QD1–QD3

compound <sup>a</sup>	sample	$\lambda_{\text{exc}}/\text{nm}$	$\tau_1$	$A_1$ (%) <sup>b</sup>	$\tau_2$	$A_2$ (%) <sup>b</sup>	$\tau_{\text{avg}}$ <sup>c</sup>
QD1	air	450	$638 \pm 64 \text{ ns}^d$	17	$69 \pm 11 \text{ ns}$	83	$174 \pm 92 \text{ ns}$
QD2	air	450	$575 \pm 5 \text{ ns}$	1	$29 \pm 1 \text{ ns}$	99	$37 \pm 1 \text{ ns}$
QD3	air	450	$550 \pm 6 \text{ ns}$	6	$41 \pm 1 \text{ ns}$	94	$72 \pm 7 \text{ ns}$
QD1	fpt <sup>e</sup>	450	$590 \pm 79 \mu\text{s}$	75	$149 \pm 51 \mu\text{s}$	25	$479 \pm 26 \mu\text{s}$
QD2	fpt	450	$482 \pm 41 \mu\text{s}$	65	$143 \pm 34 \mu\text{s}$	35	$363 \pm 15 \mu\text{s}$
QD3	fpt	450	$578 \pm 111 \mu\text{s}$	69	$166 \pm 51 \mu\text{s}$	31	$386 \pm 106 \mu\text{s}$
QD1	air	850	$537 \pm 14 \text{ ns}$	100	<i>f</i>		$537 \pm 14 \text{ ns}$
QD2	air	850	$401 \pm 4 \text{ ns}$	100	<i>f</i>		$401 \pm 4 \text{ ns}$
QD3	air	850	$430 \pm 5 \text{ ns}$	100	<i>f</i>		$430 \pm 5 \text{ ns}$
QD1	fpt	850	$270 \pm 11 \mu\text{s}$	62	$60 \pm 10 \mu\text{s}$	38	$190 \pm 16 \mu\text{s}$
QD2	fpt	850	$203 \pm 8 \mu\text{s}$	60	$57 \pm 15 \mu\text{s}$	40	$145 \pm 11 \mu\text{s}$
QD3	fpt	850	$101 \pm 5 \mu\text{s}$	100	<i>g</i>		$101 \pm 5 \mu\text{s}$

<sup>a</sup>Toluene solution. <sup>b</sup>Relative contribution to the biexponential fit. <sup>c</sup>Weighted average lifetime, calculated as  $\tau_{\text{avg}} = (A_1\tau_1 + A_2\tau_2)/100$ . <sup>d</sup>95% Confidence interval. <sup>e</sup>Freeze–pump–thawed samples ( $<10^{-5}$  Torr). <sup>f</sup>Because of instrumental limitations, the fast component could not be resolved and the data was fit to a monoexponential decay. <sup>g</sup>A biexponential fit was found to be an overparameterization of the data and was thus fit to a monoexponential decay.

As expected, the long component of the decay is significantly longer than free porphyrin by over 300 ns for air measurements and 450  $\mu\text{s}$  for FPT measurements (see Table 2). Such observations have been previously reported for other fluorophore systems.<sup>9,25,85</sup> The significantly longer component is attributed to the intercalation of the porphyrin into the passivating ligand that coats the QD surface; this protects the porphyrin from molecular collisions and other nonradiative decay processes, thereby extending the radiative lifetime. The shorter component is likely to be free porphyrin as this lifetime is comparable to free porphyrin in solution ( $\sim 150 \mu\text{s}$ , Table 2). In air, the average lifetimes for the QD–porphyrin assemblies are significantly shortened, reflecting the quenching process observed by steady-state emission.

In addition to the one-photon lifetimes, the lifetimes of FPT and aerated samples of QD1–QD3 were measured under two-photon irradiation ( $\lambda_{\text{exc}} = 850 \text{ nm}$ ) (Table 3). The observed average lifetimes for QD1 and QD2 are consistent with the results of one-photon excitation of 1 and 2. The FPT samples exhibit long ( $\sim 200 \mu\text{s}$ ) and short lifetime components ( $\sim 50 \mu\text{s}$ , compared to  $\sim 150 \mu\text{s}$  for free porphyrin). The lifetimes of the conjugates in air under two-photon excitation reflect quenching, but the short lifetime, akin to what was observed in the one-photon case, is not resolved from the instrument response function.

## CONCLUSIONS

Self-assembled QD–porphyrin nanosensor conjugates detect  $\text{O}_2$  in the 0–160 Torr range under both one- and two-photon excitation. Two *cis* pyridyl groups in the *meso* position of the Pd porphyrin macrocycle promote the most effective binding of the palladium porphyrin to the surface of a QD. The QD serves as one- or two-photon light harvesting antennae of the Pd porphyrin. Owing to the insensitivity of the QD to  $\text{O}_2$ , a ratiometric signal transduction mechanism may be established. Because of superior spectral overlap and efficient surface binding, the FRET efficiency in these systems is 67–94%.

The QD is essential in implementing sensing under two-photon conditions owing to the QD's high two-photon absorption cross-section ( $\sigma_2$ ). Although free-base QD–

porphyrin assemblies have been previously studied as FRET systems,<sup>80,86,90</sup> they have not been examined under two-photon excitation nor have they been explored as sensors. Both ruthenium bipyridine complexes<sup>94</sup> and Pt porphyrins<sup>95,96</sup> have been used as  $\text{O}_2$  sensors in conjunction with QDs, but in these systems the QD has served only as an internal intensity standard. Indeed the few examples of authentic FRET-based  $\text{O}_2$  sensing include pyrene,<sup>25</sup> platinum octaethylporphyrin ketone,<sup>97,98</sup> or osmium bipyridine complexes<sup>9</sup> as the FRET acceptor. Of these, two-photon excitation of the FRET acceptor by QD has been achieved only with the osmium bipyridine complex. This system, however, suffers from low dynamic range at biologically relevant oxygen pressures (0–160 Torr).<sup>9</sup> We now establish a viable two-photon  $\text{O}_2$  sensing mechanism over this pressure range with QD1–QD3. Having fully characterized this system in organic solvents, we are currently developing methods to translate this system to water so that it can be used for in vivo two-photon oxygen sensing applications.

## ASSOCIATED CONTENT

### Supporting Information

Detailed synthetic procedures for porphyrin precursors and alternative methods, in addition to  $^1\text{H}$  NMR spectra of all compounds, are presented in the Supporting Information. Summaries of crystallographic data, QD luminescence lifetime titration data, equilibrium constants, FRET parameters, and other relevant spectral data are included. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## AUTHOR INFORMATION

### Corresponding Author

\*E-mail: [dnocera@fas.harvard.edu](mailto:dnocera@fas.harvard.edu) (D.G.N.), [mgb@mit.edu](mailto:mgb@mit.edu) (M.G.B.).

### Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

This research was supported by the U.S. National Cancer Institute grants R01-CA126642. C.M.L. acknowledges the National Science Foundation's Graduate Research Fellowship

Program. We thank Dr. Dilek Dogutan for helpful synthetic discussions, Bryce Anderson for assistance with experiments using the Libra-F-HE laser system, Andrew Ullman for assistance in collecting X-ray diffraction data, Dr. Xiaoxing Han for assistance in acquiring two-photon lifetimes, and Dr. Thomas Kempa for acquiring the TEM images used in the TOC graphic.

## REFERENCES

- (1) Vaupel, P.; Kallinowski, F.; Okunieff, P. *Cancer Res.* **1989**, *49*, 6449–6465.
- (2) Helmlinger, G.; Yuan, F.; Dellian, M.; Jain, R. K. *Nat. Med.* **1997**, *3*, 177–182.
- (3) Chauhan, V. P.; Stylianopoulos, T.; Boucher, Y.; Jain, R. K. *Annu. Rev. Chem. Biomol. Eng.* **2011**, *2*, 281–298.
- (4) Folkman, J. *Nat. Rev. Drug Discovery* **2007**, *6*, 273–286.
- (5) Jain, R. K. *Science* **2005**, *307*, 58–62.
- (6) Snee, P. T.; Somers, R. C.; Nair, G.; Zimmer, J. P.; Bawendi, M. G.; Nocera, D. G. *J. Am. Chem. Soc.* **2006**, *128*, 13320–13321.
- (7) Somers, R. C.; Lanning, R. M.; Snee, P. T.; Greytak, A. B.; Jain, R. K.; Bawendi, M. G.; Nocera, D. G. *Chem. Sci.* **2012**, *3*, 2980–2985.
- (8) Kay, E. R.; Lee, J.; Nocera, D. G.; Bawendi, M. G. *Angew. Chem., Int. Ed.* **2013**, *52*, 1165–1169.
- (9) McLaurin, E. J.; Greytak, A. B.; Bawendi, M. G.; Nocera, D. G. *J. Am. Chem. Soc.* **2009**, *131*, 12994–13001.
- (10) Murray, C. B.; Norris, D. J.; Bawendi, M. G. *J. Am. Chem. Soc.* **1993**, *115*, 8706–8715.
- (11) Alivisatos, P. *Nat. Biotechnol.* **2004**, *22*, 47–52.
- (12) Xia, Z.; Rao, J. *Curr. Opin. Biotechnol.* **2009**, *20*, 37–44.
- (13) Baltazar, R.; Vistas, C. R.; Ferreira, G. N. M. In *Nanocomposite Particles for Bio-Applications: Materials and Bio-Interfaces*; Trindade, T., da Silva, A. L. D., Eds.; Taylor & Francis: Boca Raton, FL, 2012; pp 265–282.
- (14) Medintz, I. L.; Clapp, A. R.; Mattoussi, H.; Goldman, E. R.; Fisher, B.; Mauro, J. M. *Nat. Mater.* **2003**, *2*, 630–638.
- (15) Somers, R. C.; Bawendi, M. G.; Nocera, D. G. *Chem. Soc. Rev.* **2007**, *36*, 579–591.
- (16) Suzuki, M.; Husimi, Y.; Komatsu, H.; Suzuki, K.; Douglas, K. T. *J. Am. Chem. Soc.* **2008**, *130*, 5720–5725.
- (17) Blanton, S. A.; Dehestani, A.; Lin, P. C.; Guyot-Sionnest, P. *Chem. Phys. Lett.* **1994**, *229*, 317–322.
- (18) Larson, D. R.; Zipfel, W. R.; Williams, R. M.; Clark, S. W.; Bruchez, M. P.; Wise, F. W.; Webb, W. W. *Science* **2003**, *300*, 1434–1436.
- (19) Pu, S. C.; Yang, M. J.; Hsu, C. C.; Lai, C. W.; Hsieh, C. C.; Lin, S. H.; Cheng, Y. M.; Chou, P. T. *Small* **2006**, *2*, 1308–1313.
- (20) Richards-Kortum, R.; Sevcik-Muraca, E. *Annu. Rev. Phys. Chem.* **1996**, *47*, 555–606.
- (21) Zipfel, W. R.; Williams, R. M.; Webb, W. W. *Nat. Biotechnol.* **2003**, *21*, 1369–1377.
- (22) Jain, R. K.; Booth, M. F.; Padera, T. P.; Munn, L. L.; Fukumura, D.; Brown, E. In *Handbook of Biomedical Nonlinear Optical Microscopy*; Masters, B. R., So, P. T. C., Eds.; Oxford University Press: New York, 2008; pp 735–756.
- (23) Yoshihara, T.; Yamaguchi, Y.; Hosaka, M.; Takeuchi, T.; Tobita, S. *Angew. Chem., Int. Ed.* **2012**, *51*, 4148–4151.
- (24) Coogan, M. P.; Court, J. B.; Gray, V. L.; Hayes, A. J.; Lloyd, A. H.; Millet, C. O.; Pope, S. J. A.; Lloyd, D. *Photochem. Photobiol. Sci.* **2010**, *9*, 103–109.
- (25) Amelia, M.; Lavie-Cambot, A.; McClenaghan, N. D.; Credi, A. *Chem. Commun.* **2011**, *47*, 325–327.
- (26) Okura, I.; Kamachi, T. In *Handbook of Porphyrin Science*; Kadish, K. M., Smith, K. M., Guillard, R., Eds.; World Scientific Publishing: Singapore, 2011; Vol. 12; pp 297–348.
- (27) Tripathi, V. S.; Lakshminarayana, G.; Nogami, M. *Sens. Actuators, B* **2010**, *147*, 741–747.
- (28) Wang, X.; Meier, R. J.; Link, M.; Wolfbeis, O. S. *Angew. Chem., Int. Ed.* **2010**, *49*, 4907–4909.
- (29) Amao, Y.; Miyakawa, K.; Okura, I. *J. Mater. Chem.* **2000**, *10*, 305–308.
- (30) Zhang, H.; Sun, Y.; Ye, K.; Zhang, P.; Wang, Y. *J. Mater. Chem.* **2005**, *15*, 3181–3186.
- (31) Dunphy, I.; Vinogradov, S. A.; Wilson, D. F. *Anal. Biochem.* **2002**, *310*, 191–198.
- (32) Lakowicz, J. R. *Principles of Fluorescence Spectroscopy*, 3rd ed.; Springer: New York, 2006.
- (33) Kruk, M.; Karotki, A.; Drobizhev, M.; Kuzmitsky, V.; Gael, V.; Rebane, A. *J. Lumin.* **2003**, *105*, 45–55.
- (34) Briñas, R. P.; Troxler, T.; Hochstrasser, R. M.; Vinogradov, S. A. *J. Am. Chem. Soc.* **2005**, *127*, 11851–11862.
- (35) Finikova, O. S.; Troxler, T.; Senes, A.; DeGrado, W. F.; Hochstrasser, R. M.; Vinogradov, S. A. *J. Phys. Chem. A* **2007**, *111*, 6977–6990.
- (36) Finikova, O. S.; Lebedev, A. Y.; Aprelev, A.; Troxler, T.; Gao, F.; Garnacho, C.; Muro, S.; Hochstrasser, R. M.; Vinogradov, S. A. *ChemPhysChem* **2008**, *9*, 1673–1679.
- (37) Sinks, L. E.; Robbins, G. P.; Roussakis, E.; Troxler, T.; Hammer, D. A.; Vinogradov, S. A. *J. Phys. Chem. B* **2010**, *114*, 14373–14382.
- (38) Gryko, D.; Lindsey, J. S. *J. Org. Chem.* **2000**, *65*, 2249–2252.
- (39) Zaidi, S. H. H.; Muthukumar, K.; Tamaru, S.; Lindsey, J. S. *J. Org. Chem.* **2004**, *69*, 8356–8365.
- (40) Dogutan, D. K.; Ptaszek, M.; Lindsey, J. S. *J. Org. Chem.* **2008**, *73*, 6187–6201.
- (41) Laha, J. K.; Dhanalekshmi, S.; Taniguchi, M.; Ambrose, A.; Lindsey, J. S. *Org. Process Res. Dev.* **2003**, *7*, 799–812.
- (42) Zaidi, S. H. H.; Loewe, R. S.; Clark, B. A.; Jacob, M. J.; Lindsey, J. S. *Org. Process Res. Dev.* **2006**, *10*, 304–314.
- (43) Sharada, D. S.; Muresan, A. Z.; Muthukumar, K.; Lindsey, J. S. *J. Org. Chem.* **2005**, *70*, 3500–3510.
- (44) Leatherdale, C. A.; Woo, W. K.; Mikulec, F. V.; Bawendi, M. G. *J. Phys. Chem. B* **2002**, *106*, 7619–7622.
- (45) Fulmer, G. R.; Miller, A. J. M.; Sherden, N. H.; Gottlieb, H. E.; Nudelman, A.; Stoltz, B. M.; Bercaw, J. E.; Goldberg, K. I. *Organometallics* **2010**, *29*, 2176–2179.
- (46) Suzuki, K.; Kobayashi, A.; Kaneko, S.; Takehira, K.; Yoshihara, T.; Ishida, H.; Shiina, Y.; Oishi, S.; Tobita, S. *Phys. Chem. Chem. Phys.* **2009**, *11*, 9850–9860.
- (47) Grabolle, M.; Spieles, M.; Lesnyak, V.; Gaponik, N.; Eychmüller, A.; Resch-Genger, U. *Anal. Chem.* **2008**, *81*, 6285–6294.
- (48) Pizano, A. A.; Lutterman, D. A.; Holder, P. G.; Teets, T. S.; Stubbe, J.; Nocera, D. G. *Proc. Natl. Acad. Sci. U.S.A.* **2012**, *109*, 39–43.
- (49) Holder, P. G.; Pizano, A. A.; Anderson, B. L.; Stubbe, J.; Nocera, D. G. *J. Am. Chem. Soc.* **2012**, *134*, 1172–1180.
- (50) Loh, Z. H.; Miller, S. E.; Chang, C. J.; Carpenter, S. D.; Nocera, D. G. *J. Phys. Chem. A* **2002**, *106*, 11700–11708.
- (51) Brown, E. B.; Campbell, R. B.; Tsuzuki, Y.; Xu, L.; Carmeliet, P.; Fukumura, D.; Jain, R. K. *Nat. Med.* **2001**, *7*, 864–868.
- (52) Lanning, R. M. Ph.D. Thesis, Massachusetts Institute of Technology, Cambridge, MA, U.S.A., 2009.
- (53) Förster, T. *Ann. Phys.* **1948**, *437*, 55–75.
- (54) Steinberg, I. Z. *Annu. Rev. Biochem.* **1971**, *40*, 83–114.
- (55) *CRC Handbook of Chemistry and Physics*, 84th ed.; CRC Press: Boca Raton, FL, 2003.
- (56) Sheldrick, G. M. *Acta Crystallogr., Sect. A: Found. Crystallogr.* **2008**, *A64*, 112–122.
- (57) Lindsey, J. S.; Wagner, R. W. *J. Org. Chem.* **1989**, *54*, 828–836.
- (58) Lembo, A.; Tagliatesta, P.; Cicero, D.; Leoni, A.; Salvatori, A. *Org. Biomol. Chem.* **2009**, *7*, 1093–1096.
- (59) Adler, A. D.; Longo, F. R.; Shergalis, W. *J. Am. Chem. Soc.* **1964**, *86*, 3145–3149.
- (60) Adler, A. D.; Longo, F. R.; Finarelli, J. D.; Goldmacher, J.; Assour, J.; Korsakoff, L. *J. Org. Chem.* **1967**, *32*, 476.
- (61) Ishikawa, Y.; Yamashita, A.; Uni, T. *Chem. Pharm. Bull.* **2001**, *49*, 287–293.
- (62) Sirish, M.; Chertkov, V. A.; Schneider, H. J. *Chem.—Eur. J.* **2002**, *8*, 1181–1188.

- (63) Gianferrara, T.; Giust, D.; Bratsos, I.; Alessio, E. *Tetrahedron* **2007**, *63*, 5506–5013.
- (64) Wu, L.; Hu, P.; Xiao, Y.; Zhang, M.; Zhang, L.; Weng, X.; Wu, X.; Zhou, X.; Cao, X. *Chem. Biodiversity* **2008**, *5*, 153–161.
- (65) Dogutan, D. K.; Zaidi, S. H. H.; Thamyongkit, P.; Lindsey, J. S. *J. Org. Chem.* **2007**, *72*, 7701–7714.
- (66) Dogutan, D. K.; Lindsey, J. S. *J. Org. Chem.* **2008**, *73*, 6728–6742.
- (67) Dean, M.; Schmink, J. R.; Leadbeater, N. E.; Brückner, C. *Dalton Trans.* **2008**, 1341–1345.
- (68) Obata, M.; Matsuura, N.; Mitsuo, K.; Nagai, H.; Asai, K.; Harada, M.; Hirohara, S.; Tanihara, M.; Yano, S. *J. Polym. Sci., Part A: Polym. Chem.* **2010**, *48*, 663–670.
- (69) Milic, T. N.; Chi, N.; Yablon, D. G.; Flynn, G. W.; Batteas, J. D.; Drain, C. M. *Angew. Chem., Int. Ed.* **2002**, *41*, 2117–2119.
- (70) Deiters, E.; Bulach, V.; Hosseini, M. W. *New J. Chem.* **2006**, *30*, 1289–1294.
- (71) Yedukondalu, M.; Ravikanth, M. *J. Chem. Sci.* **2011**, *123*, 201–214.
- (72) Li, Y.; Xiao, J.; Shubina, T. E.; Chen, M.; Shi, Z.; Schmid, M.; Steinrück, H. P.; Gottfried, J. M.; Lin, N. *J. Am. Chem. Soc.* **2012**, *134*, 6401–6408.
- (73) Lipstman, S.; Goldberg, I. *Acta Crystallogr. Sect. C: Cryst. Struct. Commun.* **2008**, *C64*, m53–m57.
- (74) Fleischer, E. B.; Miller, C. K.; Webb, L. E. *J. Am. Chem. Soc.* **1964**, *86*, 2342–2347.
- (75) Gouterman, M. In *The Porphyrins*; Dolphin, D., Ed.; Academic Press: New York, 1978; Vol. 3; pp 1–165.
- (76) Kalyanasundaram, K. *Photochemistry of Polypyridine and Porphyrin Complexes*; Academic Press: San Diego, CA, 1992; pp 498–502.
- (77) Eastwood, D.; Gouterman, M. *J. Mol. Spectrosc.* **1970**, *35*, 359–375.
- (78) Callis, J. B.; Gouterman, M.; Jones, Y. M.; Henderson, B. H. *J. Mol. Spectrosc.* **1971**, *39*, 410–420.
- (79) Quimby, D. J.; Longo, F. R. *J. Am. Chem. Soc.* **1975**, *97*, 5111–5117.
- (80) Zenkevich, E. I.; Sagun, E. I.; Knyukshto, V. N.; Stasheuski, A. S.; Galievsky, A. V.; Stupak, A. P.; Blaudeck, T.; von Borczyskowski, C. *J. Phys. Chem. C* **2011**, *115*, 21535–21545.
- (81) Faure, S.; Stern, C.; Guillard, R.; Harvey, P. D. *Inorg. Chem.* **2005**, *44*, 9232–9241.
- (82) Bonin, K. D.; McIlrath, T. J. *J. Opt. Soc. Am. B: Opt. Phys.* **1984**, *1*, 52–55.
- (83) Petek, H.; Bell, A. J.; Choi, Y. S.; Yoshihara, K.; Tounge, B. A.; Christensen, R. L. *J. Chem. Phys.* **1995**, *102*, 4726–4739.
- (84) Javier, A.; Magana, D.; Jennings, T.; Strouse, G. F. *Appl. Phys. Lett.* **2003**, *83*, 1423–1425.
- (85) Wen, Y.; Liu, Y.; Yang, Y.; An, L.; Song, W.; Yang, Z. *J. Micro/Nanolith. MEMS MOEMS* **2010**, *9*, 031003/1–4.
- (86) Zenkevich, E. I.; Sagun, E. I.; Yarovoi, A. A.; Shulga, A. M.; Knyukshto, V. N.; Stupak, A. P.; von Borczyskowski, C. *Opt. Spectrosc.* **2007**, *103*, 958–968.
- (87) Jones, M.; Lo, S. S.; Scholes, G. D. *Proc. Natl. Acad. Sci. U.S.A.* **2009**, *106*, 3011–3016.
- (88) Klimov, V. I.; Mikhailovsky, A. A.; Branch, D. W.; Leatherdale, C. A.; Bawendi, M. G. *Science* **2000**, *287*, 1011–1013.
- (89) Wackerly, D. D.; Mendenhall, W.; Scheaffer, R. L. *Mathematical Statistics with Applications*, 6th ed.; Duxbury: Pacific Grove, CA, 2002; pp 124–126.
- (90) Zenkevich, E.; Cichos, F.; Shulga, A.; Petrov, E. P.; Blaudeck, T.; von Borczyskowski, C. *J. Phys. Chem. B* **2005**, *109*, 8679–8692.
- (91) Talapin, D. V.; Rogach, A. L.; Kornowski, A.; Hasse, M.; Weller, H. *Nano Lett.* **2001**, *1*, 207–211.
- (92) Balogh, L.; Zhang, C.; O'Brien, S.; Turro, N. J.; Brus, L. *Chim. Oggi* **2002**, *20*, 45–51.
- (93) Bullen, C.; Mulvaney, P. *Langmuir* **2006**, *22*, 3007–3013.
- (94) Jorge, P. A. S.; Mayeh, M.; Benrashid, R.; Caldas, P.; Santos, J. L.; Farahi, F. *Appl. Opt.* **2006**, *45*, 3760–3767.
- (95) Collier, B. B.; Singh, S.; McShane, M. *Analyst* **2011**, *136*, 962–967.
- (96) Wang, X.; Chen, X.; Xie, Z.; Wang, X. *Angew. Chem., Int. Ed.* **2008**, *47*, 7450–7453.
- (97) Zhang, C.; Ingram, J.; Schiff, S.; Xu, J.; Xiao, M. *Proc. SPIE* **2011**, 7947, 79470B/1–6.
- (98) Ingram, J. M.; Zhang, C.; Xu, J.; Schiff, S. J. *J. Neurosci. Methods* **2013**, *214*, 45–51.