

## Magnetic Properties of Binuclear Copper(II) Complexes with One Hydroxo Bridge

M. S. HADDAD and D. N. HENDRICKSON\*

School of Chemical Sciences, University of Illinois, Urbana, Ill. 61801, U.S.A.

Received February 15, 1978

There has been continuing interest in the magnetic exchange properties of dihydroxo-bridged copper(II) complexes [1–3]. For some six complexes, a linear relationship has been noted between the bridge angle, Cu–O(H)–Cu, and the exchange parameter,  $J$  (i.e., parameter in spin Hamiltonian  $-2J\hat{S}_1 \cdot \hat{S}_2$ ). The most ferromagnetic interaction ( $2J = +172 \text{ cm}^{-1}$ ) was found for  $[\text{Cu}(\text{bipy})(\text{OH})_2(\text{NO}_3)_2]$ , where bipy is 2,2'-bipyridine. This compound has a bridge angle of  $95.6(1)^\circ$ . The largest bridge angle,  $104.08(17)$ , is seen in  $[\text{Cu}(\text{tmen})(\text{OH})_2\text{Br}_2]$ , where tmen is N, N, N', N'-tetramethylethylenediamine. This second compound exhibits the most antiferromagnetic interaction with  $2J = -509 \text{ cm}^{-1}$ . To date, no copper(II) complexes have been reported with one hydroxo bridge. A considerable antiferromagnetic interaction would be expected for such a complex as a consequence of a relatively large Cu–O(H)–Cu bridge angle. The crystal structure of  $\mu$ -hydroxo-bis[pentaamminechromium(III)] does show a Cr–O(H)–Cr bridge angle of  $165.6(9)^\circ$  [4]. In this paper, we report the preparation and magnetic properties of the first two  $\mu$ -hydroxo-bridged copper(II) complexes.

The addition of an aqueous solution of either  $\text{NaClO}_4$  or  $\text{KPF}_6$  to an aqueous solution of  $\text{Cu}(\text{tren})(\text{OH})^+$  results in the precipitation of microcrystalline  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{ClO}_4)_3 \cdot \text{H}_2\text{O}$  or  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{PF}_6)_3$ , respectively. Variable-temperature magnetic susceptibility, infrared, and EPR data have been obtained for these two compounds and these data indicate the presence of binuclear copper(II) complexes bridged by a single hydroxo bridge.

The KBr-pellet IR spectrum of either of the  $[\text{Cu}_2(\text{tren})_2(\text{OH})]X_3$  compounds shows a relatively sharp and medium intensity band in a region where an O–H stretch would be expected [5]. The  $\text{PF}_6^-$  compound has a band at  $3601 \text{ cm}^{-1}$ , whereas the  $\text{ClO}_4^-$  compound has a band at  $3571 \text{ cm}^{-1}$ . No IR band is seen in this same region for  $[\text{Cu}_2(\text{tren})_2(\text{CN})]X_3$ ,  $X = \text{PF}_6^-$  or  $\text{ClO}_4^-$  [6]. The assignment of the O–H stretch was substantiated for the  $\text{PF}_6^-$  compound by preparing the corresponding deute-

rated compound,  $[\text{Cu}_2(\text{tren-d}_6)_2(\text{OD})](\text{PF}_6)_3$ . The O–H band shifted from  $3601 \text{ cm}^{-1}$  to  $2656 \text{ cm}^{-1}$ , giving a  $\nu_{\text{OH}}/\nu_{\text{OD}}$  ratio of 1.36. Similar shifts were observed for the N–H bands. In the case of the non-deuterated compound, N–H stretches are seen at  $3321$  and  $3381 \text{ cm}^{-1}$  with a relatively strong N–H bend at  $1601 \text{ cm}^{-1}$ . The deuterated compound shows N–D stretches at  $2440$ ,  $2452$ , and  $2530 \text{ cm}^{-1}$  and a N–D bend at  $1201 \text{ cm}^{-1}$ .

The Q-band EPR spectrum (either room-temperature or liquid-nitrogen temperature) of a powdered sample of  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{PF}_6)_3$  exhibits a single derivative feature at  $g = 2.128$ . The spectrum for the  $\text{ClO}_4^-$  compound also shows only a derivative at  $g = 2.132$ . This is the same type of Q-band EPR signal observed for the  $[\text{Cu}_2(\text{tren})_2(\text{CN})]X_3$  compounds [6]. Empirically, the presence of such a single-derivative signal points to a relatively strong magnetic exchange interaction. Exchange averaging between two  $\text{Cu}(\text{tren})^{2+}$  moieties which are not magnetically aligned could lead to a single-derivative spectrum.

The variable-temperature magnetic susceptibility data provide further conclusive evidence for the presence of hydroxo bridges. Figure 1 illustrates the data obtained for  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{PF}_6)_3$ . At  $285.5 \text{ }^\circ\text{K}$ , the  $\mu_{\text{eff}}/\text{Cu}$  ( $0.77\mu_{\text{B}}$ ) for this compound is already considerably below the spin-only value of  $1.73\mu_{\text{B}}$ . The solid lines in Figure 1 represent the least-squares fit of the data to the Bleaney–Bowers equation [7] for isotropic exchange in a binuclear copper(II) complex. The fitting parameters are  $2J = -700 \text{ cm}^{-1}$  and  $g = 2.05$ . The increase in  $\chi_{\text{M}}$  at very low temperatures is due to a small amount of a monomeric paramagnetic impurity; in the fitting the  $\chi_{\text{M}}$  for the impurity was taken as  $\chi_{\text{M}} = 8.0 \times 10^{-3} \text{ cgsu}$  at  $4.2 \text{ }^\circ\text{K}$ . A more limited data set was obtained for the  $\text{ClO}_4^-$  compound; the data set runs from  $285.5 \text{ }^\circ\text{K}$  where  $\mu_{\text{eff}}/\text{Cu} = 0.64\mu_{\text{B}}$

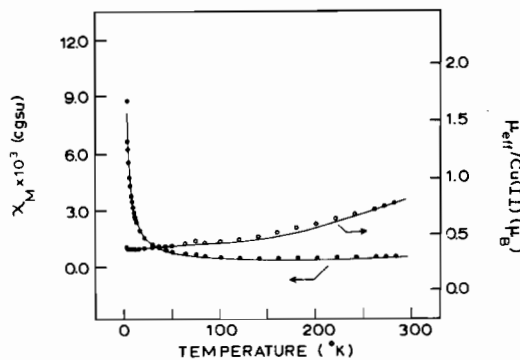


Figure 1. Corrected molar paramagnetism per binuclear complex,  $\chi_{\text{M}}$ , and effective magnetic moment per copper(II) ion,  $\mu_{\text{eff}}/\text{Cu}$ , plotted as a function of temperature. The solid lines result from least-squares fitting the data to the Bleaney–Bowers equation.

\*To whom all the correspondence should be addressed.

to 203.7 °K where  $\mu_{\text{eff}}/\text{Cu} = 0.40\mu_{\text{B}}$ . Fitting the  $\text{ClO}_4^-$  data gave  $2J = -760 \text{ cm}^{-1}$  and  $g = 2.120$ .

Both of the  $[\text{Cu}_2(\text{tren})_2(\text{OH})]\text{X}_3$  compounds exhibit antiferromagnetic interactions that are considerably stronger than the strongest antiferromagnetic interaction ( $2J = -509 \text{ cm}^{-1}$ ) seen for the dihydroxo-bridged copper(II) complexes. This is as expected because a single hydroxo bridge would lead to an appreciably larger Cu—O(H)—Cu bridge angle. However, the antiferromagnetic interactions present in the  $[\text{Cu}_2(\text{tren})_2(\text{OH})]\text{X}_3$  are not as great as would naively be expected from the established [1, 2] correlations of  $2J$  and angle for dihydroxo-bridged species. This is also expected, because the copper(II) ion ground states in  $[\text{Cu}_2(\text{tren})_2(\text{OH})]\text{X}_3$  are  $d_{z^2}$ , whereas the dihydroxo-bridged copper(II) complexes are all square pyramidal and have  $d_{x^2-y^2}$  ground states. A change in the copper(II) ground state can have a pronounced effect on the magnitude of a magnetic exchange interaction propagated by some bridging species [8]. A crystal structure of one or both of the two  $[\text{Cu}_2(\text{tren})_2(\text{OH})]\text{X}_3$  compounds would be very desirable. The difference in O—H stretching frequencies between the two compounds could reflect a change in the bridge angle. Well-formed crystals of the  $\text{ClO}_4^-$  compound have been obtained.

## Experimental

### Compound Preparations

Samples of  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{X})_3$  where  $\text{X} = \text{PF}_6^-$  or  $\text{ClO}_4^-$  and tren is 2,2', 2''-triaminotriethylamine (Ames) were prepared by the following procedure. To an aqueous solution (40 ml) of ca. 1.0g (4 mmol) of  $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$  was added ca. 0.6 ml of tren followed by an aqueous solution of ca. 0.08g (2mmol) of NaOH. To the filtered solution, an aqueous saturated solution of  $\text{KPF}_6$  or  $\text{NaClO}_4$  was added which resulted in the precipitation of microcrystalline blue solids. The perchlorate salt precipitates as a hydrate,  $[\text{Cu}_2(\text{tren})_2(\text{OH})](\text{ClO}_4)_3 \cdot \text{H}_2\text{O}$ . Recrystallization of the latter from water yields well-formed crystals of the anhydrous form. *Anal.* Calcd for  $\text{C}_{12}\text{H}_{37}\text{N}_8\text{OCu}_2\text{-P}_3\text{F}_{18}$ : C, 16.55; H, 4.25; N, 12.86; Cu, 14.59. Found: C, 16.68; H, 4.01; N, 12.99; Cu, 14.43. Calcd for the hydrate,  $\text{C}_{12}\text{H}_{39}\text{N}_8\text{O}_{14}\text{Cu}_2\text{Cl}_3$ : C, 19.15; H, 5.18; N, 14.88; Cu, 16.88 Found: C, 19.28; H, 4.90; N, 15.08; Cu, 16.96.

The preparation of  $[\text{Cu}_2(\text{tren-d}_6)_2(\text{OD})](\text{PF}_6)_3$  was carried out in the same way as the non-deuterated compound was prepared, except  $\text{D}_2\text{O}$  was used as the reaction solvent.

### Physical Measurements

Infrared spectra were obtained with a Perkin-Elmer Model 467 spectrophotometer. Samples were prepared as 13-mm KBr pellets. The EPR instrumentation and procedure for variable-temperature magnetic susceptibility determination have been previously described [9]. The magnetic susceptibility data were least-squares fit with an adapted version of the computer function minimization program known as STEPT [10].

### Acknowledgment

This research was supported by National Institutes of Health grant HL 13652. M. Haddad acknowledges a University of Illinois Fellowship, 1976–1978. D. Hendrickson is grateful for a Camille and Henry Dreyfus Teacher-Scholar Fellowship, 1972–1977, and an A. P. Sloan Foundation Fellowship, 1976–1978.

### References

- 1 D. J. Hodgson, *Prog. Inorg. Chem.*, **19**, 173 (1975).
- 2 W. E. Hatfield, chapter 7 in "Theory and Applications of Molecular Paramagnetism," E. A. Boudreaux and L. N. Mulay, Editors, Wiley (1976).
- 3 P. J. Hay, J. C. Thibeault, and R. Hoffmann, *J. Am. Chem. Soc.*, **97**, 4884 (1975).
- 4 J. T. Veal, D. Y. Jeter, J. C. Hempel, R. P. Eckberg, W. E. Hatfield, and D. J. Hodgson, *Inorg. Chem.*, **12**, 2928 (1973).
- 5 J. R. Ferraro and W. R. Walker, *Inorg. Chem.*, **4**, 1382 (1965).
- 6 D. S. Bielsza and D. N. Hendrickson, *Inorg. Chem.*, **16**, 924 (1977).
- 7 B. Bleaney and K. D. Bowers, *Proc. R. Soc., London, Ser. A*, **214**, 451 (1952).
- 8 T. R. Felthouse, E. J. Laskowski, and D. N. Hendrickson, *Inorg. Chem.*, **16**, 1077 (1977).
- 9 D. M. Duggan and D. N. Hendrickson, *Inorg. Chem.*, **13**, 2929 (1974).
- 10 J. P. Chandler, Program 66, Quantum Chemistry Program Exchange, Indiana University, Bloomington, Indiana.