

## STRESS SINGULARITIES IN BONDED ANISOTROPIC MATERIALS†

F. DELALE

Department of Mechanical Engineering and Mechanics, Philadelphia, PA 19104, U.S.A.

(Received 13 September 1982; in revised form 31 March 1983)

**Abstract**—In this paper, the general problem of stress singularities occurring near the free edge of two bonded anisotropic materials is investigated. After formulating the problem of two bonded anisotropic wedges, the stress singularity near the free edge of two bonded layers, at the tip of a crack between two materials and in the vicinity of a broken layer is obtained by simply varying the wedge angles. It is shown that, the power of singularity depends on the elastic properties of the anisotropic constituents. Several examples occurring in real layered composites structures and illustrating this fact are studied in some detail. Unlike the isotropic case the power of singularity at the tip of a crack between two materials can be real.

### 1. INTRODUCTION

In the recent past, research in anisotropic materials in general and in layered anisotropic materials in particular has attracted a great deal of interest. The reasons for this are the ever-increasing use of composites in many structures and the fact that the failure resistance of composites can be improved considerably without adding to the weight of the structure. Indeed one attractive aspect of using composites is the possibility of an economical design by reducing the weight of the structure. In layered composite structures, one of the most important design problems is the initiation and propagation of the so-called "delamination surface". From the study of bonded isotropic materials[1-3] it is well known that, the stresses near a free edge have a weak power singularity and under certain loading conditions, the normal stress can be tensile, thus enhancing the possibility of delamination failure. After the formation of new delamination surfaces, under sustained or excessive loading conditions the "crack" or "delamination surface" may further propagate in a stable or unstable manner. It is clear that, the severity of the power of singularity may have a decisive bearing upon the initiation and propagation of such delamination surfaces. Treated as single layers, the constituents of layered composites may in general be treated as anisotropic materials. Even though it is very difficult to determine all the material constants ( $a_{ij}$ ) of an anisotropic material, fiber-composites are usually modeled as orthotropic materials, one of the principal axes of orthotropy coinciding with the direction of fibers. However, if the axes do not coincide with the fiber directions, the material becomes fully anisotropic in the new coordinate system and must be treated as such. The material constants are then found by a simple coordinate transformation. The existing solutions of bonded materials deal with either isotropic[1-3] or orthotropic materials[4-7]. Lately, the problem of free edge singularities has been considered in[13]. In this paper, the stress state near the free edge of two bonded anisotropic materials will be studied by using Lekhnitskii's general formulation[8, 9] and Williams' method[10, 11]. First, the general asymptotic solution for two bonded wedges is given. Then by varying the wedge angles the stress singularities near the free-edge of two bonded anisotropic materials, near a crack tip at the interface of two materials and in the vicinity of a broken laminate are computed for different anisotropic materials obtained by varying the ply angle. Finally an example illustrating the dependence of the power of singularity on the wedge angle is given, and the application of the method to the finite element technique in formulating the special elements is discussed.

### 2. GENERAL FORMULATION

Consider two anisotropic wedges perfectly bonded along the  $x$ -axis (Fig. 1). In many applications the loads do not vary in  $z$ -direction and the dimension of the plate in the

†This work was supported by Drexel University under Faculty Development Mini-Grant, 1982.

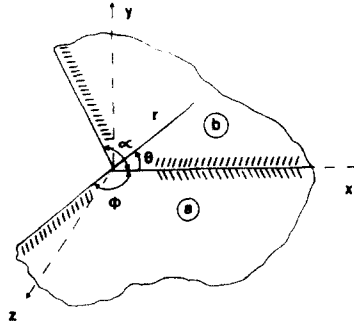


Fig. 1. Geometry of the problem.

z-direction is large enough to warrant the assumption that the stresses and displacements are independent of the z-coordinate. Since the materials are anisotropic the x-y plane is not a plane of symmetry. Therefore, despite the fact that the problem is two dimensional, the x-y plane will not remain plane after deformation, and the stress state will be three-dimensional. This type of deformation is referred to as “generalized plane strain” or “generalized plane deformation”. For an anisotropic material, the stress-strain relations can be written as:

$$\begin{aligned}
 \epsilon_x &= a_{11}\sigma_x + a_{12}\sigma_y + \dots + a_{16}\tau_{xy} \\
 \epsilon_y &= a_{12}\sigma_x + a_{22}\sigma_y + \dots + a_{26}\tau_{xy} \\
 &\dots \dots \dots \\
 \gamma_{xy} &= a_{16}\sigma_x + a_{26}\sigma_y + \dots + a_{66}\tau_{xy}
 \end{aligned}
 \tag{2.1}$$

where  $a_{ij}(i, j = 1, 6)$  are the elastic constants. Under the assumptions stated earlier we have  $\epsilon_z = 0$  and the third equation of (2.1) gives:

$$\sigma_z = -\frac{1}{a_{33}}(a_{13}\sigma_x + a_{23}\sigma_y + a_{34}\tau_{yz} + a_{35}\tau_{xz} + a_{36}\tau_{xy}).
 \tag{2.2}$$

Substituting (2.2) into eqns (2.1), we obtain:

$$\begin{aligned}
 \epsilon_x &= \beta_{11}\sigma_x + \beta_{12}\sigma_y + \beta_{14}\tau_{yz} + \beta_{15}\tau_{xz} + \beta_{16}\tau_{xy} \\
 \epsilon_y &= \beta_{12}\sigma_x + \beta_{22}\sigma_y + \beta_{24}\tau_{yz} + \beta_{25}\tau_{xz} + \beta_{26}\tau_{xy} \\
 &\dots \dots \dots \\
 \gamma_{xy} &= \beta_{16}\sigma_x + \beta_{26}\sigma_y + \beta_{46}\tau_{yz} + \beta_{56}\tau_{xz} + \beta_{66}\tau_{xy}
 \end{aligned}
 \tag{2.3}$$

$\sigma_z$  is given by (2.2) and,  $\beta_{ij} = a_{ij} - a_{i3} a_{j3}/a_{33}$  ( $i, j = 1, 2, 4, 5, 6$ ). Since we are mainly concerned with the singular state in the vicinity of the wedge vertices, it is sufficient to consider the homogeneous part of the solution only. Thus, if the stresses are related to the stress functions  $F(x, y)$  and  $\psi(x, y)$  by means of the following expressions,

$$\sigma_x = \frac{\partial^2 F}{\partial y^2}, \quad \sigma_y = \frac{\partial^2 F}{\partial x^2}, \quad \tau_{xy} = -\frac{\partial^2 F}{\partial x \partial y}, \quad \tau_{xz} = \frac{\partial \psi}{\partial y}, \quad \tau_{yz} = -\frac{\partial \psi}{\partial x}
 \tag{2.4}$$

then the equilibrium equations are satisfied identically and the compatibility equations reduce to [8],

$$L_4 F + L_3 \psi = 0
 \tag{2.5}$$

$$L_3 F + L_2 \psi = 0
 \tag{2.6}$$

where the differential operators  $L_2, L_3, L_4$  are defined by,

$$L_2 = \beta_{44} \frac{\partial^2}{\partial x^2} - 2\beta_{45} \frac{\partial^2}{\partial x \partial y} + \beta_{55} \frac{\partial^2}{\partial y^2} \quad (2.7)$$

$$L_3 = -\beta_{24} \frac{\partial^3}{\partial x^3} + (\beta_{25} + \beta_{46}) \frac{\partial^3}{\partial x^2 \partial y} - (\beta_{14} + \beta_{56}) \frac{\partial^3}{\partial x \partial y^2} + \beta_{15} \frac{\partial^3}{\partial y^3} \quad (2.8)$$

$$L_4 = \beta_{22} \frac{\partial^4}{\partial x^4} - 2\beta_{26} \frac{\partial^4}{\partial x^3 \partial y} + (2\beta_{12} + \beta_{66}) \frac{\partial^4}{\partial x^2 \partial y^2} - 2\beta_{16} \frac{\partial^4}{\partial x \partial y^3} + \beta_{11} \frac{\partial^4}{\partial y^4}. \quad (2.9)$$

Eliminating  $\psi$  from eqns (2.5) and (2.6) the following sixth order differential equation is obtained:

$$(L_4 L_2 - L_3^2) F = 0. \quad (2.10)$$

The sixth-order operator can be decomposed into six linear operators of the first order, giving[8]:

$$D_6 D_5 D_4 D_3 D_2 D_1 F = 0 \quad (2.11)$$

where,

$$D_n = \frac{\partial}{\partial y} - \mu_n \frac{\partial}{\partial x} \quad (2.12)$$

the  $\mu_n (n = 1, 2, \dots, 6)$  being the roots of the following characteristic equation:

$$l_4(\mu) l_2(\mu) - l_3^2(\mu) = 0 \quad (2.13)$$

with

$$\begin{aligned} l_2(\mu) &= \beta_{55} \mu^2 - 2\beta_{45} \mu + \beta_{44} \\ l_3(\mu) &= \beta_{15} \mu^3 - (\beta_{14} + \beta_{56}) \mu^2 + (\beta_{25} + \beta_{46}) \mu - \beta_{24} \\ l_4(\mu) &= \beta_{11} \mu^4 - 2\beta_{16} \mu^3 + (2\beta_{12} + \beta_{66}) \mu^2 - 2\beta_{26} \mu + \beta_{22} \end{aligned} \quad (2.14)$$

It has been shown that[8] the  $\mu_n (n = 1, 2, \dots, 6)$  which are the roots of (2.13), depend heavily on the elastic constants of the material and are either complex or purely imaginary.

Considering the geometry of the structure, the cylindrical coordinates are the natural coordinates of the problem. Thus, if we can transform all field quantities to the cylindrical coordinates  $(r, \theta, z)$ , then the expression of the boundary conditions will become extremely simple. After some algebra it can be shown that, in the cylindrical coordinate system the governing eqn (2.11), takes the following form:

$$\bar{D}_6 \bar{D}_5 \bar{D}_4 \bar{D}_3 \bar{D}_2 \bar{D}_1 \phi^* = 0 \quad (2.15)$$

where the linear operators  $\bar{D}_n$ , are given by:

$$\bar{D}_n = (\sin \theta - \mu_n \cos \theta) \frac{\partial}{\partial r} + (\cos \theta + \mu_n \sin \theta) \frac{1}{r} \frac{\partial}{\partial \theta} \quad (n = 1, 2, \dots, 6). \quad (2.16)$$

and the stress components can be expressed as,

$$\sigma_r = \frac{1}{r} \frac{\partial \phi^*}{\partial r} + \frac{1}{r^2} \frac{\partial^2 \phi^*}{\partial \theta^2}, \quad \sigma_\theta = \frac{\partial^2 \phi^*}{\partial r^2}, \quad \tau_{r\theta} = -\frac{\partial^2}{\partial r \partial \theta} \left( \frac{\phi^*}{r} \right), \quad \tau_{rz} = \frac{1}{r} \frac{\partial \psi^*}{\partial \theta}, \quad \tau_{\theta z} = -\frac{\partial \psi^*}{\partial r} \quad (2.17)$$

where  $\phi^*$  and  $\psi^*$  are the new stress functions. Assuming that the  $\mu_n$  are distinct, the general solution of (2.15) is of the following form:

$$\phi^* = \sum_{n=1}^6 F_n^*[r(\cos \theta + \mu_n \sin \theta)] \quad (2.18)$$

$$\psi^* = - \sum_{n=1}^6 \frac{l_1(\mu_n)}{l_2(\mu_n)} \frac{\partial \phi^*}{\partial z_n} [r(\cos \theta + \mu_n \sin \theta)] \quad (2.19)$$

where  $z_n$  denotes the argument  $r(\cos \theta + \mu_n \sin \theta)$ . If one assumes that the functions  $F_n^*$  ( $n = 1, 2, \dots, 6$ ) can be written as power series in terms of the argument  $r(\cos \theta + \mu_n \sin \theta)$ , and considering the fact that we are looking for a singular type solution, it is then sufficient to consider the leading term of the series only. Thus, assuming that the power of the leading term in the series is  $\lambda$ , the stress functions  $\phi^*$  and  $\psi^*$  may be expressed as:

$$\phi^* = \sum_{n=1}^6 A_n r^\lambda (\cos \theta + \mu_n \sin \theta)^\lambda \quad (2.20)$$

$$\psi^* = \sum_{n=1}^6 \lambda \delta_n A_n r^{\lambda-1} (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \quad (2.21)$$

where  $A_n$  ( $n = 1, \dots, 6$ ) are unknown constants and,

$$\delta_n = - \frac{l_3(\mu_n)}{l_2(\mu_n)}, \quad n = 1, 2, \dots, 6.$$

Using expressions (2.17), the stresses are obtained as:

$$\begin{aligned} \sigma_r &= \sum_{n=1}^6 \lambda(\lambda-1) A_n r^{\lambda-2} (-\sin \theta + \mu_n \cos \theta)^2 (\cos \theta + \mu_n \sin \theta)^{\lambda-2} \\ \sigma_\theta &= \sum_{n=1}^6 \lambda(\lambda-1) A_n r^{\lambda-2} (\cos \theta + \mu_n \sin \theta)^\lambda \\ \tau_{r\theta} &= - \sum_{n=1}^6 \lambda(\lambda-1) A_n r^{\lambda-2} (-\sin \theta + \mu_n \cos \theta) (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \\ \tau_{\theta z} &= - \sum_{n=1}^6 \lambda(\lambda-1) A_n \delta_n r^{\lambda-2} (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \\ \tau_{rz} &= \sum_{n=1}^6 \lambda(\lambda-1) A_n \delta_n r^{\lambda-2} (-\sin \theta + \mu_n \cos \theta) (\cos \theta + \mu_n \sin \theta)^{\lambda-1}. \end{aligned} \quad (2.22)$$

The other field quantities needed in the formulation of the problem are the components of the displacement vector. The cartesian components of the displacement vector  $u$ ,  $v$ ,  $w$  are given by[8]:

$$\begin{aligned} u &= \sum_{n=1}^6 \lambda A_n p_n r^{\lambda-1} (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \\ v &= \sum_{n=1}^6 \lambda A_n q_n r^{\lambda-1} (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \\ w &= \sum_{n=1}^6 \lambda A_n s_n r^{\lambda-1} (\cos \theta + \mu_n \sin \theta)^{\lambda-1} \end{aligned} \quad (2.23)$$

where the expressions (2.20) and (2.21) are used in deriving eqns (2.23) and the constants  $p_n$ ,  $q_n$ ,

and  $s_n$  are expressed as:

$$\begin{aligned} p_n &= \beta_{11} \mu_n^2 + \beta_{12} - \beta_{16} \mu_n + \delta_n (\beta_{15} \mu_n - \beta_{14}) \\ q_n &= \beta_{12} \mu_n + \frac{\beta_{22}}{\mu_n} + \beta_{26} + \delta_n \left( \beta_{25} - \frac{\beta_{24}}{\mu_n} \right) \\ s_n &= \beta_{14} \mu_n + \frac{\beta_{24}}{\mu_n} - \beta_{46} + \delta_n \left( \beta_{45} - \frac{\beta_{44}}{\mu_n} \right) \end{aligned}$$

$$(n = 1, 2, \dots, 6).$$

The components of the displacement vector in cylindrical coordinates ( $u_r$ ,  $u_\theta$ ,  $u_z$ ) can be obtained by the following simple transformation:

$$\begin{aligned} u_r &= u \cos \theta + v \sin \theta \\ u_\theta &= -u \sin \theta + v \cos \theta \\ u_z &= w. \end{aligned} \quad (2.25)$$

Thus,

$$\begin{aligned} u_r &= \sum_{n=1}^6 \lambda A_n C_{rn} r^{\lambda-1} \left( \cos \theta + \mu_n \sin \theta \right)^{\lambda-1} \\ u_\theta &= \sum_{n=1}^6 \lambda A_n C_{\theta n} r^{\lambda-1} \left( \cos \theta + \mu_n \sin \theta \right)^{\lambda-1} \\ u_z &= \sum_{n=1}^6 \lambda A_n C_{zn} r^{\lambda-1} \left( \cos \theta + \mu_n \sin \theta \right)^{\lambda-1} \end{aligned} \quad (2.26)$$

where

$$\begin{aligned} C_{rn} &= p_n \cos \theta + q_n \sin \theta \\ C_{\theta n} &= -p_n \sin \theta + q_n \cos \theta \\ C_{zn} &= s_n \end{aligned} \quad (2.27)$$

$$(n = 1, 2, \dots, 6)$$

### 3. APPLICATION TO THE TWO-WEDGE PROBLEM

Consider the two bonded anisotropic wedges shown in Fig. 1. The bounding surfaces are stress-free and it is further assumed that the structure is loaded at infinity with self-equilibrating forces. Thus, the following homogeneous boundary and continuity conditions can be written:

$$\sigma_\theta^a(r, 0) = \sigma_\theta^b(r, 0) \quad (3.1)$$

$$\tau_{r\theta}^a(r, 0) = \tau_{r\theta}^b(r, 0) \quad (3.2)$$

$$\tau_{\theta z}^a(r, 0) = \tau_{\theta z}^b(r, 0) \quad (3.3)$$

$$u_r^a(r, 0) = u_r^b(r, 0) \quad (3.4)$$

$$u_\theta^a(r, 0) = u_\theta^b(r, 0) \quad (3.5)$$

$$u_z^a(r, 0) = u_z^b(r, 0) \quad (3.6)$$

$$\sigma_\theta^b(r, \alpha) = 0 \quad (3.7)$$

$$\tau_{r\theta}^b(r, \alpha) = 0 \quad (3.8)$$

$$\tau_{\theta z}^b(r, \alpha) = 0 \quad (3.9)$$

$$\sigma_{\theta}^a(r, -\phi) = 0 \quad (3.10)$$

$$\tau_{r\theta}^a(r, -\phi) = 0 \quad (3.11)$$

$$\tau_{\theta z}^a(r, -\phi) = 0. \quad (3.12)$$

Using expressions (2.22) for the stresses and (2.26) for the displacements, the boundary and continuity conditions (3.1)–(3.12) give:

$$\sum_{n=1}^6 A_n^a - \sum_{n=1}^6 A_n^b = 0 \quad (3.13)$$

$$\sum_{n=1}^6 A_n^a \mu_n^a - \sum_{n=1}^6 A_n^b \mu_n^b = 0 \quad (3.14)$$

$$\sum_{n=1}^6 A_n^a \delta_n^a - \sum_{n=1}^6 A_n^b \delta_n^b = 0 \quad (3.15)$$

$$\sum_{n=1}^6 A_n^a p_n^a - \sum_{n=1}^6 A_n^b p_n^b = 0 \quad (3.16)$$

$$\sum_{n=1}^6 A_n^a q_n^a - \sum_{n=1}^6 A_n^b q_n^b = 0 \quad (3.17)$$

$$\sum_{n=1}^6 A_n^a s_n^a - \sum_{n=1}^6 A_n^b s_n^b = 0 \quad (3.18)$$

$$\sum_{n=1}^6 A_n^b \left( \cos \alpha + \mu_n^b \sin \alpha \right)^\lambda = 0 \quad (3.19)$$

$$\sum_{n=1}^6 A_n^b (-\sin \alpha + \mu_n^b \cos \alpha) \left( \cos \alpha + \mu_n^b \sin \alpha \right)^{\lambda-1} = 0 \quad (3.20)$$

$$\sum_{n=1}^6 A_n^b \delta_n^b \left( \cos \alpha + \mu_n^b \sin \alpha \right)^{\lambda-1} = 0 \quad (3.21)$$

$$\sum_{n=1}^6 A_n^a \left( \cos \phi - \mu_n^a \sin \phi \right)^\lambda = 0 \quad (3.22)$$

$$\sum_{n=1}^6 A_n^a (\sin \phi + \mu_n^a \cos \phi) (\cos \phi - \mu_n^a \sin \phi)^{\lambda-1} = 0 \quad (3.23)$$

$$\sum_{n=1}^6 A_n^a \delta_n^a \left( \cos \phi - \mu_n^a \sin \phi \right)^{\lambda-1} = 0 \quad (3.24)$$

where  $A_n^a$  and  $A_n^b$  ( $n = 1, 2, \dots, 6$ ) are unknown constants. Equations (3.13)–(3.24) constitute a  $12 \times 12$  system of homogeneous equations for the 12 unknowns  $A_n^a$  and  $A_n^b$ . For a non-trivial solution the determinant of coefficients must vanish, thus giving the following characteristic equation:

$$\Delta(\lambda) = 0. \quad (3.25)$$

Equation (3.25) is a transcendental equation in  $\lambda$  and has infinite number of roots which can be determined numerically.

#### 4. SOLUTION AND RESULTS

As stated earlier, the main objective of this study is to determine the power of singularity near the free edge of two materials. Equation (3.25) has infinite number of roots. By imposing

the physical condition that the strain energy be bounded in a finite region around the bi-material interface, it can easily be shown that the real part of  $\lambda$  must be greater than one. Furthermore, a singular stress-state will prevail if only  $\text{Re}(\lambda) < 2$ . Therefore, it is sufficient to search for a root whose real part is the smallest and satisfies the following condition:

$$1 < \text{Re}(\lambda) < 2. \quad (4.1)$$

We assume that each layer is a fiber reinforced composite, such that the fibers lie in the  $y$ - $z$  plane, and make the angles  $-\theta_\alpha^*$  with the  $y$  axis. (The angles  $\theta_\alpha^*$  ( $\alpha = a, b$ ) are measured from the  $y$ -axis in the counter-clockwise direction.) The engineering constants of the fiber reinforced composite are given as follows:

$$\begin{aligned} E_L &= 163.4 \times 10^9 \text{ N/m}^2 & \nu_{LT} &= 0.3 \\ E_T &= 11.9 \times 10^9 \text{ N/m}^2 & \nu_{LZ} &= 0.3 \\ E_z &= 11.9 \times 10^9 \text{ N/m}^2 & \nu_{TZ} &= 0.5 \\ G_{LT} &= 6.5 \times 10^9 \text{ N/m}^2 \\ G_{ZL} &= 6.5 \times 10^9 \text{ N/m}^2 \\ G_{ZT} &= 3.5 \times 10^9 \text{ N/m}^2 \end{aligned}$$

The constants  $a_{ij}$  ( $i = 1, \dots, 6, j = 1, \dots, 6$ ) which appear in eqns (2.1) can be obtained by rotating the material by an angle  $\theta_\alpha^*$  about the  $x$ -axis. Thus, the composite material which can be considered as orthotropic in the  $(L, T, Z)$  coordinate system is fully anisotropic in the  $(x, y, z)$  coordinate system. Since the solution given in this paper breaks down for orthotropic materials,† the following restrictions are imposed on the angles  $\theta_\alpha^*$ :

$$\theta_\alpha^* \neq 0^\circ, \theta_\alpha^* \neq \pm 90^\circ \text{ and } \theta_a^* \neq \theta_b^* \quad (4.2)$$

Using the general two-wedge formulation, the following problems are studied:

(a) Two bonded layers with a stress free-edge (Fig. 1a): This problem arises in studying the edge effects or boundary layer effects in composites. For this case, the wedge angles are taken as  $\alpha = 90^\circ$  and  $\phi = 90^\circ$ . The stress singularity is computed for different composite materials obtained by varying the angle  $\theta_b^*$  that the fibers make with the  $y$ -axis (Table 1). The results show that the power of singularity ( $\lambda - 2$ ) is real, and although it can vary from material to material, remains relatively small.

(b) The case of a broken laminate (Fig. 2b): This geometry is obtained by letting  $\alpha = 90^\circ$  and  $\phi = 180^\circ$ . The variation of the power of singularity is given in Table 2. It can be observed that for this case the power of singularity ( $\lambda - 2$ ) is again real, close to  $-0.5$  and is much higher than that obtained for the previous case. The implication of this is that, from the viewpoint of delamination failure the case of a broken laminate appears to be more severe than that of a free-edge.

(c) A wedge bonded to a half-plane (Fig. 2c): In this case the ply angles  $\theta_a^*$  and  $\theta_b^*$  are fixed and the effect of the wedge angle  $\alpha$  is investigated. The results are given in Table 3 and are displayed in Fig. 3. As it can be observed from Fig. 3, the power of singularity becomes more severe as the wedge angle increases, reaching the value of  $-1/2$  for a crack between two anisotropic materials. For the particular material used in this paper, the power of singularity is real for all values of the wedge angle  $\alpha$ . However, for isotropic materials, it is known that the power of singularity at the crack tip is complex (i.e. of oscillatory nature) with real part equal to  $-1/2$  (see for example [12]). A complex power of singularity has for many years puzzled researchers about its physical and mathematical meaning. Even though the physical explanation of the complex power of singularity may still remain obscure, the results presented in this

†For orthotropic materials differential eqns (2.5) and (2.6) uncouple, meaning that the plane elasticity problem and the anti-plane problem must be formulated independently. Thus the roots  $\mu_n$  given by the characteristic eqn (2.13) cannot be used to construct the general solution.

Table 1. Variation of the power of singularity ( $\lambda-2$ ) near the free edge of two layers with  $\theta_b^*$  (Fig. 2a, with  $\theta_a^* = 30^\circ$ )

$\theta_b^*$	$-75^\circ$	$-60^\circ$	$-45^\circ$	$-30^\circ$	$-15^\circ$	$15^\circ$	$45^\circ$	$60^\circ$	$75^\circ$
$\lambda - 2$	-0.0731	-0.0582	-0.0388	-0.0256	-0.0235	-0.0113	-0.0167	-0.0507	-0.0733

Table 2. Variation of the power of singularity ( $\lambda-2$ ) near the edge of a broken laminate with  $\theta_b^*$  (Fig. 2b, with  $\theta_a^* = 30^\circ$ )

$\theta_b^*$	$-75^\circ$	$-60^\circ$	$-45^\circ$	$-30^\circ$	$-15^\circ$	$15^\circ$	$45^\circ$	$60^\circ$	$75^\circ$
$\lambda - 2$	-0.4184	-0.4333	-0.4490	-0.4578	-0.4614	-0.4559	-0.4355	-0.4229	-0.4187

Table 3. Variation of the power of singularity ( $\lambda - 2$ ) near the vertex of a wedge bonded to a half-plane with the wedge angle. (Fig. 2c,  $\theta_a^* = 30^\circ$ ,  $\theta_b^* = 60^\circ$ )

$\alpha$	$5^\circ$	10	20	30	60	$90^\circ$	$120^\circ$	150	160	170	175	178	$179^\circ$
$(\lambda-2)$	-0.0408	-0.0785	-0.1465	-0.2050	-0.3356	-0.4229	-0.4743	-0.4888	-0.4900	-0.4947	-0.4974	-0.4990	-0.4995



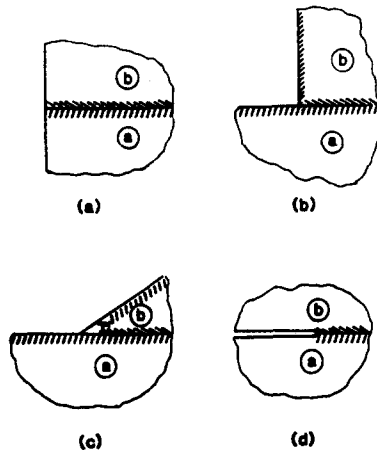


Fig. 2. Geometry of problems considered in the study.

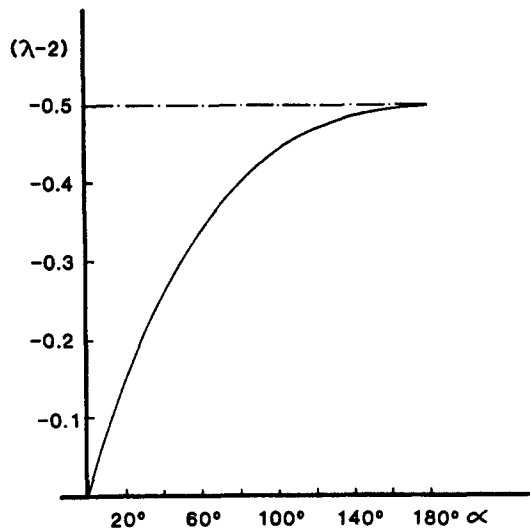


Fig. 3. Variation of the power of singularity  $(\lambda-2)$  with the wedge angle  $\alpha$ , for a wedge bonded to a half-plane ( $\theta_a^* = 30^\circ$ ,  $\theta_b^* = 60^\circ$ ).

paper, together with the explanation given in [4,5] may shed some light on the mathematical explanation of the phenomenon†. The characteristic equation (3.25) has infinite number of roots some real, some complex. These roots depend heavily on the elastic constants of the anisotropic constituents and the wedge angle. As shown in [4, 5] for orthotropic materials the dominant root may be real or complex. Therefore, the oscillatory singularity found for a crack at a bimaterial interface is by no means a universal fact. For anisotropic materials the power of singularity, as shown in this paper, may very well be real.

(d) A crack at the interface of two anisotropic materials (Fig. 2d): This configuration is obtained as a limiting case of the problem studied in (c) by letting  $\alpha \rightarrow 180^\circ$ . Since for  $\alpha = 180^\circ$  the system of equation becomes unstable, the power of singularity in this case is obtained by a limiting process, carried out by assigning to  $\alpha$  closer and closer values of  $180^\circ$ . As stated earlier, for this configuration the power of singularity is found to be real and equal to  $-1/2$ . The results obtained in this paper are of great importance in performing the stress analysis of layered composite structures. In real structures, generally the geometry is very complex to lend itself to

†It may be worthwhile to note that the oscillatory singularity found for isotropic materials is a direct consequence of the linear theory used in modeling the material. It has been shown that, this anomaly disappears when the non-linear theory of harmonic elastic materials is used [14].

analytical formulation. Therefore, one has to resort to purely numerical techniques, such as the finite element method. As shown in this paper, near free-edges, at the base of a broken laminate, or near a crack tip between two layers the stress state is singular and the results obtained by ignoring the singularity can be very erroneous, specially when computing physical quantities near the singular field. Therefore, near a singular stress field, special elements must be designed and incorporated into the finite element grid. The asymptotic expressions given in this paper for the displacements and the strains can be used to formulate those special elements.

#### REFERENCES

1. F. Erdogan and V. Biricikoglu, Two bonded half planes with a crack going through the interface. *Int. J. Engng Sci.* **11**, 745–766 (1973).
2. V. L. Hein and F. Erdogan, Stress singularities in a two-material wedge. *Int. J. Fracture Mech.* **7**, 317–330 (1971).
3. D. B. Bogy, Edge-bonded dissimilar orthogonal elastic wedges under normal and shearing loading. *J. Appl. Mech.* **35**, 460–466 (1968).
4. M. C. Kuo and D. B. Bogy, Plane solutions for the displacement and traction—displacement problems for anisotropic elastic wedges, ASME. *J. Appl. Mech.* 197–202 (1974).
5. M. C. Kuo and D. B. Bogy, Plane solution for traction problems on orthotropic unsymmetrical wedges and symmetrically twinned wedges. *J. App. Mech.* **41**, 203–208 (1974).
6. F. Erdogan and F. Delale, On the problem of stress singularities in bonded orthotropic materials. *Advances in Engng Sci.* **1**, 291–300 (1976).
7. F. Delale and F. Erdogan, Bonded orthotropic strips with cracks. *Int. J. Fracture Mech.* **15**, 343–364 (1979).
8. S. G. Lekhnitskii, *Theory of Elasticity of an Anisotropic Elastic Body*. Holden-Day, New York (1963).
9. S. G. Lekhnitskii, *Anisotropic Plates*. Gordon and Breach, New York (1968).
10. M. L. Williams, Stress singularities resulting from various boundary conditions in angular cornes of plates in extension. *J. Appl. Mech.* **19**, 526–528 (1952).
11. M. L. Williams, Surface singularities resulting from various boundary conditions in angular corners of plates under bending. *Proc. U.S. Nat. Cong. Appl. Mech.* Illinois Institute of Technology, Chicago, Illinois (1951).
12. F. Erdogan and G. Gupta, The stress analysis of multi-layered composites with a flaw. *Int. J. Solids Structures* **7**, 39–61 (1971).
13. S. S. Wang and I. Choi, Boundary-layer effects in composite laminates: Part I—Free edge stress singularities. *J. Appl. Mech.* **49**, 541–548 (1982).
14. J. K. Knowles and E. Sternberg, On the singularity induced by certain mixed boundary conditions in linearized and non-linear elastostatics. *Int. J. Solids Structures* **11**, 1173–1201 (1975).