

Structural Characterization of Lignin Isolated from Coconut (*Cocos nucifera*) Coir Fibers

Jorge Rencoret,^{*,†} John Ralph,[‡] Gisela Marques,[†] Ana Gutiérrez,[†] Ángel T. Martínez,[§] and José C. del Río[†]

[†]Instituto de Recursos Naturales y Agrobiología de Sevilla (IRNAS), CSIC, PO Box 1052, E-41080 Sevilla, Spain

[‡]Departments of Biochemistry and Biological Systems Engineering, the Wisconsin Energy Institute, and the DOE Great Lakes Bioenergy Research Center, University of Wisconsin, Madison, Wisconsin 53726, United States

[§]Centro de Investigaciones Biológicas (CIB), CSIC, Ramiro de Maeztu 9, E-28040 Madrid, Spain

ABSTRACT: The structure of the isolated milled “wood” lignin from coconut coir has been characterized using different analytical methods, including Py-GC/MS, 2D NMR, DFRC, and thioacidolysis. The analyses demonstrated that it is a *p*-hydroxyphenyl-guaiacyl-syringyl (H-G-S) lignin, with a predominance of G units (S/G ratio 0.23) and considerable amounts of associated *p*-hydroxybenzoates. Two-dimensional NMR indicated that the main substructures present in this lignin include β -O-4' alkyl aryl ethers followed by phenylcoumarans and resinols. Two-dimensional NMR spectra also indicated that coir lignin is partially acylated at the γ -carbon of the side chain with *p*-hydroxybenzoates and acetates. DFRC analysis showed that acetates preferentially acylate the γ -OH in S rather than in G units. Despite coir lignin's being highly enriched in G-units, thioacidolysis indicated that β - β' resinol structures are mostly derived from sinapyl alcohol. Finally, we find evidence that the flavone triclin is incorporated into the coconut coir lignin, as has been recently noted for various grasses.

KEYWORDS: coconut coir, lignin, Py-GC/MS, TMAH, HSQC, DFRC, thioacidolysis, *p*-hydroxybenzoates, triclin

■ INTRODUCTION

Coconut coir fibers are extracted from the tissues surrounding the seed of the coconut palm (*Cocos nucifera*), a member of the family *Arecaceae* (palm family). Coir fibers are odorless, lightweight, thick, and strong and have resistance to abrasion.¹ Industrial products from coconut coir include sacking, brushes, doormats, rugs, mattresses, insulation panels, and packaging.² Coir fibers are mostly composed of cellulose (44%), hemicelluloses (12%), lignin (33%), and extractives (6%),³ which makes this material an interesting feedstock for the production of high value-added chemicals and/or biofuels, in the context of the so-called lignocellulose biorefinery.^{4–7}

The key for exploiting the chemical value of lignocellulosic feedstocks, including coir, is to depolymerize the lignocellulosic matrix to obtain smaller molecules that can be utilized or further converted to platform chemicals and/or biofuels. However, the presence of lignin, an aromatic, highly complex and amorphous polymer, constitutes the major barrier against cost-effective lignocellulosic biofuels by complexing with hemicelluloses and cellulose and limiting the accessibility of enzymes to the polysaccharides, thus reducing the efficiency of the hydrolysis/saccharification.^{8,9} Pretreatment of lignocellulosic materials to remove or modify the lignin is therefore needed to enhance the hydrolysis of carbohydrates. The efficiency of the pretreatment methods is highly dependent on the lignin structure, and hence the knowledge of the exact structure of the lignin polymer is important to develop appropriate pretreatment methods for lignin modification and/or removal.

Lignin is a complex polymer synthesized by enzymatic polymerization of three main precursors, the monolignols *p*-coumaryl (4-hydroxycinnamyl), coniferyl

(4-hydroxy-3-methoxycinnamyl), and sinapyl (4-hydroxy-3,5-dimethoxycinnamyl) alcohols.¹⁰ These monolignols produce the *p*-hydroxyphenyl (H), guaiacyl (G), and syringyl (S) phenylpropanoid lignin units when incorporated into the lignin polymer, in which they are linked by several types of C–C and ether bonds. The lignin composition depends on the botanical origin. Thus, hardwood lignins are composed of S and G units in varying ratios, softwood lignins are primarily composed of G units and a small amount of H units, and grass lignins include the three units (together with ferulates and *p*-coumarates). The H-unit content is usually small (typically <5%), but it is often reported as being higher because of conflation with various other *p*-hydroxyphenyl units that do not arise from the incorporation of *p*-coumaryl alcohol into the lignin.^{11,12}

Previous papers have reported the high lignin content of coconut coir (around 33%);³ however, the composition and structure of the lignin has not yet been studied. In this paper, we perform a detailed characterization of the lignin of coconut coir. A main challenge in elucidating the structure of lignins is obtaining high-yield isolation in a chemically unaltered form. The “milled-wood lignin” (MWL) is a lignin preparation considered to be the most representative of the whole native lignin in the plant,¹³ despite its low yield and the possibility of some modifications during isolation, especially during the milling process.¹⁴ In this work, the MWL was isolated from

Received: November 2, 2012

Revised: February 5, 2013

Accepted: February 12, 2013

Published: February 12, 2013

coconut coir and subsequently analyzed by an array of analytical techniques, including pyrolysis–gas chromatography/mass spectrometry (Py-GC/MS) in the absence and in the presence of tetramethylammonium hydroxide (TMAH), 2D NMR, thioacidolysis (followed by Raney nickel desulfurization), and derivatization followed by reductive cleavage (DFRC). Py-GC/MS is a rapid and sensitive analytical method for analyzing the composition of lignin in terms of its H, G, and S units.^{15–17} However, the presence of *p*-hydroxycinnamates (*p*-coumarates and ferulates) or *p*-hydroxybenzoates, which are abundant in the lignins of many plants,^{11,12,15,18,19} constitutes a complication for lignin analysis by analytical pyrolysis, as they yield products similar to those from lignins. This problem can however be solved by using pyrolysis in the presence of tetramethylammonium hydroxide (TMAH), which avoids decarboxylation and releases intact fully methylated derivatives.^{11,12,15,19,20} Additional information regarding the different lignin units and interunit linkages present was provided by 2D NMR spectroscopy, a powerful tool for lignin structural characterization.^{12,21–32} Thioacidolysis is a selective chemical degradative method that cleaves the most frequent interunit linkage in lignins, i.e., the β -O-4' ether linkage. The total yields and relative distribution of the thioacidolysis monomers reflect the amount and ring type (S, G, or H) of lignin units involved in these alkyl aryl ether bonds. In addition, the dimers recovered after thioacidolysis can provide information about the units involved in the various carbon–carbon and diaryl ether linkages, often referred to as the “condensed” lignin bonds (including 5–5', 4–O–5', β -1', β -5', and β - β').^{33–35} Finally, DFRC provided additional information regarding the nature and extent of γ -acylation of the lignin side chain.^{36–39} Detailed knowledge of the composition and structure of coconut coir lignin will help to maximize the exploitation of this important food crop waste as a feedstock for different biorefinery processes.

MATERIALS AND METHODS

Samples. The coconut (*C. nucifera*) coir fibers selected for this study were supplied by the CELESA pulp mill (Tortosa, Spain). The air-dried fibers were ground in an IKA MF10 cutting mill to pass through a 100-mesh screen and were subsequently extracted with acetone in a Soxhlet apparatus for 8 h and with hot water (3 h at 100 °C). Klason lignin content was estimated as the residue after sulfuric acid hydrolysis of the pre-extracted material, corrected for ash and protein content, according to the TAPPI method T222 om-88.⁴⁰ The acid-soluble lignin was determined, after the insoluble lignin was filtered off (Duran filter crucible 4; nominal pore size max. 10–16 μ m), by UV-spectroscopic determination at 205 nm wavelength using 110 L cm⁻¹ g⁻¹ as the extinction coefficient. Ash content was estimated as the residue after 6 h of heating at 525 °C, according to the TAPPI method T211 om-02.⁴⁰ Three replicates were used for each sample.

MWL Isolation. The lignins were obtained according to the classical procedure.¹³ Extractive-free material (40 g) was finely ball-milled in a Retsch S100 centrifugal ball mill at 400 rpm (3 \times 15 h) using an agate jar and balls. The ball-milled material was then extracted with dioxane–water (9:1, v/v) (20 mL of solvent/g of milled fiber). The solution was centrifuged and the supernatant subsequently evaporated to dryness at 40 °C at reduced pressure. The residue obtained (raw MWL) was redissolved into a solution of acetic acid/water 9:1 (v/v) (25 mL of solvent/g of raw MWL). The lignin from the solution was precipitated into water, and the formed precipitate was separated by centrifugation, milled in an agate mortar, and subsequently dissolved in a solution of 1,2-dichloroethane:ethanol (1:2, v/v). The mixture was then centrifuged to eliminate the insoluble material. The lignin in the supernatant was precipitated into diethyl

ether, and the obtained residue was separated by centrifugation. This residue was then resuspended in diethyl ether, centrifuged, and finally resuspended in petroleum ether. The final purified MWL sample was recovered by centrifugation and dried under a N₂ current. The final yields ranged from 10 to 12% of the original Klason lignin content.

Gel Permeation Chromatography (GPC). GPC was performed on a Shimadzu LC-20A liquid chromatography (LC) system (Shimadzu, Kyoto, Japan) equipped with a photodiode array (PDA) detector (SPD-M20A; Shimadzu) using the following conditions: column, TSK gel α -M + α -2500 (Tosoh, Tokyo, Japan); eluent, 0.1 M LiBr in dimethylformamide (DMF); flow rate, 0.5 mL min⁻¹; temperature, 40 °C; sample detection, PDA response at 280 nm. The data acquisition and computation used Lcsolution version 1.25 software (Shimadzu). The molecular weight calibration was via polystyrene standards (*M_w* range from 2.66 \times 10² up to 3.84 \times 10⁶ Da, Tosoh Bioscience).

Analytical Pyrolysis. Pyrolysis of MWL (approximately 100 μ g) was performed with a 2020 microfurnace pyrolyzer (Frontier Laboratories Ltd.) connected to an Agilent 6890 GC/MS using a DB-1701 fused-silica capillary column (30 m \times 0.25 mm i.d., 0.25 μ m film thickness) and an Agilent 5973 mass selective detector (EI at 70 eV). The pyrolysis was performed at 500 °C. The oven temperature was programmed from 50 °C (1 min) to 100 °C at 30 °C min⁻¹ and then to 300 °C (10 min) at 10 °C min⁻¹. Helium was the carrier gas (1 mL min⁻¹). The compounds were identified by comparing their mass spectra with those of the Wiley and NIST libraries and those reported in the literature.^{16,17} Peak molar areas were calculated for the lignin degradation products, the summed areas were normalized, and the data for three repetitive analyses were averaged and expressed as percentages. The relative standard deviation for the pyrolysis data was less than 5%.^{11,12,15}

NMR Spectroscopy. 2D NMR spectra were recorded at 25 °C on a Bruker AVANCE III 500 MHz instrument, equipped with a cryogenically cooled 5 mm TCI gradient probe with inverse geometry (proton coils closest to the sample). Unacetylated MWL (40 mg) was dissolved in 0.75 mL of dimethyl sulfoxide (DMSO)-*d*₆, or 80 mg of acetylated MWL (after 48 h treatment in acetic anhydride/pyridine, 1:1 v/v, and recovered by precipitation into water) was dissolved in 0.75 mL of chloroform-*d*. The central solvent peaks were used as internal reference (DMSO δ_C/δ_H 39.5/2.49; chloroform, δ_C/δ_H 77.0/7.26). The HSQC (heteronuclear single quantum coherence) experiment on the unacetylated sample used Bruker's “hsqcetg-psisp2.2” pulse program (adiabatic-pulsed version) with spectral widths of 5000 Hz (from 10 to 0 ppm) and 20843 Hz (from 165 to 0 ppm) for the ¹H and ¹³C dimensions. The number of transients was 64, and 256 time increments were always recorded in the ¹³C dimension. The ¹J_{CH} used was 145 Hz. Processing used typical matched Gaussian apodization in the ¹H dimension and squared cosine-bell apodization in the ¹³C dimension. Prior to Fourier transformation, the data matrices were zero-filled up to 1024 points in the ¹³C dimension. The HMBC (heteronuclear multiple bond correlation) experiment on the acetylated sample used Bruker's “hmbcgp1pndqf” pulse program and a long-range *J*-coupling evolution time of 70 ms.

Two-dimensional NMR cross-signals were assigned by literature comparison.^{12,21–32} A semiquantitative analysis of the volume integrals of the HSQC correlation peaks was performed using Bruker's Topspin 3.1 processing software. Integration of signals corresponding to chemically analogous C–H pairs with similar ¹J_{CH} coupling values was performed separately for the different regions of the spectra. In the aliphatic oxygenated region, interunit linkages were estimated from C _{α} –H _{α} correlations, except for structure E described below where C _{γ} –H _{γ} correlations had to be used, and the relative abundance of side chains involved in different substructures and terminal structures were calculated. In the aromatic/unsaturated region, C₂–H₂ correlations from H, G, and S lignin units and from *p*-hydroxybenzoates were used to estimate their abundances (note that *p*-hydroxybenzoate quantitation relative to the lignin might be overestimated because of the longer relaxation times of these end-units compared to the rapidly relaxing polymer and the more extensive relaxation the latter

experiences during the significant duration of the pulse experiment itself). An estimation of the percentage of γ -acylation of the lignin side chain was performed by integration of the signals corresponding to the hydroxylated vs acylated γ -C/H correlations.

Thioacidolysis. Thioacidolysis of 5 mg of MWL was performed according to the described protocol³³ using 0.2 M BF_3 etherate in dioxane/ethanethiol 8.75:1. The reaction products were extracted with dichloromethane, dried, and concentrated. GC analysis of trimethylsilylated samples [using *N,O*-bis(trimethylsilyl)trifluoroacetamide, BSTFA], was performed with a Hewlett-Packard 6890 instrument using an Rtx5 column from Restec Corporation (45 m \times 0.32 mm i.d., 0.25 μm film thickness) and a flame-ionization detector. The temperature was programmed from 180 $^\circ\text{C}$ to 270 $^\circ\text{C}$ (15 min) at 40 $^\circ\text{C min}^{-1}$ and then to 300 $^\circ\text{C}$ (5 min) at 4 $^\circ\text{C min}^{-1}$. Injector and detector were at 250 $^\circ\text{C}$ and 280 $^\circ\text{C}$, respectively, and helium was the carrier gas.

Desulfurization of Thioacidolysis Degradation Products. Two-hundred microliters of the CH_2Cl_2 solution containing the thioacidolysis products was desulfurized with 1 mL of Raney nickel aqueous slurry and 5 mL of methanol, as previously described.³⁴ The desulfurization was allowed to proceed at 80 $^\circ\text{C}$ (oil bath) for 4 h with occasional shaking. GC/MS analysis of the dimeric compounds (as their trimethylsilyl ether derivatives) was performed on a Varian Star 3400 coupled to an ion-trap Varian Saturn 2000 detector, using a DB-5HT fused-silica capillary column from J&W Scientific (30 m \times 0.25 mm i.d., 0.1 μm film thickness). The temperature was programmed from 50 $^\circ\text{C}$ to 110 $^\circ\text{C}$ at 30 $^\circ\text{C min}^{-1}$ and then to 320 $^\circ\text{C}$ (13 min) at 6 $^\circ\text{C min}^{-1}$. The injector and transfer line were at 300 $^\circ\text{C}$; the injector was programmed from 120 $^\circ\text{C}$ (0.1 min) to 380 $^\circ\text{C}$ at 200 $^\circ\text{C min}^{-1}$. Helium was the carrier gas (2 mL min^{-1}), and tetracosane was used as internal standard. Dimer identification was based on previously reported mass spectra^{21,34,41–43} and mass fragmentography.

DFRC. To assess the incorporation of naturally acetylated monolignols into the lignin, resulting in γ -acetylated lignin side chains, a modification of the standard DFRC method using propionylation instead of acetylating reagents³⁹ was made in the present study. Lignins (10 mg) were stirred for 2 h at 50 $^\circ\text{C}$ with propionyl bromide in propionic acid (8:92, v/v). The solvents and excess bromide were removed by rotary evaporation. The products were then dissolved in dioxane/propionic acid/water (5:4:1, v/v/v), and 50 mg powdered Zn was added. After being stirred for 40 min at room temperature, the mixture was transferred into a separatory funnel with dichloromethane and saturated ammonium chloride. The aqueous phase was adjusted to pH < 3 by adding 3% HCl, the mixture vigorously mixed, and the organic layer separated. The water phase was extracted twice more with dichloromethane. The combined dichloromethane fractions were dried over anhydrous NaSO_4 , and the filtrate was evaporated to dryness using a rotary evaporator. The residue was subsequently propionylated for 1 h in 1.1 mL of dichloromethane containing 0.2 mL of propionic anhydride and 0.2 mL of pyridine. The propionylated (and naturally acetylated) lignin degradation compounds were collected after rotary evaporation of the solvents and subsequently analyzed by GC/MS.

The GC/MS analyses were performed with an Agilent 7820A chromatograph coupled to an Agilent 5975 mass detector, using a capillary column (Agilent HP-5 ms, 30 m \times 0.25 mm i.d., 0.25 μm film thickness). The oven was heated from 140 $^\circ\text{C}$ (1 min) to 280 at 3 $^\circ\text{C min}^{-1}$, ramped at 20 $^\circ\text{C min}^{-1}$ to 300 $^\circ\text{C}$, and then held for 5 min at the final temperature. The injector was set at 250 $^\circ\text{C}$, and the transfer line was kept at 280 $^\circ\text{C}$. Helium was used as the carrier gas at a rate of 2 mL min^{-1} .

RESULTS AND DISCUSSION

The relative abundances of the main constituents of coir are presented in Table 1. The high lignin content observed (32.1%) agrees well with previously published data.³ In this work, we have thoroughly studied the coconut coir lignin composition and structure. For this purpose, the MWL was isolated according to the traditional lignin isolation proce-

Table 1. Abundance of the Main Constituents of Coconut Coir (% of dry weight)

water-solubles	1.7
acetone extractives	0.3
Klason lignin ^a	32.1
acid-soluble lignin	1.4
carbohydrates ^b	62.9
ash	1.6

^aCorrected for proteins and ash. ^bDetermined by subtracting other components from 100%

dures,¹³ and subsequently analyzed by GPC, Py-GC/MS, 2D NMR, thioacidolysis, and DFRC. As said before, MWL preparation is considered to be the most representative of the whole native lignin in the plant. However, we must keep in mind that the results obtained here reflect the structure of isolated MWL, which represents only a part of the whole lignin in the plant.

Molecular Weight Distribution of Coconut Coir MWL.

The molecular weight-average (M_w) and number-average (M_n) values were estimated from the GPC curves (relative values related to polystyrene standards). The MWL exhibited a M_w of 7900 g mol^{-1} and a M_n molecular weight of 2900 g mol^{-1} . Therefore, the MWL exhibited relatively narrow polydispersity, with M_w/M_n of 2.7 compared to other isolated lignins.⁴⁴

Py-GC/MS. The MWL from coconut coir was analyzed by Py-GC/MS. The pyrogram is shown in Figure 1a, and the identities and relative molar abundances of the released compounds are listed in Table 2. Pyrolysis of coir MWL released phenolic compounds that are derived from H, G and S lignin units, the most predominant ones being phenol (1), guaiacol (4), 4-methylguaiacol (6), 4-vinylguaiacol (9), syringol (10), vanillin (13), *trans*-isoeugenol (15), and *trans*-conifer-aldehyde (31). The pyrolysis data indicate a predominance of G- over S-lignin units, with a S/G ratio of 0.29. In addition, high levels of phenol (~27% of all phenolic compounds) were released upon pyrolysis from coconut coir MWL. This fact might suggest the presence of *p*-hydroxybenzoates in coir lignin, as also occurs in the lignin of other palms.¹⁹ It is important to note that *p*-hydroxybenzoates decarboxylate upon pyrolysis^{19,20} and produce similar compounds as those derived from *p*-hydroxyphenyl lignin, such as phenol, which will overestimate the relative abundance of H-lignin units. It is obvious then that the abundance of phenol cannot be used here for the estimation of the lignin H:G:S composition upon Py-GC/MS, as the major part of it does not arise from the core lignin structural units but from *p*-hydroxybenzoates, as will be shown below.

The occurrence of *p*-hydroxybenzoates in the lignin of coconut coir was assessed by pyrolysis in the presence of TMAH as methylating agent. Py/TMAH efficiently prevents decarboxylation and results in depolymerization and subsequent methylation of the phenolic and carboxyl groups.^{11,12,20} Py/TMAH of coconut coir lignin (shown in Figure 1b) released significant levels of 4-methoxybenzoic acid methyl ester, confirming the occurrence of *p*-hydroxybenzoates in this lignin. In contrast, the amounts methoxybenzene, which arises exclusively from H-lignin, were very low (only 2% of the 4-methoxybenzoic acid methyl ester peak area). This means that the great majority of phenols released after Py-GC/MS arise from *p*-hydroxybenzoates. The occurrence of *p*-hydroxybenzoates in the lignin of other plants, such as sago palm, was also

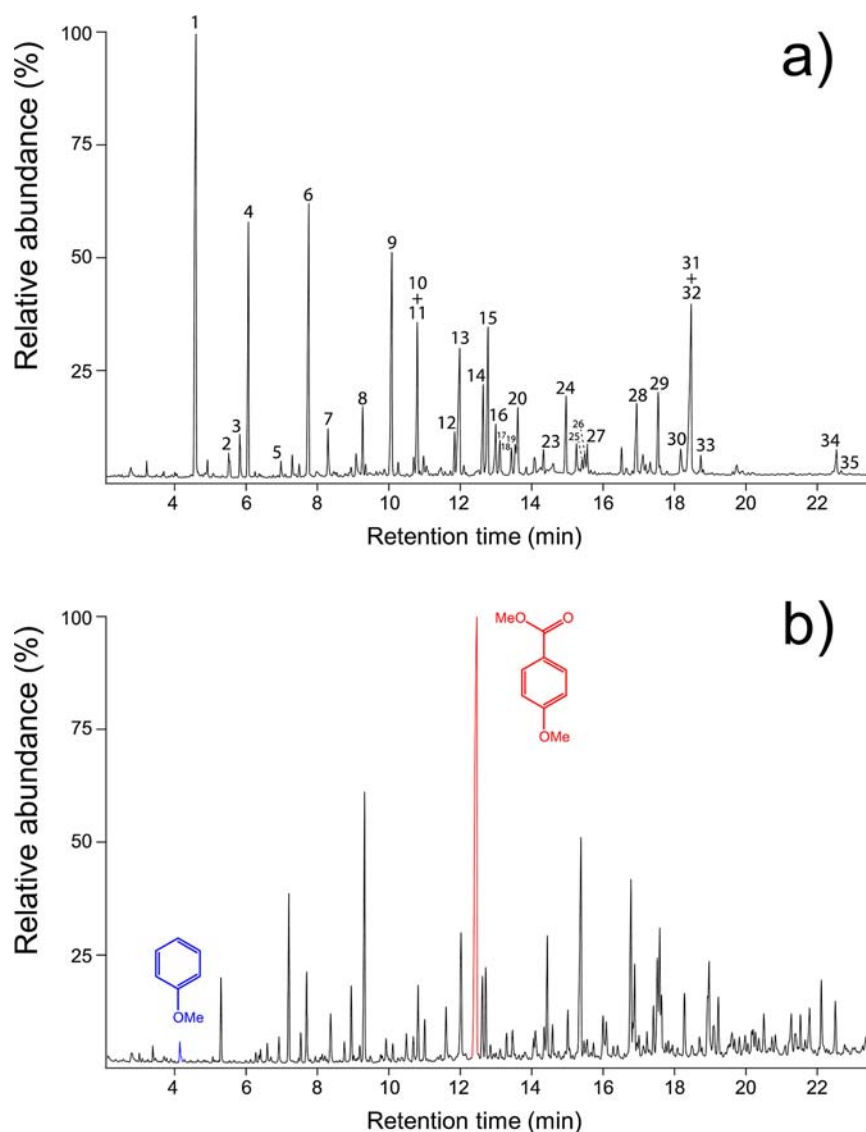


Figure 1. Py-GC/MS (a) and Py-TMAH-GC/MS (b) chromatograms of the MWL isolated from coconut coir. The identities and relative abundances of the compounds released by Py-GC/MS are listed in Table 2. Only the identities of peaks of interest (methoxybenzene and 4-methoxybenzoic acid methyl ester) are shown in the case of Py-TMAH-GC/MS.

successfully determined by Py/TMAH.¹⁹ Only minor amounts of *p*-coumarates (2% with respect to *p*-hydroxybenzoates) could be detected (as the dimethyl derivative) in coir lignin upon Py/TMAH.

2D NMR. To obtain additional information on the structure of coir lignin, the MWL was analyzed by 2D NMR, which provides information on the interunit linkages as well as the lignin composition. The side chain (δ_C/δ_H 50–90/2.5–6.0) and the aromatic/unsaturated (δ_C/δ_H 90–155/6.0–8.5) regions of the HSQC NMR spectrum of the MWL from coconut coir are shown in Figure 2. The main lignin cross-signals assigned in the HSQC spectrum are listed in Table 3, and the main substructures present are also depicted in the Figure 2.

The side chain region of the spectrum gives useful information about the different interunit linkages present in the lignin (Figure 2a). The spectrum shows prominent signals corresponding to β -O-4' alkyl-aryl ether linkages (substructures A and A'). The C_α - H_α correlations in β -O-4' substructures were observed in overlapping signals at δ_C/δ_H

71.0/4.75 and 71.7/4.87 for structures linked to G or S lignin-units. Likewise, the C_β - H_β correlations were observed at δ_C/δ_H 83.9/4.28 for β -O-4'-G units and at δ_C/δ_H 85.9/4.12 for β -O-4'-S units; C_β - H_β correlations for β -O-4'-H units were observed at δ_C/δ_H 83.3/4.48. The C_γ - H_γ correlations in β -O-4' substructures were observed at δ_C/δ_H 59.8/3.24 and 3.61, partially overlapped with other signals. In addition, the spectrum clearly showed the presence of signals in the range δ_C/δ_H 63.3/4.46–4.30 corresponding to the C_γ - H_γ correlations of γ -acylated units (substructure A', R = acyl). The HSQC spectrum therefore indicates that the coconut coir lignin is partially acylated at the γ -position of the lignin side chain. Signals for α -acylated β -O-4' substructures, which should appear at \sim 6.1/75 ppm, were not observed in the spectrum. Therefore, it is possible to conclude that the lignin of coconut coir MWL is partially acylated and that this acylation occurs exclusively at the γ -position of the lignin side chain. An estimation of the percentage of γ -acylation of the lignin side chain was performed by integration of the signals correspond-

Table 2. Identities and Relative Molar Abundances of the Compounds Released after Py-GC/MS of Coconut Coir MWL^{a,b}

label	compound	origin	rel abundance
1	phenol	LH/PB	27.1
2	3-methylphenol	LH	0.7
3	4-methylphenol	LH	1.6
4	guaiacol	LG	7.8
5	4-ethylphenol	LH	0.5
6	4-methylguaiacol	LG	9.2
7	4-vinylphenol	LH	1.8
8	4-ethylguaiacol	LG	1.7
9	4-vinylguaiacol	LG	8.0
10	syringol	LS	3.4
11	eugenol	LG	0.9
12	<i>cis</i> -isoeugenol	LG	1.0
13	vanillin	LG	5.7
14	4-methylsyringol	LS	2.6
15	<i>trans</i> -isoeugenol	LG	4.5
16	homovanillin	LG	1.6
17	4-hydroxybenzoic acid methyl ester	LH	1.0
18	propynguaiacol	LG	0.7
19	propynguaiacol	LG	0.7
20	acetovanillone	LG	1.9
21	ethylsyringol	LS	0.3
22	vanillic acid methyl ester	LG	0.2
23	guaiacylacetone	LG	0.6
24	vinylsyringol	LS	2.1
25	propiovanillone	LG	0.3
26	guaiacyl vinyl ketone	LG	0.5
27	4-allylsyringol	LS	0.5
28	syringaldehyde	LS	2.2
29	<i>trans</i> -propenylsyringol	LS	1.9
30	acetosyringone	LS	0.8
31	<i>trans</i> -coniferaldehyde	LG	4.3
32	<i>trans</i> -coniferyl alcohol	LG	2.7
33	syringylacetone	LS	0.3
34	<i>trans</i> -sinapaldehyde	LS	0.6
35	<i>trans</i> -sinapyl alcohol	LS	0.1

^aS/G ratio = 0.29. ^bLH: H lignin units; LG: G lignin units; LS: S lignin units; PB: *p*-hydroxybenzoates.

ing to the C_γ-H_γ correlations of hydroxylated vs acylated γ -carbon, indicating up to 11% of lignin acylation.

Strong signals for phenylcoumaran substructures (B) were also found in the spectrum of coconut coir MWL, the signals for their C_α-H_α and C_β-H_β correlations being observed at δ_C/δ_H 86.8/5.46 and 53.1/3.45, and those of C_γ-H_γ correlations overlapping with other signals around δ_C/δ_H 62.6/3.71. Resinol substructures (C) were also clearly observed in the spectrum, with their C_α-H_ω, C_β-H_β, and the double C_γ-H_γ correlations at δ_C/δ_H 84.9/4.67, 53.5/3.06, and 71.0/3.82 and 4.18 (i.e., the two diastereotopic protons attached to the γ -carbon are well separated). Small signals corresponding to dibenzodioxocin substructures (D) were also observed in the spectra, their C_α-H_α and C_β-H_β correlations being at δ_C/δ_H 83.2/4.84 and 85.4/3.87. Finally, other signals observed in the side chain region of the spectrum corresponded to the C_γ-H_γ correlations of cinnamyl alcohol end-groups (E) at δ_C/δ_H 61.4/4.09.

The main cross-signals in the aromatic region of the HSQC spectrum (Figure 2b) corresponded to the aromatic rings of the different H, G, and S lignin units and to *p*-hydroxybenzoates

that are attached to the lignin (see below). The S-lignin units showed a prominent signal for the C_{2,6}-H_{2,6} correlation at δ_C/δ_H 103.9/6.71, whereas the G units showed different correlations for C₂-H₂ (δ_C/δ_H 110.9/7.00) and C₅-H₅/C₆-H₆ (δ_C/δ_H 115.0/6.74 and 6.94, and δ_C/δ_H 118.8/6.79). Signals corresponding to C_{3,5}-H_{3,5} and C_{2,6}-H_{2,6} correlations in H-lignin units were observed at δ_C/δ_H 106.8/7.32 and 127.8/7.20. Strong signals for the C_{2,6}-H_{2,6} and C_{3,5}-H_{3,5} correlations of *p*-hydroxybenzoate units were observed at δ_C/δ_H 131.2/7.68 and 114.3/6.61 (the latter overlapping with the G₅/G₆ signals). Other signals in this HSQC region of the spectrum are from cinnamyl alcohol end-groups (E), with their C_α-H_α and C_β-H_β correlations observed at δ_C/δ_H 129.0/6.23 and 129.0/6.45, and cinnamaldehyde end-groups (I), with the C_α-H_α and C_β-H_β correlations observed at δ_C/δ_H 153.8/7.63 and 126.7/6.77. The relative content of the cinnamaldehyde end-groups was estimated by comparison of the intensities of the C_β-H_β correlations in cinnamyl alcohols (E) and aldehydes (I). Other cross-signals revealing the presence of coniferaldehyde end-groups corresponded to C₂-H₂ and C₆-H₆ correlation signals at δ_C/δ_H 111.1/7.40 and δ_C/δ_H 123.6/7.21. Interestingly, in this region of the HSQC spectrum, it was also possible to detect two signals at δ_C/δ_H 94.1/6.56 and 98.8/6.20 corresponding to the C₈-H₈ and C₆-H₆ correlations of triclin (T), a flavone that is apparently incorporated into the lignins in some grasses.¹² Coconut, like the grasses, belongs to the monocots; it is beginning to appear that triclin may be a feature restricted to monocot lignins although its clade range remains to be determined.

The relative abundances of the main lignin interunit linkages and end-groups, as well as the percentage of γ -acylation of the lignin side chain, the molar abundances of the different lignin units (H, G, and S) and of the *p*-hydroxybenzoates, and the molar S/G ratio of the coir lignin, all estimated from volume integration of contours in the HSQC spectrum, are shown in Table 4. The main substructure present in the lignin of coconut coir was the β -O-4' aryl ether (A/A'), that accounts for 82% of all interunit linkages, followed by β -5' phenylcoumaran substructures (B) that involved 13% of all linkages, β - β' resinol substructures (C) that involved 4%, and a small amount of S-S' dibenzodioxocin substructures (D) that involved 1% of all linkages. The lignin S/G ratio determined with NMR (0.23) was similar to that obtained with Py-GC/MS, as shown above.

p-Hydroxybenzoates are known to acylate the γ -OH of the lignin side chain in many plants, including palms.^{19,32,45-49} The fact that the side chain of the lignin in coir is partially acylated at the γ -OH (11% of lignin side chains), together with the presence of significant amounts of *p*-hydroxybenzoates (13% with respect to lignin), seems to indicate that these could also acylate the γ -OH in the lignin of coir. However, the HSQC spectrum only indicates that the lignin in coir is partially acylated at the γ -position and cannot provide information on the nature of the acyl group. For this purpose, we performed HMBC experiments that correlate protons with carbons separated by two or three bonds; such long-range coupling experiments give important information about the connectivity of the ester moiety to the lignin skeleton. The HMBC experiments were performed on acetylated MWL to reduce the viscosity of the lignin solutions and thus enhance the spectral properties. Figure 3 shows the section of the HMBC spectrum of (acetylated) coconut coir MWL for the correlations of the carbonyl carbon of *p*-hydroxybenzoates acylating the lignin γ -OH. The correlations of the carbonyl carbon at δ_C 165.0 with

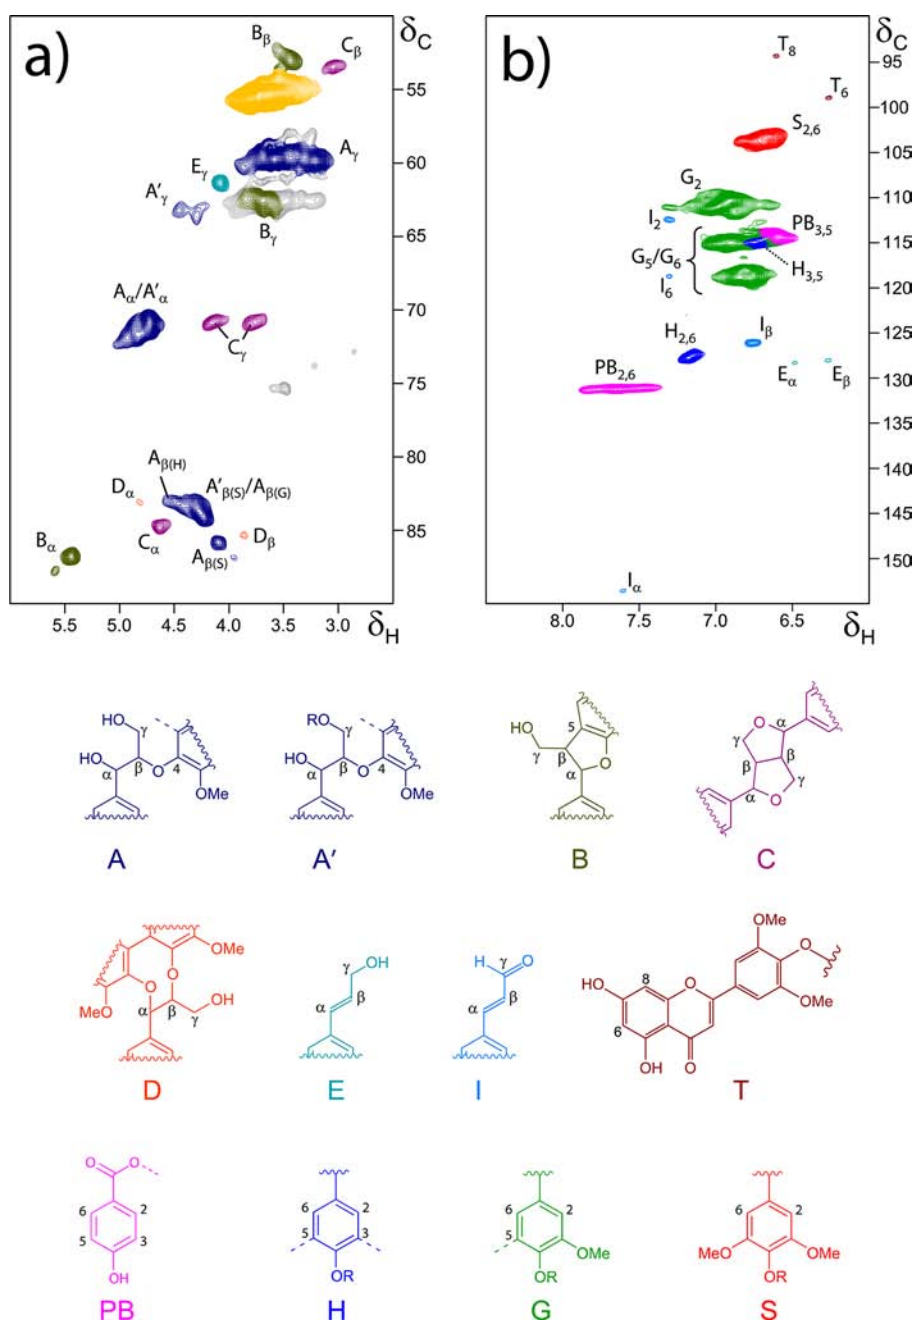


Figure 2. Side chain (a) and aromatic (b) regions in the 2D-HSQC NMR spectrum of coconut coir MWL (in DMSO- d_6). See Table 3 for signal assignments. Main structures present in the lignin from the coconut coir: (A) β -O-4' alkyl-aryl ethers; (A') β -O-4' alkyl-aryl ethers with acylated γ -OH; (B) phenylcoumarans; (C) resinols; (D) dibenzodioxins; (E) *p*-hydroxycinnamyl alcohol end-groups; (I) *p*-hydroxycinnamaldehyde end-groups; (T) triclin end-units; (PB) *p*-hydroxybenzoates; (H) H units; (G) G units; (S) S units.

the 2- and 6-protons at δ_H 7.68 confirm that they belong to the *p*-hydroxybenzoates. In addition, the correlations of this carbonyl carbon with several protons in the range δ_H 4.5–5.0 conclusively demonstrate that *p*-hydroxybenzoates are acylating the γ -position of the lignin side chains in coir lignin, as also occurs in the lignins of other plants.^{19,32,45–49} On the other hand, it is known that the lignin of many plants are also acylated by acetate groups.^{50–54} This HMBC spectrum, however, could not show the correlations of the carbonyl carbon for native acetate groups that may be eventually acylating the γ -carbon of the lignin side chain in coir, as this lignin was acetylated for improving the spectral and solubility properties. Unfortunately the unacetylated materials are

unsuitable for high quality HMBC experiments because of their rapid relaxation rates.

DFRC. Additional information regarding the presence of native acetate groups acylating the γ -OH of the lignin side chain in coconut coir MWL was obtained by DFRC analysis. The DFRC degradation method cleaves α - and β -ether linkages in the lignin polymer leaving γ -esters intact and is an appropriate and sensitive method for the analysis of natively γ -acylated lignin.^{36–38} The original DFRC degradation method does not allow the analysis of native acetylated lignin because the degradation products are acetylated during the degradation procedure, but with a modification by substituting acetylating reagents with propionylating reagents (DFRC'), it is possible to

Table 3. Assignments of the Lignin ^{13}C - ^1H Correlation Signals in the 2D HSQC Spectra of the MWL Isolated from Coconut Coir

label	$\delta_{\text{C}}/\delta_{\text{H}}$	assignment
B_{β}	53.1/3.45	C_{β} - H_{β} in phenylcoumaran substructures (B)
C_{β}	53.5/3.06	C_{β} - H_{β} in β - β' resinol substructures (C)
OCH_3	55.5/3.74	C-H in methoxyls
A_{γ}	59.8/3.24 and 3.61	C_{γ} - H_{γ} in γ -hydroxylated β -O-4' substructures (A)
I_{γ}	61.4/4.09	C_{γ} - H_{γ} in cinnamyl alcohol end-groups (I)
B_{γ}	62.6/3.71	C_{γ} - H_{γ} in phenylcoumaran substructures (B)
A'_{γ}	63.3/4.46 and 4.30	C_{γ} - H_{γ} in γ -acylated β -O-4' substructures (A')
$A_{\alpha(\text{G})}$	71.0/4.75	C_{α} - H_{α} in β -O-4' substructures (A) linked to a G unit
C_{γ}	71.0/3.82 and 4.18	C_{γ} - H_{γ} in β - β' resinol substructures (C)
$A_{\alpha(\text{S})}$	71.7/4.87	C_{α} - H_{α} in β -O-4' substructures (A) linked to a S unit
$A_{\beta(\text{H})}$	83.3/4.48	C_{β} - H_{β} in β -O-4' substructures (A) linked to a H unit
D_{α}	83.2/4.84	C_{α} - H_{α} in dibenzodioxocin substructures (D)
$A_{\beta(\text{G})}$	83.9/4.28	C_{β} - H_{β} in β -O-4' substructures (A) linked to a G unit
C_{α}	84.9/4.67	C_{α} - H_{α} in β - β' resinol substructures (C)
D_{β}	85.4/3.87	C_{β} - H_{β} in dibenzodioxocin substructures (D)
$A_{\beta(\text{S})}$	85.9/4.12	C_{β} - H_{β} in β -O-4' substructures linked (A) to a S unit
B_{α}	86.8/5.46	C_{α} - H_{α} in phenylcoumaran substructures (B)
T_8	94.1/6.56	C_8 - H_8 in triclin (T)
T_6	98.8/6.20	C_6 - H_6 in triclin (T)
$S_{2,6}$	103.9/6.71	C_2 - H_2 and C_6 - H_6 in S units
G_2	110.9/7.00	C_2 - H_2 in G units
I_2	112.4/7.31	C_2 - H_2 in cinnamaldehyde end-groups (I)
$\text{PB}_{3,5}$	114.3/6.61	C_3 - H_3 and C_5 - H_5 in <i>p</i> -hydroxybenzoate (PB)
$H_{3,5}$	114.9/6.76	$C_{3,5}$ - $H_{3,5}$ in H units
G_5/G_6	115.0/6.74 and 6.94 118.8/6.79	C_5 - H_5 and C_6 - H_6 in G units
I_6	118.7/7.31	C_6 - H_6 in cinnamaldehyde end-groups (I)
I_{β}	126.3/6.76	C_{β} - H_{β} in cinnamaldehyde end-groups (I)
$H_{2,6}$	127.8/7.20	$C_{2,6}$ - $H_{2,6}$ in H units
E_{β}	129.0/6.23	C_{β} - H_{β} in cinnamyl alcohol end-groups (E)
E_{α}	129.0/6.45	C_{α} - H_{α} in cinnamyl alcohol end-groups (E)
$\text{PB}_{2,6}$	131.2/7.68	C_2 - H_2 and C_6 - H_6 in <i>p</i> -hydroxybenzoate (PB)
I_{α}	153.5/7.60	C_{α} - H_{α} in cinnamaldehyde end-groups (I)

obtain information about the occurrence and extent of native lignin acetylation.^{39,51}

Figure 4 shows the chromatogram of the DFRC' products released from the MWL from coconut coir. The DFRC' released the cis- and trans-isomers of H- (cH and tH), G- (cG and tG), and S-type (cS and tS) lignin monomers, as their propionylated derivatives, arising from normal γ -OH units in lignin. In addition, the presence of γ -acetylated G (cGac and tGac) and S (cSac and tSac) lignin units, arising from originally

Table 4. Structural Characteristics (lignin interunit linkages, cinnamyl end-groups, percentage of γ -acylation, aromatic units and S/G ratio, and *p*-hydroxybenzoate content) from Integration of ^{13}C - ^1H Correlation Signals in the HSQC Spectra of the MWL Isolated from Coconut Coir

lignin interunit linkages (%)	
β -O-4' aryl ethers (A/A')	82
phenylcoumarans (B)	13
resinols (C)	4
dibenzodioxocins (D)	1
lignin end-groups ^a	
cinnamyl alcohol end-groups (E)	5
cinnamaldehyde end-groups (I)	15
lignin side chain γ -acylation (%)	
lignin aromatic units ^b	11
H (%)	4
G (%)	78
S (%)	18
H/G ratio	0.05
S/G ratio	0.23
<i>p</i> -hydroxybenzoates ^c	13

^aExpressed as a fraction of the total lignin interunit linkage types A-D.

^bMolar percentages (H + G + S = 100). ^c*p*-Hydroxybenzoate molar content as percentage of lignin content (H + G + S).

acetylated lignin units, could also be observed in the chromatogram, indicating that some γ -acetylation occurred on the lignin side chain. The DFRC' analyses indicated a low extent of acetylation, preferentially on S-monomers (6%), whereas only 1% of G-monomers were γ -acetylated.

Thioacidolysis. The MWL from coconut coir was also analyzed by thioacidolysis. The composition of the lignin monomers released after thioacidolysis showed a predominance of G over S units and smaller amounts of H units, with a H:G:S composition of 7:68:25 (Table 5). As expected, the molar S/G ratio obtained (0.37) is higher than those estimated from Py-GC/MS (0.29) and NMR (0.23), because S units are mostly involved in alkyl aryl ether linkages (β -O-4' and α -O-4'), which are the ones cleaved during thioacidolysis.^{10,33-35}

The dimers recovered after thioacidolysis can provide useful information about the different units involved in the various carbon-carbon and diaryl ether linkages,^{34,35} often referred to as the "condensed" bonds (including 5-5', 4-O-5', β -1', β -5', and β - β'). To study lignin dimers, the thioacidolysis degradation products were subjected to a Raney nickel desulfurization, and the products obtained were analyzed by GC-MS. The chromatograms of the trimethylsilylated thioacidolysis degradation products are shown in Figure 5. The released compounds were identified according to previously reported mass spectra.^{21,24,35,41-43} The structures of the main compounds identified are shown in Figure 6, and their relative molar abundances are summarized in Table 6. The dimers identified were 5-5' (dimers 1-4, 6, and 8), 4-O-5' (dimers 5, 9, and 12), β -1' (dimers 7, 10, 13, 16, and 18), β -5' (dimers 11, 14, 15, 17, 19, and 24), and β - β' tetralin (dimers 20-23 and 25) types. The relative molar abundances of the different types of condensed dimers released from the MWL of coconut coir are shown in Table 7.

Dimeric compounds with β -5' structures, arising from opening the α -O-4' ethers in phenylcoumaran substructures, were the most prominent thioacidolysis dimers released from the lignin of coconut coir, accounting for 45.8% of the total

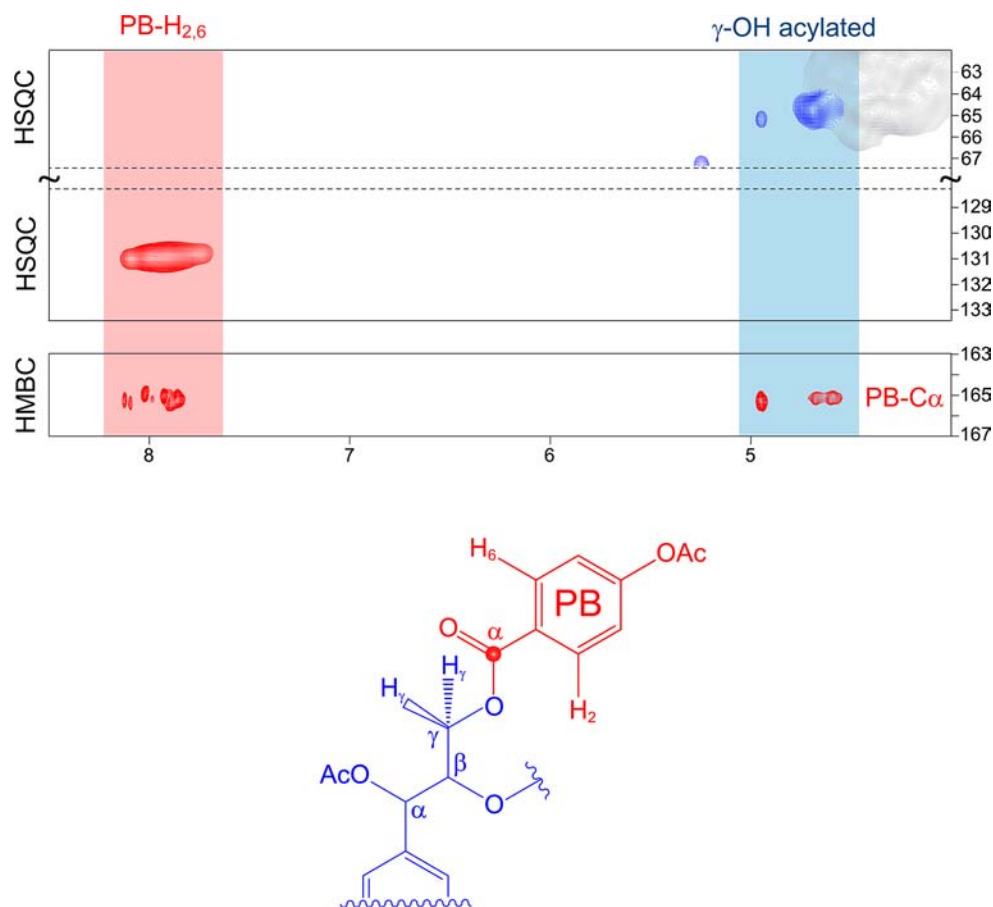


Figure 3. Section of the HMBC spectrum (δ_C/δ_H 163–167/4.0–8.5) of acetylated coconut coir MWL (in CDCl_3) showing the main correlations for the carbonyl carbon of the *p*-hydroxybenzoates acylating the γ -positions of the lignin side chains. Appropriate sections of the HSQC spectrum showing the $\text{C}_\gamma\text{-H}_\gamma$ correlations of the acylated lignin γ -carbon (δ_C 62–68) and the $\text{C}_{2,6}\text{-H}_{2,6}$ correlations of *p*-hydroxybenzoates (δ_C 128–133) are also depicted.

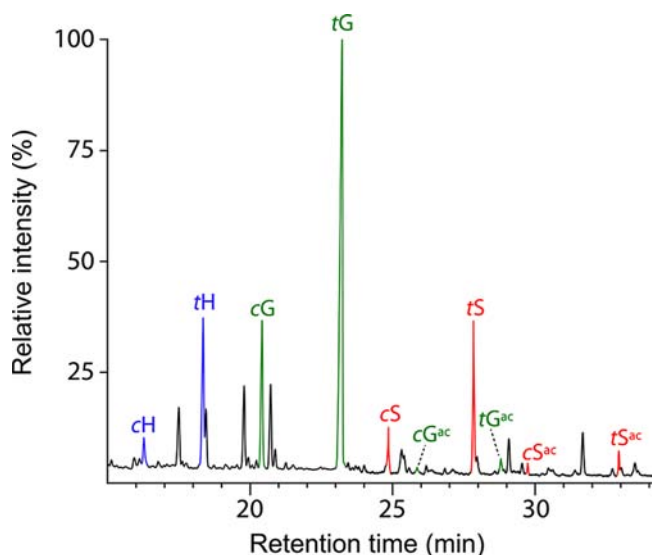


Figure 4. Total-ion chromatogram (TIC) from GC/MS of the DFRC' degradation products from the MWL isolated from coconut coir. cH, tH, cG, tG, cS, and tS are the normal *cis*- and *trans*-*p*-hydroxyphenyl, -coniferyl, and -sinapyl alcohols (as their dipropionylated derivatives). cGac, tGac, cSac, and tSac are the natively γ -acetylated *cis*- and *trans*-coniferyl and -sinapyl alcohols (as their phenol-propionylated derivatives).

Table 5. Yields of the Monomers ($\mu\text{mol/g}$ lignin) Released after Thioacidolysis

monomers	yields ($\mu\text{mol/g}$ lignin)
H	62
G	594
S	218
total	874
H/G ratio	0.10
S/G ratio	0.37

identified dimers. The most important dimeric β -5' structures (**15** and **17**) were composed of two G units, whereas GH (**11** and **14**) and SG (**19** and **24**) dimers were released in smaller amounts. These data are in agreement with the 2D NMR spectrum shown above that indicates that phenylcoumaran structures are the most important condensed structures in coir lignin.

Dimeric β -1' structures were also observed among the thioacidolysis dimers in coconut coir lignin. The existence of β -1' dimeric substructures in lignin has been a matter of controversy. Two β -1'-linked substructures, spirodienones, and phenylisochromans, were identified using 2D NMR in combination with DFRC.^{55,56} Phenylisochromans are resistant toward thioacidolysis; therefore, only spirodienones or opened forms of the β -1' units could be at the origin of the β -1' dimers observed here.²¹ In the MWL of coconut coir, β -1'

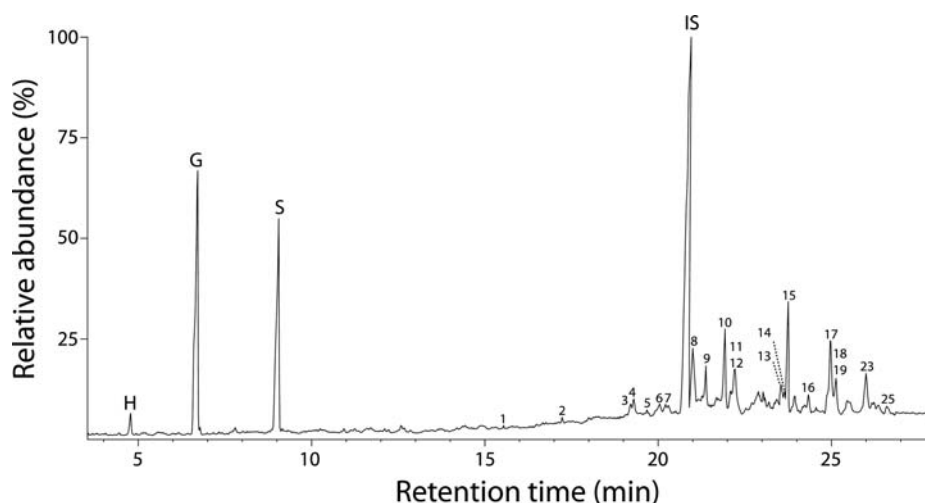


Figure 5. Chromatogram (GC-TIC) of the thioacidolysis degradation products (after Raney nickel desulfurization) released from coconut coir MWL, as trimethylsilyl derivatives. The numbers refer to the dimeric compounds listed in Table 6; the structures are shown in Figure 6.

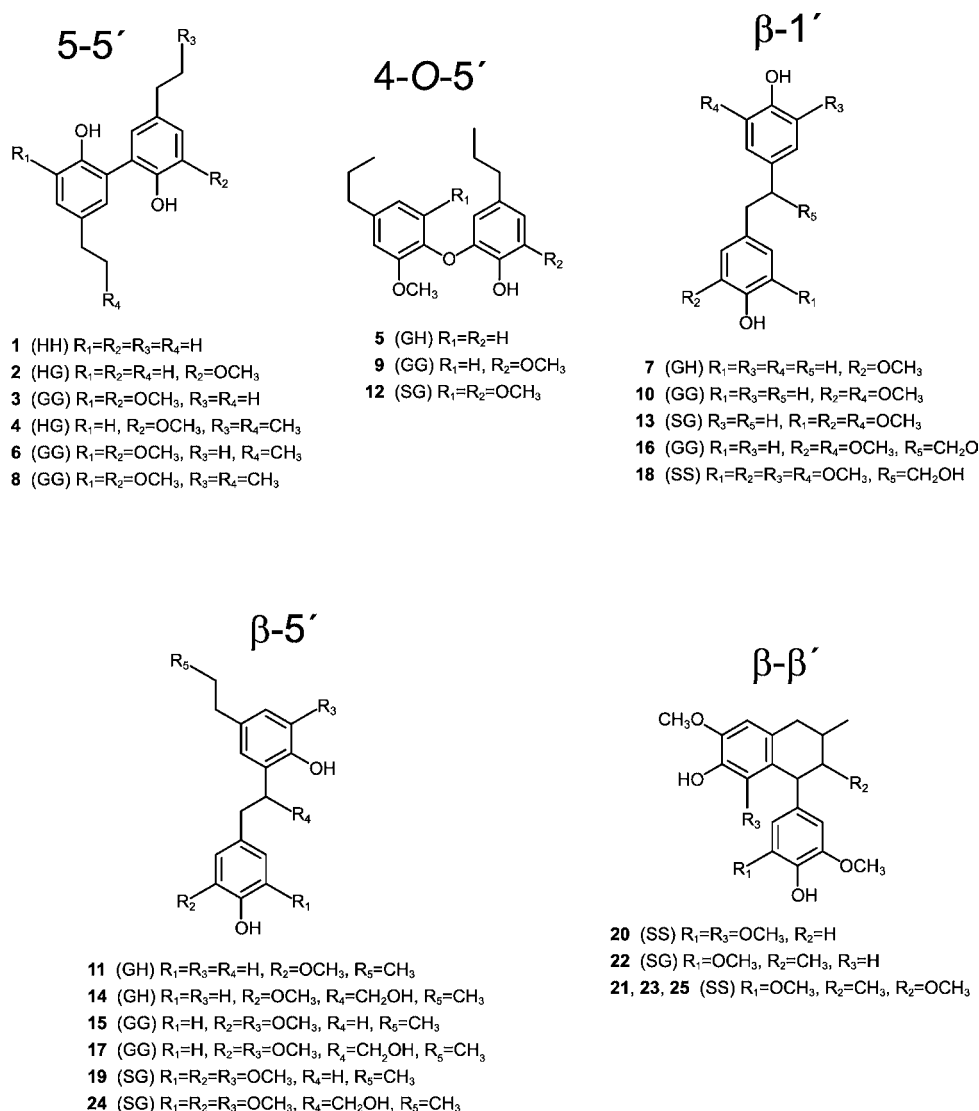


Figure 6. Structures of dimeric compounds obtained after thioacidolysis and Raney nickel desulfurization of the MWL isolated from coconut coir.

dimers represent the second most abundant dimers (22.1% of all dimeric structures). However, the relatively large amounts of

β -1' dimers observed upon thioacidolysis are not in agreement with the NMR spectra shown above, which indicated the

Table 6. Identification and Relative Molar Abundances of the Dimers Released after Thioacidolysis and Raney Nickel Desulfurization of the MWL from Coconut Coir^a

compd	linkage	MW	rel abundance (%)
1	5-5' (HH)	386	0.1
2	5-5' (HG)	416	0.4
3	5-5' (GG)	446	1.4
4	5-5' (HG)	444	2.0
5	4-O-5' (GH)	372	0.4
6	5-5' (GG)	460	1.5
7	β -1' (GH)	388	1.9
8	5-5' (GG)	474	10.6
9	4-O-5' (GG)	402	5.4
10	β -1' (GG)	418	13.6
11	β -5' (GH)	430	3.5
12	4-O-5' (SG)	432	1.7
13	β -1' (SG)	448	3.1
14	β -5' (GH)	532	1.3
15	β -5' (GG)	460	24.5
16	β -1' (GG)	520	1.8
17	β -5' (GG)	562	12.2
18	β -1' (SS)	478	1.7
19	β -5' (SG)	490	4.3
20	β - β' (SS)	518	0.6
21	β - β' (SS)	532	0.2
22	β - β' (SG)	502	0.7
23	β - β' (SS)	532	6.1
24	β -5' (SG)	592	0.2
25	β - β' (SS)	532	1.0

^aThe structures are depicted in Figure 6.

Table 7. Relative Molar Percentages of the Different Dimer Types (see Table 6 and Figure 6) Released after Thioacidolysis and Raney Nickel Desulfurization of Coconut Coir MWL

linkage type	units involved	percentage	total
5-5'	HH	0.1	15.9
	HG	2.4	
	GG	13.4	
4-O-5'	HG	0.4	7.4
	GG	5.4	
	GS	1.7	
β -1'	HG	1.9	22.1
	GG	15.5	
	GS	3.1	
	SS	1.7	
	HG	4.7	
β -5'	GG	36.6	45.8
	GS	4.5	
β - β'	GS	0.7	8.7
	SS	8.0	

absence (or the occurrence below the detection level of the NMR technique) of spirodienones in coir lignin. The apparent thioacidolysis dimer anomaly is largely explained by the difficulty of releasing other dimers that are therefore produced in low yields, and the special nature of the β -1'-units, the spirodienones, which are etherified only at one 'end' as dictated by their mode of formation;¹⁰ their release is therefore disproportionately high. As occurs with the β -5' structures, the most significant β -1' dimeric structure (10, but also 16)

was composed of two G units, whereas other β -1' dimeric structures, the GH (11), SG (13), and SS (18) dimers, were present in smaller amounts.

Dimers of 5-5' biphenyl structure were the third most abundant dimeric compounds in these lignin samples, accounting for 15.9% of all dimeric compounds. Dimers composed of two G units (3, 6, 8) were the most abundant, with smaller amounts of HH (1) and HG (2, 4) 5-5' dimeric structures. Dibenzodioxocins are considered to be the main biphenyl structures in lignin;⁵⁷ therefore, the 5-5' thioacidolysis dimers can be considered mostly as being dibenzodioxocin degradation products, although simple biphenyl structures have also been reported in lignin;²⁷ how readily dibenzodioxocins release 5-5-dimers upon thioacidolysis has not yet been well documented.

The remainder of the thioacidolysis dimeric compounds, such as β - β' and 4-O-5' dimers, was present in smaller amounts. Among these, it is interesting to note the low proportion of β - β' dimers observed after thioacidolysis (8.7% of total dimeric structures) compared to β -1' dimers that contrast with the relatively large amounts of β - β' resinol-type structures observed in the HSQC spectra (4% of all interunit linkages). This fact may indicate that β - β' resinol-type structures, particularly those with guaiacyl units, could be linked via other condensed bonds and, therefore, after thioacidolysis, they will form trimers or higher oligomers that cannot be detected. Thioacidolysis trimeric compounds formed by β - β' tetralin dimers linked by a 4-O-5' ether bond to a G lignin unit have been identified in the lignins of many plants, including herbaceous,⁴² hardwoods,^{21,58} and softwoods.⁵⁹ Nearly all (92%) the β - β' dimers released from coir lignin upon thioacidolysis were of the syringaresinol type (pinoresinol being absent and the G-S structure appearing only as a minor substructure) (Table 7). This is much more than expected from random coupling in a monolignol mixture with ~4-fold higher concentration of coniferyl alcohol than sinapyl alcohol (as indicated by the S/G ratio of this lignin). The almost exclusive occurrence in coir lignin of β - β' dimeric structures from syringaresinol, together with the lack of pinoresinol-derived structures, was also observed in the lignins of other angiosperms, such as eucalypt²¹ and jute;⁴² however, this is the first time that the almost exclusive occurrence of syringaresinol has been found to occur in a lignin highly depleted in S-units.

A Comment on Lignin Attributes and Plant Phylogeny. Although the aim of this paper is not on plant phylogeny, nor on chemotaxonomy, there are some potentially interesting observations regarding the coir's lignin structural units relating to coconut's place in the Arecales order, and the *Areaceae* (palm) family in the monocot class of plant phylogeny. As noted above, we find rather compelling evidence that the flavone triclin is incorporated into the coconut coir lignin, as we have noted recently in various grasses (Poales order, *Poaceae* family).¹² However, unlike in grasses, there is no significant *p*-coumarate component acylating the lignin. Like its palm (*Arecales* order, *Areaceae* or *Palmae* family) relatives (but as also noted in angiosperm/dicot lines, *Salix* and *Populus*, both in the *Salicaceae* family), and unlike in grasses, the lignins are acylated by *p*-hydroxybenzoate.^{18,19,32,43-49} Other groups are currently examining *p*-coumarate involvement across various monocots;⁶⁰ we suggest that tracking the distribution of triclin and delineating the *p*-coumarate vs *p*-hydroxybenzoate distribution may also prove interesting.

In conclusion, we have performed the first detailed structural characterization of the abundant lignin in coconut coir. The study, by a range of powerful analytical methods, indicated that it is an H:G:S lignin with a strong predominance of G-lignin units (S/G 0.23). Two-dimensional NMR indicated that the main linkages present in this lignin are β -O-4' alkyl aryl ethers, followed by phenylcoumarans, resinols, and small amounts of dibenzodioxocins, together with cinnamyl alcohol and cinnamaldehyde end-groups. Two-dimensional NMR also indicated that the lignin of coconut coir is partially acylated (11% of all side chains), and exclusively at the γ -OH of the side chain, with *p*-hydroxybenzoates. DFRC analyses indicated that the γ -carbon is additionally acylated with acetates, although to a lower extent. Despite coir lignins being highly enriched in G-units, thioacidolysis degradation indicated that β - β' resinol structures are mostly of the syringaresinol type, pinosresinol units being completely absent. Finally, the tricin units recently identified in grass lignins are also present, at a fairly low level here, suggesting that they might be a feature of monocot lignins. These data, highlighting the similarities and differences between coir lignin and lignins from other biomass sources, will help to optimize the use of this coir resource for products and biomaterials.

AUTHOR INFORMATION

Corresponding Author

*Tel: +34-95-4624711; fax: +34-95-4624002; e-mail: jrencoret@irnase.csic.es.

Funding

This study has been funded by the Spanish project AGL2011-25379, the CSIC project 201040E075, and the EU-project LIGNODECO (KBBE-244362). Dr. Jorge Rencoret thanks the CSIC for a JAE-DOC contract of the program "Junta para la Ampliación de Estudios" cofinanced by Fondo Social Europeo (FSE). John Ralph was funded by the DOE Great Lakes Bioenergy Research Center (DOE Office of Science BER DE-FC02-07ER64494).

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We thank José M. Gras and Gerardo Artal (CELESA, Spain) for providing the coconut coir. Yuki Tobimatsu (Univ. Wisconsin, Madison) is acknowledged for performing the GPC analyses, and Fachuang Lu and Hoon Kim (Univ. Wisconsin, Madison) for their valuable technical advice. We also thank Dr. Manuel Angulo (CITIUS, Universidad de Sevilla) for performing the NMR analyses.

REFERENCES

- (1) Wang, W.; Huang, G. Characterisation and utilization of natural coconut fibres composites. *Mater. Des.* **2009**, *30*, 2741–2744.
- (2) Kirby, R. H. *Vegetable Fibers, Botany, Cultivation and Utilization*; Leonard Hill Ltd: London, UK, 1963.
- (3) Abdul Khalil, H. P. S.; Siti Alwani, M.; Mohd Omar, A. K. Chemical composition, anatomy, lignin distribution, and cell wall structure of Malaysian plant waste fibers. *BioResources* **2006**, *1*, 13.
- (4) Malherbe, S.; Cloete, T. E. Lignocellulose biodegradation: Fundamentals and applications. *Rev. Environ. Sci. Biotechnol.* **2002**, *1*, 105–114.
- (5) Ragauskas, A. J.; Williams, C. K.; Davison, B. H.; Britovsek, G.; Cairney, J.; Eckert, C. A.; Frederick, W. J.; Hallett, J. P.; Leak, D. J.; Liotta, C. L.; Mielenz, J. R.; Murphy, R.; Templer, R.; Tschaplinski, T.

The path forward for biofuels and biomaterials. *Science* **2006**, *311*, 484–489.

(6) Somerville, C.; Youngs, H.; Taylor, C.; Davis, S. C.; Long, S. P. Feedstocks for lignocellulosic biofuels. *Science* **2010**, *329*, 790–792.

(7) Sarkar, N.; Ghosh, S. K.; Bannerjee, S.; Aikat, K. Bioethanol production from agricultural wastes: An overview. *Renew. Energy* **2012**, *37*, 19–27.

(8) Simmons, B. A.; Loqué, D.; Ralph, J. Advances in modifying lignin for enhanced biofuel production. *Curr. Opin. Plant Biol.* **2010**, *13*, 313–320.

(9) Abramson, M.; Shoseyov, O.; Shani, Z. Plant cell wall reconstruction toward improved lignocellulosic production and processability. *Plant Sci.* **2010**, *178*, 61–72.

(10) Ralph, J.; Lundquist, K.; Brunow, G.; Lu, F.; Kim, H.; Schatz, P. F.; Marita, J. M.; Hatfield, R. D.; Ralph, S. A.; Christensen, J. H.; Boerjan, W. Lignins: natural polymers from oxidative coupling of 4-hydroxyphenylpropanoids. *Phytochem. Rev.* **2004**, *3*, 29–60.

(11) del Río, J. C.; Prinsen, P.; Rencoret, J.; Nieto, L.; Jiménez-Barbero, J.; Ralph, J.; Martínez, Á. T.; Gutiérrez, A. Structural characterization of the lignin in the cortex and pith of elephant grass (*Pennisetum purpureum*) Stems. *J. Agric. Food Chem.* **2012**, *60*, 3619–3634.

(12) del Río, J. C.; Rencoret, J.; Prinsen, P.; Martínez, Á. T.; Ralph, J.; Gutiérrez, A. Structural characterization of wheat straw lignin as revealed by analytical pyrolysis, 2D-NMR, and reductive cleavage methods. *J. Agric. Food Chem.* **2012**, *60*, 5922–5935.

(13) Björkman, A. Studies on finely divided wood. Part I. Extraction of lignin with neutral solvents. *Sven. Papperstidn.* **1956**, *59*, 477–485.

(14) Fujimoto, A.; Matsumoto, Y.; Chang, H. M.; Meshitsuka, G. Quantitative evaluation of milling effects on lignin structure during the isolation process of milled wood lignin. *J. Wood Sci.* **2005**, *51*, 89–91.

(15) del Río, J. C.; Gutiérrez, A.; Rodríguez, I. M.; Ibarra, D.; Martínez, Á. T. Composition of non-woody plant lignins and cinnamic acids by Py-GC/MS, Py/TMAH and FT-IR. *J. Anal. Appl. Pyrol.* **2007**, *79*, 39–46.

(16) Ralph, J.; Hatfield, R. D. Pyrolysis-GC-MS characterization of forage materials. *J. Agric. Food Chem.* **1991**, *39*, 1426–1437.

(17) Faix, O.; Meier, D.; Fortmann, I. Thermal degradation products of wood. Gas chromatographic separation and mass spectrometric characterization of monomeric lignin-derived products. *Holz Roh-Werkst.* **1990**, *48*, 281–289.

(18) Ralph, J. Hydroxycinnamates in Lignification. *Phytochem. Revs.* **2010**, *9*, 65–83.

(19) Kuroda, K.; Ozawa, T.; Ueno, T. Characterization of sago palm (*Metroxylon sagu* Rottb.) lignin by analytical pyrolysis. *J. Agric. Food Chem.* **2001**, *49*, 1840–1847.

(20) del Río, J. C.; Martin, F.; Gonzalez-Vila, F. J. Thermally assisted hydrolysis and alkylation as a novel pyrolytic approach for the structural characterization of natural biopolymers and geomacromolecules. *Trends Anal. Chem.* **1996**, *15*, 70–79.

(21) Rencoret, J.; Marques, G.; Gutiérrez, A.; Ibarra, D.; Li, J.; Gellerstedt, G.; Santos, J. I.; Jimenez-Barbero, J.; Martinez, A. T.; del Río, J. C. Structural characterization of milled wood lignins from different eucalypt species. *Holzforchung* **2008**, *62*, 514–526.

(22) Capanema, E. A.; Balakshin, M. Y.; Kadla, J. F. A comprehensive approach for quantitative lignin characterization by NMR spectroscopy. *J. Agric. Food Chem.* **2004**, *52*, 1850–1860.

(23) Capanema, E. A.; Balakshin, M. Y.; Kadla, J. F. Quantitative characterization of a hardwood milled wood lignin by nuclear magnetic resonance spectroscopy. *J. Agric. Food Chem.* **2005**, *53*, 9639–9649.

(24) Rencoret, J.; Gutiérrez, A.; Nieto, L.; Jiménez-Barbero, J.; Faulds, C. B.; Kim, H.; Ralph, J.; Martínez, Á. T.; del Río, J. C. Lignin composition and structure in young versus adult *Eucalyptus globulus* plants. *Plant Physiol.* **2011**, *155*, 667–682.

(25) Ralph, S. A.; Ralph, J.; Landucci, L. *NMR Database of Lignin and Cell Wall Model Compounds*; US Forest Prod. Lab.: Madison, WI, 2004.

(26) Balakshin, M. Y.; Capanema, E. A.; Chen, C. L.; Gracz, H. S. Elucidation of the structures of residual and dissolved pine kraft lignins

using an HMQC NMR technique. *J. Agric. Food Chem.* **2003**, *51*, 6116–6127.

(27) Balakshin, M. Y.; Capanema, E. A.; Goldfarb, B.; Frampton, J.; Kadla, J. F. NMR studies on Fraser fir *Abies fraseri* (Pursh) Poir. lignins. *Holzforschung* **2005**, *59*, 488–496.

(28) Ibarra, D.; Chavez, M. I.; Rencoret, J.; del Río, J. C.; Gutierrez, A.; Romero, J.; Camarero, S.; Martinez, M. J.; Jimenez-Barbero, J.; Martinez, A. T. Structural modification of eucalypt pulp lignin in a totally chlorine-free bleaching sequence including a laccase-mediator stage. *Holzforschung* **2007**, *61*, 634–646.

(29) Ibarra, D.; Chavez, M. I.; Rencoret, J.; del Río, J. C.; Gutierrez, A.; Romero, J.; Camarero, S.; Martinez, M. J.; Jimenez-Barbero, J.; Martinez, A. T. Lignin modification during *Eucalyptus globulus* kraft pulping followed by totally chlorine-free bleaching: A two-dimensional nuclear magnetic resonance, Fourier transform infrared, and pyrolysis-gas chromatography/mass spectrometry study. *J. Agric. Food Chem.* **2007**, *55*, 3477–3490.

(30) Ralph, J.; Marita, J. M.; Ralph, S. A.; Hatfield, R. D.; Lu, F.; Ede, R. M.; Peng, J.; Quideau, S.; Helm, R. F.; Grabber, J. H.; Kim, H.; Jimenez-Monteon, G.; Zhang, Y.; Jung, H.-J. G.; Landucci, L. L.; MacKay, J. J.; Sederoff, R. R.; Chapple, C.; Boudet, A. M. Solution-state NMR of lignins. In *Advances in Lignocellulosics Characterization*; Argyropoulos, D. S., Ed.; TAPPI Press: Atlanta, GA, 1999; pp 55–108.

(31) Martinez, A. T.; Rencoret, J.; Marques, G.; Gutierrez, A.; Ibarra, D.; Jimenez-Barbero, J.; del Río, J. C. Monolignol acylation and lignin structure in some nonwoody plants: A 2D NMR study. *Phytochemistry* **2008**, *69*, 2831–2843.

(32) Ralph, J.; Landucci, L. L. NMR of Lignins. In *Lignin and Lignans; Advances in Chemistry*; Heitner, C.; Dimmel, D. R.; Schmidt, J. A., Eds.; CRC Press (Taylor & Francis Group): Boca Raton, FL, 2010; pp 137–234.

(33) Rolando, C.; Monties, B.; Lapiere, C. Thioacidolysis. In *Methods in Lignin Chemistry*; Dence, C. W.; Lin, S. Y., Eds. Springer-Verlag: Berlin, 1992; pp 334–349.

(34) Lapiere, C.; Pollet, B.; Monties, B.; Rolando, C. Thioacidolysis of spruce lignin: gas chromatography-mass spectroscopy analysis of the main dimers recovered after Raney nickel desulfurization. *Holzforschung* **1991**, *45*, 61–68.

(35) Lapiere, C.; Pollet, B.; Rolando, C. New insights into the molecular architecture of hardwood lignins by chemical degradative methods. *Res. Chem. Intermed.* **1995**, *21*, 397–412.

(36) Lu, F.; Ralph, J. DFRC method for lignin analysis. 1. New method for β -aryl ether cleavage: Lignin model studies. *J. Agric. Food Chem.* **1997**, *45*, 4655–4660.

(37) Lu, F.; Ralph, J. Derivatization followed by reductive cleavage (DFRC method), a new method for lignin analysis: protocol for analysis of DFRC monomers. *J. Agric. Food Chem.* **1997**, *45*, 2590–2592.

(38) Lu, F.; Ralph, J. The DFRC method for lignin analysis. 2. Monomers from isolated lignins. *J. Agric. Food Chem.* **1998**, *46*, 547–552.

(39) Ralph, J.; Lu, F. The DFRC method for lignin analysis. 6. A simple modification for identifying natural acetates on lignins. *J. Agric. Food Chem.* **1998**, *46*, 4616–4619.

(40) Tappi. *Tappi Test Methods 2004–2005*; Tappi Press: Norcross, GA, 2004.

(41) Saito, K.; Fukushima, K. Distribution of lignin interunit bonds in the differentiating xylem of compression and normal woods of *Pinus thunbergii*. *J. Wood Sci.* **2005**, *51*, 246–251.

(42) del Río, J. C.; Rencoret, J.; Marques, G.; Li, J. B.; Gellerstedt, G.; Jimenez-Barbero, J.; Martinez, A. T.; Gutierrez, A. Structural characterization of the lignin from jute (*Corchorus capsularis*) fibers. *J. Agric. Food Chem.* **2009**, *57*, 10271–10281.

(43) del Río, J. C.; Rencoret, J.; Gutiérrez, A.; Nieto, L.; Jiménez-Barbero, J.; Martínez, A. T. Structural characterization of guaiacyl-rich lignins in flax (*Linum usitatissimum*) fibers and shives. *J. Agric. Food Chem.* **2011**, *59*, 11088–11099.

(44) Baumberger, S.; Abacherli, A.; Fasching, M.; Gellerstedt, G.; Gosselink, R.; Hortling, B.; Li, J.; Saake, B.; de Jong, E. Molar mass

determination of lignins by size-exclusion chromatography: towards standardisation of the method. *Holzforschung* **2007**, *61*, 459–468.

(45) Nakano, J.; Ishizu, A.; Migita, N. Studies on lignin. XXXII. Ester groups of lignin. *Tappi* **1961**, *44*, 30–32.

(46) Landucci, L. L.; Deka, G. C.; Roy, D. N. A ^{13}C NMR study of milled wood lignins from hybrid *Salix* clones. *Holzforschung* **1992**, *46*, 505–511.

(47) Sun, R. C.; Fang, J. M.; Tomkinson, J. Fractional isolation and structural characterization of lignins from oil palm trunk and empty fruit bunch fibres. *J. Wood Chem. Technol.* **1999**, *19*, 335–356.

(48) Meyermans, H.; Morreel, K.; Lapiere, C.; Pollet, B.; De Bruyn, A.; Busson, R.; Herdewijn, P.; Devreese, B.; Van Beeumen, J.; Marita, J. M.; Ralph, J.; Chen, C.; Burggraef, B.; Van Montagu, M.; Messens, E.; Boerjan, W. Modifications in lignin and accumulation of phenolic glucosides in poplar xylem upon down-regulation of caffeoyl-coenzyme A O-methyltransferase, an enzyme involved in lignin biosynthesis. *J. Biol. Chem.* **2000**, *275*, 36899–36909.

(49) Lu, F.; Ralph, J.; Morreel, K.; Messens, E.; Boerjan, W. Preparation and relevance of a cross-coupling product between sinapyl alcohol and sinapyl *p*-hydroxybenzoate. *Org. Biomol. Chem.* **2004**, *2*, 2888–2890.

(50) Ralph, J. An unusual lignin from kenaf. *J. Nat. Prod.* **1996**, *59*, 341–342.

(51) del Río, J. C.; Marques, G.; Rencoret, J.; Martinez, A. T.; Gutierrez, A. Occurrence of naturally acetylated lignin units. *J. Agric. Food Chem.* **2007**, *55*, 5461–5468.

(52) del Río, J. C.; Rencoret, J.; Marques, G.; Gutierrez, A.; Ibarra, D.; Santos, J. I.; Jimenez-Barbero, J.; Zhang, L. M.; Martinez, A. T. Highly acylated (acetylated and/or *p*-coumaroylated) native lignins from diverse herbaceous plants. *J. Agric. Food Chem.* **2008**, *56*, 9525–9534.

(53) Lu, F.; Ralph, J. Preliminary evidence for sinapyl acetate as a lignin monomer in kenaf. *Chem. Commun.* **2002**, 90–91.

(54) Lu, F.; Ralph, J. Novel tetrahydrofuran structures derived from β - β -coupling reactions involving sinapyl acetate in kenaf lignins. *Org. Biomol. Chem.* **2008**, *6*, 3681–3694.

(55) Ralph, J.; Peng, J.; Lu, F. Isochroman structures in lignin: A new β -1 pathway. *Tetrahedron Lett.* **1998**, *39*, 4963–4964.

(56) Zhang, L.; Gellerstedt, G. NMR observation of a new lignin structure, a spiro-dienone. *Chem. Commun.* **2001**, 2744–2745.

(57) Karhunen, P.; Rummakko, P.; Sipilä, J.; Brunow, G.; Kilpeläinen, I. Dibenzodioxocins; a novel type of linkage in softwood lignins. *Tetrahedron Lett.* **1995**, *36*, 169–170.

(58) Önnnerud, H.; Gellerstedt, G. Inhomogeneities in the chemical structure of hardwood lignins. *Holzforschung* **2003**, *57*, 255–265.

(59) Önnnerud, H. Lignin structures in normal and compression wood. Evaluation by thioacidolysis using ethanethiol and methanethiol. *Holzforschung* **2003**, *57*, 377–384.

(60) Harris, P. J. Diversity in plant cell walls. In *Plant Diversity and Evolution: Genotypic and Phenotypic Variation in Higher Plants*; Henry, R. J., Ed.; CAB International Publishing: Wallingford, UK, 2005; pp 201–227.