

Development of an Easily Deinkable Copy Toner Using Soy-Based Copolyamides

XIAO-DONG FAN,¹ YULIN DENG,¹ JOHN WATERHOUSE,¹ PETER PFROMM,¹ WALLACE W. CARR²

¹ Institute of Paper Science and Technology, 500 10th Street, N.W., Atlanta, Georgia 30318

² Georgia Institute of Technology, School of Textile and Fiber Engineering, Atlanta, Georgia 30332

Received 26 January 1999; accepted 15 May 1999

ABSTRACT: To develop an easily deinkable toner for office copiers and laser printers, a series of homo- and copolyamide toner resins were synthesized via condensation polymerization of a soy-based dimer acid, 1,4-phenylenediamine, and L-tyrosine (an α -amino acid). The thermal properties of the resins were examined using differential scanning calorimetry (DSC) and thermal gravimetric analysis (TGA). It was found that the glass transition temperature (T_g), melting point (T_m), decomposition temperature (T_d), and crystallinity of the copolyamides were remarkably decreased as the content of L-tyrosine was increased. By using both homo- and copolyamides as binders, respectively, two dual-component toners were developed. The triboelectrical charge, particle size, and particle-size distribution of these toners were examined. The printing trials demonstrated that the images of the soy-based toners are similar to those of commercially available toners. However, because of the low crystallinity and high water-uptake ability of the amino acid-containing polyamide, the copolymer is swellable in an alkaline solution. Initial results from flotation deinking suggest that the amino acid-containing toners are more easily deinked, likely due to their high swellability. © 1999 John Wiley & Sons, Inc. *J Appl Polym Sci* 74: 1563–1570, 1999

Key words: deinking; polyamide; soy; toner

INTRODUCTION

Wastepaper recycling is of growing importance, both for better utilization of the natural resources of wood and for reduction of the amount of solid waste. Legislation requiring specific percentages of recycled fiber in paper products is forcing paper manufacturers to utilize waste streams that were previously sent to landfills. However, it has been found that office wastepaper printed with a polymer-based toner is one of the most difficult paper grades to deink.^{1,2} Although many new techniques^{3–5} have been developed for deinking elec-

trostatically printed papers, the relative high cost and low deinking efficiency are still problems to be resolved. Therefore, a toner resin that can be easily deinked is desirable for paper recycling.

Different petroleum-based polymers, such as polystyrene, polyester, polyamide, polyethylene, poly(ethylene-co-vinyl acetate), and poly(styrene-co-butyl methacrylate), have been widely used as toner binders.^{6–10} To develop a high-performing toner, the polymer binder must have suitable molecular weight, glass transition temperature (T_g), melting viscosity, and electrical properties.¹¹ The common toners have a T_g ranging from 50 to 65°C, and a fusing temperature of approximately 60–120°C above their T_g . The toner's melt viscosity is dependent on various parameters such as the copolymer ratio, molecular weight, and

Correspondence to: Y. Deng.




Contract grant sponsor: Ohio Soybean Council.

Journal of Applied Polymer Science, Vol. 74, 1563–1570 (1999)

© 1999 John Wiley & Sons, Inc.

CCC 0021-8995/99/061563-08

Table I Characteristics of the Monomers

Monomer	Acronym	Structure	T_m (°C)
Dimer acid ^a	D		Liquid at room temperature
1,4-Phenylene-diamine (99%)	P		143–145
L-Tyrosine	T		135

^a D: Dimer acid (Empol 1016) contains 97% dimer, 2% trimer, and 1% monomer acids.

branching and crosslinking and can directly impact the xerographic performance. Although many different petroleum-based polymers have been used as toner binders, little work has been done to use a natural product as a raw material for toner production. Compared to currently used petroleum-based toner resins, soy-based resins possess some advantages: The materials are renewable, nontoxic, of potentially lower cost, and provide strong adhesion to most paper surfaces. In this study, soy-based dimer acids were chosen as a raw material for the preparation of toner resins.

In a typical xerographic process, the toner particles are melted and fused into the paper matrix at high temperature and pressure. Because the toner resin strongly anchors with the fibers during cooling, it is difficult to remove the toner particles from the fibers,¹² resulting in poor fiber-ink separation and low deinking efficiency of the wastepapers. To improve the deinking efficiency of toner-printed paper, one of the possible methods is to produce a swellable toner. Therefore, it might be easier to remove the toner particles from the wood fiber surface due to the swelling of the toner particles, which might reduce the bonding strength between the toner and fibers during repulping of the wastepaper.

Recently, Arvanitoyannis et al.^{13–15} prepared a series of amino acid-containing polyamides. They reported that these polyamides are biodegradable. Because amino acids contain both amine and acid groups, incorporation of amino acid into a polymer backbone may significantly impact the polymer structure, the crystallinity, and the swellability. Although the incorporation of amino

acids into polyamides has been reported,^{13–15} the copolymerization and the characterization of an amino acid with soy-based polyamides have not been reported in the literature. In this study, soy-based polyamides with and without an α -amino acid (L-tyrosine) were synthesized. The thermal and swelling behavior of both homo- and copolyamides were examined. The compounding and the processing of a dual-component toner using these polyamides as binders were explored. The printing and flotation deinking trials were also carried out using toners produced in our laboratories.

EXPERIMENTAL

Materials

The dimer acid used in the synthesis was supplied by the Emery Group of the Henkel Corp. (Cincinnati, OH). Empol 1016 dimer acid is a yellowish viscous liquid at room temperature with the ratio of dimer to trimer to monomer at 97 : 2 : 1. L-tyrosine (1-3-[4-hydroxyphenyl]alanine) was obtained from Sigma (St. Louis, MO) and 1,4-phenylenediamine was purchased from Aldrich (Milwaukee, WI). Both were used as received without further purification. Their acronyms, reported purity, molecular structure, and melting points are listed in Table I.

Polymer and Copolymer Synthesis

Copolymers were synthesized by condensation polymerization. A typical example of polymerization

for a copolymer with 12.7 wt % tyrosine (based on total weight of starting monomers) is described here. Fifty grams of the dimer acid (equivalent to 0.174 mol of acid groups) was charged into a 250-mL three-necked round-bottom flask equipped with a mechanical stirrer, a thermometer, and a nitrogen inlet. The monomer was first heated to 80°C under a nitrogen atmosphere and vigorous stir; then, 9.6 g of 1,4-phenylenediamine (equivalent to the total acid groups) and 8.7 g of L-tyrosine were added. The reactants were gradually heated to 250°C over 3 h and kept at this temperature for another 5 h, being stirred vigorously and then the system was allowed to cool down to room temperature. The next day the reactants were heated again to 250°C and subjected to a vacuum of approximately 2 mmHg for 4 h. The product was then discharged from the flask.

DSC and TGA Analysis

DSC measurements were performed on a SEICO DSC equipped with a thermal analysis station. TGA measurements were carried out on a SEICO TGA. Both DSC and TGA measurements were performed under nitrogen at a 20 and 10°C/min heating rate, respectively.

Swelling Test

Water uptake of the samples was determined at different pH values at 70°C to study the polymer's swelling behavior. Dry polymer film samples with a fixed surface area and thickness ($15 \times 10 \times 0.05$ mm) were carefully weighed and put into a test tube; then, 15 mL water at the required pH was added. The test tube was put into an isothermal bath at a fixed temperature for 24 h. The sample was then taken out and washed with distilled water. Before weighing the sample, the film surface was carefully wiped with a paper towel to remove free water. The water uptake was then calculated as the weight difference before and after water immersion.

Toner Production

A homopolyamide (D-P) and a copolyamide (D-P-T) made by adding 7.7 wt % of L-tyrosine to the monomers were used in the toner production. The resin was first blended with carbon black as the pigment (Regal 330, CABOT Corp.) and a charge-controlling agent (Copy Blue PR, Hoechst High Chem Pigment) in a two-roll mill at 80°C for 30 min. A homogeneous dispersion of pigment in the

polymer was observed. The polymer was then ground to the required particle size of about 10 μm , using an Air-Jet Mill (Toner Research Services) at a feed rate of 3 g/min and air pressure of 100 psi. After pulverization, the dry toner was subjected to classification to remove particles less than 5 and greater than 15 μm using a CCE Model 100 Classifier.

Toner Characterization

A multichannel particle counter, Model PCA II (Coulter Electronics Inc.), was employed to measure the particle size and particle-size distribution. In an effort to minimize coagulation of the toner particles, 10 mL of a soap solution (2 g/L) was added to the system before measuring. The triboelectric charge value of the toner with a carrier (Type 29 Carrier Power, Vertex Image Products Inc.) was measured using the blow-off technique with an apparatus built at the Georgia Institute of Technology. This technique measures the charge per mass of the developer in micro-Coulombs/gram.

Flotation Deinking

The pulp suspension used for the flotation deinking was made from bond paper printed using the two soy-based toners with a fixed pattern of letter X to control the amount of toner deposited. The papers were pulped at pH of 7.0 and 10.8, respectively, with a consistency of 10.5% without adding other chemicals. Flotation deinking was carried out using a laboratory flotation cell. The deinking cell was made from a polyacrylate pipe with a height of 80 cm and a diameter of 10 cm. Nitrogen gas was blown into the pulp suspension at a rate of 14 ± 0.075 SLPM (standard liters per minute) through an air filter (pore size 50 μm) at the bottom of the flotation cell for all experiments. The flotation time was 10 min. The air-flow rate was measured with an Omega FMA 1700/1800 flowmeter. The consistency of the pulp used in the flotation was 0.5%. A nonionic surfactant, TX-100, was used as a frothing agent.

Brightness Measurement

The handsheets for the brightness analysis (deinking efficiency) of deinked pulp were made on a 15-cm Büchner funnel according to TAPPI Standard Method T218 om-91. The brightness of a handsheet was measured using a UV-vis spec-

Table II Characteristics of the Polymers

Copolymer	Structure
D-P (homopolyamide of dimer acid and phenylenediamine)	
D-P-T (based on dimer acid 1016, phenylenediamine and tyrosine)	

trophotometer (Shimadzu UV-160A) using the TAPPI Standard Method T452 om-92.

RESULTS AND DISCUSSION

Physical Properties of Homo- and Copolyamides

The synthesis of polyamides using a dimer acid and a diamine is a typical condensation polymerization, which usually takes place through the elimination of water molecules at certain reaction conditions. The molecular weight of dimer acid-based polyamides can be affected by the reaction time, temperature, monomer ratio, catalyst, etc. If other parameters remain constant, the reaction temperature, which is directly related to the rate of distillation of the condensing water, will significantly affect both the polymerization rate and the molecular weight. The reaction conditions as well as their effect on the homopolyamide's physical properties were given in a previous publication.¹⁶ The acronyms and molecular structures of soy-based polyamides that were used here for toner production and printing are given in Table II. The DSC and TGA measurements indicate that this soy-based polyamide has a glass transition temperature of 68°C, a melting temperature of 127°C, and a decomposition temperature of 397°C. These values suggest that it is a suitable candidate for a toner resin.¹¹

It is well known that incorporation of α -amino acids, such as glutamic acid and lysine, in polymers can produce functional polymers and enhance the polymer's water sensitivity and biodegradability.¹³⁻¹⁵ To modify the soy-based polyamide's swelling and biodegradation properties, and to thereby create an easily deinkable toner, a

series of soy-based copolyamide resins was synthesized by incorporating different amounts of L-tyrosine into the homopolymer. Because amino acid has both amine and acid groups, it can be easily copolymerized with dimer acid and diamine at a high temperature. The thermal properties of copolyamides with different weight percentages of tyrosine are shown in Figure 1 and Table III. Evidently, by increasing the content of tyrosine, the copolymer's glass transition temperature (T_g), melting temperature (T_m), enthalpy of fusion (ΔH), and decomposition temperature (T_d) are gradually decreased. The results suggest that tyrosine can copolymerize with soybean dimer acid and phenylenediamine.

The incorporation of tyrosine segments into the dimer acid-phenylenediamine (D-P) matrix will interrupt the original regular chain structure of D-P. As a result, the crystallinity decreased, which led to lower T_g , T_m , ΔH , and T_d . Interestingly, when the tyrosine content increased to over 20 wt %, the copolymer's melting peak completely disappeared (Fig. 1) and both T_g and T_d shifted to lower temperatures. The result may imply that when over 20 wt % of tyrosine was incorporated in the copolymer, the crystallization process could be greatly inhibited by introducing a large number of heterogeneous segments.¹⁷ Unfortunately, the T_g of the copolymer with 20 wt % of tyrosine is too low, resulting in a soft and tacky polymer at room temperature. Therefore, it cannot be used as a toner resin.¹¹

Swelling Behavior of Homo- and Copolyamides

One of the methods to produce an easily deinkable toner for copiers may be to use a water-swelling polymer binder in the toner formula-

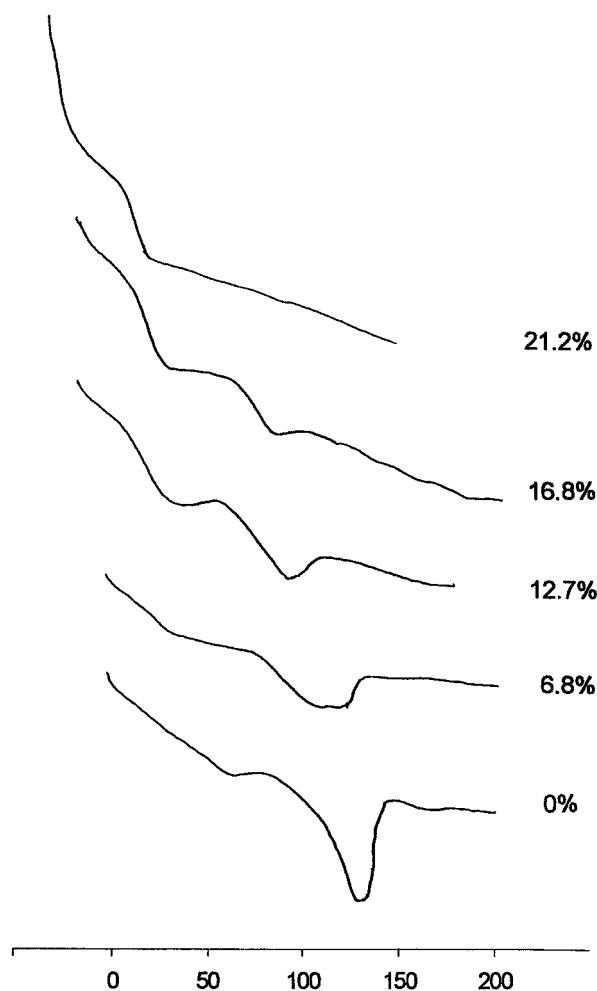


Figure 1 DSC diagrams for D-P and D-P-T with varying L-tyrosine content.

tion. The swelling properties of the polymer samples in the aqueous solution measured over a wide range of pH values are shown in Figure 2. Evidently, the values of water uptake of the D-P homopolymer is almost unchanged from pH 2 to

12 at 70°C for 24 h. The poor swelling properties of the homopolyamide are closely related to the molecular chain structure and crystallinity. From Table I, it can be seen that the soybean dimer acid contains a cyclic structure with several long flexible aliphatic branches.

Compared to phenylenediamine, the structure of soybean dimer acids is more complicated. The average molecular weight of the soybean dimer acid is about 570, which is much larger than that of phenylenediamine (108). When both monomers react stoichiometrically to form a polymer, the mass ratio of amide in the polymer should be relatively low. Thus, the characteristics of the molecular chain structure of the homopolyamide could be considered as containing mostly hydrophobic segments with a small amount of amide linkages, which possess certain hydrophilic properties. On the other hand, in our previous study,¹⁶ it was demonstrated that soy-based aromatic polyamides (D-P) are typical semicrystalline polymers with a relatively high crystallinity, better mechanical performance, and excellent thermal stability. As a result, its chain character and physical properties could effectively resist the penetration of water molecules into its amorphous matrix even in a strong alkaline, or acid solution, or a relatively high temperature environment.

However, compared to the homopolyamide, the swellability of copolyamides is improved remarkably by increasing the content of amino acid. As can be seen from Figure 2, the increase in the swellability of the copolymers is a function of the amount of amino acid incorporated, that is, the more amino acid in a copolymer, the more water uptake can be obtained. The results are attributed to the enlarged amorphous phase due to the lowered crystallinity of copolyamides (Fig. 1) and the presence of more hydrophilic functional

Table III Physical Properties of Soy-based Polyamides

Copolymers with Different Weight Percent of Tyrosine (%)	Glass Transition Temperature (°C)	Melting Temperature (°C)	Enthalpy of Fusion (J/g)	Decomposition Temperature (°C)
0.00	68	127	16.7	397
6.80	30	113	13.1	393
12.70	29	93	7.5	374
16.80	26	87	—	361
21.20	21	—	—	361

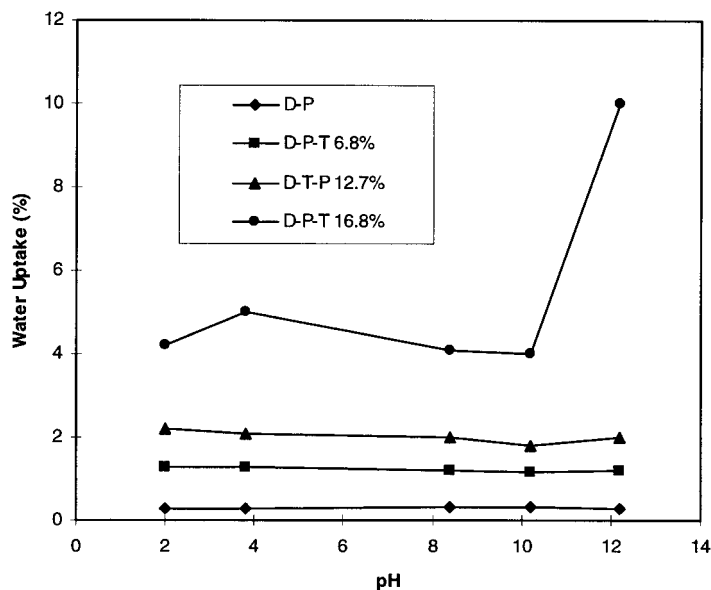


Figure 2 Water-uptake percentage for D-P and D-P-T L-tyrosine content versus pH at 70°C for 24 h.

groups of amino acid in the polymer matrix. Figure 2 also shows that, for the sample containing 16.8% D-P-T, there is a great increase in the amount of water uptake at pH 12 and 70°C. The result may imply that higher levels of amino content in copolymers could lead to easier attack by strong alkaline solutions, resulting in enhanced swelling.

Toner Production and Testing

Two dual-component toners produced from D-P and D-P-T (7.7%) are listed in Table IV. The physical properties of the toners indicate that both D-P and D-P-T (7.7%) can be successfully compounded and ground into the required particle size, that is, an average particle size around 10 μm and a particle-size distribution around 90% > 5 microns. Compared with the Colorocs Co.'s

toner, soy-based polyamide toners have the potential to achieve a similar print quality to that produced by commercial toners. It should be noted that the particle size and its distribution are two critical properties that can greatly affect resolution, imaging, and printing background during copying. Usually, larger particles decrease the resolution of the image, and smaller particles may result in smearing of the image, increasing the gray background, and even damaging the print. In general, the toner particle size required for a commercial toner is around 10 μm .¹¹

The particle size and particle-size distribution depend on many factors, such as the T_g of the polymer binders and the processing conditions during production. As mentioned previously, the polymer's T_g is quite important for producing a high-performance toner. If the T_g is too low, it is

Table IV Characteristics of the Toners

Polymer	Particle Size (Volume Average) n_v (μm)	Particle Size (Population Average) n_p (μm)	Particle-Size Distribution (Volume Average)	Triboelectric Charge ^a ($\mu\text{c/g}$)
Colorocs	10.4	—	98.64% > 5 μm	8.5
D-P	11.5	9.0	90.71% > 5 μm	12.6
D-P-T ^b	10.8	8.2	91.88% > 5 μm	15.5

^a Vertex Image carries were used, and toner concentration was 6%.

^b L-Tyrosine content in the copolymer was 7.7%.

difficult to grind an amorphous polymer to the required particle size because the polymer particles are likely to stick together in the process. However, our results suggest that soy-based polyamides, both with and without amino acid, can be easily compounded and ground to the required particle size using a standard air mill.

The triboelectric charge is another key parameter for toners. The triboelectric charge evaluates the electrical performance of a particular carrier-toner combination. Since a Colorocs Color Paper Copier (Model CP 4007) is used in our printing test, the commercial Colorocs black toner was used as a standard for comparison. The Colorocs black toner has a triboelectric charge of 10.0 microCoulomb/gram ($\mu\text{C/g}$). Compared to the values of 12.6 and 15.5 $\mu\text{C/g}$ of our soy-based toner (Table IV) made from D-P and D-P-T (7.7%), soy-based toners made in this study have a close triboelectric charge to that of the Colorocs toner. The visual impression of the printing results indicated that the soy-based toners are capable of producing a high-quality image and are at least equivalent to the standard commercial toner.

Deinking Tests

In customary deinking tests, printed sheets of paper are disintegrated into a pulp (repulping) and then deinked by flotation. Flotation takes advantage of the hydrophobic surface properties of polymeric toners, compared to the hydrophilic surfaces of wood fibers. The deinked pulp is then used to manually form sheets of paper (called handsheets) according to standardized methods.

The deinking efficiency of toner-printed paper was evaluated by measuring the brightness gain of the handsheets made from deinked pulps after flotation deinking. From Figure 2, it is clear that the amino acid-containing polyamide can swell at elevated pH and temperature, but that the homopolyamide sorbs much less water. To examine the effect of toner swellability on the ink-fiber detachment, the repulping and deinking of wastepapers printed using both toners was carried out at pH 11 and a temperature of 60°C. The flotation deinking results are shown in Figure 3. It can be seen that the brightness gain of handsheets from repulped and flotation deinked paper printed with the D-P-T (7.7%) toner is consistently higher than that of handsheets produced from repulped and deinked D-P toner-printed paper. Further experiments indicate that the ink particles of the amino acid-containing toner [D-P-T

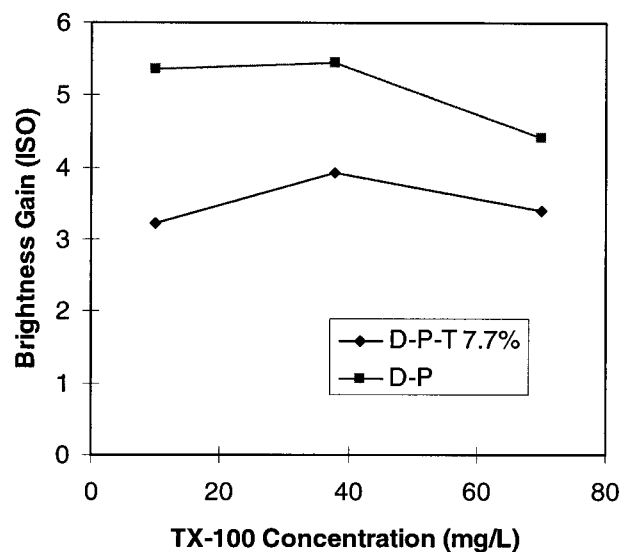


Figure 3 Brightness of handsheets made by flotation deinked pulps as a function of surfactant concentration.

(7.7%)] are much smaller than those of the homopolyamide toner. These results suggest that the amino acid-containing toner may be more easily separated from fiber surfaces and broken into small particles at a high pH and temperature during the repulping. However, it should be noted that the flotation deinking efficiency depends on many factors, including the surface chemistry of the toner particles, the foam stability and structure, the size of the toner particles, and air bubbles. Therefore, more work is needed to obtain a full understanding of the effect of toner-particle swelling on the toner-fiber detachment during the repulping.

CONCLUSIONS

It has been demonstrated in this study that amino acids, such as L-tyrosine, can be copolymerized into soy-based polyamide using a condensation polymerization technique. The copolymer's glass transition temperature (T_g), melting temperature (T_m), enthalpy of fusion (ΔH), and decomposition temperature (T_d) are gradually decreased as the content of tyrosine is increased. Compared to a homopolyamide, the swellability of copolyamides at elevated pH and 70°C increases with increasing content of amino acid in the polymer backbone. Both soy-based homo- and copolyamides were compounded and processed into dual-component toners, which

achieved the same printing performance as that of a commercial toner.

The performance of our toners in recycling of toner-printed paper (toner removal from repulped paper by flotation) was investigated. Flotation deinking results indicated that the toner with an amino acid-containing copolyamide can be more easily removed from the repulped paper slurry at an elevated pH of the solution. It can be speculated that this is due to increased water sorption of the copolymer-based toner.

The financial support from the Ohio Soybean Council is gratefully acknowledged. We wish to thank Mr. John F. Cooper of Toner Research Services, Black Mountain, NC, for his help and advice in the production of the toners.

REFERENCES

1. Johnson, D. A.; Thompson, E. V. In 1995 TAPPI Pulping Conference Proceedings; TAPPI: Atlanta, GA, 1995, p 1291.
2. Miller, J. D.; Azevedo, M. A. D.; Xie, X.; Drelich, J. In Paper Recycling Challenge; Vol. 2, Deinking & Bleaching; Doshi, M. R.; Dyer, J. M., Eds.; Doshi & Associates Inc.: Appleton, WI, 1997; p 167.
3. Kim, T.; Ow, S.; Eom, T. In 1991 TAPPI Pulping Conference Proceedings; TAPPI: Atlanta, GA, 1991; p 1023.
4. Praasad, D.; Heitmann, J.; Joyce, T. *Prog Pap Recycl* 1992, 1(3), 21.
5. Welt, T.; Dinus, R. J. *Prog Pap Recycl* 1995, 4(2), 36.
6. Sacripante, G. U.S. Patent 5194356 (1996).
7. Bayley, R. D. U.S. Patent 5194358 (1996).
8. Wilson, J. C.; DeMejo, L. P. U.S. Patent 5194472 (1996).
9. Vreeland, W. B.; Tyagi, D.; Pierce, Z. R. U.S. Patent 5198320 (1996).
10. Beng, S.; Croucher, M. D.; Wong, R. W. U.S. Patent 5200290 (1996).
11. Johnson, R. W. In *Encyclopedia of Polymer Science and Engineering*; Wiley: New York, 1988; Vol. 17, p 918.
12. Johanson, B.; Wickman, M.; Strom, G. J. *Pulp Pap Sci* 1996, 22(10), 381.
13. Arvanitoyannis, I.; Nikolaou, E.; Yamamoto, N. *Polymer* 1995, 36, 493.
14. Arvanitoyannis, I.; Nikolaou, E.; Yamamoto, N. *Polymer* 1994, 35, 4678.
15. Arvanitoyannis, I.; Nikolaou, E.; Yamamoto, N. *Macromol Chem Phys* 1995, 196, 1129.
16. Fan, X.; Deng, Y.; Waterhouse, J.; Pfromm, P. *J Appl Polym Sci* 1998, 68, 305.
17. Nagata, M.; Kiyotsukuri, T. *Eur Polym J* 1992, 28, 1069.