



Interaction of immunoglobulin G with N,N,N',N'-ethylenediaminetetramethylenephosphonic acid-modified zirconia

Anuradha Subramanian^{a,*}, Sabyasachi Sarkar^b

^aDepartment of Chemical Engineering, University of Nebraska, Lincoln, NE 68588, USA

^bBiosystems and Agricultural Engineering, University of Minnesota, St. Paul, MN 55108, USA

Abstract

Zirconia beads (25–38 μm in diameter) were modified with N,N,N',N'-ethylenediaminetetramethylenephosphonic acid to generate a pseudo-biospecific support, r_PEZ. To better understand the force of interaction between the IgG and the r_PEZ, the equilibrium dissociation constant (K_d) was determined by static binding isotherms, as a function of temperature and by frontal analysis at different linear velocities. Temperature had no significant impact on the maximum static binding capacity (Q_{max}) and the equilibrium-binding constant (K_d), whereas pH and the salt concentration had a noticeable impact on both Q_{max} and K_d values. Q_{max} was found to be in the range of 55–65 mg IgG per ml of beads and unaffected by temperature. The maximum dynamic binding capacity (Q_x) was found to be in the range of 20–12 mg IgG per ml of beads. The adsorption rate constant (k_a) was determined by a split-peak approach to be between 982 and 3242 $\text{l mol}^{-1} \text{s}^{-1}$ depending on the linear velocity. Adsorption rate of IgG on r_PEZ was studied as a function of both feed concentration and linear velocity. The standard enthalpy and entropy values were estimated for the interaction of IgG with this novel support. The binding constants were also determined by modeling the batch protein-uptake data.

© 2002 Elsevier Science B.V. All rights reserved.

Keywords: Zirconia; Adsorption; Thermodynamic parameters; Binding studies; Immunoglobulins; Proteins; Ethylenediaminetetramethylenephosphonic acid

1. Introduction

Economics, efficiency and practicality are some of the constraints dictating the search for novel chromatographic supports relevant for use in the industrial or large-scale purification of proteins. In this regard, affinity chromatography, ion-exchange chromatography and other forms of electrostatic chromatography that exploit differences in biological specificity or surface charge anisotropy of proteins, have the greatest potential of impacting future trends in

scalable protein separation methodologies. Research-based prediction of mass transport, biological activity behavior, kinetic and thermodynamic parameters that impact protein retention and separation are thus essential for the integration of these chromatographic-based unit-operations into the purification scheme.

Affinity chromatography uses biological ligands like protein A or biotin–avidin to achieve exquisite specificity and separation. However, many of these biological ligands are macromolecular and fragile, expensive to obtain from bacterial or tissue-culture sources and are difficult to immobilize without losing activity. The use of protein A and protein G in affinity chromatography is also negatively impacted by the harsh elution conditions and pose special

*Corresponding author. Tel.: +1-402-472-3463; fax: +1-402-472-6989.

E-mail address: asubramanian2@unl.edu (A. Subramanian).

challenges regarding regeneration and sanitation [1]. Some of these drawbacks preclude the use of biological ligands in practical and commercial applications and this has prompted many researchers to turn their attention to the development of synthetic ligands [2]. In contrast, smaller molecules like dyes, amino acids, metal ions and chemical moieties show comparable affinities and their specificities can be increased or decreased either at adsorption or desorption to attain resolutions and degrees of purification comparable to those of immuno-adsorption [3–13].

The effectiveness of a pseudo-biospecific chromatography support that has been synthesized by post-derivatization of zirconia particles with N,N,N',N'-ethylenediaminetetramethylenephosphonic acid (EDTPA), and termed r_PEZ, for the separations of immunoglobulins from complex biological fluids has been demonstrated elsewhere [14]. Although the elution of retained IgG from both serum and cell culture supernatants was effected by mild desorption buffer, not much is known about the mechanism underlying the selective recognition of immunoglobulins. While the ionic properties of both the immobilized ligand and the target protein may play an important role, the fact that selective adsorption takes place at or around the isoelectric pH of IgG is of particular interest. The influence of pH, salt concentration and the effect of chaotropic salts have been studied. Additionally, with the aim of an eventual scale-up, a study of kinetic and thermodynamic factors, such as affinity constants and adsorption rate constants, of this adsorption was undertaken.

2. Materials and methods

2.1. Reagents

All chemicals were of analytical-grade or better. Sodium chloride was purchased from Fischer (Hanover Park, IL, USA). EDTPA was purchased from TCI America (Portland, OR, USA). Bovine serum albumin (BSA), pure human immunoglobulin G (hIgG), all horseradish peroxidase conjugated anti-immunoglobulins used for enzyme-linked immunosorbent assay (ELISA) and human serum albumin (HSA) were obtained from Sigma (St. Louis, MO,

USA). All proteins were used without further purification. Human immunoglobulin A (hIgA) and human immunoglobulin M (hIgM) were purchased from Jackson ImmunoResearch (West Grove, PA, USA). Protein A-hyper D column was purchased from Sigma. Zirchrom (Anoka, MN, USA) provided the prepacked r_PEZ columns.

Immulon II microtiter plates were purchased from Fisher. Affinity purified goat anti-mouse (whole molecule) immunoglobulins and goat anti-mouse immunoglobulins conjugated to horseradish peroxidase (HRP) were purchased from Sigma. *o*-Phenylenediamine·2HCl (OPD) tablets were purchased from Abbott Labs. (Chicago, IL, USA). Precast NuPage 4–12% Bis-Tris gels were purchased from Invitrogen (Carlsbad, CA, USA). A Genesys 5 model from Spectronic Instruments UV-visible spectrophotometer (Rochester, NY, USA) was used to record the adsorption measurements. A benchtop microcentrifuge (Eppendorf Centrifuge 5415C) was used to sediment the r_PEZ particles for batch experiments.

2.2. Kinetic binding experiment

A small-scale kinetic experiment was conducted to obtain binding kinetics data. Approximately 0.4 ml of a 50% (v/v) slurry r_PEZ and loading buffer was transferred into 5.0-ml plastic test tubes to yield approximately 200 μ l of beads. The beads were allowed to settle for at least 5 min and the liquid overlay was then pipetted off. A sample solution of hIgG at a concentration of 1.0 mg/ml was prepared in 20 mM 2-(*N*-morpholino)ethanesulfonic acid (MES), 4 mM EDTPA, 50 mM NaCl, pH 5.5 (further referred to as LB). A 3.0-ml volume of this solution was added to the each tube. Tubes were placed on an end-to-end rotator and allowed to rotate for 24 h at 4 °C. Aliquots were taken at times equal to 0.5, 1, 5, 10, 20, 30, 45, 60, 120, 240 min and 24 h. Immunoglobulin concentrations were measured by measuring the absorbance at 280 nm.

2.3. Determination of dissociation constant, K_d and dynamic bead capacity

For this study, a solution of pure hIgG in LB was

used. This protein solution was added to the column, which was equilibrated with the loading buffer, at concentration of hIgG ranging at 0.5 mg/ml to 2.0 mg/ml and linear velocities of 3.01 cm/min to 12.05 cm/min. The absorbance of the effluent at 280 nm was monitored continuously. The injection was continued until the absorbance of the effluent reached 80% of the inlet concentration. The column was then washed with loading buffer until the absorbance at 280 nm reached the baseline. The adsorbed hIgG was then eluted with the 20 mM MES, 4 mM EDTPA, 1.0 M NaCl, pH 5.5 (further referred to as EB). For each linear velocity the dynamic capacity of the column was determined as the amount of hIgG maintained per milliliter of bead.

2.4. Determination of adsorption rate constants

This experiment was done by using the split-peak approach as described elsewhere [15]. For this experiment a 0.83-ml column equilibrated with LB. A 30-ml volume of a 2.0 mg/ml solution of hIgG was prepared in LB. Aliquots of 1 ml were consecutively injected into the column. Unabsorbed protein was collected for each aliquot injected giving a total of ten fractions collected for a particular linear velocity. In each peak the total amount of protein was determined by measuring absorbance at OD 280 nm. After all ten 1-ml aliquots were injected the retained protein was eluted and absorbance was measured at 280 nm.

2.5. Identification of the binding site

It is important to determine whether hIgG was bound to r_{PEZ} at the F_c or F_{ab} or F_{(ab)₂}. Antibody fragments [F_c or F_{ab} or F_{(ab)₂}] were purchased commercially or prepared by enzymatic hydrolysis of hIgG using commercially available pepsin and papain kits from Pierce. Antibody fragments were chromatographed separately under identical conditions, as used for IgG retention and elution protocol as described earlier. The column-wash and elution fractions were assayed by specific ELISA assays [16]. The total recovery and yield of each fragment was assessed quantitatively.

In a separate experiment, 2.0-ml protein A immobilized on a hyper D support was packed into a Pharmacia column and antibody fragments were chromatographed according to the manufacturer's instructions. In a typical application, 1-ml of antibody fragment solution was diluted with 1.0 ml of 0.5 M sodium citrate buffer at pH 8.4 (LB₁). Feed was filtered using a Millipore 0.45- μ m membrane filter and loaded on to the column at a linear velocity of 1.0 cm/min. Loosely bound proteins were washed with LB₁. The elution of the bound monoclonal antibody (mAb) was effected with 0.5% acetic acid. The pH of the elution fraction was immediately raised to 7.0 with 1 M Tris base. All chromatographic fractions were saved and analyzed for total protein content at an absorbance of 280 nm and specific antibody fragment content by specific ELISA assays.

2.6. Detection of IgG fragments by ELISA assays

Immulon II microtiter plates were incubated with 100 μ l/well of 5 μ g/ml rabbit anti-human Fab specific antisera coating buffer (0.1 M NaHCO₃, 0.1 M NaCl, pH 9.3) for 24 h at 4 °C. Wells were washed with washing buffer (50 mM NaCl, 20 mM Tris-HCl, 0.05% Tween, pH 7.2) and residual sites were blocked with blocking/dilution buffer (50 mM NaCl, 20 mM Tris-HCl, 0.5% casein, pH 7.2) for 30 min at room temperature. A 100- μ l volume of diluted standard and samples in blocking/dilution buffer were added to the each well and incubated for 30 min at 37 °C. After incubation wells were washed three times with washing buffer and 100 μ l/well of 1:2500 diluted HRP conjugated rabbit anti-human IgG was added to each well and incubated at 37 °C for 30 min. Wells were washed three times and 100 μ l/well of OPD substrate was added. The colorimetric reaction was stopped after approximately 3 min by the addition of 100 μ l/well of 1.5 M sulfuric acid. Bound chromophore was detected using a Bio-Tek microplate ELISA reader at 490 nm.

A similar ELISA procedure was used for the determination of F_{(ab)₂} and F_c and with the following changes. The plates were coated with 100 μ l/well of 5 μ g/ml goat anti-human F_{(ab)₂} and F_c specific antisera, for F_{(ab)₂} and F_c determination, respectively.

3. Results

3.1. Effect of temperature on the binding of hIgG to r_PEZ

Static binding experiments were conducted to determine the effect of temperature on the binding of hIgG to r_PEZ. The temperature does not seem to have any significant effect on the binding capacities of hIgG to r_PEZ, as observed from the similar shapes of the isotherms [14]. The maximum static binding capacity (Q_{\max}) was found to range from 47 to 51 mg hIgG bound per ml of beads. The K_d values were found to range from $4.13 \cdot 10^{-6}$ to $5.67 \cdot 10^{-6}$ M [moles of hIgG bound per liter of (wet) r_PEZ beads].

In order to determine whether there were any cooperative effects due to protein–protein interaction during the adsorption process, the isotherm data (from static experiments) were analyzed by a Hill plot using the transformed Langmuir equation [17] (Fig. 1. A cooperativity coefficient (n) of unity indicates no cooperativity. Analysis of the isotherms at 4, 10, 22 and 35 °C indicated n values of 0.82, 1.10, 1.10 and 0.97, respectively, which suggests that

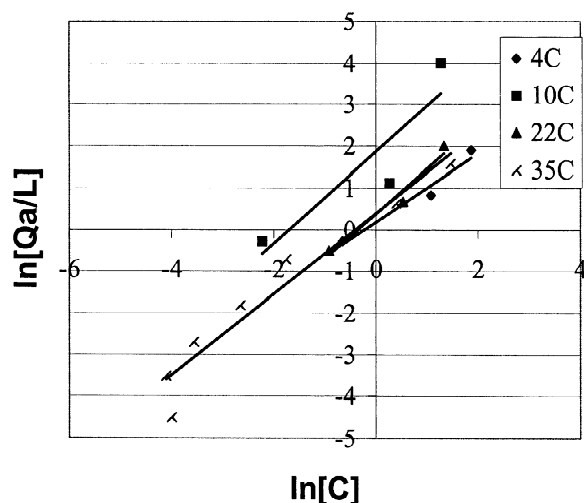


Fig. 1. Determination of the protein interaction cooperativity (Hill plot of the data). Data was analyzed by the transformed Langmuir equation, $\ln [Q_a/L] = \ln K_a + n \ln C$; where $L = Q_x - Q_a$ is the equilibrium free ligand concentration and n the cooperativity coefficient. The value n was obtained from the slope of the linear plot of $\ln [Q_a/L]$ versus $\ln C$.

there is no cooperativity due to protein–protein interactions.

3.2. Kinetic experiment

Fig. 2 shows the rate of disappearance of hIgG from solution. Analysis of hIgG concentrations, for all time points, was estimated by hIgG ELISA. Since the experiment was conducted as a closed system it is assumed that all hIgG measured not in solution is bound to the support. Maximum hIgG retention was observed at 24 h with 93% disappearance of protein from solution from an initial hIgG concentration of 1 mg/ml. The largest percent of hIgG disappearance, or greatest adsorption rate, occurs within the first 5 min of the batch experiment. Of the total equilibrium binding 50% has occurred by 5.7 min, when C_0 equals 1.0 mg/ml. At 12 min approximately 80% of total binding has occurred according to our experimental data with 90% having occurred at 50 min.

The experimental data for the protein adsorption obtained under static conditions was compared to the kinetic rate constant model discussed in detail else-

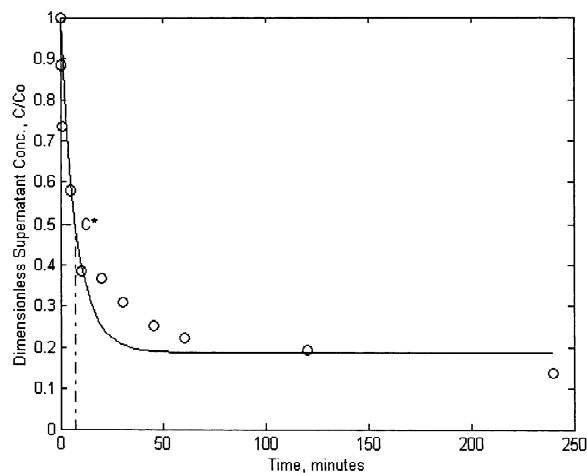


Fig. 2. Batch adsorption profile for the uptake of hIgG by Ligosep Alpha beads. The open circles indicate the experimental data, and the solid lines were calculated by the kinetic rate constant model. Ligosep Alpha beads were contacted with hIgG solution as described in the methods section. The supernatant was analyzed at different time intervals for the residual hIgG concentration. The data were normalized with respect to the hIgG concentration at time $t=0$. Experiments were done in duplicate and the standard deviation was less than 8%. C^* designates the time required to reach 50% of the initial concentration.

where [18]. The only unknown parameter was the forward rate constant (k_1), whereas the isotherm parameters K_d and Q_{\max} determined from static binding experiments were used and the reverse rate constant (k_2) was equated to $K_d \cdot k_1$. The simulation was run with a variety of values of the unknown parameter k_1 and the value that gave the best fit to the experimental data was reported. The agreement between the experimental data and simulation is shown in Fig. 3. A k_1 value of 0.024 min^{-1} and a k_2 value of 0.017 min^{-1} was obtained, respectively.

3.3. Determination of the dynamic capacity

Fig. 3 shows the dynamic isotherm at a linear velocity of 12.04 cm/min and similar profiles were obtained at other linear velocities studied. The

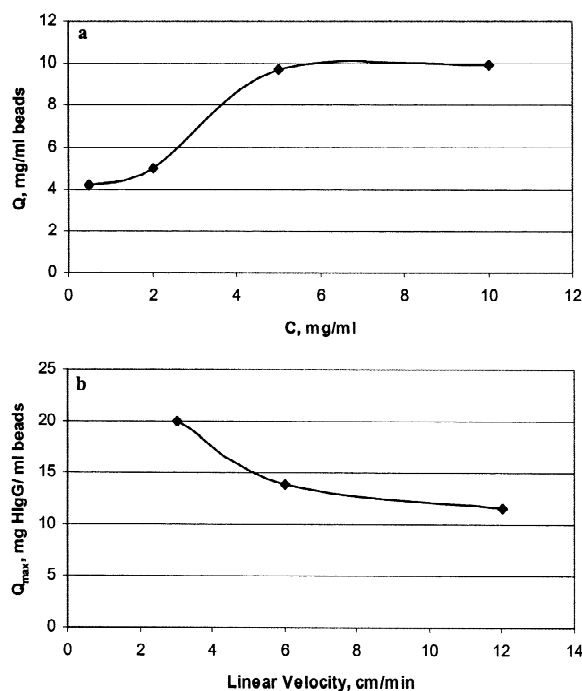


Fig. 3. (a,b) Solution of pure hIgG at concentrations ranging from 0.5 to 25 mg/ml was continuously fed to the column until the absorbance of the effluent reached 0.8–0.97 of the inlet concentration. The column was then washed with loading buffer and the adsorbed hIgG was eluted. For each concentration the dynamic capacity of the column was determined as the amount of hIgG maintained per milliliter of bead. Separate experiments were carried out at linear velocities of 3.01, 6.02 and 12.04 cm/min .

isotherm shapes indicate Langmuir-type adsorption and the dynamic bead capacity (Q_x) was obtained by Scatchard analyses. The effects of Q_x on r_PEZ beads as a function of linear velocity is shown in Fig. 3b. A dynamic hIgG adsorption capacity of 20.00, 13.85 and 11.53 mg/ml bead was obtained at linear velocities of 3.01, 6.02 and 12.04 cm/min , respectively.

3.4. Determination of the adsorption rate constant

Fig. 4 shows the effect of the linear velocity on

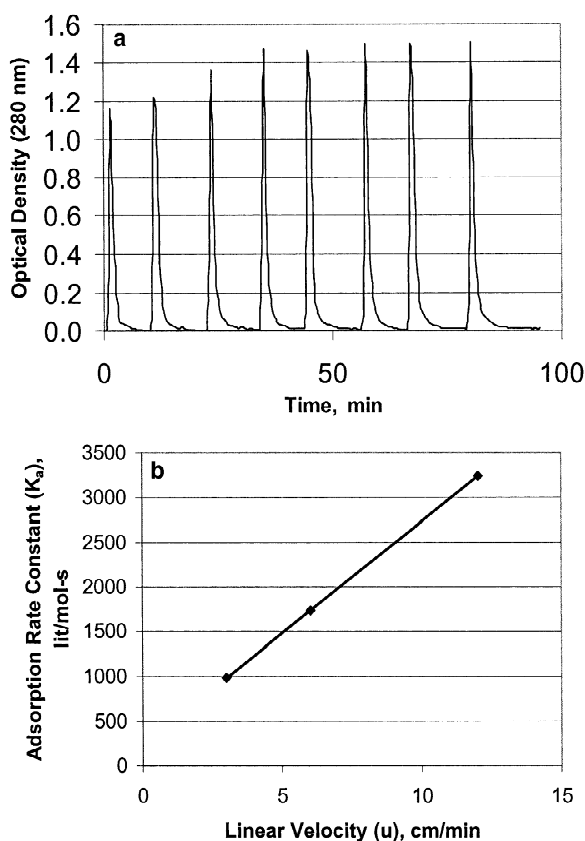


Fig. 4. (a,b) At a given constant linear velocity, 15 aliquots (1 ml each) of a 3.5 mg/ml solution of hIgG were consecutively injected into the column. The cumulative amount of injected protein, and unadsorbed protein was calculated. The ratio of unadsorbed protein to the injected protein was expressed as f and $1 - f$ gave the adsorption yield. The rate constant k_a was determined from the linear region of the graph and plotted as a function of the linear velocity. Similar experiments were performed at other linear velocities studied (3.01, 6.02 and 12.04 cm/min).

the adsorption rate constant. An association rate constant (k_a) of 982.48, 1731.65 and 3242.49 $1 \text{ mol}^{-1} \text{ s}^{-1}$ was obtained for linear velocities of 3.0, 6.0 and 12.0 cm/min, respectively. A best fit of the data in Fig. 3 reveals a linear trend for the data described by the equation $k_a = 689.12 (u) - 903.39$, where k_a is the rate constant ($1 \text{ mol}^{-1} \text{ s}^{-1}$) and u is the linear velocity (cm/min), gives a good linear fit with an R^2 value of 0.994 within the range tested.

3.5. Effects of adsorption rate at varying linear velocities

The effect of hIgG feed concentration on the adsorption rate of hIgG on r_PEZ was evaluated as a function of linear velocities. The adsorption rate increases with increasing hIgG feed concentration and linear velocity. Empirical equations that relate the adsorption rate changes with feed concentration at linear velocities of 1.1, 3.0, 5.6 and 9.0 cm/min are shown in Table 2. The adsorption rate is the highest at the highest experimental feed concentration of 10 mg hIgG/ml, more than twenty times than that of the lowest concentration at 0.5 mg hIgG/ml.

3.6. Estimation ΔH_o and ΔS_o of adsorption and comparison with literature

The thermodynamic parameters for the adsorption can be obtained by determining K_d at different

temperatures. The dependence of K_d as a function of temperature was evaluated from the Langmuirian analyses of the isotherm data [11]. From the Van't Hoff reaction isotherm $\Delta G = \Delta G^\circ - RT \ln [K_D]$; when $\Delta G = 0$, the value of ΔG° can be calculated ($\Delta G^\circ = RT \ln [K_D]$). ΔG° can then be calculated at a given temperature from the value of K_D . The slope of the plot of $\ln [K_D]$ versus $1/T$ yielded ΔH° , assuming ΔH° is independent of temperature [19]. A ΔH_o (adsorption) value of -5.64 kJ/mol and a ΔS_o (adsorption) value of 120 kJ/K were obtained for the interaction of hIgG with r_PEZ.

3.7. Identification of binding site

Table 1 lists the total yield and recovery obtained with each IgG fragment, as separate chromatographic experiments. The F_{ab} and the $F_{(ab)_2}$ fragment were both retained on the r_PEZ column. It appears that the F_{ab} and $F_{(ab)_2}$ fragments were retained to a similar extent or in other words r_PEZ has similar affinity for the F_{ab} and $F_{(ab)_2}$ fragments. F_c fragment was also retained but to a lesser extent. Similar trends and percentages were obtained when the binding of the IgG fragment were tested under batch conditions (data not included).

In contrast, the F_c fragment was quantitatively retained on the protein A column as expected (Table 1). Both F_{ab} and $F_{(ab)_2}$ fragments were not retained on the protein A column. Similar trends and percentages were obtained when the binding of the IgG

Table 1

Percent total recovery and yield of antibody fragments on r_PEZ and protein-A column. r_PEZ were challenged with pure antibody fragments (F_c or F_{ab} or $F_{(ab)_2}$) as separate experiments. Chromatographic fractions were assayed for the specific fragment content by ELISA assays, as detailed in Materials and methods. In general, an average of triplicate application of three different dilutions in ELISA were used for yield calculations

		Fragment F_c			Fragment $F_{(ab)_2}$			Fragment F_{ab}		
		% TR	% Y	[%Y]/[%TR]	% TR	% Y	[%Y]/[%TR]	% TR	% Y	[%Y]/[%TR]
Protein A	Run 1	88.8	85.0	0.96	91.0	0.9	0.01	97.8	0.1	0.01
	Run 2	92.5	88.0	0.95	83.0	2.0	0.02	94.9	1.9	0.02
r_PEZ	Run 1	57.5	16.3	0.28	47.5	35.8	0.75	57.3	42.0	0.73
	Run 2	67.5	20.0	0.30	48.0	38.0	0.79	62.5	39.1	0.63

Percent total recovery (TR) is defined as the ratio of the sum of the total protein in the eluate and column fall-through fractions to the total protein present in the feed. Percent yield (Y) is defined as the ratio of the IgG present in the eluate fraction to the total amount of IgG in the feed. Fragments were also chromatographed on Protein A–hyper D column according to manufacturer's instructions. The chromatographic fractions were assayed as outlined in Methods.

fragment to protein A beads was tested under batch conditions (data not included).

4. Discussion

To gain a better understanding of the effect of support characteristics, support activation chemistry on the parameters impacting the binding of immunoglobulins from biological fluids, further studies aimed at understanding the adsorption mechanism and the nature of interactive forces between immunoglobulins and binding site on EDTPA-modified zirconia beads were undertaken. Moreover, with the aim of an eventual scale-up, a study of the kinetic and thermodynamic parameters, such as affinity constants and adsorption rate constants of this interaction was employed.

The success of a chromatographic separation depends upon the biospecific interaction between the protein of interest and the binding site on the stationary phase. All other components in the feed mixture should have little or no affinity for the binding site. To gain a better understanding of the interaction between the protein and the binding site it is often necessary to quantify important factors such as capacity of the affinity matrix and the dissociation constant of the corresponding protein–ligand interaction. These parameters are useful in the scale-up separation of immunoglobulins by process scale chromatography. It is therefore useful to study equilibrium adsorption data with the intention of determining how the support reacts to protein binding with increasing concentrations. The shape of the equilibrium adsorption curve at temperatures studied indicates a Langmuir-type isotherm. We hypothesize that at these temperatures, hIgG binds uniformly with a high affinity for the binding sites until it reaches a maximum binding energy. The static capacity of r_PEZ as determined by the Langmuir adsorption data was calculated to be 64–87 mg IgG per ml of beads, which is comparable to that reported for protein A–Sepharose and protein A–Ultragel¹. The dissociation constant, K_d , was determined to be in the range of $1.12 \cdot 10^{-5}$ to $2.4 \cdot 10^{-5}$ M, which

indicates medium affinity and is typical for a pseudo-affinity ligand [20].

The high capacity and selectivity displayed by the matrix for immunoglobulins in equilibrium prompted us to study the kinetic aspects of this adsorption for an eventual scale-up of IgG separation from plasma or biological fluids. The values obtained for the dynamic capacity at the experimental linear velocities tested ranged from 9.7 to 18.1 mg IgG per ml of beads, which again is comparable to the values reported for protein A–Sepharose and protein A–Ultragel. The dynamic dissociation constants were in the range of $4 \cdot 10^{-7}$ to $1.6 \cdot 10^{-5}$ M for the linear velocities tested, indicating weak to medium affinity and consistent with the easy and nondenaturing desorption of bound IgG in column-mode. In the range of velocities tested the dynamic dissociation constant appears to be dependent of linear velocity, increasing with increasing flow-rate until a plateau value at a linear velocity of 5.6 cm/min was reached. After which an increase in linear velocity gives no appreciable change in the dissociation constant value.

The adsorption rate constant, k_a , as determined by the split-peak method gave a range of values from 46.1 to 404.2 $l \text{ mol}^{-1} \text{ s}^{-1}$ for linear velocities of 1.1 to 9.0 cm/min, respectively. The linear increase in k_a for the range of velocities tested indicates that the adsorption is velocity dependent and a change in linear velocity will influence IgG retention. This equation can be utilized in the scale-up separation of immunoglobulins by process scale chromatography with r_PEZ support.

An estimation of the rate of adsorption is also necessary for the design of an automated operation. In our work, the adsorption rate increases with increasing linear velocity. This is in good agreement with our adsorption rate constant results, which follow the same linear trend. Additionally, for the same linear velocity the adsorption rate increases with increasing hIgG feed concentration. This is due to the greater number of IgG molecules in solution and consequently more in the vicinity of the binding sites. Empirical relationships relating the adsorption rate with linear velocity, u , in the form of $AR = au + b$ were derived for column-mode hIgG retention and are presented in Table 2. These equations can be used in the scale-up design of hIgG separations.

¹Technical Handbook, Pierce, Rockford, IL.

Table 2

Effect of the flow-rate on the rate of adsorption. The data obtained was approximated to the following equation; $AR = au + b$ where a and b are constants and u is the linear velocity and AR is the adsorption rate. The adsorption rate ($\text{mg ml}^{-1} \text{min}^{-1}$) was calculated as follows: amount of protein retained per ml of support (mg/ml)/time of adsorption (min)

Feed concentration (mg/ml)	Empirical equation
0.5	$y = 9 \cdot 10^{-8}x + 2 \cdot 10^{-7}$
2	$y = 3 \cdot 10^{-7}x + 8 \cdot 10^{-7}$
5	$y = 1 \cdot 10^{-6}x - 2 \cdot 10^{-7}$
10	$y = 2 \cdot 10^{-6}x - 6 \cdot 10^{-8}$

We postulate that the interactions are governed by a combination of ionic, electrostatic and Van der Waals interactions. We conclude that hydrophobic forces probably play a minor role. It is possible to fine tune the selectivity of r_{PEZ} for a special subset or subclass of IgG, by choosing the appropriate buffer. r_{PEZ} was found to interact with all the IgG fragments and no preferential interaction with either domain was observed. This finding supports our notion that the interaction between r_{PEZ} and IgG molecule is not based on any bioactive-recognition.

The weak affinity interactions are very advantageous for a high throughput and recovery of labile proteins, like IgG, compared with protein A immobilized gels. The high capacity and the reproducibility are attractive features in using such a system for scaling-up operations.

References

- [1] E. Bill, U. Lutz, B. Karlsson, M. Sparrman, H. Allgaier, J. Mol. Recognit. 8 (1995) 90.
- [2] N. Labrou, Y. Clonis, J. Biotechnol. 36 (1994) 95.
- [3] T. Ngo, N. Khatler, J. Chromatogr. 597 (1992) 101.
- [4] L. Guerrier, I. Flayeux, A. Schwarz, G. Fassina, E. Boschetti, J. Mol. Recognit. 11 (1998) 107.
- [5] G. Fassina, A. Verdoliva, M. Odierna, M. Ruvo, G. Cassini, J. Mol. Recognit. 9 (1996) 564.
- [6] G. Fassina, A. Verdoliva, G. Palombo, M. Ruvo, G. Cassani, J. Mol. Recognit. 11 (1998) 128.
- [7] G. Palombo, A. Verdoliva, G. Fassina, J. Chromatogr. B 715 (1998) 137.
- [8] S. Mandijiny, M. Vijayalakshmi, Biotechnology of Blood Proteins, Coll. INSERM 227 (1993) 189.
- [9] A. El-Kak, M. Vijayalakshmi, J. Chromatogr. 570 (1991) 29.
- [10] C. Legallais, F. Anspach, S. Bueno, K. Haupt, M. Vijayalakshmi, J. Chromatogr. B 691 (1997) 33.
- [11] X. Wu, K. Haupt, M. Vkjayalakshmi, J. Chromatogr. 584 (1992) 35.
- [12] S. Bueno, K. Haupt, M. Vijayalakshmi, Inter. J. Art. Org. 18 (1995) 392.
- [13] M. Beena, T. Chandy, C. Sharma, J. Biomater. Appl. 8 (1994) 385.
- [14] A. Subramanian, S. Sarkar, J. Chromatogr. A 944 (2002) 179.
- [15] A. El-Kak, S. Manjini, M. Vijayalakshmi, J. Chromatogr. 604 (1992) 29.
- [16] A. Subramanian, W.H. Velander, Intl. J. Biochromatogr. 5 (1) (2000) 67.
- [17] S. Bueno, K. Haupt, M. Vijayalakshmi, J. Chromatogr. B 667 (1995) 57.
- [18] G.L. Skidmore, H.A. Chase, J. Chromatogr. 498 (1990) 113.
- [19] G. Fisher, in: A. Schellenberger (Ed.), Enzymkatalyse, Gustav Fisher, Jena, 1990, p. 25.
- [20] M. Vijayalakshmi, Trends Biotechnol. 7 (1989) 71.