



Adamantyl-functionalized polymer monolith for capillary electrochromatography

Kaname Ohyama^{a,b,*}, Yuki Fukahori^a, Kenichiro Nakashima^c, Tomoyuki Sueyoshi^a, Naoya Kishikawa^a, Naotaka Kuroda^a

^a Department of Environmental and Pharmaceutical Sciences, Graduate School of Biomedical Sciences, Nagasaki University, Nagasaki 852-8521, Japan

^b Nagasaki University Strategy for Fostering Young Scientists, Nagasaki 852-8521, Japan

^c Department of Clinical Pharmacy, Graduate School of Biomedical Sciences, Nagasaki University, Nagasaki 852-8521, Japan

ARTICLE INFO

Article history:

Received 11 August 2009

Received in revised form

17 December 2009

Accepted 22 December 2009

Available online 4 January 2010

Keywords:

Adamantane

Basic solute

Capillary electrochromatography

Peak tailing

Polymer-based monolith

ABSTRACT

An adamantyl (ADM)-functionalized monolithic stationary phase was newly synthesized by a single-step copolymerization of 1-adamantyl-(α -trifluoromethyl) acrylate, ethylene dimethacrylate, and 2-acrylamido-2-methyl-1-propanesulfonic acid in order to prevent the peak tailing of basic solutes in capillary electrochromatography and was compared with butyl methacrylate (BMA)-based one. The ADM structure shields the negatively charged groups on the surface of monolith from basic solutes, resulting in better peak shapes than BMA-based monolithic stationary phase. As the monomers ratio decreased, the monolithic column had lower retention and higher column efficiency which was likely due to lower phase ratio and smaller globule size of monolith, respectively. The ADM-functionalized monolithic columns exhibited a good repeatability and reproducibility of column preparation with relative standard deviation values below 9% in the studied chromatographic parameters.

© 2009 Elsevier B.V. All rights reserved.

1. Introduction

Organic polymer-based monolithic columns have been successfully used in capillary electrochromatography (CEC) [1–8]. Polymer-based monoliths are attractive because there are a wide variety of different monomers available and can be used within a broad pH-range where they are chemically stable. They are prepared by a single-step copolymerization with monomer, cross-linker, pore-forming solvent and initiator.

Different from the monolithic columns in high performance liquid chromatography (HPLC), the introduction of charged moiety into the monolithic network is essential in CEC for generation of electroosmotic flow (EOF). Consequently, moderately or strongly ionic monomers, *i.e.* 2-acrylamido-2-methyl-1-propanesulfonic acid (AMPS), [2-(methacryloyloxy)ethyl]-trimethylammonium chloride, are extensively utilized in the preparation of polymer monoliths for CEC [1–5]. In the CEC separation of charged solutes, these monoliths work as a mixed-mode stationary phase that


combines two retentive interaction (*i.e.* hydrophobic and cationic-exchange or anion-exchange) [9,10]. However, CEC of charged solutes on such stationary phases often suffers from severe peak tailing due to Coulombic attraction between solutes and monolith surface of opposite charges.

In order to juggle production of stable EOF and prevention of peak tailing in CEC, new type of capillary monolithic columns have been developed. One type has a positively charged polymer layer on the inner wall of capillary and a neutral monolithic packing as the bulk stationary phase [11]. Another type is the shielded stationary phase which was prepared via photoinitiated grafting of a covering layer of hydrophobic polymer chain onto the ionizable surface of a porous monolith [12]. However, the preparation of these columns requires the multi-step procedure.

HPLC using the columns packed with silica-gel particles also suffers from peak tailing of basic solutes due to the interaction between solutes and silanols of packing material. In this context, some groups proposed the steric exclusion of the solute from the surface of silica-gel particles to reduce the interaction. Hemetsberger et al. observed that longer alkyl chains partially prevent solutes from reaching the underlying surface and play an important role in blocking the silanols [13]. Gilpin et al. and Guiochon et al. demonstrated improved peak symmetry for basic solutes by the bulky rigid structure of adamantane shielding the unreacted silanols from even small solutes [14,15].

* Corresponding author at: Department of Environmental and Pharmaceutical Sciences, Graduate School of Biomedical Sciences, Nagasaki University, 1-14 Bunkyo-machi, Nagasaki 852-8521, Japan. Tel.: +81 95 819 2446; fax: +81 95 819 2446.

E-mail address: k-ohyama@nagasaki-u.ac.jp (K. Ohyama).

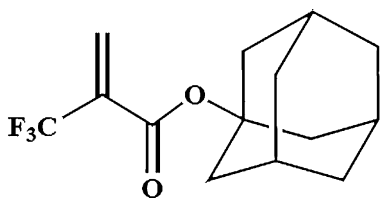

1-adamantyl-(α -trifluoromethyl)acrylate

Fig. 1. Structure of 1-adamantyl-(α -trifluoromethyl)acrylate (MAF-ADE).

With the idea to use adamantane as a shield to reduce the peak tailing of charged solutes in CEC, we newly synthesized adamantyl (ADM)-functionalized polymer monolith by a single-step copolymerization with the monomer containing ADM structure and a cross-linker. In the present study, small basic solutes were used to evaluate the peak symmetry on ADM-functionalized and butyl methacrylate (BMA)-based monolithic columns. To use the ADM-functionalized monolithic column in CEC, some fundamental properties of it were also investigated. To the best of our knowledge, this is the first attempt to develop the polymer-based monolith by a single-step copolymerization for prevention of peak tailing of ionic analytes in CEC.

2. Materials and methods

2.1. Chemicals

Butyl methacrylate (BMA), ethylene dimethacrylate (EDMA), 2-acrylamido-2-methyl-1-propanesulfonic acid (AMPS), α, α' -azobisisobutyronitrile (AIBN), 1,4-butanediol and 3-(trimethoxysilyl)propyl methacrylate were obtained from Nacalai Tesque (Kyoto, Japan). 1-Adamantyl-(α -trifluoromethyl)acrylate (MAF-ADE, Fig. 1) was kindly gifted from Tosoh Organic Chemical (Yamaguchi, Japan). 1-Propanol, acetic acid, sodium acetate, potassium dihydrogenphosphate, dipotassium hydrogen phosphate, aniline, *N*-methylaniline, *N,N*-dimethylaniline, benzene, naphthalene and anthracene were from Wako (Osaka, Japan). Thiourea was obtained from Kishida Chemical (Osaka). HPLC grade of acetonitrile (ACN) was purchased from Kanto Chemical (Tokyo, Japan).

2.2. Instrumentation

All the CEC experiments were performed on a CAPI-3200 system equipped with a photodiode array UV detector (Otsuka Electronics, Osaka). Fused-silica capillaries (375 μm o.d. \times 75 μm i.d.) were obtained from Polymicro Technologies (Phoenix, AZ, USA). Total, packed and effective lengths of capillary columns used here were 42.0, 30.0 and 30.5 cm, respectively. The mobile phase, prepared by mixing ACN and the buffer (phosphate or acetate buffer), was degassed thoroughly prior to use. At the beginning of each day's work, the capillary column was conditioned with a mobile phase for 1 h and equilibrated by applying voltage 1, 5, 10 kV for 5 min each. Instead of pressuring at both ends of the capillary column, the CEC system was thermostatically maintained at 18 $^{\circ}\text{C}$ throughout the analysis in order to avoid bubble formation within the capillary column. The separation voltage was set at 10 kV and the injections were made by applying a voltage of 10 kV for 8 s.

2.3. Column preparation

Monoliths were prepared by *in situ* polymerization in fused-silica capillary. To ensure covalent attachment of monolith to the

inner capillary wall, surface modification of the wall was performed with 3-(trimethoxysilyl)propyl methacrylate prior to the polymerization reaction [16]. Monoliths were prepared by thermally initiated free-radical polymerization of the bulk monomer (MAF-ADE), a cross-linker (EDMA) and a monomer with a sulfonic acid group (AMPS) for the generation of EOF. A mixture of water, 1-propanol and 1,4-butanediol were used as pore-forming solvents following a recipe developed for BMA-based monolith [1,4]. Each material in a solution was bubbled with nitrogen for 20 min before mixing and after mixing, the mixture was sonicated for 10 min. From one end, 50-cm-long surface-modified capillaries were filled with the polymerization mixture up to a length of 45 cm and both ends were plugged with a piece of septum. Both the capillary and the vial containing the remainder mixture were kept at 60 $^{\circ}\text{C}$ in an oven for 20 h. The resulting columns were flushed first with water-ACN mixture (20/80, v/v) to remove pore-forming solvents and unreacted monomers and then with mobile phase by an HPLC pump. A detection window was made adjacent to the monolithic material by burning the polyimide coating away. The capillary columns were equilibrated by successively applying 1, 5, 10 kV for 10 min each.

The polymer monolith in the vial was cut into small pieces and Soxhlet extracted with methanol for 20 h to remove any soluble compounds and then vacuum-dried at 60 $^{\circ}\text{C}$ for 6 h. This polymer was used for the determination of pore size distribution by mercury-intrusion porosimeter (PoreMaster 60GT, Sysmex, Hyogo, Japan).

3. Results and discussion

The retention factor (k) was determined by:

$$k = \frac{t_r - t_0}{t_0}$$

in which t_r and t_0 were retention time of analytes and an EOF marker, respectively.

The EOF mobility (μ_{EOF}) was calculated by:

$$\mu_{\text{EOF}} = \frac{u}{E}$$

where $E = 10 \text{ kV}/420 \text{ mm}$; $u = 300 \text{ mm}/t_0$.

A measure of the symmetry of a peak, given by the following equation:

$$S = \frac{W_{0.05}}{2f}$$

where S is symmetry factor, $W_{0.05}$ is the peak width at 5% height and f is the distance from peak front to apex point at 5% height.

The column efficiency (N) was calculated from the number of theoretical plates per meter:

$$N = 5.55 \left(\frac{t_r}{W_{0.5}} \right)^2$$

where $W_{0.5}$ is peak width at half height.

Height equivalent to a theoretical plate (H) was determined by:

$$H = \frac{L}{N}$$

where L is the capillary length packed with monolithic material (*i.e.* 300 mm).

3.1. Chromatographic property of ADM-functionalized monolithic stationary phase

Chromatographic characterization was performed using aromatic hydrocarbons as a neutral model compound and thiourea

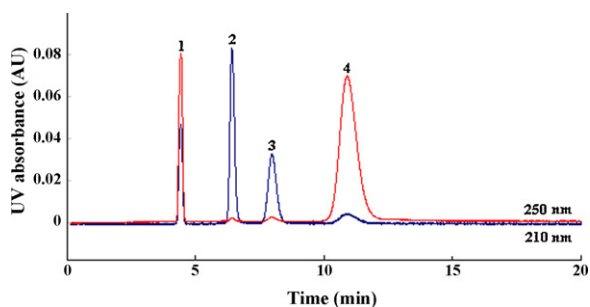


Fig. 2. CEC separation of aromatic hydrocarbons on ADM-functionalized monolithic column. Monolith (wt%): 23.6% MAF-ADE; 16.0% EDMA; 0.4% AMPS; 6.0% water; 35.1% 1-propanol; 18.9% 1,4-butanediol. CEC conditions: mobile phase, 5 mM phosphate buffer (pH 7.0)/ACN=20/80 (v/v); voltage, 10 kV; injection, 10 kV for 8 s; UV detection, 210 and 250 nm. Peaks: 1, thiourea; 2, benzene; 3, naphthalene; 4, anthracene.

as an EOF marker. A typical electrochromatogram of a separation of a mixture (benzene, naphthalene and anthracene) at 10 kV is shown in Fig. 2. Based on the hydrophobic nature of adamantane, the elution order of model compounds were according to their hydrophobicity, indicating reversed-phase mode retention. The EOF mobilities ($\times 10^{-8}$ mm/Vs) on the ADM-functionalized and BMA-based monolithic columns were 4.79 and 3.83, respectively. The ADM groups shielding of sulfonic acid groups never brings about a decrease in EOF.

3.2. Peak shapes of basic compounds

Using a mobile phase of 5 mM acetate buffer (pH 4.0) and ACN mixture, the test solutes (aniline, *N*-methylaniline and *N,N*-dimethylaniline) were analyzed on ADM-functionalized and BMA-based monolithic columns made from the polymerization mixture consisting 23.6% MAF-ADE or BMA, 16.0% EDMA, 0.4% AMPS, 6.0% water, 35.1% 1-propanol and 18.9% 1,4-butanediol. Table 1 shows retention time, retention factor and symmetry factor for the test solutes on both columns.

On BMA-based monolithic column, the peaks were apparently tailing. The solutes (pK_a 4.6–5.1 [17]) are partially or fully positively charged, but they eluted slower than thiourea, which indicates the stronger effect of the interaction between the basic solutes and stationary phase than that of the electrophoretic mobility. Increased peak asymmetry on BMA-based monolith was observed in accordance with the increased basicity of the solutes. Elevating ACN content from 80 to 85% (v/v) increased symmetry factor of the peaks. From these results, the poor peak shapes are most likely due to the binding of solutes to the sulfonic acid groups of the monolithic stationary phase.

On the other hand, the peak shapes were obviously better on ADM-functionalized monolithic column. The peaks of test solutes eluted slower than thiourea, indicating that the CEC separation is still mainly based on a chromatographic partition rather than electrophoretic principles. The better peak shapes on ADM-functionalized monolithic column should be due to the reduction of the accessibility of basic solutes to sulfonic acid groups. This shielding effect of adamantane observed in polymer-based monolith conforms with that in the ADM-modified silica used for HPLC [18]. Additionally, as shown in Table 1, the retention factor for basic solutes on ADM-functionalized monolithic column were lower than those on BMA-based one under the mobile phase conditions. This also supports the existence of the shielding effects which provides a decrease in Coulombic interaction between basic solutes and sulfonic acid groups.

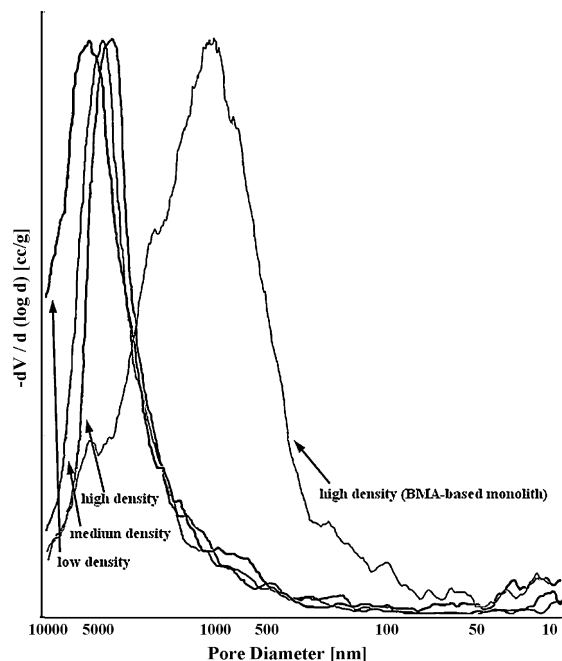


Fig. 3. Pore size distributions of ADM-functionalized and BMA-based monoliths as obtained with different ratio of monomers and pore-forming solvents. High-density monolith (wt%): 23.6% MAF-ADE; 16.0% EDMA; 0.4% AMPS; 6.0% water; 35.1% 1-propanol; 18.9% 1,4-butanediol. Medium-density monolith (wt%): 18.0% MAF-ADE; 12.0% EDMA; 0.4% AMPS; 7.0% water; 40.7% 1-propanol; 21.9% 1,4-butanediol. Low-density monolith (wt%): 11.8% MAF-ADE; 8.0% EDMA; 0.4% AMPS; 8.0% water; 46.7% 1-propanol; 25.1% 1,4-butanediol.

3.3. Influence of the composition of the polymerization mixture

The morphology of monoliths is a direct consequence of the ratio between the monomer and pore-forming solvent phases, which is closely related to their chromatographic performance [4,19]. In this study, three monolithic stationary phases were prepared with different ratio between the monomer and pore-forming solvent phases in order to evaluate the influence of the ratio on retention and efficiency. The high-density polymer monolith was prepared with 40 wt% monomers and 60 wt% pore-forming solvents in the mixture. The medium- and low-density ones were prepared with monomers to pore-forming solvents ratios of 30:70 and 20:80, respectively. During this experiment, the content of AMPS, the ratio of MAF-ADE and EDMA and the composition of pore-forming solvents were kept constant.

For BMA-based monolith, it was reported that while a unimodal pore size distribution was observed for high-density material, pore size of low-density material was much broader and in some cases truly bimodal [4]. The broad pore size distribution of low-density material might lead to low column-to-column reproducibility of preparation. In our experiments, contrastingly, a unimodal distribution was obtained on all the ADM-functionalized monoliths including low-density monolith (Fig. 3). The preparation conditions (*i.e.* the ratio of monomers to pore-forming solvents, the composition of pore-forming solvents and polymerization temperature) for each monolithic material are similar to those of BMA-based monolith [4,20]; therefore, the difference in the pore size distribution could be attributed to the nature of MAF-ADE. Large pore size (around 5000 nm) of ADM-functionalized monoliths was obtained, while the pore size of high-density BMA monolith prepared in this study was 1030 nm (Fig. 3). The timing of the phase separation in the polymerization process determines the pore size and in general, earlier phase separation provides larger macropores. Therefore, the

Table 1
Peak shapes of basic solutes on ADM-functionalized and BMA-based monolithic columns^a.

	Aniline			N-Methylaniline			N,N-Dimethylaniline		
	RT (min)	<i>k</i>	<i>S</i>	RT (min)	<i>k</i>	<i>S</i>	RT (min)	<i>k</i>	<i>S</i>
ADM-functionalized monolith ^b	7.04	0.29	1.1	7.46	0.50	1.2	7.92	0.76	1.3
BMA-based monolith ^b	9.60	0.44	1.2	11.7	0.79	2.4	13.2	1.10	2.7
BMA-based monolith ^c	9.40	0.36	1.3	12.6	0.76	3.9	14.4	0.96	5.8

^a Monolith (wt%): 23.6% MAF-ADE; 16.0% EDMA; 0.4% AMPS; 6.0% water; 35.1% 1-propanol; 18.9% 1,4-butanediol. Separation condition: voltage, 10 kV; injection, 10 kV for 8 s; UV detection, 210 nm. Other conditions as mentioned in Section 2.2.

^b 5 mM acetate buffer (pH 4.0)/acetonitrile = 20/80 (v/v).

^c 5 mM acetate buffer (pH 4.0)/acetonitrile = 15/85 (v/v).

larger pore size of ADM-functionalized monolith seemed to be due to early phase separation.

As the density was decreased by decreasing the contents of monomers, the *k* values of aromatic hydrocarbons became lower due to a decrease in the phase ratio. This is consistent with the previous study using BMA-based stationary phase [20]. Medium- and low-density monoliths were found to have 2-fold and 3-fold higher column efficiency, respectively, in comparison to high-density one. The pore sizes of three monoliths were within similar range from 4290 to 5560 nm; therefore, the higher efficiency on lower density monolithic column should be attributed to the smaller globule size [4]. In the present state, ADM-functionalized monolithic columns exhibited low efficiency for benzene (*k* = 0.45, 19600 N/m), naphthalene (*k* = 0.80, 9600 N/m) and anthracene (*k* = 1.45, 4300 N/m). On the other hand, the efficiency on BMA-based monolithic columns prepared in this study for benzene (*k* = 0.43, 29300 N/m), naphthalene (*k* = 0.79, 9600 N/m) and anthracene (*k* = 1.37, 2800 N/m) is also lower than those in the other literatures [1,4,20]. This means that the low efficiency on ADM-functionalized monolithic columns was not due to the MAF-ADE monomer but due to unknown reason in our preparation procedure. Hence, the effect of degassing method in column preparation on improving the efficiency is now under the examination.

3.4. Effect of mobile phase composition and buffer concentration

The effect of the ACN content in the mobile phase on the retention factors of the aromatic hydrocarbons was studied, using 5 mM phosphate buffer (pH 7.0). The retention decreased with an increase in ACN content, in accordance with a reversed-phase mechanism. A linear relationship between log *k* versus ACN content was obtained and the slopes were almost equal for all the different hydrocarbons. No significant change in EOF mobility was observed with the change in ACN content at a constant buffer concentration.

The effect of buffer concentration on EOF mobility in the range of 5–15 mM was examined with the mobile phase of phosphate buffer (pH 7.0) and 80% ACN. At the ionic strength used in this experiment, double-layer overlap which results in a decrease in the EOF mobility was expected to be negligible for the pores with μ -meter size. A constant EOF mobility across ionic concentration range investigated was observed.

3.5. Repeatability and reproducibility of monolithic column

There are a few data on the reproducibility of preparation of acrylate monolithic columns in the literatures [20–24]. In accordance with previous work [21], the repeatability and reproducibility of preparation of ADM-functionalized monoliths were studied with five monolithic columns synthesized from a polymerization mixture (10.0% MAF-ADE, 10.0% EDMA, 0.4% AMPS, 8.0% water, 53.6% 1-propanol, 18.0% 1,4-butanediol). The three columns (No. 1–3) were prepared from one polymerization mixture and

Table 2

Repeatability and reproducibility of preparation of ADM-functionalized monolithic columns expressed as RSD% of EOF mobility, retention time, retention factor and plate height^a.

Parameter	Repeatability (RSD%)		Reproducibility (RSD%)
	Run-to-run Column No. 1 (<i>n</i> = 6)	Column-to-column Columns No. 1–3	Mixture-to-mixture Columns No. 1–5
μ_{EOF}	≤1.8	≤3.5	≤3.4
<i>t_r</i>	≤2.5	≤3.6	≤3.9
<i>k</i>	≤2.8	≤2.4	≤5.2
<i>H</i>	≤5.9	≤7.5	≤8.5

^a Monolith (wt%): 10.0% MAF-ADE; 10.0% EDMA; 0.4% AMPS; 8.0% water; 53.6% 1-propanol; 18.0% 1,4-butanediol. Separation condition: voltage, 10 kV; injection, 10 kV for 8 s; UV detection, 210 nm. Other conditions as mentioned in Section 2.2. Test solutes: benzene, naphthalene and anthracene.

the others (No. 4 and 5) were prepared from another polymerization mixture but both of the same composition. The repeatability and reproducibility were expressed as relative standard deviations (RSD) of the chromatographic parameters, *i.e.* EOF mobility, retention times, retention factors and plate height, measured with the same set of aromatic hydrocarbons (Table 2). The run-to-run repeatability was evaluated with the No. 1 column for six measurements. The column-to-column repeatability was calculated within the first set of three columns (No. 1–3). The run-to-run repeatability was lower than 6% and the column-to-column one was below 8% for EOF mobility and all other parameters about the aromatic hydrocarbons. The reproducibility of five columns was also less than 9% for all the parameters. The repeatability and reproducibility obtained here permits the application of ADM-functionalized monolith for practical use in CEC.

4. Conclusion

It is demonstrated that CEC with ADM-functionalized monolithic stationary phase can provide good peak shape of basic solutes. The chromatographic retention was found to be based on a mixed-mode retention mechanism (hydrophobic interaction and Coulombic interaction). However, Coulombic interaction for positively charged solutes should be attenuated compared with BMA-based monolithic column by the shielding effect of adamantyl groups. Preparing three monolithic columns with different ratio between the monomer and pore-forming solvent phases, the monolith with lower density of monomers was observed to give lower retention and higher efficiency. For low-density monolithic column, satisfactory run-to-run and column-to-column repeatability and mixture-to-mixture reproducibility for electrochromatographic parameters were observed. Since the mechanism of preventing the peak tailing is likely based on shielding of the ionic groups on monolith surface from ionic solutes, ADM-functionalized monolith will be useful for CEC separation of acidic and basic solutes in both of anodic and cathodic EOF modes.

Acknowledgements

K.O. is grateful to the support by Special Coordination Funds for Promoting Science and Technology of the Ministry of Education, Culture, Sports, Science and Technology (MEXT). The authors thank Tosoh Organic Chemical for kindly supplying MAF-ADE monomer and also gratefully acknowledge the technical support on the measurement of pore size distribution by Mr. Masahide Takase (Daiso Co., Ltd., Osaka).

References

- [1] E.C. Peters, M. Petro, F. Svec, J.M.J. Fréchet, *Anal. Chem.* 70 (1998) 2288.
- [2] F. Švec, J.M.J. Fréchet, in: F. Švec, T.B. Tennikova, Z. Deyl (Eds.), *Monolithic Materials*, Elsevier, Amsterdam, 2003, p. 20.
- [3] T. Jiang, J. Jiskra, H.A. Claessens, C.A. Cramers, *J. Chromatogr. A* 923 (2001) 215.
- [4] S. Eeltink, J.M. Herrero-Martinez, G.P. Rozing, P.J. Schoenmakers, W.Th. Kok, *Anal. Chem.* 77 (2005) 7342.
- [5] B.L. Waguespack, S.A. Hodges, M.E. Bush, L.J. Sondergeld, M.M. Bushey, *J. Chromatogr. A* 1078 (2005) 171.
- [6] P. Pruijm, M. Öhman, Y. Huo, P.J. Schoenmakers, W.Th. Kok, *J. Chromatogr. A* 1208 (2008) 109.
- [7] X. Wang, H. Lü, X. Lin, Z. Xie, *J. Chromatogr. A* 1190 (2008) 365.
- [8] X. Wang, X. Lin, Z. Xie, J.P. Giesy, *J. Chromatogr. A* 1216 (2009) 4611.
- [9] K. Ohyama, N. Kuroda, *J. Liq. Chromatogr. Relat. Technol.* 30 (2007) 833.
- [10] X. Yang, J. Dai, P.W. Carr, *J. Chromatogr. A* 996 (2003) 13.
- [11] Y. Li, R. Xiang, C. Horváth, J.A. Wilkins, *Electrophoresis* 25 (2004) 545.
- [12] E.F. Hilder, F. Svec, J.M.J. Fréchet, *Anal. Chem.* 76 (2004) 3887.
- [13] H. Hemetsberger, W. Maasfeld, H. Ricken, *Chromatographia* 7 (1976) 303.
- [14] S.S. Yang, R.K. Gilpin, *Anal. Chem.* 59 (1987) 2750.
- [15] M.T. Aubel, J.J. Pesek, G. Guichon, *J. Chromatogr.* 514 (1990) 11.
- [16] C. Yu, M.N. Davey, F. Svec, J.M.J. Fréchet, *Anal. Chem.* 73 (2001) 5088.
- [17] SciFinder, *The Values Calculated Using Advanced Chemistry Development (ACD) Software Solaris*, American Chemical Society, Washington, DC, 2007.
- [18] M.T. Matyska, J.J. Pesek, S. Tong, J.E. Sandoval, *J. Liq. Chromatogr. Relat. Technol.* 26 (2003) 1169.
- [19] F. Svec, *J. Sep. Sci.* 27 (2004) 747.
- [20] S. Eeltink, G.P. Rozing, P.J. Schoenmakers, W.Th. Kok, *J. Chromatogr. A* 1109 (2006) 74.
- [21] J. Grafnetter, P. Coufal, E. Tesařová, J. Suchánková, Z. Bosáková, J. Ševčík, *J. Chromatogr. A* 1049 (2004) 43.
- [22] V. Augustin, A. Jardy, P. Gareil, M.-C. Hennion, *J. Chromatogr. A* 1119 (2006) 80.
- [23] A. Cantó-Mirapeix, J.M. Herrero-Martínez, C. Mongay-Fernández, E.F. Simó-Alfonso, *Electrophoresis* 29 (2008) 3866.
- [24] A. Cantó-Mirapeix, J.M. Herrero-Martínez, C. Mongay-Fernández, E.F. Simó-Alfonso, *Electrophoresis* 29 (2008) 4399.