

This article was downloaded by: [Institute Of Atmospheric Physics]
On: 09 December 2014, At: 15:15
Publisher: Taylor & Francis
Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Coordination Chemistry

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gcoo20>

Vanadium(V) complexes with hydrazone and benzohydroxamate ligands: synthesis, structures and catalytic epoxidation

An-Mei Li^a

^a College of Chemical Engineering and Pharmacy, Jingchu University of Technology, Jingmen, PR China

Accepted author version posted online: 06 Jun 2014. Published online: 30 Jun 2014.



CrossMark

[Click for updates](#)

To cite this article: An-Mei Li (2014) Vanadium(V) complexes with hydrazone and benzohydroxamate ligands: synthesis, structures and catalytic epoxidation, Journal of Coordination Chemistry, 67:12, 2076-2085, DOI: [10.1080/00958972.2014.931577](https://doi.org/10.1080/00958972.2014.931577)

To link to this article: <http://dx.doi.org/10.1080/00958972.2014.931577>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform. However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms &


Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>

Vanadium(V) complexes with hydrazone and benzohydroxamate ligands: synthesis, structures and catalytic epoxidation

AN-MEI LI*

College of Chemical Engineering and Pharmacy, Jingchu University of Technology, Jingmen, PR China

(Received 4 March 2014; accepted 23 April 2014)

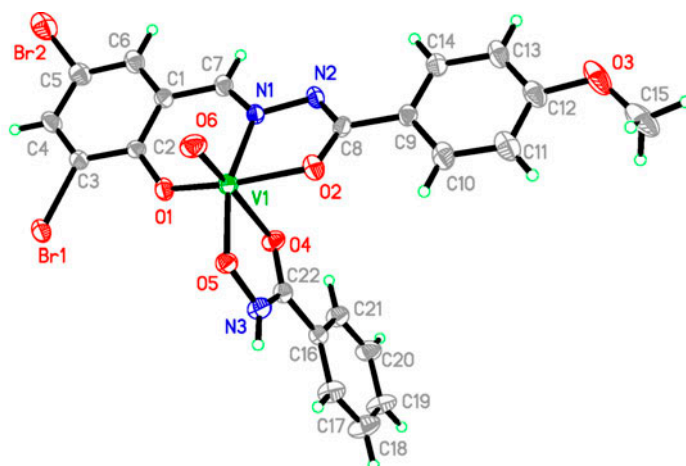

Two structurally similar vanadium(V) complexes, $[\text{VOL}^1\text{L}]$ (**1**) and $[\text{VOL}^2\text{L}]$ (**2**), where L^1 is the dianionic form of *N'*-(3,5-dibromo-2-hydroxybenzylidene)-4-methoxybenzohydrazide, L^2 is the dianionic form of *N'*-(3,5-dibromo-2-hydroxybenzylidene)nicotinohydrazide, and L is benzohydroxamate, were prepared and characterized by elemental analysis, infrared spectra, and single crystal X-ray diffraction. **1** crystallizes in the monoclinic space group $P2_1/c$, with unit cell dimensions $a = 12.0262(7)$, $b = 16.5629(9)$, $c = 12.3449(8)$ Å, $\beta = 105.160(2)^\circ$, $V = 2373.4(2)$ Å³, $Z = 4$, $R_1 = 0.0376$, $wR_2 = 0.0844$, $\text{GOOF} = 1.058$; **2** crystallizes in the monoclinic space group $P2_1/c$, with unit cell dimensions $a = 10.6439(7)$, $b = 16.1968(9)$, $c = 13.1108(8)$ Å, $\beta = 104.180(2)^\circ$, $V = 2191.4(2)$ Å³, $Z = 4$, $R_1 = 0.0521$, $wR_2 = 0.1142$, $\text{GOOF} = 1.018$. X-ray analysis indicates that vanadium in the complexes are coordinated by phenolate oxygen, imino nitrogen, and enolate oxygen of the hydrazone, two oxygens of the benzohydroxamate, and one oxo, generating octahedral coordination. Oxidations of olefins with the complexes as catalysts were evaluated. The complexes showed effective catalytic efficiency in oxidation of several aliphatic and aromatic substrates under mild conditions, using *tert*-butyl hydrogen peroxide as oxidant.

Keywords: Hydrazone ligand; Vanadium complex; Crystal structure; Catalytic epoxidation

*Email: amli2010@163.com

1. Introduction

The development of processes for oxidation of olefins is a goal that has long been pursued. The challenge is to make such processes environmental friendly using nontoxic reagents and energy-efficient catalytic methods [1]. Vanadium complexes are well known for use in organic synthesis, in particular for oxidations of various organic compounds [2–7]. Vanadium complexes have attracted attention for sulfoxidation and epoxidation of olefins [8–13]. The synthesis and catalytic properties of a number of vanadium complexes with Schiff bases have been reported [4, 7, 14–16]. However, the number of documented vanadium complexes catalyzing the peroxidic oxidation of sulfides is still limited and the structure-activity relationship is not clear. In this work, two new structurally similar vanadium(V) complexes, [VOL¹L] (**1**) and [VOL²L] (**2**), where L¹ is the dianionic form of *N'*-(3,5-dibromo-2-hydroxybenzylidene)-4-methoxybenzohydrazide (H₂L¹), L² is the dianionic form of *N'*-(3,5-dibromo-2-hydroxybenzylidene)nicotinohydrazide (H₂L²), and L is benzohydroxamate, were prepared and studied for their structures and catalytic oxidation of olefins (scheme 1).


2. Experimental

2.1. Materials and methods

All chemicals and solvents were analytical reagent grade and purchased from Beijing Chemical Reagent Company. H₂L¹ and H₂L² were prepared according to the literature method [17]. Microanalyses (C, H, N) were performed using a Perkin-Elmer 2400 elemental analyzer. Infrared spectra were carried out using the JASCO FT-IR model 420 spectrophotometer with KBr disk from 4000 to 400 cm⁻¹. GC analyses were performed on a Shimadzu GC-2014 gas chromatograph. UV–vis spectra were measured with a Perkin-Elmer Lambda 18 spectrophotometer.

2.2. Syntheses of the complexes

[VOL¹L] (**1**). A methanolic solution (15 mL) of VO(acac)₂ (0.26 g, 1.0 mM) was added to a methanolic solution (15 mL) of H₂L¹ (0.43 g, 1.0 mM) and benzohydroxamic acid (0.14 g, 1.0 mM). The mixture was stirred at room temperature for 1 h to give a brown solution. Single crystals of the complex, suitable for X-ray diffraction, were formed at the bottom of the vessel on slow evaporation of the solution in air for a few days. Yield: 54%. Anal. Calcd for C₂₂H₁₆Br₂N₃O₆V: C, 42.00; H, 2.56; N, 6.68. Found: C, 41.86; H, 2.67; N, 6.81%.

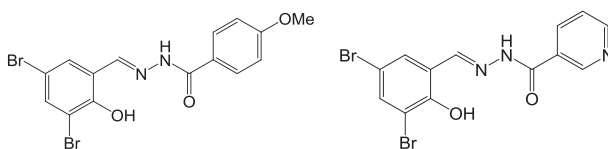

Scheme 1. The hydrazone ligands H₂L¹ (left) and H₂L² (right).

[VOL²L] (**2**). This complex was prepared according to the same method as **1**, but with H₂L¹ replaced by H₂L² (0.40 g, 1.0 mM). Yield: 67%. Anal. Calcd for C₂₀H₁₃Br₂N₄O₅V: C, 40.03; H, 2.18; N, 9.34. Found: C, 40.22; H, 2.30; N, 9.17%.

2.3. X-ray structure determination

X-ray measurement was performed using a Bruker Smart 1000 CCD diffractometer with graphite monochromated Mo K α radiation ($\lambda = 0.71073 \text{ \AA}$) using the ω -scan technique. Determination of the Laue class, orientation matrix, and cell dimensions were performed according to established procedures where Lorentz polarization and absorption corrections were applied. Absorption corrections were applied by fitting a pseudoellipsoid to the ψ -scan data of selected strong reflections over a range of 2θ angles. The positions of non-hydrogen atoms were located with direct methods. Subsequent Fourier syntheses were used to locate the remaining non-hydrogen atoms. All non-hydrogen atoms were refined anisotropically. The amino hydrogens were located from difference Fourier maps and refined isotropically, with N–H distances restrained to 0.90(1) \AA . The remaining hydrogens were placed in calculated positions and constrained to ride on their parent atoms. The analysis was performed with the aid of the SHELXS-97 and SHELXL-97 suite of codes [18, 19]. The crystallographic data for the complexes are summarized in table 1. Selected bond lengths and angles are given in table 2.

Table 1. Crystal data for **1** and **2**.

	1	2
Chemical formula	C ₂₂ H ₁₆ Br ₂ N ₃ O ₆ V	C ₂₀ H ₁₃ Br ₂ N ₄ O ₅ V
Fw	629.1	600.1
Crystal shape/color	Block/deep brown	Block/deep brown
Crystal size (mm)	0.20 × 0.18 × 0.16	0.18 × 0.17 × 0.17
<i>T</i> (K)	298(2)	298(2)
λ (Mo K α) (\AA)	0.71073	0.71073
Crystal system	Monoclinic	Monoclinic
Space group	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> 2 ₁ / <i>c</i>
<i>a</i> (\AA)	12.0262(7)	10.6439(7)
<i>b</i> (\AA)	16.5629(9)	16.1968(9)
<i>c</i> (\AA)	12.3449(8)	13.1108(8)
β ($^\circ$)	105.160(2)	104.180(2)
<i>V</i> (\AA^3)	2373.4(2)	2191.4(2)
<i>Z</i>	4	4
μ (Mo K α) (cm^{-1})	3.829	4.140
<i>T</i> (min)	0.5148	0.5228
<i>T</i> (max)	0.5794	0.5396
<i>D</i> _{calcd} (g cm^{-3})	1.761	1.819
<i>F</i> (000)	1240	1176
Collected reflections	25,139	21,696
Unique reflections	4402	4492
Observed reflections [<i>I</i> ≥ 2 σ (<i>I</i>)]	3523	3289
Parameters	311	292
Restraints	1	1
Goodness of fit on <i>F</i> ²	1.058	1.018
<i>R</i> _{int}	0.0431	0.0415
<i>R</i> ₁ [<i>I</i> ≥ 2 σ (<i>I</i>)]	0.0376	0.0521
<i>wR</i> ₂ [<i>I</i> ≥ 2 σ (<i>I</i>)]	0.0844	0.1142
<i>R</i> ₁ (all data)	0.0551	0.0807
<i>wR</i> ₂ (all data)	0.0923	0.1295

Table 2. Selected bond lengths (Å) and angles (°) for **1** and **2**.

1			
<i>Bond lengths</i>			
V1–O1	1.873(2)	V1–O2	1.948(2)
V1–O5	1.855(2)	V1–O6	1.581(3)
V1–O4	2.168(3)	V1–N1	2.094(3)
<i>Bond angles</i>			
O6–V1–O5	97.24(13)	O6–V1–O1	98.68(14)
O5–V1–O1	102.76(11)	O6–V1–O2	97.85(14)
O5–V1–O2	93.51(11)	O1–V1–O2	155.06(11)
O6–V1–N1	100.11(13)	O5–V1–N1	160.29(11)
O1–V1–N1	83.84(11)	O2–V1–N1	74.95(10)
O6–V1–O4	173.67(12)	O5–V1–O4	76.69(10)
O1–V1–O4	84.57(11)	O2–V1–O4	80.91(11)
N1–V1–O4	85.61(10)		
2			
<i>Bond lengths</i>			
V1–O1	1.889(3)	V1–O2	1.944(3)
V1–O4	1.848(3)	V1–O5	1.583(3)
V1–O3	2.196(3)	V1–N1	2.073(3)
<i>Bond angles</i>			
O5–V1–O4	95.89(15)	O5–V1–O1	98.69(15)
O4–V1–O1	105.29(13)	O5–V1–O2	101.32(15)
O4–V1–O2	90.55(12)	O1–V1–O2	152.99(13)
O5–V1–N1	98.92(15)	O4–V1–N1	161.03(13)
O1–V1–N1	84.17(13)	O2–V1–N1	74.99(12)
O5–V1–O3	171.30(15)	O4–V1–O3	75.85(12)
O1–V1–O3	81.18(12)	O2–V1–O3	81.72(12)
N1–V1–O3	89.73(12)		


2.4. Oxidation

Catalytic experiments were carried out in a 50 mL glass round-bottom flask fitted with a reflux condenser and placed in an oil bath at prearranged temperature under continuous stirring. The oxidation was carried out as follows: the complexes (0.032 mM) were dissolved in 10 mL 1,2-dichloroethane. Then 10 mM alkene was added to the reaction mixture and 30 mM TBHP was added. The reaction mixture was refluxed for 1 h. The reaction products were monitored at periodic time intervals using gas chromatography. The oxidation products were identified by comparison with authentic samples (retention times in GC).

3. Results and discussion

3.1. Synthesis

The hydrazones were readily prepared by condensation of 3,5-dibromo-2-hydroxybenzohydrazide with 4-methylbenzohydrazide and nicotinohydrazide, respectively, in methanol. The vanadium complexes were synthesized by stirring equimolar quantities of the hydrazone ligands, benzohydroxamic acid and VO(acac)₂ in methanol at room temperature (scheme 2). The chemical formulas of the complexes have been confirmed by elemental analyses, IR spectra, and single crystal X-ray diffraction.

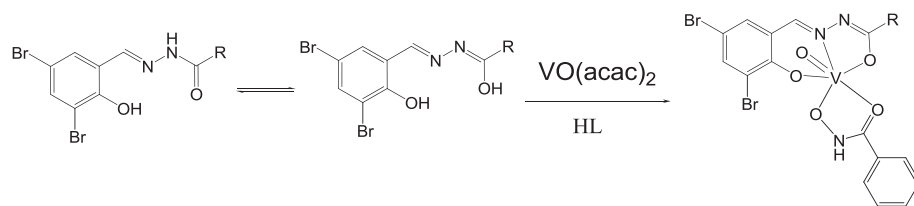

Scheme 2. Preparation of the complexes. **1**: R = *p*-OMePh; **2**: R = *m*-pyridine.

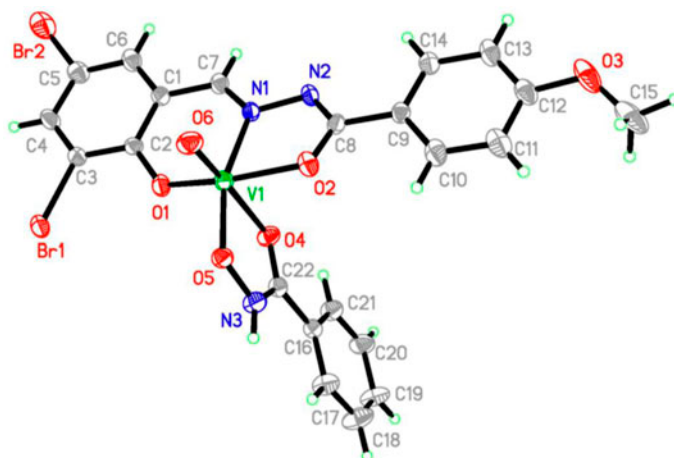


Figure 1. Molecular structure of **1** with 30% probability thermal ellipsoids.

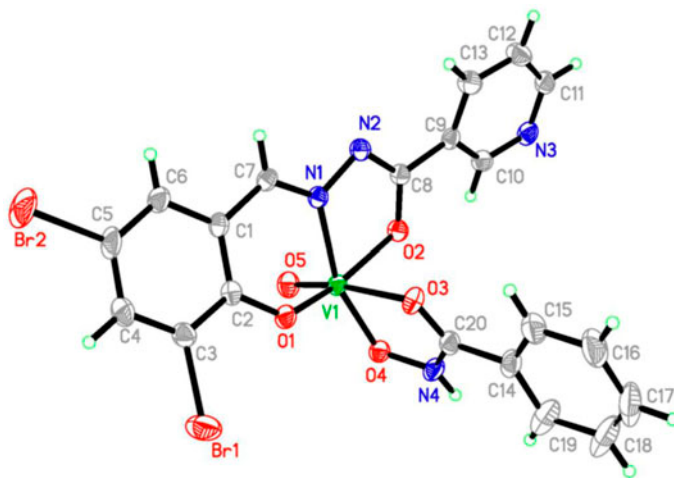


Figure 2. Molecular structure of **2** with 30% probability thermal ellipsoids.

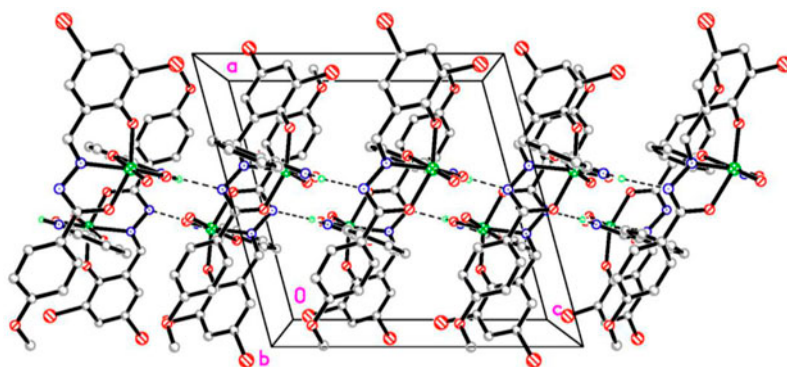


Figure 3. Molecular packing of **1** viewed along the *b* axis. Hydrogen bonds are drawn as thin dotted lines.

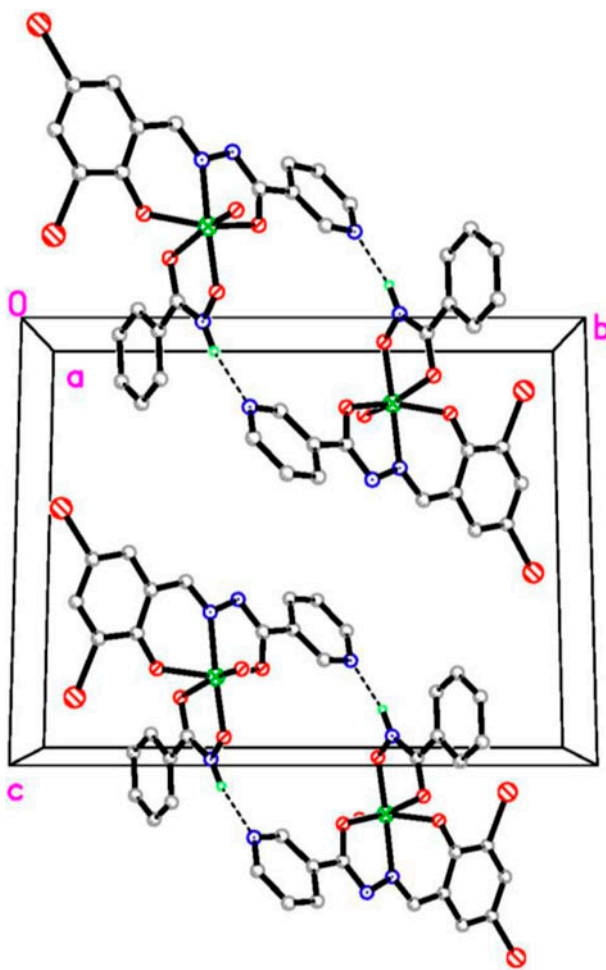


Figure 4. Molecular packing of **2**. Hydrogen bonds are drawn as thin dotted lines.

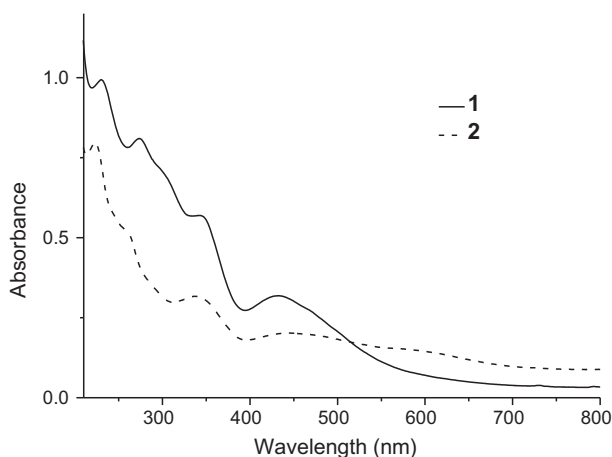


Figure 5. UV-vis spectra of the complexes.

3.2. Structure description of the complexes

The molecular structures of **1** and **2** are shown in figures 1 and 2, respectively. The coordination geometry around *V* can be described as distorted octahedral, with the phenolate oxygen, imino nitrogen, and enolate oxygen of the hydrazone, and one hydroxy oxygen of the benzohydroxamate defining the equatorial plane, and with the carbonyl oxygen of the benzohydroxamate and the oxo occupying axial positions. The hydrazone ligands coordinate to *V* in a meridional fashion forming five- and six-membered chelate rings with bite angles of $74.95(10)^\circ$ and $83.84(11)^\circ$ for **1**, and $74.99(12)^\circ$ and $84.17(13)^\circ$ for **2**. The dihedral angles between the aromatic rings of the hydrazone ligands are $1.9(2)^\circ$ for **1** and $39.4(3)^\circ$ for **2**. The displacements of *V* in **1** and **2** from the equatorial mean planes toward the apical oxo are $0.281(1)$ and $0.284(1)$ Å, respectively. The hydrazone ligands are coordinated in their dianionic form, which is evident from the N2–C8 and O2–C8 bond lengths. The abnormal bond values indicate the presence of the enolate form of the ligand amide groups. The V–O, V–N and V=O bonds are within normal ranges and are similar to those observed in similar vanadium complexes [20, 21]. The distances between *V* and the hydroxy oxygen are much longer than the other bonds, caused by the *trans* effect of the oxo.

In the crystal structure of **1**, the molecules are linked through intermolecular N3–H3···N2 hydrogen bonds [$N3-H3 = 0.90(1)$ Å, $H3\cdots N2^i = 2.09(1)$ Å, $N3\cdots N2^i = 2.990(4)$ Å, $N3-H3\cdots N2^i = 173(5)^\circ$; symmetry code for *i*: $x, 1/2-y, -1/2+z$] to form chains along the *c*-axis (figure 3). In the crystal structure of **2**, adjacent molecules are linked through two intermolecular N–H4···N3 hydrogen bonds [$N4-H4 = 0.90(1)$ Å, $H4\cdots N3^{ii} = 1.86(2)$ Å, $N4\cdots N3^{ii} = 2.749(5)$ Å, $N4-H4\cdots N3^{ii} = 168(6)^\circ$; symmetry code for *ii*: $2-x, -y, 1-z$] (figure 4).

















3.3. IR and UV-vis spectra

The hydrazones show stretching bands attributed to C=O, C=N, C–OH and NH at $1645-1672$, $1619-1625$, $1175-1183$, and $3210-3230$ cm^{-1} , respectively [22]. For the

complexes, absence of the bands characteristic of N–H and C=O groups indicates enolization of the hydrazone ligands and coordination through deprotonated enolic oxygens. The V=O stretches occur as single sharp bands at 978 cm^{-1} for **1** and 973 cm^{-1} for **2** [23]. The strong bands indicative of C=N groups of the complexes are located at 1605 cm^{-1} for **1** and 1610 cm^{-1} for **2** [24]. The weak peaks observed at low wavenumbers ($420\text{--}600\text{ cm}^{-1}$) may be attributed to V–O and V–N vibrations.

The UV–vis spectra of the complexes were recorded in acetonitrile. In the UV–vis region, **1** shows bands at 230, 274, 346, and 433 nm, and **2** shows bands at 223, 262, 341, and 445 nm (figure 5). The weak bands at 390–500 nm were attributed to ligand-to-metal charge transfer (LMCT) from the p_π orbital on the phenolate oxygen to the empty d orbitals of the vanadium ion [25]. The bands at 310–350 nm were assigned to $n\text{--}\pi^*$ transitions [26]. The intense bands at 250–280 nm were assigned to intra-ligand $\pi\text{--}\pi^*$ transitions [26].

Table 3. Catalytic oxidation of olefins catalyzed by **1** and **2**.^a

Substrate	Product		Conversion (%) ^b
		1	72.0
		2	75.4
		1	68.2
		2	65.3
		1	77.8
		2	82.0
		1	87.2
		2	90.3
		1	85.5
		2	88.0
		1	92.7
		2	95.6
		1	98.3
		2	99.1
		1	95.5
		2	93.0

^aThe molar ratio of catalyst : substrate : TBHP is 1 : 300 : 1000. The reactions were performed in mixture of $\text{CH}_3\text{OH}/\text{CH}_2\text{Cl}_2$ ($V : V = 6 : 4$; 1.5 mL).

^bThe GC conversion (%) was measured relative to the starting substrate after 1 h.

3.4. Catalytic oxidation results

Vanadium complexes often show interesting catalytic properties [27–30]. When compared to reported species, the present two complexes have excellent performance. The catalytic results are listed in table 3. Effective epoxide yields and 100% selectivity were observed for all aliphatic and aromatic substrates. In general, oxidation of aromatic substrates gave the corresponding epoxides in over 80% yields, while in oxidation of aliphatic substrates the conversion is lower than 80%. Based on this consideration, isolated double bonds are less reactive than the conjugated ones, in agreement with those reported previously [31–33]. When comparing the results of **1** and **2**, they are similar. This indicates that the slight difference of the hydrazone ligands is not essential for influence of the catalytic properties.

4. Conclusion

Two structurally similar vanadium complexes with hydrazone and benzohydroxamate ligands have been prepared and structurally characterized by single crystal X-ray structure determination and infrared spectra. The hydrazones coordinate to *V* through the phenolate oxygen, imino nitrogen, and enolate oxygen with vanadium in octahedral coordination geometry. The complexes are effective catalysts for oxidation of aliphatic and aromatic olefins.

Supplementary material

CCDC 988425 (**1**) and 988426 (**2**) contain the supplementary crystallographic data for the complex. These data can be obtained free of charge via <http://www.ccdc.ac.uk/conts/retrieving.html>, or from the Cambridge Crystallographic Data Center, 12 Union Road, Cambridge CB2 1EZ, UK; Fax: (+44)1223-336-033; or Email: deposit@ccdc.cam.ac.uk.

Acknowledgement

The author greatly acknowledges Jingchu University of Technology for financial support.

References

- [1] M. Bagherzadeh, M. Amini, H. Parastar, M. Jalali-Heravi, A. Ellern, L.K. Woo. *Inorg. Chem. Commun.*, **20**, 86 (2012).
- [2] G. Grivani, V. Tahmasebi, A.D. Khalaji, K. Fejfarová, M. Dušek. *Polyhedron*, **51**, 54 (2013).
- [3] H. Hosseini-Monfared, N. Asghari-Lalami, A. Pazio, K. Wozniak, C. Janiak. *Inorg. Chim. Acta*, **406**, 241 (2013).
- [4] M. Amini, A. Arab, R. Soleyman, A. Ellern, L.K. Woo. *J. Coord. Chem.*, **66**, 3770 (2013).
- [5] U. Saha, T.K. Si, P.K. Nandi, K.K. Mukherjea. *Inorg. Chem. Commun.*, **38**, 43 (2013).
- [6] G. Romanowski, J. Kira, M. Wera. *J. Mol. Catal. A: Chem.*, **381**, 148 (2014).
- [7] G. Romanowski, J. Kira, M. Wera. *Polyhedron*, **67**, 529 (2014).
- [8] K. Nomura, S. Zhang. *Chem. Rev.*, **111**, 2342 (2011).
- [9] J.-Q. Wu, Y.-S. Li. *Coord. Chem. Rev.*, **255**, 2303 (2011).

- [10] Q.L. Zeng, H.Q. Wang, W. Weng, W.S. Lin, Y.X. Gao, X.T. Huang, Y.F. Zhao. *New J. Chem.*, **29**, 1125 (2005).
- [11] E.V. Ashikhmina, S.A. Rubtsova, I.A. Dvornikova, A.V. Kuchin. *Russ. J. Org. Chem.*, **45**, 1509 (2009).
- [12] S. Barroso, P. Adão, F. Madeira, M.T. Duarte, J.C. Pessoa, A.M. Martins. *Inorg. Chem.*, **49**, 7452 (2010).
- [13] N. Hall, M. Orio, A. Jorge-Robin, B. Gennaro, C. Marchi-Delapierre, C. Duboc. *Inorg. Chem.*, **52**, 13424 (2013).
- [14] G. Grivani, A.D. Khalaji, V. Tahmasebi, K. Gotoh, H. Ishida. *Polyhedron*, **31**, 265 (2012).
- [15] G. Romanowski, M. Wera. *Polyhedron*, **50**, 179 (2013).
- [16] S. Tangestaninejad, M. Moghadam, V. Mirkhani, I. Mohammadpoor-Baltork, K. Ghani. *Catal. Commun.*, **10**, 853 (2009).
- [17] W.-X. Xu, W.-H. Li. *Synth. React. Inorg. Met.-Org. Nano-Met. Chem.*, **42**, 160 (2012).
- [18] G.M. Sheldrick. *SHELX-97, Program for Crystal Structure Solution and Refinement*, Göttingen University, Germany (1997).
- [19] G.M. Sheldrick. *SHELXTL (Version 5)*, Siemens Industrial Automation Inc., Madison, Wisconsin, USA (1995).
- [20] S. Gao, Z.-Q. Weng, S.-X. Liu. *Polyhedron*, **17**, 3595 (1998).
- [21] S. Nica, A. Buchholz, M. Rudolph, A. Schweitzer, A. Wachtler, H. Breitzke, G. Buntkowsky, W. Plass. *Eur. J. Inorg. Chem.*, **14**, 2350 (2008).
- [22] S.N. Rao, K.N. Munshi, N.N. Rao, M.M. Bhadbhade, E. Suresh. *Polyhedron*, **18**, 2491 (1999).
- [23] E. Kwiatkowski, G. Romanowski, W. Nowicki, M. Kwiatkowski, K. Suwinska. *Polyhedron*, **22**, 1009 (2003).
- [24] N.K. Ngan, K.M. Lo, C.S.R. Wong. *Polyhedron*, **30**, 2922 (2011).
- [25] G. Asgedom, A. Sreedhara, J. Kivikoski, E. Kolehmainen, C.P. Rao. *J. Chem. Soc., Dalton Trans.*, 93 (1996).
- [26] M.R. Maurya, S. Agarwal, C. Bader, M. Ebel, D. Rehder. *Dalton Trans.*, 537 (2005).
- [27] A. Erçağ, M. Şahin, A. Koca, E. Bozkurt. *J. Coord. Chem.*, **66**, 1635 (2013).
- [28] M. Amini, A. Arab, R. Soleyman, A. Ellern, L.K. Woo. *J. Coord. Chem.*, **66**, 3770 (2013).
- [29] R. Hajian, S. Tangestaninejad, M. Moghadam, V. Mirkhani, I. Mohammadpoor-Baltork, A.R. Khosropour. *J. Coord. Chem.*, **64**, 4134 (2011).
- [30] M. Bagherzadeh, M. Amini. *J. Coord. Chem.*, **63**, 3849 (2010).
- [31] W.-X. Xu, Y.-M. Yuan, W.-H. Li. *J. Coord. Chem.*, **66**, 2726 (2013).
- [32] X.-Q. He. *J. Coord. Chem.*, **66**, 966 (2013).
- [33] S.-B. Ding, W.-H. Li. *J. Coord. Chem.*, **66**, 2023 (2013).