

# Synthesis, Fluorescence Properties and Theoretical Calculations of Novel Stilbene Derivatives Based on 1,3,4-Oxadiazole Bearing Anthracene Core

Xinwei Li · Huixiong Lu · Daohang He · Chun Luo · Jianjun Huang

Received: 23 February 2013 / Accepted: 30 April 2013 / Published online: 12 May 2013  
© Springer Science+Business Media New York 2013

**Abstract** Two novel stilbene derivatives bearing anthracene core based on 1,3,4-oxadiazole were efficiently synthesized and characterized by  $^1\text{H-NMR}$ , mass spectrometry and elemental analysis. The optical properties of the title compounds were investigated by UV–vis absorption and fluorescence emission spectra in different solvents. Chemical calculations were performed by density functional theory (DFT) at the (B3LYP)/6-31G\* level. The results show the two compounds exhibit strong green fluorescence emission ranged from 489–493 nm, and the fluorescence quantum yield ranged from 0.78–0.92. Their HOMO and LUMO levels are (–5.44 eV, –2.25 eV) and (–5.45 eV, –2.28 eV), respectively. The influence of the solvent on the fluorescence intensities was also discussed.

**Keywords** Synthesis · Stilbene · 1,3,4-Oxadiazole · Anthracene · Fluorescence properties · DFT

## Introduction

Over the past few years,  $\pi$ -conjugated organic materials have attracted much attention due to the increasing development of

potentially active components for a wide range of electronic and optoelectronic devices [1]. As an important class of five-membered hetero cyclic compounds, 1,3,4-oxadiazoles are well-known not only for their considerable biological and medical activities, which include anti-inflammatory, antifungal, anti-HIV, anticancer, and antimicrobial activities [2–5], but also for their sufficient fluorescence in the visible light range, large Stokes shifts, high quantum yields [6–8], and so on. Another feature of the 1,3,4-oxadiazole derivatives is that the photophysical and spectroscopic properties can be readily modified by the introduction of substituents in the structure of the oxadiazole, giving more flexibility to fit well in various applications [9]. In addition, oxadiazole unit can improve electron injection and transport properties of the molecules. Thus, many 1,3,4-oxadiazole derivatives with good hole-transporting capabilities and high fluorescence emission, have actually been used as electron-injection materials [10]. Nowadays, compounds with blue luminescence are highly desirable because of their wide applicability in organic materials to tune the emission colours in the entire region of visible spectrum [11]. The fluorescent characteristics mainly depend on molecular structure, such as conjugate system, coplanarity and rigidity. The longer the conjugate system is, the stronger the fluorescent intensity and greater emission wavelength will be [12]. Anthracene derivatives have rigid structure, wide energy gaps and high fluorescent quantum efficiency [13, 14]. Moreover, anthracene derivatives have been extensively utilized as fluorescence sensors for metal ions and biological molecules [15]. Great deals of compounds which contain anthracene core electroluminescent materials have been developed till now.

In continuation of our work in organic fluorescent materials [16–18], herein, two novel stilbene derivatives bearing

X. Li · H. Lu · D. He (✉)  
School of Chemistry and Chemical Engineering,  
South China University of Technology, Guangzhou 510640,  
People's Republic of China  
e-mail: daohanghe@yahoo.com.cn

X. Li · C. Luo · J. Huang  
Guangzhou Baiyunshan Hanfang Pharmaceutical Co.Ltd.,  
Guangzhou 510970, People's Republic of China

anthracene core based on 1,3,4-oxadiazole were synthesized by introducing anthracene core and 1,3,4-oxadiazole unit into the stilbene skeleton. The fluorescence properties of the title compounds are investigated by UV–vis absorption and fluorescence emission spectra in dimethylformamide (DMF), chloroform (CHCl<sub>3</sub>) and tetrahydrofuran (THF). Quantum-chemical calculation was performed to obtain their optimized structures and the electron distribution. The synthetic route is outlined in Scheme 1.

## Experimental

### Instrumentation

Melting points were determined using RY-1 melting point apparatus and were uncorrected. <sup>1</sup>H NMR spectra were recorded in CDCl<sub>3</sub> on a Bruker AVANCE-400 MHz NMR spectrometer using TMS as internal standard. Mass spectra were obtained with a HPLC/MS LCQDECA spectrometer (APCI). Elemental analyses were performed on a Vario EL III CHN elemental analyzer. UV–vis absorption spectra were recorded on a Hitachi UV-3010 spectrophotometer. Fluorescence spectra were obtained on a Hitachi F-4500 spectrophotometer at room temperature.

### Synthesis

Synthesis of 2-(anthracen-9-yl)-5-(p-tolyl)-1,3,4-oxadiazole (1)

Synthesis of 2-(anthracen-9-yl)-5-(4-(bromomethyl)phenyl)-1,3,4-oxadiazole(2)

Synthesis of 4-(5-(anthracen-9-yl)-1,3,4-oxadiazol-2-yl)benzylphosphonate(3)

Intermediates of compounds 1, 2 and 3 were prepared by the reported methods [17].


### Typical Procedure for the Synthesis of Compounds(4)

To a stirred solution of aromatic aldehydes (1.7 mmol) and the intermediate 3 (0.9 g, 1.7 mmol) in anhydrous N,N-dimethylformamide (15 mL) under nitrogen atmosphere was added dropwise a solution of *t*-BuOK (2 g, 3 %) in ethanol. The reaction proceeded at room temperature overnight. Then the resulting mixture was filtered and washed with ethanol. The residue was recrystallized from ethanol/DMSO.

2-(anthracen-9-yl)-5-(4-(2,4-dichlorostyryl)phenyl)-1,3,4-oxadiazole (4a), yellow crystals, yield 92.5 %; m.p. 256–257 °C; <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>) δ 8.71 (s, 1H, anthracen-H), 8.21 (d, *J*=8.4 Hz, 2H, C<sub>6</sub>H<sub>4</sub> 2,6-H), 8.14–8.00 (m, 4H, anthracen-H), 7.71 (d, *J*=8.4 Hz, 2H, C<sub>6</sub>H<sub>4</sub> 3,5-H), 7.65 (d, *J*=8.5 Hz, 1H, C<sub>6</sub>H<sub>3</sub> 6-H), 7.61–7.52 (m, 4H, anthracen-H), 7.57 (d, *J*=16.2 Hz, 1H, CH=CH), 7.44 (d, *J*=2.1 Hz, 1H, C<sub>6</sub>H<sub>3</sub> 3-H), 7.28 (d, *J*=8.5 Hz, 1H, C<sub>6</sub>H<sub>3</sub> 5-H), 7.12 (d, *J*=16.3 Hz, 1H, CH=CH); APCI MS: *m/z*, 493(M<sup>+</sup>, 100), 495(M+2, 80), 496(M+3, 20); Anal. Calcd. for C<sub>30</sub>H<sub>18</sub>Cl<sub>2</sub>N<sub>2</sub>O (493.2):C, 73.03; H, 3.68; N, 5.68; Found: C, 73.41; H, 3.65; N, 5.72.

2-(anthracen-9-yl)-5-(4-(3,4-dichlorostyryl)phenyl)-1,3,4-oxadiazole (4b), yellow crystals, yield 91.2 %; m.p. 253–254 °C; <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>) δ 8.71 (s, 1H, anthracen-H), 8.20 (d, *J*=8.2 Hz, 2H, C<sub>6</sub>H<sub>4</sub> 2,6-H), 8.15–8.02 (m, 4H, anthracen-H), 7.68 (d, *J*=8.3 Hz, 2H, C<sub>6</sub>H<sub>4</sub> 3,5-H), 7.63 (s, 1H, C<sub>6</sub>H<sub>3</sub> 2-H), 7.61–7.51 (m, 4H, anthracen-H), 7.45 (d, *J*=8.3 Hz, 1H, C<sub>6</sub>H<sub>3</sub>, 5-H), 7.37 (d, *J*=8.4 Hz, 1H, C<sub>6</sub>H<sub>3</sub> 6-H), 7.14 (s, 2H, CH=CH); APCI MS: *m/z*, 493(M<sup>+</sup>, 100), 495(M+2, 70), 496(M+3, 25); Anal. Calcd. for C<sub>30</sub>H<sub>18</sub>Cl<sub>2</sub>N<sub>2</sub>O(493.2):C, 73.03; H, 3.68; N, 5.68; Found: C, 72.99; H, 3.75; N, 5.76.

**Scheme 1** The synthetic route of the title compounds

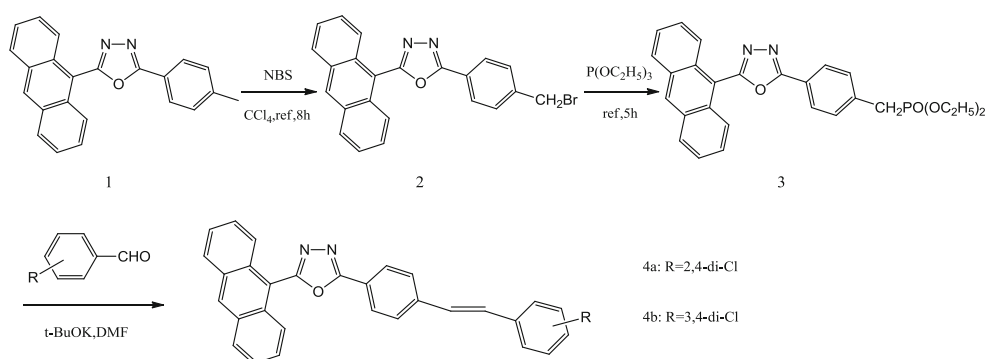

**Table 1** The fluorescence characteristics of the title compounds in CHCl<sub>3</sub>, THF, and DMF solution at room temperature (concentration:  $1 \times 10^{-5}$  mol/L)

compound	solution	$\lambda_{\max}$ (nm)	$\times 10^{-4} \epsilon_{\max}$	$\lambda_{\text{ex}}$ (nm)	$\lambda_{\text{em}}$ (nm)	Stokes shifts	$\Phi_x$
4a	DMF	336	4.79	341	493	152	0.81
	THF	338	5.07	340	489	149	0.78
	CHCl <sub>3</sub>	335	4.43	343	489	146	0.88
4b	DMF	338	5.22	341	493	152	0.91
	THF	337	6.15	341	489	148	0.71
	CHCl <sub>3</sub>	337	4.92	342	489	147	0.92

## Results and Discussion


### <sup>1</sup>H NMR Spectra

In the <sup>1</sup>H NMR spectra of two compounds, 4a showed two fine doublets corresponding to the olefinic protons (CH=CH) from stilbene at  $\delta$ : 7.57 ppm and 7.12 ppm ( $J=16.3$  Hz). At  $\delta$ : 7.65, 7.28, and 7.44 ppm, two doublets and a singlet could be assigned to 6-H, 5-H and 3-H from aromatic protons (C<sub>6</sub>H<sub>3</sub>-protons), respectively. At  $\delta$ : 8.71, 8.14–8.00, and 7.61–7.52 ppm, two multiplets and a singlet could be assigned to the protons of anthracen. In addition, another two downfield doublets were also found at  $\delta$ : 8.21 and 7.71 ppm which could be assigned to the contribution of aromatic protons (C<sub>6</sub>H<sub>4</sub>-protons). In contrast, the compound 4b in its <sup>1</sup>H NMR spectrum showed the similar resonance peaks accountable to the protons of anthracen and aromatic protons (C<sub>6</sub>H<sub>4</sub>-protons), respectively, only a singlet was found corresponding to the olefinic protons (CH=CH) from stilbene at  $\delta$ : 7.14 ppm. From the <sup>1</sup>H NMR spectra of two


compounds, it was found that their olefinic protons (CH=CH) from stilbene had different coupling, which indicated the different substituents on benzene had an effect on olefinic proton-proton coupling.

### Fluorescence Properties

The data of fluorescence properties for compounds 4a and 4b are summarized in Table 1. It can be seen that compounds 4a and 4b had the similar optical properties such as the maximum absorption wavelengths, the maximum emission wavelengths, the Stokes shift and the fluorescence quantum yields, indicating that the different position Cl have a limited effect on their fluorescence properties. In Table 1, compared with  $\lambda_{\max}$  and  $\epsilon_{\max}$  for the same compound in DMF, CHCl<sub>3</sub> and THF, the maximum absorption wavelengths of the two compounds had little change in different solvents, especially, in DMF and CHCl<sub>3</sub>, the absorbency is lower than that in THF. This is because the dispersion force, permanent dipole and induction of dipole

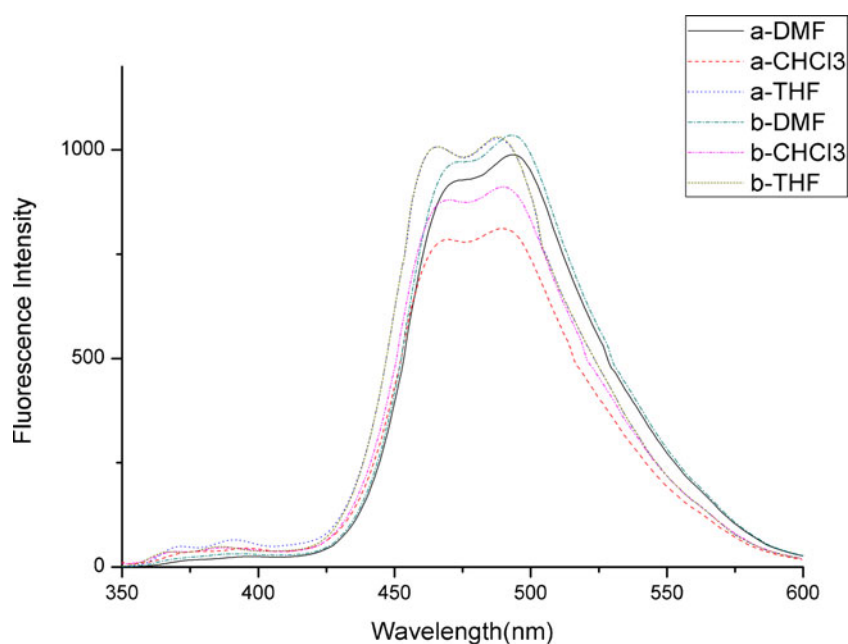**Fig. 1** The fluorescence emission spectra of the compounds 4a, 4b in CHCl<sub>3</sub>, THF, and DMF solvent at room temperature (concentration:  $1 \times 10^{-5}$  mol L<sup>-1</sup>)

**Fig. 2** The fluorescence emission spectra of the compounds 1, 4a and 4b in THF (concentration:  $1 \times 10^{-5}$  mol L $^{-1}$ )

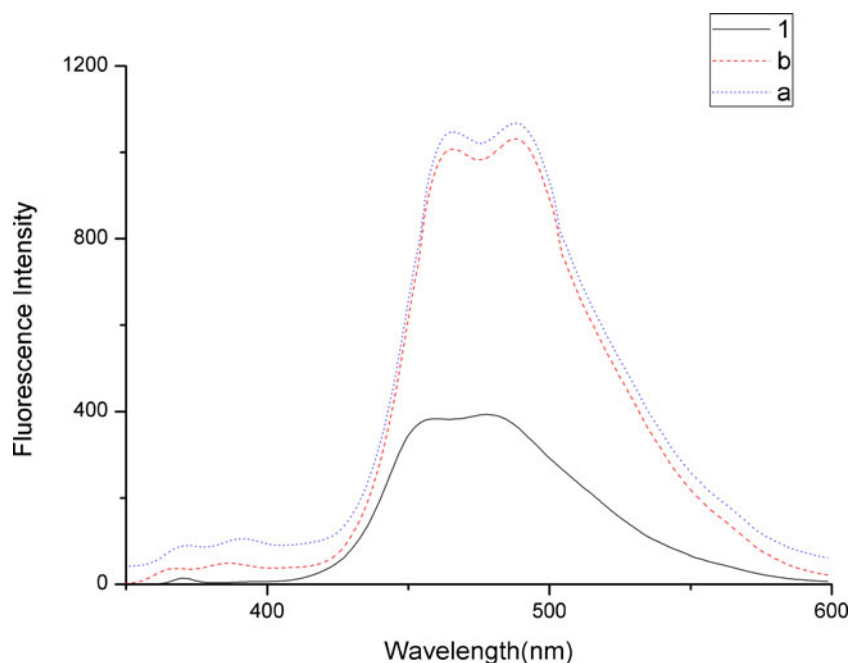


in the strongly polar THF with stilbene derivatives are stronger than that in DMF and CHCl $_3$ , which makes  $\lambda_{\max}$  have a little red-shift.


Figure 1 showed fluorescence emission spectra of two stilbene derivatives in CHCl $_3$ , THF, and DMF (Concentration:  $1 \times 10^{-5}$  mol/L). The influence of solvent on the fluorescence intensities of the 4a and 4b was investigated. We could see that the emission wavelengths and fluorescence intensity of the two compounds were different in three solvents at the same concentration. The fluorescence intensity of the two compounds in CHCl $_3$  was lower than that in the other solvents. All these

indicated that the solutions molecules had strong coordination effect and the environment played an important role in determining the fluorescence intensity of the compounds. As shown in Fig. 2, compared with the fluorescence characteristic emission wavelengths of the title compounds in THF solvent, the maximum fluorescence emission wavelength of compound 4a and 4b had a greater shift (12 nm) towards higher wavelengths than the intermediate of compound 1 owing to increasing the conjugation length of the molecule, which would make the electron-pair in the highest occupied molecular orbit possess a lower energy; the electron-pair could be excited easily to

**Fig. 3** The fluorescence spectra of compounds 4a and 4b at different concentration of THF ( $1.0 \times 10^{-4}$  mol/L;  $1.0 \times 10^{-5}$  mol/L;  $1.0 \times 10^{-6}$  mol/L)

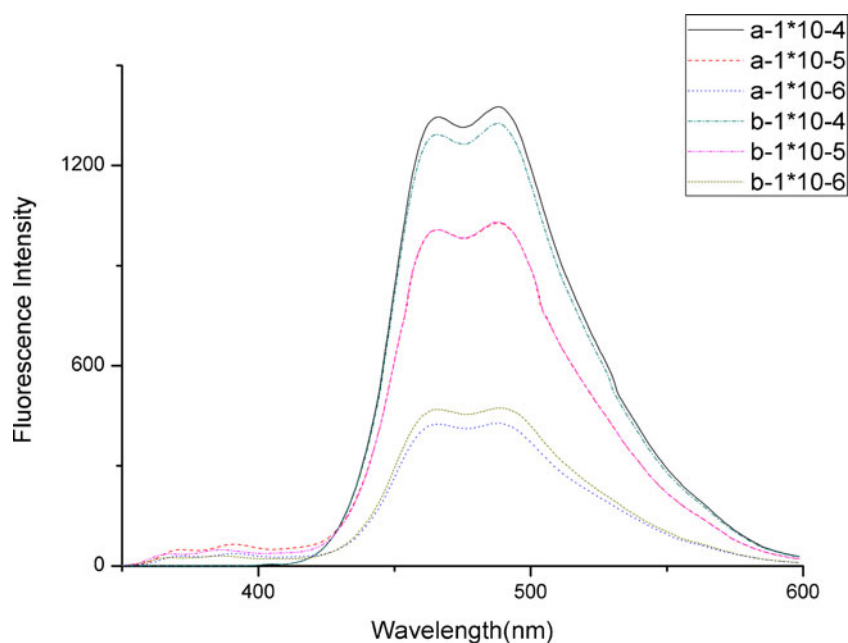

**Fig. 4** Optimized geometric structure and frontier molecular orbital profiles of 4a and 4b

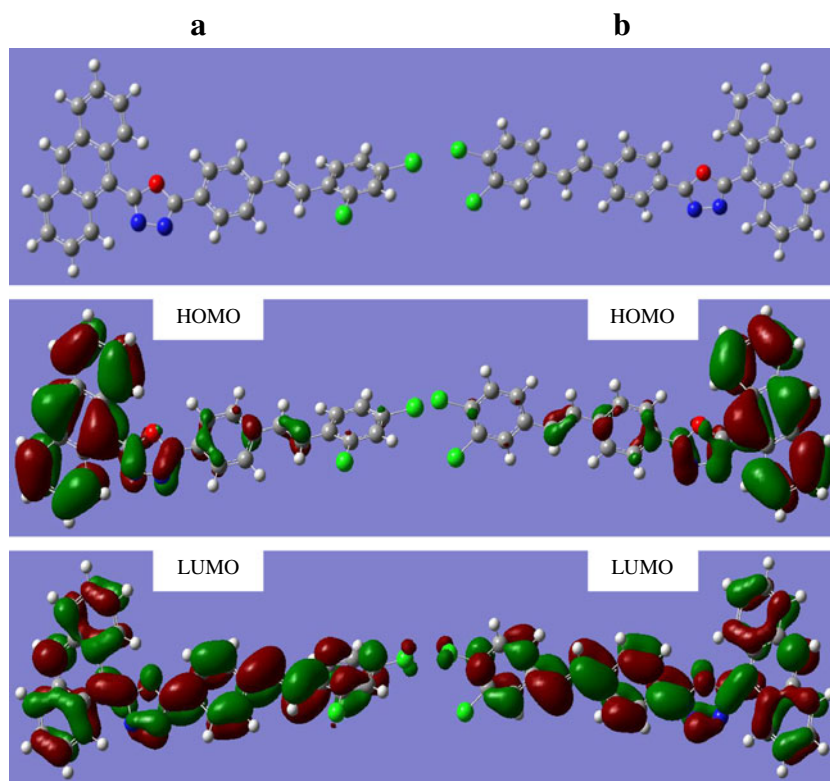

transit into a higher orbit. The influence of concentration on fluorescence intensity of the two compounds was also studied (Fig. 3). It can be seen that the emission intensity of fluorescence were greatly decreased with gradual increasing in concentration of 4a and 4b in THF. The fluorescence quantum yields:  $\Phi_x = \frac{A_s \times F_x \times n_s^2 \times \Phi_s}{A_x \times F_s \times n_x^2}$  where A is the absorbance at the excitation wavelength, F the area under the fluorescence curve and n the refractive index. Subscripts *s* and *x* refer to the standard and to the sample of unknown quantum yield, respectively. Rhodamine B in ethanol ( $\Phi=0.89$ ) was taken as the standard [19]. The two compounds had a large fluorescence quantum yield ( $\Phi$ ), which was due to the conjugative effect. The molecular structure containing stilbene, anthracene core and 1,3,4-oxadiazole unit can increase the conjugation length and rigid structure of the molecule.

#### Theoretical Study

The geometries and electronic structures of molecules 4a and 4b were studied by density function theory (DFT) calculations at the B3LYP/6-31G\* level [20]. The optimized structures and the frontier molecular orbital profiles of 4a and 4b are shown in Fig. 4. As expected, molecules 4a and 4b both have non-planar, twisted structures attributed to steric hindrance imposed by the 1,3,4-oxadiazole, anthracene skeleton,  $\pi$ -bridges, linkages and dihedral angles between two units. The dihedral angle of two molecules

between anthracene and 1,3,4-oxadiazole is around  $134^\circ$ , and the dihedral angle in 4a between vinyl and 2,4-dichlorobenzene is  $21^\circ$ . Thus the -Cl group attached to the *o*-position phenyl seems to affect the planarity of the molecules. In both cases, the HOMO are mainly localized on the anthracene and 1,3,4-oxadiazole, while the LUMO are delocalized along the whole molecules, indicating that these molecules possess intramolecular charge transfer ability. It also implies that the anthracene core and 1,3,4-oxadiazole unit play an important part in their emission. Two molecules possess a high HOMO energy level ( $-5.44$  and  $-5.46$  eV), which could lead to their better hole-transport properties. Their LUMO energy level ( $-2.25$  and  $-2.28$  eV) is supposed to facilitate the acceptance of electrons from the cathode [21]. The band gaps are 3.19 eV and 3.18 eV, respectively. Two energy gaps are close, indicating they have the similar the emission spectra which agree well with the experimental observations.

#### Conclusions

Two novel stilbene derivatives bearing anthracene core based on 1,3,4-oxadiazole were synthesized, characterized by spectral studies, theoretical calculations and their fluorescence spectra were recorded in order to study the changes in the photophysical properties with different solvents. The results showed the compounds exhibited strong green



fluorescence emission with high fluorescence quantum yield (0.78–0.92). The influence of solvent on the fluorescence intensities of the compounds indicated that the solvents played an important role in determining the fluorescence intensity of the compounds. The DFT calculations establish that they possess good charge-transport characteristics. Thus, they may serve as potential applications in organic electroluminescent materials.

**Acknowledgements** The authors thank the Fundamental Research Funds for the Central Universities (No.2012ZM0035) and Guangdong Provincial Natural Science Foundation of China (No.04300531) for the financial assistance.

## References

1. Liu Y, Nishiura M, Wang Y, Hou ZM (2006) pi-Conjugated aromatic enynes as a single-emitting component for white electroluminescence. *J Am Chem Soc* 128:5592–5593
2. Husain A, Ajmal M (2009) Synthesis of novel 1,3,4-oxadiazole derivatives and their biological properties. *Acta Pharm* 59:223–233
3. Nagalakshmi G (2008) Synthesis, antimicrobial and anti-inflammatory activity of 2,5-disubstituted-1,3,4-oxadiazoles. *Indian J Pharm Sci* 70:49–55
4. Iqbal R, Zareef M, Ahmed S, Zaidi JH, Arfan M, Shafique M, Al-Masoudi NA (2006) Synthesis, antimicrobial and anti-HIV activity of some novel benzenesulfonamides bearing 2,5-disubstituted-1,3,4-oxadiazole moiety. *J Chin Chem Soc* 53:689–696
5. Kumar D, Sundaree S, Johnson EO, Shah K (2009) An efficient synthesis and biological study of novel indolyl-1,3,4-oxadiazoles as potent anticancer agents. *Bioorg Med Chem Lett* 19:4492–4494
6. Zhang TL, Li HH, Yuan ZL (2005) Synthesis and light-emitting characters of 2,5-bis 4(2-arylviny)phenyl -1,3,4-oxadiazoles. *Chin J Org Chem* 25:997–1000
7. Qian Y, Lu ZF, Lu CG, Chen ZM, Cui YP (2007) Synthesis and two-photon absorption properties of 2,5-bis 4-(2-arylviny)phenyl -1,3,4-oxadiazoles. *Dyes Pigment* 75:641–646
8. Feng LH, Wang XJ, Chen ZB (2008) Synthesis, characterization, and photophysics of a novel conjugated polymer with 1,3,4-oxadiazole, carbazole, and naphthalene units. *J Appl Polym Sci* 108:1995–2000
9. Kamtekar KT, Wang CS, Bettington S, Batsanov AS, Perepichka IF, Bryce MR, Ahn JH, Rabinal M, Petty MC (2006) New electroluminescent bipolar compounds for balanced charge-transport and tuneable colour in organic light emitting diodes: triphenylamine oxadiazole-fluorene triad molecules. *J Mater Chem* 16:3823–3835
10. Fang ZJ, Wang SM, Zhao L, Xu ZX, Ren J, Wang XB, Yang QF (2008) Synthesis and characterization of blue light emitting materials containing imidazole. *Mater Chem Phys* 107:305–309
11. Shen Z, Burrows PE, Bulović V, Forrest SR, Thompson ME (1997) Three-color, tunable, organic light-emitting devices. *Science* 276:2009–2011
12. Fei X, Gu Y, Li C, Yang X (2012) Study on synthesis and spectrum of novel styryl cyanine dyes with a carbazole bridged chain. *J Fluoresc* 22:807–814
13. Zhang H, Yu TZ, Zhao YL, Fan DW, Xia YJ, Zhang P (2010) Synthesis, crystal structure, photo- and electro-luminescence of 3-(4-(anthracen-10-yl)phenyl)-7-(N, N'-diethylamino)coumarin. *Synth Met* 160:1642–1647
14. Zhu YL, Yin QF, Ma KR, Cao L, Jing X, Zhong H (2010) Synthesis and photo-electric properties of 9-4,5-Bis-(hexadecylthio)-1,3-dithiol-2-ylidene anthracen-10(9H)-one. *Chin J Org Chem* 30:865–870
15. Zhang H, Yu TZ, Zhao YL, Fan DW, Xia YJ, Zhang P, Qiu YQ, Chen LL (2010) Synthesis, crystal structure and photoluminescence of 3-(4-(anthracen-10-yl)phenyl)-benzo 5,6 coumarin. *Spectrochim Acta A Mol Biomol Spectrosc* 75:325–329
16. He DH, Li XW, Yang C, Yang J (2012) Characterization and optical properties of novel unsymmetrical stilbene-based 1,3,4-oxadiazole derivatives. *Spectrochim Acta A Mol Biomol Spectrosc* 95:184–187
17. Li XW, He DH (2012) Synthesis and optical properties of novel anthracene-based stilbene derivatives containing an 1,3,4-oxadiazole unit. *Dyes Pigments* 93:1422–1427
18. Zhu Y-C, He D-H, Yang Z-R (2009) Synthesis and optical properties of two novel stilbene derivatives containing 1, 3, 4-oxadiazole moiety. *Spectrochim Acta A Mol Biomol Spectrosc* 72:417–420
19. Yang X, Pan ZT, Ma Y (2003) Rhodamine B as standard substance to measure the fluorescence quantum yield of dichlorofluorescein. *Chin J Anal Sci* 19:588–599
20. Frisch MJ, Trucks G, Schlegel H, Scuseria G, Robb M, Cheeseman J, Scalmani G, Barone V, Mennucci B, Petersson G (2009) Gaussian 09, Revision A. 02. Gaussian, Inc, Wallingford
21. Wang H-Y, Shi J-J, Wang C, Zhang X-X, Wan Y, Wu H (2012) Novel fluorescence dyes based on entirely new chromeno[4,3,2-de][1,6]naphthyridine framework. *Dyes Pigments* 95:268–274